INTERNATIONAL STANDARD



First edition 2020-05

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for determining thermal expansion coefficient and residual stress of CVD ceramic coatings

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 23458:2020 https://standards.iteh.ai/catalog/standards/sist/3606b038-f591-4928-841da1a13ae5a81d/iso-23458-2020



Reference number ISO 23458:2020(E)

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 23458:2020</u> https://standards.iteh.ai/catalog/standards/sist/3606b038-f591-4928-841da1a13ae5a81d/iso-23458-2020



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Fax: +41 22 749 09 47 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland

Contents

Page

Fore	eword	iv			
1	Scope				
2	Normative references				
3	Terms and definitions				
4	Principle	2			
5	Apparatus5.1General5.2Heating and cooling device5.3Temperature measurement5.4Test piece mounting5.5Data recording system5.6Dimensional measuring devices	2 3 3 3 3 4			
6	Specimens 6.1 Test piece 6.2 Dimensions 6.3 Test piece preparation 6.3.1 General 6.3.2 Test piece handling and storage 6.3.3 Number of test pieces				
7	Test procedure7.1Measurement of the test piece dimensions 1.217.2Measurement of the elastic modulus7.3Measurement of the thermal expansion coefficient of CVD coatings7.4Calculation of the residual stress in CVD coatings [59]-4928-841d				
8	Calculationa1a13ae5a81d/iso-23458-20208.1Thermal expansion coefficient of the CVD ceramic coatings, α_c 8.2Residual stress in CVD coatings, σ_c	7			
9	Test report				
Bibl	Bibliography				

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 206, *Fine ceramics*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at <u>www.liso.org/members.html</u>.

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for determining thermal expansion coefficient and residual stress of CVD ceramic coatings

1 Scope

This document specifies a test method for determining thermal expansion coefficient up to 2 300 K and the residual stress of chemical vapour deposition (CVD) ceramic coatings (thickness > 0,03 mm) at room temperature. Procedures for test piece preparation, test modes, heat rate, data collection, property calculations and reporting procedures are given.

This document applies to CVD ceramic coatings on metal or ceramic substrates. This test method can be used for material research, quality control, characterization and design data-generation purposes.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3611, Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics

ISO 17139, Fine ceramics (advanced ceramics, advanced technical ceramics) — Thermophysical properties of ceramic composites — Determination of thermal expansion

ISO 19603, Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for determining elastic modulus and bending strength of thick ceramic coatings

IEC 60584-1, Thermocouples — Part 1: EMF specifications and tolerances

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at https://www.iso.org/obp
- IEC Electropedia: available at http://www.electropedia.org/

3.1

relative method

indirect test method to obtain the measured parameter

Note 1 to entry: The expected parameter A is usually difficult to measure directly, but parameters B and C are known parameters or easy to obtain. If the analytical relationship of A = f(B, C) is established, the parameter A can be calculated.

3.2

linear thermal expansion

positive or negative change in one dimension that occurs when a material is subjected to a change in temperature

4 Principle

The deformation of a coated bar during heating or cooling involves two effect factors, i.e. thermal expansion coefficient and residual stress in the coating and the substrate. The thermal expansion coefficient is a material characteristic. However, the residual stresses in the coating are not only due to a material property but depend also on the size of the component and the cross-sectional area ratio of the coating and substrate.

The thermal expansion coefficient of CVD ceramic coatings is deduced by the relative method, i.e. it is related with the expansion coefficient of the substrate and the coefficient of the coated bar. Two types of test piece, a bar with CVD ceramic coating (composite) and a bar without coating (substrate), shall be used to measure the thermal expansion coefficient according to ISO 17139. After determining the elastic modulus of the substrate and coating, the thermal expansion coefficient of both the composite and the substrate are obtained. The thermal expansion coefficient of CVD ceramic coating shall then be calculated.

The sample length change and environment temperature are measured continuously at regular, frequent intervals during the imposed cycle. The residual stress of CVD ceramic coatings is usually generated due to the mismatch of thermal expansion coefficient between the coating and the substrate. Based on the uniform strain model, geometric compatibility analysis and internal stress equilibrium, the residual stress calculation formula of CVD ceramic coatings is deduced by the relative method, which is a function of many factors including elastic modulus, expansion coefficient, configurations and temperature. After getting the thermal expansion coefficient of the coating, the residual stress of CVD ceramic coatings shall be calculated from elastic modulus, expansion coefficient, cross-sectional area ratio of the coating to substrate and the temperature during coating preparation.

5 Apparatus

(standards.iteh.ai)

5.1 General

<u>ISO 23458:2020</u>

https://standards.iteh.ai/catalog/standards/sist/3606b038-f591-4928-841d-

Recommended testing equipment is showh in <u>Figure 1</u>.2This 2can be used to measure the thermal expansion coefficient of two testing pieces in the same environment. If not, the two testing pieces shall be tested respectively in the same environment using the normal thermal expansion equipment in accordance with ISO 17139.

NOTE The two test pieces can be of the same materials or different materials. In this document, one is the composite with CVD coating and the other is the substrate.

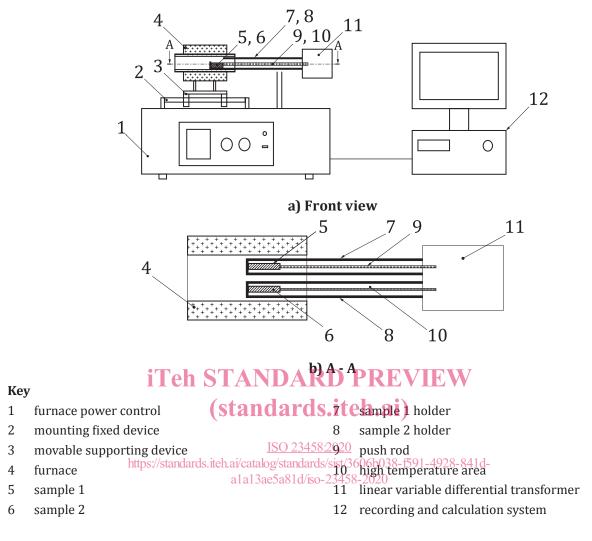


Figure 1 — Schematic of testing equipment

5.2 Heating and cooling device

Furnace, capable of working in a controlled atmosphere when required and of controlling the temperature of the test piece to within 1 % of its mean temperature, expressed in K, in accordance with ISO 17139.

5.3 Temperature measurement

Thermocouple, in accordance with IEC 60584-1, subject to the conditions of the testing environment. For temperatures in excess of 2 000 K, infrared detectors or any suitable device may be used.

5.4 Test piece mounting

The device used shall allow free axial movement of the test piece. The mechanical environment shall minimize stresses. For measuring apparatus that is horizontal, the sideways movement or twist of the test piece shall be restricted, without any restriction of axial movement by a suitable arrangement.

5.5 Data recording system

A system capable of measuring displacements to an accuracy better than 0,000 1 mm. The system shall allow recording of the test piece temperature and the displacement simultaneously.

An analogue chart recorder or digital data collection system should be used. The error of the recording system shall be 1 % or lower. The minimum data collection frequency shall be 15 Hz and a response frequency of 50 Hz is deemed adequate.

5.6 Dimensional measuring devices

The dimensions of the test piece shall be measured using a Vernier calliper conforming with ISO 3611 and with precision of 0,02 mm or better, or other calibrated measuring device providing the same or better measurement accuracy.


Coating thickness shall be measured by using a calibrated optical microscope with magnification of 1 000 times or better. Sample displacement shall be measured using a calibrated electronic micrometer with a precision of at least 0,001 mm and resolution of 0,000 5 mm or better, or other measuring device providing the same or better measurement accuracy. All calibrations shall be traceable to national standards.

6 Specimens

6.1 Test piece iTeh STANDARD PREVIEW

In order to simplify the preparation of test pieces, three different symmetrical structures of coating configurations are considered:

- a) coating on upper and lower surfaces of the test pieces only (two-face coating, Figure 2 a);
- https://standards.iteh.ai/catalog/standards/sist/3606b038-f591-4928-841d-
- b) coating on four surfaces of the test pieces (four-face coating, Figure 2 b);
- c) coating on cylinder surface of the test pieces (around coating, Figure 2 c). Any of the three coating configurations may be used for evaluating the properties of the coating layer.

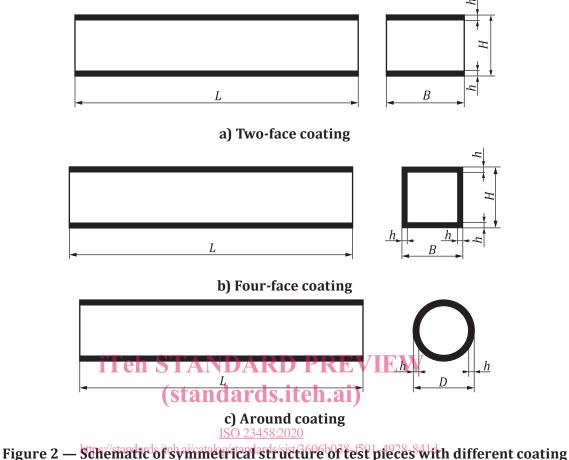

igure 2 — Schematic of symmetrical structure of test pieces with different coatin configurations for the thermal expansion coefficient tests

6.2 Dimensions

The geometrical dimensions of the coated test piece for the thermal expansion coefficient tests are displayed in Figure 2. Table 1 gives the recommended test piece dimensions. The total data are the sum of the coating and substrate for the composite. For coating on a rectangular test piece shown in Figure 2 a) or b), the recommended dimensions shall be 30 mm to 50 mm long, 5 mm wide and 5 mm thick. The thickness of the coating, *h*, shall be larger than 0,03 mm. The thickness ratio, *h*/*H*, should be lower than 1/4. The parallelism tolerance on the opposite longitudinal face shall be 0,015 mm.

For coating on cylinder test pieces shown in Figure 2 c), the recommended dimensions shall be 30 mm to 50 mm long and 5 mm in diameter. The thickness of the coating shall be larger than 0,03 mm. The thickness ratio, h/D, should be lower than 1/4.

It is recommended that a cylinder testing piece is used for testing the thermal expansion coefficient.

Table 1 — Recommended test piece dimensions for the thermal expansion coefficient tests

Dimensions in millimetres

Туре	Dimension	Description	Value	Tolerance
Rectangular bar	L	Total length	30 to 50	±0,5
	В	Total width	5	±0,2
testing piece	Н	Total thickness	5	±0,2
	h	Thickness of the coating	> 0,03	_