



Designation: E 796 – 94 (Reapproved 2000)

## Standard Test Method for Ductility Testing of Metallic Foil<sup>1</sup>

This standard is issued under the fixed designation E 796; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the determination of ductility, that is, the ability to undergo plastic deformation in tension or bending before fracturing, of metallic foil in thicknesses up through 0.150 mm (0.0059 in.).

1.2 Values stated in SI units are to be regarded as the standard. Inch-pound units are provided for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

E 3 Methods of Preparation of Metallographic Specimens<sup>2</sup>

E 6 Terminology Relating to Methods of Mechanical Testing<sup>2</sup>

E 8 Test Methods for Tension Testing of Metallic Materials<sup>2</sup>

E 111 Test Method for Young's Modulus, Tangent Modulus, and Chord Modulus<sup>2</sup>

E 345 Test Methods of Tension Testing of Metallic Foil<sup>2</sup>

E 513 Definitions of Terms Relating to Constant-Amplitude Low-Cycle Fatigue Testing<sup>3</sup>

E 606 Practice for Strain Controlled Fatigue Testing<sup>2</sup>

E 1150 Definitions of Terms Relating to Fatigue<sup>2</sup>

### 3. Terminology

#### 3.1 Definitions:

3.1.1 The definitions of terms appearing in Definitions E 6, E 1150, E 513, and Practice E 606, shall be considered as applying to the terms used in this test method.

3.1.2 *fatigue ductility,  $D_f$* —the ability of a material to deform plastically before fracturing, determined from a constant-strain amplitude, low-cycle fatigue test.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee E28 on Mechanical Testing and is the direct responsibility of Subcommittee E28.02 on Ductility and Flexure Testing.

Current edition approved Feb. 15, 1994. Published April 1994. Originally published as E 796–81. Last previous edition E 796–88 (1993).

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 03.01.

<sup>3</sup> Discontinued—See 1986 *Annual Book of ASTM Standards*, Vol 03.01.

NOTE 1—Fatigue ductility is usually expressed in percent in direct analogy with elongation and reduction of area ductility measures.

NOTE 2—The fatigue ductility corresponds to the fracture ductility, the true tensile strain at fracture. Elongation and reduction of area represent the engineering tensile strain after fracture.

NOTE 3—For the purpose of this definition the fatigue ductility exponent,  $c$ , is defined as  $c = -0.60$  (see equation in 9.1).<sup>4</sup>

### 4. Summary of Test Method

4.1 The specimen is subjected to a fatigue test which employs precisely controlled, symmetric, cyclic, constant-amplitude, flexural strains of a magnitude that will cause fracture in the low-cycle fatigue regime.<sup>4</sup>

4.2 The fatigue ductility is determined from an equation derived from universal, empirical, relationships between tensile properties and fatigue behavior which utilizes the strain range employed and the fatigue life obtained in the fatigue test, as well as the modulus of elasticity, the tensile strength and the fracture strength determined in accordance with Test Method E 111 and Test Methods E 8, with the provisions in Test Methods E 345 and in this standard.

### 5. Significance and Use

5.1 For bulk specimens, tension tests provide an adequate means to determine the ductility of materials either through the measurement of elongation or reduction of area. For foil specimens, however, tension tests are not very useful for the determination of ductility. This test method, employing low-cycle fatigue, circumvents the difficulties arising from the continuous application of strain until fracture and determines the ductility indirectly from empirical low-cycle fatigue relationships for metals.

5.2 The results of ductility tests from selected portions of a metallic foil may not totally represent the ductility of the entire foil or its in-service behavior in different environments.

5.3 This test method is considered satisfactory for acceptance testing of commercial shipments, design purposes, service evaluation, manufacturing control, and research and development.

<sup>4</sup> Engelmaier, W., "A Method for the Determination of Ductility for Thin Metallic Materials," *Formability 2000 A.D.*, ASTM STP 753, ASTM, 1981, in press.

6. Apparatus

6.1 *Fatigue Ductility Flex Tester* as schematically shown in Fig. 1. A photograph of the tester is shown in Fig. 2.<sup>5</sup> The tester consists of a juxtaposed pair of precision test mandrels moving vertically a total of  $38 \pm 3$  mm ( $1\frac{1}{2} \pm \frac{1}{8}$  in.) at 50 cycles/min. The specimen, held in a horizontal position by six rollers and positioned between the two test mandrels, is subjected to cyclic flexural strains by being bent alternately around the two test mandrels. The precision test mandrels shall have uniform roundness, a maximum surface roughness height of 0.25  $\mu$ m (10  $\mu$ in.), and a minimum surface hardness of 60 HRC. The diameter of the test mandrels used shall be measured within 1 %. The specimen is held in an invariant position relative to the test mandrels by a tension weight. The tension weight, together with the specimen-holder loop (see Fig. 1), provides for precisely repeated contact between the specimen and the test mandrels. The weight tension also serves to assure conformance of the specimen to the test mandrel curvature. The tensile stress due to the tension weight shall not exceed 10 % of the yield strength (0.2 % offset, determined in accordance with Test Methods E 8 with the provisions in Test Methods E 345) of the material. A 100-g (3-oz) tension weight is suitable for most specimens; however, for very thin foil specimens it might be necessary to use a lighter tension weight.

6.2 *Double-Bladed Specimen Cutter*,<sup>6</sup> as required in Test Methods E 345, but capable of cutting specimens to the width required herein (Section 7).

7. Test Specimens

7.1 *Specimen Preparation*—Test specimens shall be prepared in accordance with Test Methods E 345, Type B speci-

<sup>5</sup> Model 2 FDF Flex Ductility Tester, manufactured in accordance with the original Bell Laboratories design, available from Universal Tool and Machine, Inc., 171 Coit St., Irvington, NJ 07111, has been found satisfactory.

<sup>6</sup> The Model JDC-125 Precision Sample Cutter, available from Thwing-Albert Instrument Co., 10960 Dutton Road, Philadelphia, PA 19154, has been found satisfactory.

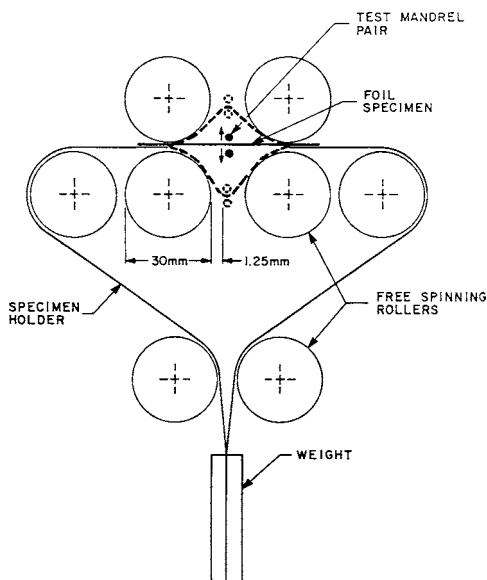


FIG. 1 Schematic of Fatigue Ductility Flex Tester Showing Principle of Operation

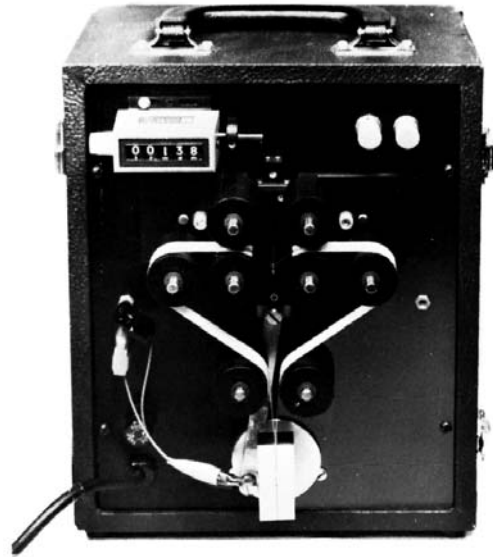


FIG. 2 Fatigue Ductility Flex Tester, Model 2 FDF

mens, with the dimensions as specified herein. The specimens may be prepared individually by use of a double-bladed cutter. The cutting edges of the blades should be lubricated with a material such as stearic acid in alcohol or other suitable material. The finished specimens shall be examined under about 20 $\times$  magnification to ascertain that the edges are smooth and that there are no surface scratches or creases. Specimens showing discernible surface scratches, creases, or edge discontinuities shall be rejected.

7.2 *Specimen Thickness*—Specimen thickness shall be determined in accordance with Test Methods E 345. The thickness of each specimen may be determined by any suitable means, provided that the thickness of each specimen is measured to an accuracy of 2 %.

NOTE 4—For specimens for which the density is not known, for example, plated foil, the thickness of the specimens will have to be measured directly even for soft materials or materials thinner than 0.025 mm (0.001 in.).

NOTE 5—For specimens with rough surfaces, it is necessary to determine the minimum core thickness, that is, the specimen thickness without the rough surface features, from a metallographic cross section, prepared in accordance with Methods E 3.

7.3 *Specimen Dimensions*—The test specimens shall have the following dimensions:

7.3.1 *Width*—2.5 to 7.5 mm (0.1 to 0.3 in.) with 3.2 mm (0.125 in.) the preferred width.

7.3.2 *Length*—30 mm (1.2 in.) minimum.

7.4 *Number of Specimens*—It is recommended that at least three specimens in both the main orientation direction (direction of rolling for wrought foil, direction of plating solution agitation for plated foil) and the orthogonal direction be tested.

7.5 *Mechanical Properties*—For purposes of performing the test and calculating the fatigue ductility, it is desirable to have available in both the main orientation direction and the orthogonal direction the following mechanical properties, obtained in accordance with the applicable standards such as Test