

---

---

**Carbon fibres — Determination of  
polyacrylonitrile-based (PAN-based)  
carbon fibre tow characteristics —  
Heat transfer parameter**

*Fibres de carbone — Détermination des caractéristiques du câble en  
fibres de carbone à base de polyacrylonitrile (PAN) — Paramètre de  
transfert de chaleur*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/TS 23483:2022](https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-d39d7377d757/iso-ts-23483-2022)

[https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-  
d39d7377d757/iso-ts-23483-2022](https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-d39d7377d757/iso-ts-23483-2022)



iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/TS 23483:2022

<https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-d39d7377d757/iso-ts-23483-2022>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
Introduction.....	v
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references.....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>1</b>
<b>4 Principle.....</b>	<b>1</b>
<b>5 Test devices.....</b>	<b>2</b>
<b>6 Test conditions on carbon fibre tow.....</b>	<b>3</b>
<b>7 Traceability — Calibration.....</b>	<b>3</b>
<b>8 Test procedures.....</b>	<b>3</b>
8.1 Type.....	3
8.2 Size.....	3
8.3 Thermal imaging camera.....	3
8.3.1 Working parameters of thermal imaging camera.....	3
8.4 Thermal imaging camera scan range on a sample.....	3
8.5 Sample preparations.....	4
8.5.1 Mounting and handling.....	4
8.6 No. of samples and no. of measurements.....	4
8.7 Data.....	4
<b>9 Test report.....</b>	<b>5</b>
<b>Annex A (informative) Typical set-up for heat transfer parameter measurement.....</b>	<b>6</b>
<b>Annex B (informative) Determination of 12 K carbon fibre tow heat transfer parameter.....</b>	<b>9</b>
<b>Bibliography.....</b>	<b>10</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

ISO/TS 23483:2022

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

Currently, contact-type (1) and noncontact-type thermal conductivity method (2) are used to measure the thermal conductivity. The contact-type method exhibits measurement non-uniformity in the carbon fibre thickness direction to unable uniform sampling, and the error occurrence rate is known to be high. Also, the noncontact-type method, fibre porosity and tow gap can create lower accuracy, and the error occurrence rate is similarly high. Therefore, this document is made to provide a quantitative method for the measurement of carbon fibre thermal conductivity, using a thermal imaging camera, that will alleviate problems observed in prior described methods.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/TS 23483:2022](https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-d39d7377d757/iso-ts-23483-2022)

<https://standards.iteh.ai/catalog/standards/sist/e84a24fa-d090-4b65-85f6-d39d7377d757/iso-ts-23483-2022>



# Carbon fibres — Determination of polyacrylonitrile-based (PAN-based) carbon fibre tow characteristics — Heat transfer parameter

## 1 Scope

This document specifies a method using a thermal imaging camera for measuring the heat transfer parameter of PAN-based 12 K carbon fibre tow with a filament diameter of 7 µm. This document is applicable to both sized and unsized carbon fibres.

NOTE At the time of publication, the experience is on 12 K tow. Other tows will be included when the experience becomes available.

## 2 Normative references

There are normative references in this document.

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### **carbon fibre**

fibrous carbon materials having a mass content of carbon element of 90 % or more, obtained by pyrolysis of organic materials

### 3.2

#### **carbon fibre tow**

untwisted bundle of continuous carbon fibre filaments

Note 1 to entry: The tow is provided in a wide variety of sizes from 1 K, 3 K, 6 K, 12 K, 24 K, etc. 12 K indicates 12 000 filaments. The 12 K carbon fibre tow used in this experiment has filaments with about 7 µm in diameter.

### 3.3

#### **polyacrylonitrile**

#### **PAN**

polymer of acrylonitrile

Note 1 to entry: PAN is a raw material used for the carbon fibre production.

[SOURCE: ISO 472:2013, 2.721, modified — A note to entry has been added.]


## 4 Principle

A thermal imaging camera is used to measure the temperature difference of the carbon fibre tow from one side of electrode A to the other side of electrode B (distance of  $15_{-0}^{+5}$  mm) between which the heating is measured (see [Figure 2](#)). According to the heating power and the cross-sectional area of the tow, the

heat transfer parameter of the carbon fibre tow is calculated by the Fourier's thermal conductivity law in 8.7.

## 5 Test devices

The test equipment shown in Figure 1 consists of thermal image camera, camera tripod, sample holder, and power supply.

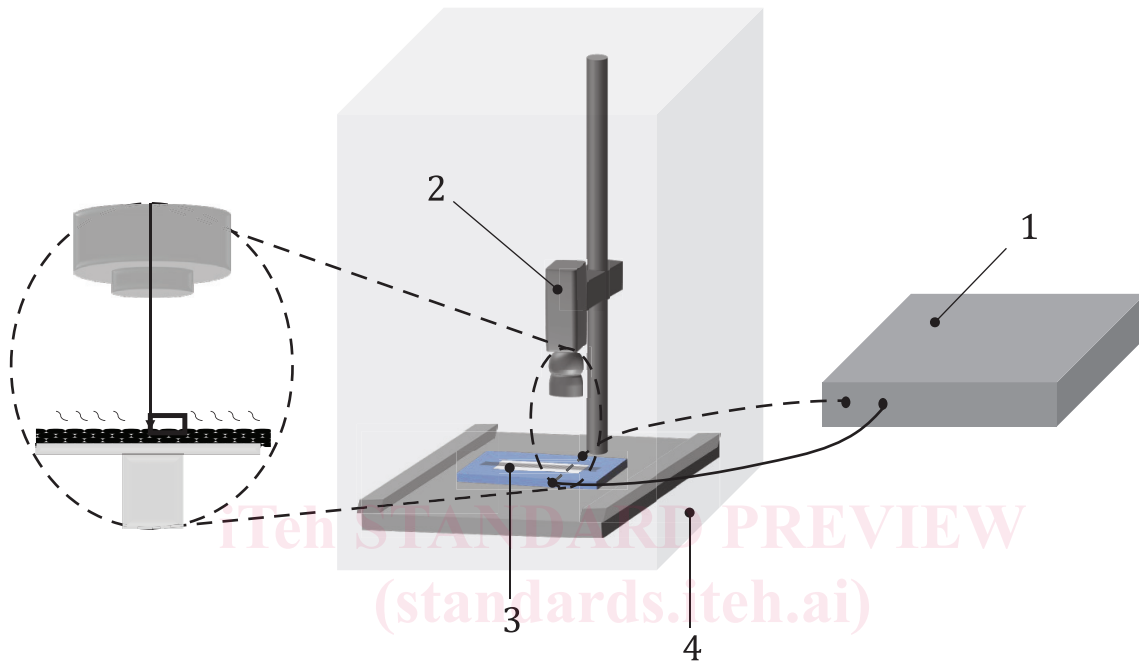

### Key

- 1 DC power supply
- 2 infrared thermal imaging camera
- 3 carbon fibre tow specimen
- 4 adiabatic black box chamber

Figure 1 — A typical diagram of carbon fibre tow heat transfer parameter measurement system

5.1 Thermal image camera, camera which can measure temperature gradient appeared on sample surface.

### 5.1.1 Resolution

The minimum requirement on resolution of the thermal image camera shall be 640 × 480 and the accuracy is within ±275 K of reading.

### 5.1.2 Emissivity

Emissivity is the total amount of thermal energy emitted per unit area per unit time for all possible wavelengths and is a value between 0 and 1. For carbon (graphite), emissivity value at 298 K is 0,97[3].

NOTE One of the most important conditions when measuring the temperature using a thermal image camera is the emissivity of the object to be measured. The emissivity determines how accurately the temperature can be measured. Therefore, each material has its unique emissivity value.

5.2 Sample holder, which consists of two copper electrodes, insulation cover, and clamps which are used to fix the carbon fibre tow in a straight line (see Figure A.1.) One of the electrode (see A in



[Figure 2.](#)) from which heat is transferred to the carbon fibre tow shall be a fixed part and the other electrode, B, shall be made of a moving part so as to enable adjustment the length of the carbon fibre tow located between the electrodes. When the carbon fibre tow is mounted in a straight line between two electrodes, tow is fixed with clamps at positions with electrode having insulation cover.

**5.3 Power supply**, a DC power supply having 50 V, 20 A with constant supply of 1 000 W power shall be used.

## 6 Test conditions on carbon fibre tow

When measuring heat transfer parameter, the temperature and the relative humidity shall be maintained at  $(296 \pm 2)$  °C and  $(50 \pm 10)$  %, respectively. The surroundings shall be maintained so as to not affect the temperatures being measured.

Convective chambers shall not be as the convective air can affect the carbon fibre tow temperature. A simple black box chamber has been shown to be effective in isolating the carbon fibre tow temperature from the surroundings.

## 7 Traceability — Calibration

The thermal imaging camera shall be calibrated once a year in accordance to the manufacture's recommendations [standard calibration procedure for radiation thermometers (CP801-50204-1) and the National Metrology Institute].

## 8 Test procedures [standards.iteh.ai](https://standards.iteh.ai)

### 8.1 Type

PAN-based 12K carbon fibre tow shall be used for measuring heat transfer parameter.

### 8.2 Size

The length of the carbon fibre tow should be  $100^{+5}_{-0}$  mm.

NOTE The total length of the carbon fibre tow does not have any significance and 100 mm length is chosen for the purpose of handling during the test.

### 8.3 Thermal imaging camera

#### 8.3.1 Working parameters of thermal imaging camera


When measuring the thermography image of the fibre with a thermal imaging camera, the temperature value of the sample is providing (emissivity, distance to the sample, and sample area) as camera correction values.

#### 8.4 Thermal imaging camera scan range on a sample

The temperature measurements shall be taken at electrode positions A (temperature  $T_1$ ) and B (temperature  $T_2$ ) using a thermal imaging camera as shown in [Figure 2](#). The temperature difference ( $\Delta T = T_1 - T_2$ ) is measured after reaching and stabilizing the temperature for 60 s.

The temperature  $T_1$  is the mean temperature value measured at two vertical positions at A' and A'' and  $T_2$  is the mean temperature taken at positions B' and B'' (see [Figure 2](#)).

NOTE A' and A'' are positions at electrode location A. They are vertically separated as shown in [Figure 2](#). Same for positions B' and B''.

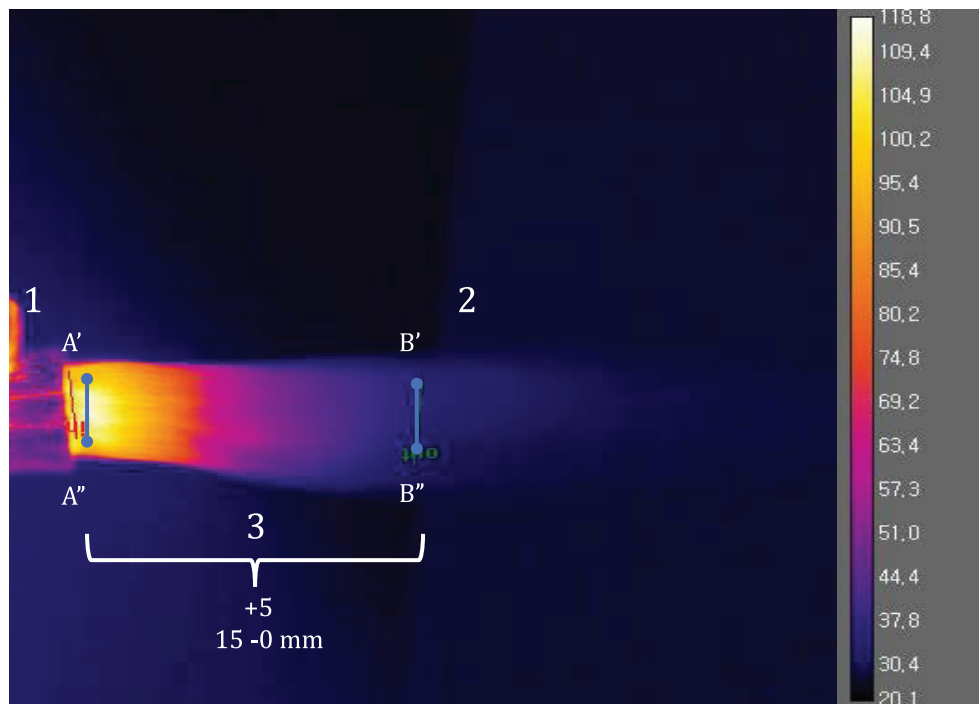

**Key**

- 1 T1 : the mean temperature value of two vertical positions at A' and A''
- 2 T2 : the mean temperature value of two vertical positions at B' and B''
- 3 length between electrodes

**Figure 2 — Thermography images of carbon fibre tow measurement**

**8.5 Sample preparations**

**8.5.1 Mounting and handling**

Mount the test sample on the tray and adjust the height of the cylinder until the thermal imaging camera make focus with the test sample. The distance between the thermal imaging camera and the sample shall be 200 mm to 300 mm.

**8.6 No. of samples and no. of measurements**

Minimum of five specimens shall be tested and at least 15 points shall be measured for each specimen.

If more than 30 points are measured consecutively for the accuracy of the measurement temperature, the test shall be stopped, and the test resumed with a minimum of 30 s rest.

**8.7 Data**

The data obtained from the thermal imaging camera is applied to the Fourier’s thermal conductivity formula [shown as [Formula \(1\)](#)] for calculating the heat transfer parameter value of the 12 K carbon fibre tow.

$$K = \frac{L}{\Delta T} \times \frac{Q}{A} \tag{1}$$