



SLOVENSKI STANDARD
SIST ISO 3547-7:2021

01-oktober-2021

Nadomešča:
SIST ISO 3547-7:2008

Drsni ležaji - Zvite puše - 7. del: Merjenje debeline stene tankostenskih puš

Plain bearings - Wrapped bushes - Part 7: Measurement of wall thickness of thin-walled bushes

iTeh STANDARD PREVIEW

Paliers lisses - Bagues roulées (Partie 7: Mesurage de l'épaisseur de paroi des bagues minces)

[SIST ISO 3547-7:2021](https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-0107d6306a8/sist-iso-3547-7-2021)

Ta slovenski standard je istoveten z: ISO 3547-7:2020

ICS:

21.100.10 Drsni ležaji Plain bearings

SIST ISO 3547-7:2021 **en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 3547-7:2021](#)

<https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021>

INTERNATIONAL
STANDARD

ISO
3547-7

Second edition
2020-05

**Plain bearings — Wrapped bushes —
Part 7:
Measurement of wall thickness of
thin-walled bushes**

Paliers lisses — Bagues roulées —

Partie 7: Mesurage de l'épaisseur de paroi des bagues minces

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

[SIST ISO 3547-7:2021](https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021)

<https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021>



Reference number
ISO 3547-7:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST ISO 3547-7:2021

<https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and units	2
5 Purpose of checking	2
6 Checking methods	2
6.1 Measuring principle.....	2
6.2 Line measurement around the circumference.....	3
6.3 Point measurement.....	4
7 Requirements for measuring equipment for the contact method	4
7.1 Radius of the measuring pin on the outside surface.....	4
7.2 Radius of the measuring pin on the inside surface.....	5
7.3 Measuring pin load.....	5
8 Checking of measuring equipment	5
Bibliography	6

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 3547-7:2021](https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021)

<https://standards.iteh.ai/catalog/standards/sist/3126938e-c7ff-4929-b84a-6fb07d0506a8/sist-iso-3547-7-2021>

ISO 3547-7:2020(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 123, *Plain bearings*, Subcommittee SC 5, *Quality analysis and assurance*.

This second edition cancels and replaces the first edition (ISO 3547-7:2007), which has been technically revised.

The main changes compared to the previous edition are as follows:

- [Clauses 2, 3, 4, 5, 6, 7](#) and [8](#) have been updated;
- [Figure 3](#) has been updated;
- [Figure 5](#) has been implemented.

A list of all parts in the ISO 3547 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Plain bearings — Wrapped bushes —

Part 7:

Measurement of wall thickness of thin-walled bushes

1 Scope

This document describes, following ISO 12301, the checking methods and measuring equipment used for measuring the total wall thickness of thin-walled bushes in the finished state.

NOTE All dimensions in this document are given in millimetres.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 12301, *Plain bearings — Quality control techniques and inspection of geometrical and material quality characteristics*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>


3.1

wall thickness

s_3

radial distance between the opposing measuring points at the inner and outer cylindrical surface

Note 1 to entry: See [Figure 1](#).

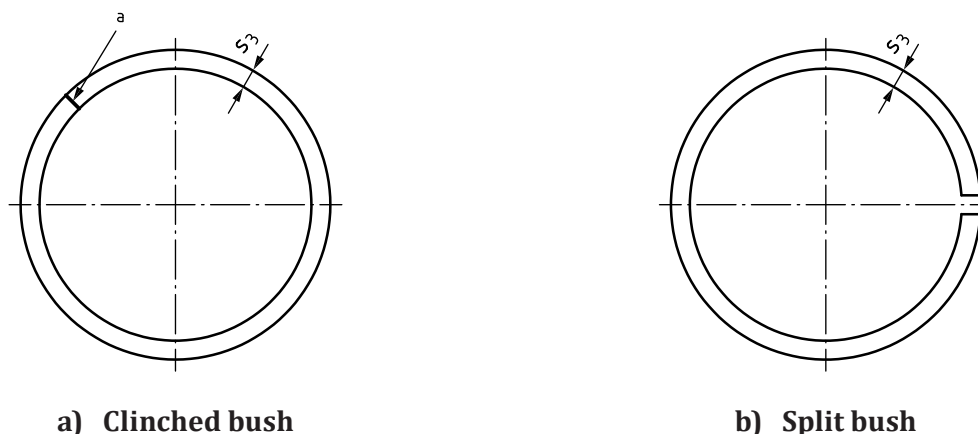

a Clinch.

Figure 1 — Wall thickness, s_3

4 Symbols and units

For the purposes of this document, the symbols and units given in Table 1 apply.

Table 1 — Symbols and units

Symbol	Parameter	SI unit
a_{ch}	axial distance to measuring position from the edge of the bush	millimetre
B	width of the bush	millimetre
D_o	outside diameter of the bush	millimetre
F_{pin}	measuring pin load	newton
M	number of measuring lines	—
s_3	wall thickness	millimetre

5 Purpose of checking

The purpose of checking is to ensure that the wall thickness and wall thickness tolerances are in accordance with ISO 3547-1. If this measurement is required, it is designated by s_3 ; see ISO 3547-1.

6 Checking methods

6.1 Measuring principle

The gauging axis of the measuring device shall be in the radial direction and perpendicular to the outside surface of the test piece in order to find the minimum value of the wall thickness. The measured values may be recorded by a single measurement or by a sum measurement, as represented symbolically in Figure 2.

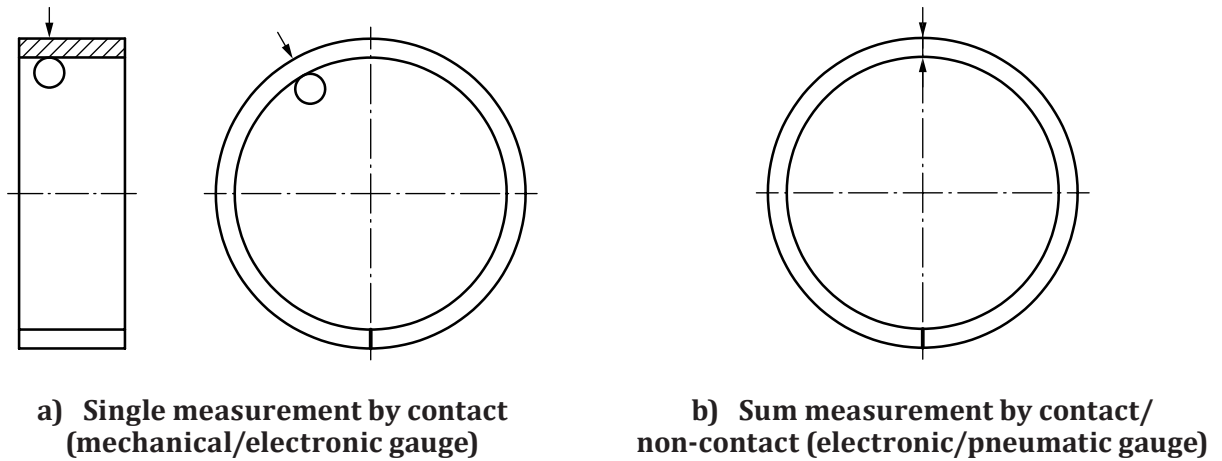



Figure 2 — Measuring principle of wall thickness measurement

The presence of lubricating holes, oil pockets, oil grooves, markings or special chamfers can require deviation from the measuring lines and measuring points specified in 6.2 and 6.3. Any such deviation shall be agreed between customer and supplier.

Any wall thickness not conforming to the specified values due to the manufacturing process, because of deformation of the bearing backing in the area of marking or at non-load-bearing places of wrapped bushes, shall be agreed between customer and supplier.

6.2 Line measurement around the circumference

Continuous measurement of the wall thickness around the circumference shall be carried out at the measuring lines specified in Figure 3 and Table 2.

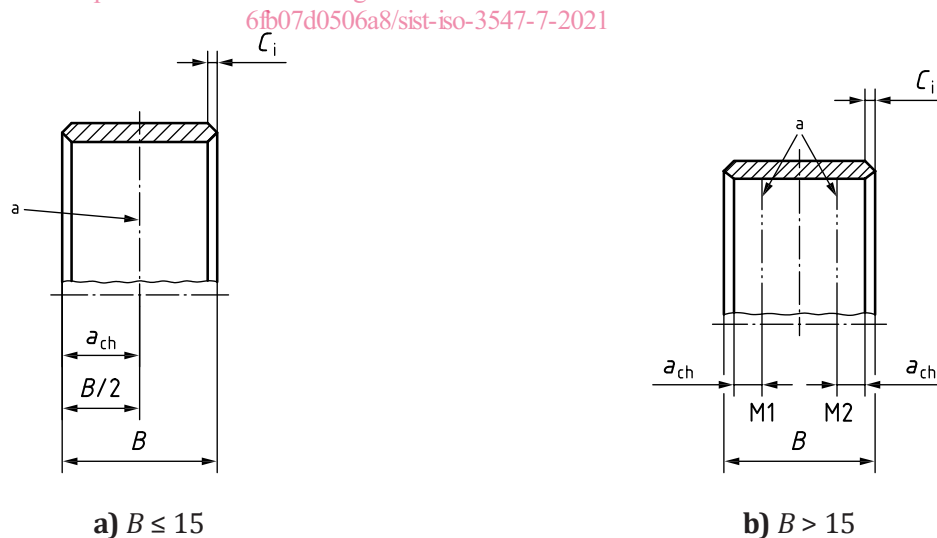

Key

- B bearing width
- a_{ch} distance of measuring position
- C_i lateral limitation of sliding surface
- a Measuring lines, M .

Figure 3 — Position of measuring lines

Table 2 — Distance of measuring position a_{ch}


Width B mm	Distance to measuring position a_{ch} mm	Number of measuring lines M
$B < 15$	$B/2$	1
$15 < B < 50$	$C_i + 4$	2^a
$50 < B < 90$	$C_i + 4$	2^a
$B > 90$	$C_i + 8$	2^b

^a Only valid for: $C_i + 4 \text{ mm} \leq B/2 - 2 \text{ mm}$, otherwise only one measuring line should be used.

^b Only valid for: $C_i + 8 \text{ mm} \leq B/2 - 2 \text{ mm}$, otherwise only one measuring line should be used.

6.3 Point measurement

Point-by-point measurement of wall thickness shall be carried out at the measuring points specified in [Figure 4](#) for widths of $B \leq 90 \text{ mm}$ and outside diameter $D_o \leq 150 \text{ mm}$. In the case where $B > 90 \text{ mm}$ and $D_o > 150 \text{ mm}$, the measurement method shall be subject to agreement between the supplier and user. The measuring position distance, a_{ch} , shall be taken from [Table 2](#).

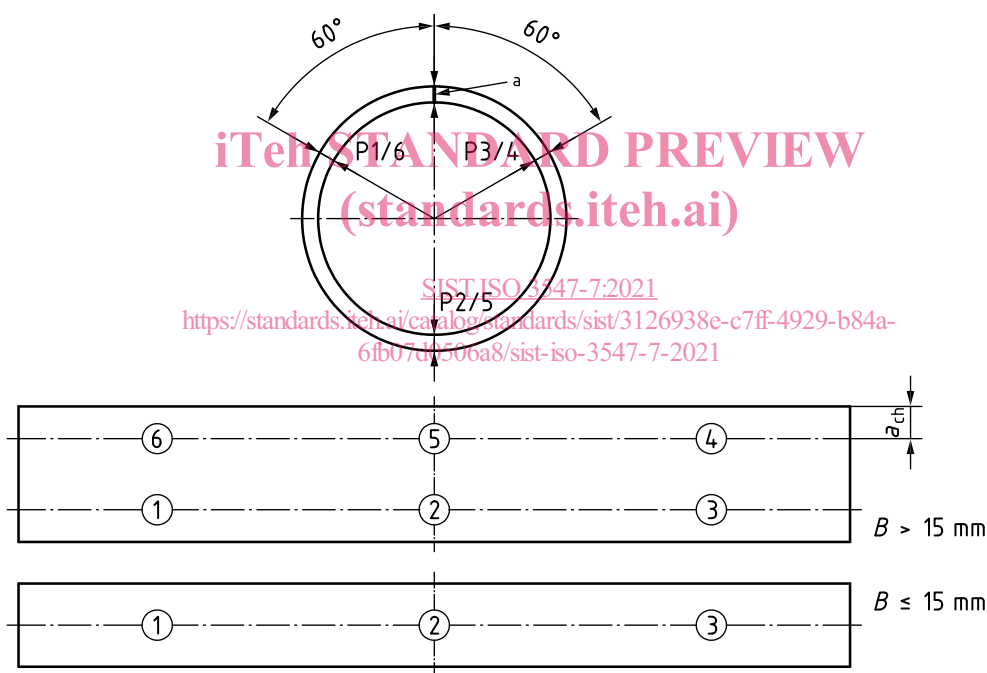

Key

- P measuring point
^a Split position.

NOTE [Figure 4](#) shows the three- or six-point measuring scheme on the bearing and in a developed view, depending on part width.

Figure 4 — Three- or six-point measuring scheme

7 Requirements for measuring equipment for the contact method

7.1 Radius of the measuring pin on the outside surface

The radius of the measuring pin positioned on the outside as shown in [Figure 5](#) shall be $1,5 \text{ mm} \pm 0,2 \text{ mm}$.