



SLOVENSKI STANDARD
SIST-TS CEN/TS 927-12:2023

01-julij-2023

**Barve in laki - Premazi in premazni sistemi za zaščito lesa za zunanjo uporabo - 12.
del: Prepustnost ultravijoličnih in vidnih žarkov**

Paints and varnishes - Coating materials and coating systems for exterior wood - Part
12: Ultraviolet and visible radiation transmittance

Beschichtungsstoffe - Beschichtungsstoffe und Beschichtungssysteme für Holz im
Außenbereich - Teil 12: Durchlässigkeit für ultraviolette und sichtbare Strahlung

Peintures et vernis - Produits de peinture et systèmes de peinture pour le bois extérieur -
Partie 12: Transmission du rayonnement ultraviolet et visible

Ta slovenski standard je istoveten z: CEN/TS 927-12:2023

ICS:

71.100.50	Kemikalije za zaščito lesa	Wood-protecting chemicals
87.040	Barve in laki	Paints and varnishes

SIST-TS CEN/TS 927-12:2023 **en**

TECHNICAL SPECIFICATION
SPÉCIFICATION TECHNIQUE
TECHNISCHE SPEZIFIKATION

CEN/TS 927-12

May 2023

ICS 87.040

English Version

Paints and varnishes - Coating materials and coating systems for exterior wood - Part 12: Ultraviolet and visible radiation transmittance

Peintures et vernis - Produits de peinture et systèmes de peinture pour le bois extérieur - Partie 12: Transmission du rayonnement ultraviolet et visible

Beschichtungsstoffe - Beschichtungsstoffe und Beschichtungssysteme für Holz im Außenbereich - Teil 12: Durchlässigkeit für ultraviolette und sichtbare Strahlung

This Technical Specification (CEN/TS) was approved by CEN on 24 March 2023 for provisional application.

The period of validity of this CEN/TS is limited initially to three years. After two years the members of CEN will be requested to submit their comments, particularly on the question whether the CEN/TS can be converted into a European Standard.

CEN members are required to announce the existence of this CEN/TS in the same way as for an EN and to make the CEN/TS available promptly at national level in an appropriate form. It is permissible to keep conflicting national standards in force (in parallel to the CEN/TS) until the final decision about the possible conversion of the CEN/TS into an EN is reached.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents	Page
European foreword	3
Introduction	4
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions.....	5
4 Abbreviations.....	5
5 Principle.....	6
6 Apparatus and materials.....	6
6.1 Film applicator for coating material.....	6
6.2 Substrate for free coating film preparation	6
6.2.1 Preparation of free film and test specimen.....	6
6.2.2 Coating application	6
6.3 Film thickness measurement	7
6.4 UV/VIS spectrophotometer	7
6.5 Long-pass filter specification for check.....	8
7 Test procedure.....	8
7.1 Test procedure with spectrophotometer.....	8
7.2 Check of spectrophotometer with long-pass filter	9
7.3 Spectral transmittance of the specimen (film)	9
7.4 Calculation of transmittance.....	10
8 Precision	10
9 Test report.....	10
Annex A (normative) Spectral transmittance of long-pass filter.....	12
Annex B (informative) Application and evaluation references	13
Bibliography	14

European foreword

This document (CEN/TS 927-12:2023) has been prepared by Technical Committee CEN/TC 139 “Paints and varnishes — Coating materials and coating systems for exterior wood — Ultraviolet and visible radiation transmittance”, the secretariat of which is held by DIN.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

Any feedback and questions on this document should be directed to the users’ national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN/CENELEC Internal Regulations, the national standards organisations of the following countries are bound to announce this Technical Specification: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST-TS CEN/TS 927-12:2023

<https://standards.iteh.ai/catalog/standards/sist/df94bc30-c746-4112-8a00-96a3cd0a70a5/sist-ts-cen-ts-927-12-2023>

Introduction

Wood is a natural material that must be protected against solar radiation, heat, rain, and microorganisms to maintain its appearance and mechanical integrity when used outdoors. Wood and its components (especially lignin) are sensitive to photo oxidation and must therefore be protected by suitable coatings, particularly against ultraviolet (UV) and visible (VIS) radiation in the violet and blue region.

Clear and transparent coating films may be modified by fine sized transparent (mostly yellow or red ferrous oxide-based) pigments and more or less colourless, organic and inorganic UV-absorbers to reduce the harmful part of solar radiation. As these additives are not visible, there is a demand for a test method to determine their efficiency.

The transmittance in a specific wavelength range allows to evaluate the UV and VIS radiation protection of a coating film.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST-TS CEN/TS 927-12:2023](https://standards.iteh.ai/catalog/standards/sist/df94bc30-c746-4112-8a00-96a3cd0a70a5/sist-ts-cen-ts-927-12-2023)

<https://standards.iteh.ai/catalog/standards/sist/df94bc30-c746-4112-8a00-96a3cd0a70a5/sist-ts-cen-ts-927-12-2023>

1 Scope

This document describes a test method to measure the ultraviolet (UV) and visible (VIS) spectral transmittance in the wavelength range from 280 nm to 700 nm of coatings for exterior wood. From the spectral transmittance the transmittance of UV, VIS and the combined UV and VIS wavelength range can be calculated.

It is applicable to free coatings films or coatings applied on a UV-transparent substrate.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 2808, *Paints and varnishes - Determination of film thickness (ISO 2808)*

EN ISO 4618, *Paints and varnishes - Terms and definitions (ISO 4618)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 4618 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

transmittance

τ

quotient of transmitted radiant flux, Φ_t , and incident radiant flux, Φ_m

$$\tau = \frac{\Phi_t}{\Phi_m}$$

Note 1 to entry: Transmittance is also defined spectrally in terms of wavelength, in which case, "spectral" is added before the quantity name.

Note 2 to entry: Due to energy conservation, $\alpha + \rho + \tau = 1$ except when polarized radiation is observed, where α is absorptance and ρ is reflectance.

Note 3 to entry: Transmittance, τ , is the sum of regular transmittance, τ_r , and diffuse transmittance, τ_d : $\tau = \tau_r + \tau_d$.

Note 4 to entry: The transmittance has unit one.

[SOURCE: CIE S 017:2020]

4 Abbreviations

UV ultraviolet radiation in the wavelength range from 280 nm to 400 nm

VIS visible radiation in the wavelength range from 400 nm to 700 nm

5 Principle

The UV and VIS transmittance through a coating film is measured using an UV/VIS spectrophotometer equipped with a radiation source, a limiting aperture, an integrating sphere (Ulbricht sphere), and a spectroradiometer with a diffraction element and a detector.

A beam of optical radiation, limited by an aperture, with an incident radiant flux Φ_m is directed on a film specimen. The transmitted radiant flux Φ_t enters an integrating sphere. The sphere is equipped with the input optics of a spectroradiometer with which spectrally resolved measurements of the unfiltered $\Phi_m(\lambda)$ and the filtered (transmitted) radiant flux $\Phi_t(\lambda)$ can be performed. The quotient $\Phi_t(\lambda)/\Phi_m(\lambda)$ is the spectral transmittance $\tau(\lambda)$. $\tau(\lambda)$ multiplied by 100 represents the percentage of the transmitted radiant flux at a specific wavelength or wavelength range passing through the film compared to the incident radiant flux $\Phi_m(\lambda)$. From the spectral transmittance, the transmittance in a specific wavelength range can be calculated as described in 7.4.

The spectral transmittance is recorded in wavelength increments over the entire wavelength range of 280 nm to 700 nm continuously during a wavelength scanning (e.g. in 2 nm to 10 nm steps depending on the apparatus used and the resolution needed). Depending on the application the transmittance of the specific wavelength ranges for UV, VIS, and UV+VIS can be calculated.

6 Apparatus and materials

6.1 Film applicator for coating material

A suitable doctor blade to apply coatings films of defined wet layer thickness shall be used. As an example for high build wood stains a dry film thickness of approximately 90 μm to 120 μm should be achieved.

6.2 Substrate for free coating film preparation

6.2.1 Preparation of free film and test specimen

A clean and plane substrate shall be used to apply the wet coating materials to prepare the free coating films of correct uniform layer thickness. Ideal as substrate to separate later the coating film without damage is a PTFE¹⁾ coated smooth metal plate or a PE-, PP-foil, or silicone paper fixed on e.g. a smooth glass or metal plate. In case of low viscosity coatings silicone rubber rings can be used after balancing them horizontally, on e.g. a glass plate to fill in the liquid coating material. The coating material normally is sufficiently dry after a minimum of 7 days or better of 28 days at $(23 \pm 2)^\circ\text{C}$ at $(50 \pm 5)\%$ relative humidity (according to EN 23270) or as per the coating supplier's specification.

NOTE Soaking in water is another suitable method for the detachment of free films from a substrate. But this method of preparation of free films can influence the test results. The usual method for preparation of free films is without using water on a low energy substrate such as polypropylene. Alternatively, the coatings can be measured directly on a UV-transparent substrate like quartz.

For each coating, a minimum of three specimens shall be cut out from a uniform section of the film without any damages. The size of the specimens shall be adjusted to the specific spectrophotometer under use.

6.2.2 Coating application

The coating shall be applied on a 1 mm to 2 mm thick quartz substrate with a spectral transmittance of at least 90 % in the wavelength range from 280 nm to 700 nm.

¹⁾ PTFE – Poly tetra fluoro ethylene.

6.3 Film thickness measurement

The film thickness shall be measured according to EN ISO 2808.

6.4 UV/VIS spectrophotometer

The following are the minimum requirements for the UV/VIS spectrophotometer:

- a) Wavelength range: 280 nm to 700 nm;
- b) Radiation source: alternatively or both:
 - 1) Deuterium,
 - 2) FEL (quartz halogen lamp);
- c) Limiting aperture: defines the radiation beam so that all radiation enters the integrating sphere;
- d) Integrating sphere: to guarantee that all transmitted radiation is measured:
 - 1) cosine response. the normalized response matches the ideal cosine function to within 6 % of the cosine value up to incident angles of 60° and to within 8 % up to 80°,
 - 2) minimum sphere diameter 50 mm (see Note 4),
 - 3) maximum size of the input aperture: 20 % of the sphere diameter,
 - 4) barium sulphate or PTFE-coated.
- e) Spectro-radiometer: to measure the spectral irradiance:
 - 1) stray light suppression: dynamic range 3 decades (see NOTE 1),
 - 2) dark current correction: shall be performed as appropriate (see NOTE 2),
 - 3) higher order correction: shall be performed as appropriate (see NOTE 3),
 - 4) facility for wavelength calibration,
 - 5) wavelength resolution 2 nm,
 - 6) measuring increments at least 2 nm,
 - 7) detector sensitive in the wavelength range from 280 nm to 700 nm.
- f) Software to calculate the spectral transmittance.

NOTE 1 Stray light level is the ratio of a measured signal in the blocking range of an absorption filter to the maximum desired signal. Stray light results from a wavelength range which is not part of the measured wavelength range and depends on the used radiation source and the geometry of the spectrophotometer. Stray light influences the dynamic range of the spectrophotometer.

NOTE 2 Dark current is related to the noise of the electronic amplifier (signal-to-noise ratio).


NOTE 3 State of the art spectrophotometers provide high order correction automatically with appropriate filters.

FprCEN/TS 927-12:2022 (E)

NOTE 4 The diameter of the integrating sphere can have an influence on the measurement. A larger diameter might lead to more accurate results, but this needs to be balanced with the amount of signal that the detector is capable of measuring

6.5 Long-pass filter specification for check

The long-pass filter shall have a transmittance lower than 10^{-4} in the absorption range. The 50 % transmittance shall be in the range from 320 nm to 360 nm (example of transmittance see Figure 1).

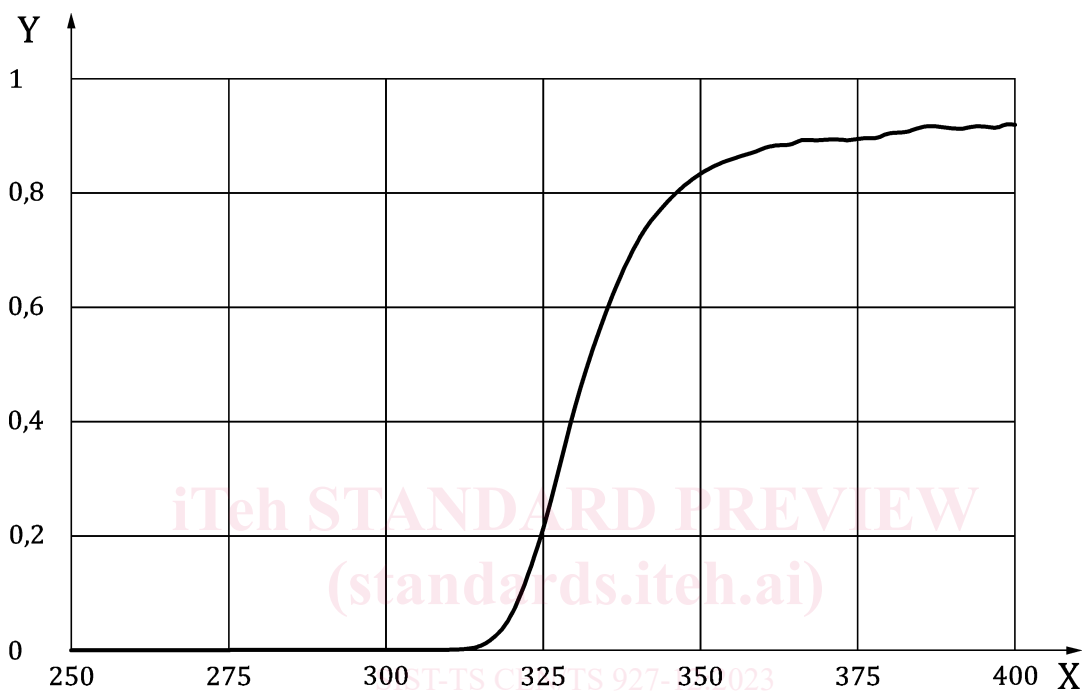

Key

X wavelength, in nanometers

Y spectral transmittance

Figure 1 — Example of a spectral transmittance of an long-pass filter.

The filter can be used to check the performance of a UV/VIS spectrophotometer.

7 Test procedure

7.1 Test procedure with spectrophotometer

7.1.1 Measure the spectral distribution ($\Phi_m(\lambda)$) with the spectrophotometer without any filter or films. Dark current measurement and higher order correction shall be provided as appropriate.

NOTE Information about dark current measurement and higher order correction are provided by the instrument manufacturer.

7.1.2 Mount the prepared specimen as close as possible to the entrance port of the integrating sphere to ensure that even scattered radiation enters the sphere.

NOTE The operative instructions and size of the requested specimens depends on the type of spectrophotometer used.