

ISO/TC 35/SC 9

Secretariat: BSI

Voting begins on:
2022-12-05

Voting terminates on:
2023-01-30

Paints and varnishes — Coating systems for wind-turbine rotor blades —

Part 5: Measurement of transmittance properties of UV protective coatings

Matériaux de revêtement pour pales de turbines éoliennes —

Partie 5: Mesurage des propriétés du facteur de transmission des revêtements de protection anti UV

ISO/TS 19392-5

<https://standards.iteh.ai/catalog/standards/sist/3aba6158-4f19-4906-9f5c-41ce05274d76/iso-ts-19392-5>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/DTS 19392-5:2022(E)

© ISO 2022

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/TS 19392-5

<https://standards.iteh.ai/catalog/standards/sist/3aba6158-4f19-4906-9f5c-41ce05274d76/iso-ts-19392-5>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus and materials	2
5.1 Film applicator for coating material.....	2
5.2 Substrate for free coating film preparation.....	2
5.2.1 Preparation of free film and test specimen.....	2
5.2.2 Coating application.....	3
5.3 Film thickness measurement.....	3
5.4 UV/VIS spectrophotometer.....	3
5.5 Long pass specification for check.....	4
6 Test procedure	4
6.1 Test procedure with spectrophotometer.....	4
6.2 Check of spectrophotometer with long pass filter.....	5
6.3 Spectral transmittance of the specimen (film).....	6
6.4 Calculation of transmittance.....	6
7 Precision	6
8 Test report	6
Annex A (normative) Check of the spectral transmittance of the long pass filter	8
Annex B (informative) Application and evaluation references	9
Bibliography	11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

A list of all parts in the ISO 19392 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

In the wind energy industry, coatings are applied to rotor blades surface to protect the glass fibre reinforced polymer composite substrate from environmental stresses. Rain drops and hailstones can damage these coatings in such a way that individual layers come off or the whole coating delaminates from the substrate. This applies mostly to the leading edge. Glass fibre reinforced polymer composites and other blade materials can be also sensitive to UV degradation and thus can be damaged during outdoor operation, if not protected accurately against irradiation by solar radiation. Failure of protection can lead to delamination and a subsequent failure of the full blade.

An important function of the rotor blade coating is therefore to protect the blade material from UV radiation. This applies to the leading edge, but also to the other surface areas of the blade.

The damage by solar radiation is mainly induced by the most energetic ultraviolet (UV) radiation, but also visible (VIS) radiation (e.g. violet or blue radiation) is still energetic enough to have a negative input on the appearance and durability of the blade.

Pigments and organic or inorganic UV absorbers can be used to reduce the coating film transmittance against UV (and visible) radiation and cause a positive effect on lifetime and functional aspects of the blade material. Pigments and UV absorbers can affect the transmittance in the visible range. This may lead to colour change of the coated blade.

This document, as part of the ISO 19392 series on rotor blade coatings, describes a method to measure the spectral transmittance or the transmittance in a specific wavelength range. This allows evaluating the UV and VIS radiation protection quality of a coatings film on the sensitive blade substrate below. The focus is to avoid damage of the blade by natural solar radiation especially caused by the most energetic part, the ultraviolet and short wavelength visible radiation.

ISO/TS 19392-5

<https://standards.iteh.ai/catalog/standards/sist/3aba6158-4f19-4906-9f5c-41ce05274d76/iso-ts-19392-5>

Paints and varnishes — Coating systems for wind-turbine rotor blades —

Part 5: Measurement of transmittance properties of UV protective coatings

1 Scope

This document specifies a test method to measure the ultraviolet (UV) and visible (VIS) spectral transmittance in the wavelength range from 280 nm to 700 nm of coatings for wind turbine rotor blades. Single and multilayer coatings or coating systems can be tested.

From the spectral transmittance the transmittance of UV, VIS and the combined UV and VIS wavelength range can be calculated.

It is applicable to free coatings films or coatings applied on a UV-transparent quartz substrate.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3270, *Paints and varnishes and their raw materials — Temperatures and humidities for conditioning and testing*

ISO 2808, *Paints and varnishes — Determination of film thickness (ISO 2808)*

ISO 4618, *Paints and varnishes — Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4618 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1 transmittance

τ

quotient of transmitted radiant flux, Φ_t , and incident radiant flux, Φ_m , $\tau = \frac{\Phi_t}{\Phi_m}$

Note 1 to entry: Transmittance is also defined spectrally in terms of wavelength, in which case, “spectral” is added before the quantity name.

Note 2 to entry: Due to energy conservation, $\alpha + \rho + \tau = 1$ except when polarized radiation is observed, where α is absorptance and ρ is reflectance.

Note 3 to entry: Transmittance, τ , is the sum of regular transmittance, τ_r , and diffuse transmittance, τ_d : $\tau = \tau_r + \tau_d$.

Note 4 to entry: The transmittance has unit one.

[SOURCE: CIE S 017:2020; 17-24-065]

3.2 ultraviolet radiation

UV
radiation in a wavelength range from 280 nm to 400 nm

3.3 visible radiation

VIS
radiation in a wavelength range from 400 nm to 700 nm

4 Principle

The UV and VIS transmittance through a coating film is measured using an UV/VIS spectrophotometer equipped with a radiation source, a limiting aperture, an integrating sphere, and a spectroradiometer with a diffraction element and a detector. See Annex B for application and evaluation references.

A beam of optical radiation, limited by an aperture, with an incident radiant flux, Φ_m , is directed on a film specimen. The transmitted radiant flux, Φ_t , enters an integrating sphere. The sphere is equipped with the input optics of a spectroradiometer with which spectrally resolved measurements of the unfiltered radiant flux $\Phi_m(\lambda)$ and the filtered (transmitted) radiant flux $\Phi_t(\lambda)$ can be performed. The quotient $\Phi_t(\lambda)/\Phi_m(\lambda)$ is the spectral transmittance $\tau(\lambda)$.

NOTE $\tau(\lambda)$ multiplied by 100 represents the percentage of the transmitted radiant flux at a specific wavelength or wavelength range passing through the film compared to the incident radiant flux $\Phi_m(\lambda)$.

From the spectral transmittance, the transmittance in a specific wavelength range can be calculated as described in 6.4.

The spectral transmittance is recorded in wavelength increments over the entire wavelength range of 280 nm to 700 nm continuously during a wavelength scanning (e.g. in 2 nm to 10 nm steps depending on the apparatus used and the resolution needed). Depending on the application the transmittance of the specific wavelength ranges for UV, VIS and UV + VIS can be calculated.

5 Apparatus and materials

5.1 Film applicator for coating material

A suitable blade or spatula to apply coatings films of defined wet layer thickness shall be used.

NOTE A typical dry layer thickness is approx. 90 μm to 120 μm .

5.2 Substrate for free coating film preparation

5.2.1 Preparation of free film and test specimen

A clean and plane substrate shall be used to apply the wet coating materials to prepare the free coating films of correct uniform layer thickness. For a substrate to separate the coating film without damage, it is ideal to use a polytetrafluoroethylene (PTFE) coated smooth metal plate or a PE-, PP-foil or silicone paper fixated on a smooth glass or metal plate, for example. In case of lower viscosity coatings, silicone rubber rings can be used after balancing them horizontally, on a glass plate to fill in the liquid coating material for example. The coating material shall be sufficiently dry. This normally requires drying for a

minimum of 7 days or better, 28 days at $(23 \pm 2) ^\circ\text{C}$ at $(50 \pm 10) \%$ relative humidity in accordance with ISO 3270 or as per the coating supplier's specification.

NOTE Soaking in water is another suitable method for the detachment of free films from a substrate. However, this method of preparation of free films can influence the test results. The usual method for preparation of free films is without using water on a low energy substrate such as polypropylene. Alternatively, the coatings can be measured directly on a UV-transparent substrate like quartz.

For each coating, a minimum of three specimens shall be cut out from a uniform section of the film without any damages. The size of the specimens shall be adjusted to the specific spectrophotometer under use.

5.2.2 Coating application

The coating shall be applied on a 1 mm to 2 mm thick quartz substrate with a spectral transmittance of at least 90 % in the wavelength range from 280 nm to 700 nm.

5.3 Film thickness measurement

The film thickness shall be measured in accordance with ISO 2808.

5.4 UV/VIS spectrophotometer

The following are the minimum requirements for the UV/VIS spectrophotometer:

- a) wavelength range: 280 nm to 700 nm;
- b) Radiation source: alternatively or both:
 - 1) Deuterium,
 - 2) 1000 W quartz halogen lamp [FEL lamp (see Reference [5])];
- c) Limiting aperture: defines the radiation beam so that all radiation enters the integrating sphere;
- d) Integrating sphere: to guarantee that all transmitted radiation is measured, including:
 - 1) cosine response. The normalized response matches the ideal cosine function to within 6 % of the cosine value up to incident angles of 60° and to within 8 % up to 80° ,
 - 2) minimum sphere diameter 50 mm (see NOTE 4);
 - 3) maximum size of the input aperture: 20 % of the sphere diameter;
 - 4) barium sulfate or PTFE coated;
- e) Spectroradiometer: to measure the spectral irradiance:
 - 1) stray light suppression: dynamic range 3 decades (see NOTE 1),
 - 2) dark current correction: shall be performed appropriate (see NOTE 2),
 - 3) higher order correction: shall be performed appropriate (see NOTE 3),
 - 4) facility for wavelength calibration,
 - 5) wavelength resolution 2 nm,
 - 6) measuring increments at least 2 nm,
 - 7) detector sensitive in the wavelength range from 280 nm to 700 nm;
- f) software to calculate the spectral transmittance.

NOTE 1 Stray light level is the ratio of a measured signal in the blocking range of an absorption filter to the maximum desired signal. Stray light results from a wavelength range which is not part of the measured wavelength range and depends on the used radiation source and the geometry of the spectrophotometer. Stray light influences the dynamic range of the spectrophotometer.


NOTE 2 Dark current is connected to the noise of the electronic amplifier (signal-to-noise ratio).

NOTE 3 State of the art spectrophotometers provide high order correction automatically with appropriate filters.

NOTE 4 The diameter of the integrating sphere can have an influence on the measurement. A larger diameter can lead to more accurate results, but the limiting factor is the amount of signal that the detector is capable of measuring.

5.5 Long pass specification for check

The long pass filter shall have a transmittance lower than 10^{-4} in the absorption range. The 0,5 transmittance shall be in the range from 320 nm to 360 nm. See [Figure 1](#) for an example.

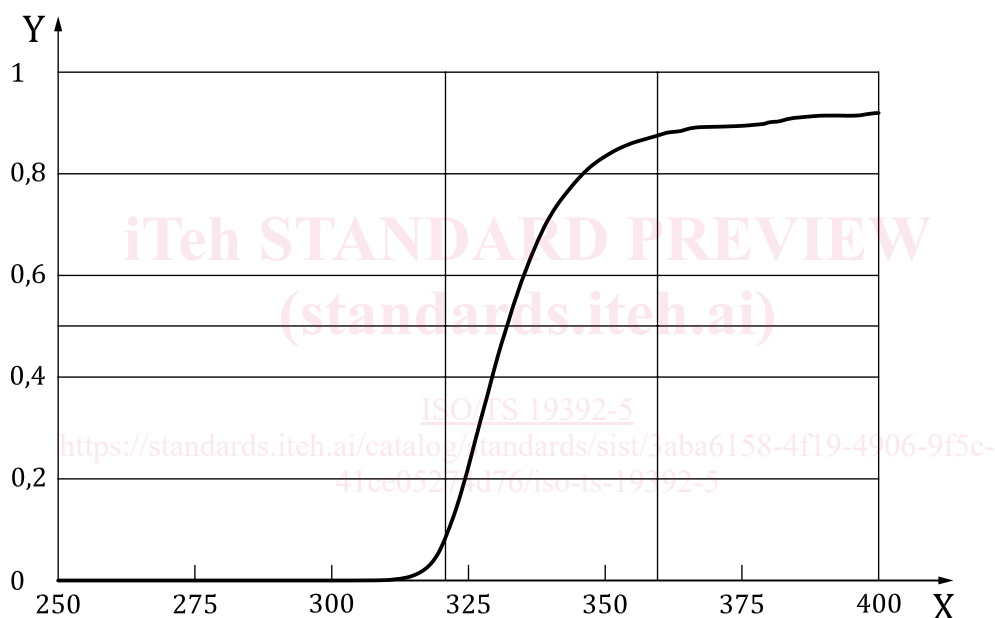

Key

X wavelength, in nanometres

Y spectral transmittance

Figure 1 — Example of a spectral transmittance of an absorption filter.

The filter can be used to check the performance of a UV/VIS spectrophotometer.

6 Test procedure

6.1 Test procedure with spectrophotometer

6.1.1 Measure the spectral irradiance with the spectrophotometer without any filter or films. Dark current measurement and higher order correction shall be provided, if appropriate.

NOTE Information about dark current measurement and higher order correction are provided by the instrument manufacturer.