



Designation: A 947M – 95 (Reapproved 2000)

METRIC

## Standard Specification for Textured Stainless Steel Sheet [Metric]<sup>1</sup>

This standard is issued under the fixed designation A 947M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This specification covers stainless steel, textured sheets, especially for use in electronic packaging applications, for example, cabinet, rack, enclosure, and shelf constructions for telecommunication, computer, and data-processing equipment.

1.2 This specification applies to all finished flat-rolled stainless products specified by standards organizations such as International Standards Organization (ISO), American Society for Testing and Materials (ASTM), European Committee for Standardization (CEN), German Institute for Standardization (DIN), and others participating in a global standards harmonization effort.

1.3 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

### 2. Referenced Documents

#### 2.1 ASTM Standards:

- A 176 Specification for Stainless and Heat-Resisting Chromium Steel Plate, Sheet, and Strip<sup>2</sup>
- A 370 Test Methods and Definitions for Mechanical Testing of Steel Products<sup>2</sup>
- A 480/A480M Specification for General Requirements for Flat-Rolled Stainless and Heat-Resisting Steel Plate, Sheet, and Strip<sup>2</sup>
- A 700 Practices for Packaging, Marking, and Loading Methods for Steel Products for Domestic Shipment<sup>3</sup>
- A 751 Test Methods, Practices, and Terminology for Chemical Analysis of Steel Products<sup>2</sup>
- B 117 Practice for Operating Salt Spray (Fog) Apparatus<sup>4</sup>
- B 193 Test Method for Resistivity of Electrical Conductor Material<sup>5</sup>

D 257 Test Methods for D-C Resistance or Conductance of Insulating Materials<sup>6</sup>

D 523 Test Method for Specular Gloss<sup>7</sup>

#### 2.2 ISO Standards:

ISO 1462 Accelerated Corrosion Tests and Evaluation of Results<sup>8</sup>

ISO 6892 Metallic Materials Tensile Testing<sup>8</sup>

#### 2.3 IEC Standard:

IEC 68 Environmental Testing<sup>9</sup>

#### 2.4 CEN Standard:

EN 10002/1 Metallic Materials Tensile Testing<sup>10</sup>

#### 2.5 DIN Standards:

DIN 17441 Stainless Steel Technical Delivery Conditions for Stainless Cold Rolled Steel<sup>11</sup>

DIN 50021-SS Spray Test with Different Sodium Chloride Solutions<sup>11</sup>

DIN 50980 Evaluation of Corrosion Tests<sup>11</sup>

### 3. Terminology

#### 3.1 Definitions of Terms Specific to This Standard:

3.1.1 *textured*—a three-dimensional design pattern, regardless of the specific production-process approach.

### 4. Ordering Information

4.1 It is the responsibility of the purchaser to specify all requirements that are necessary for material ordered under this specification. Such requirements may include, but are not limited to the following:

4.1.1 *Quantity*—Number of sheets or weight.

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel, and Related Alloys and is the direct responsibility of Subcommittee A01.17 on Wrought Stainless Products.

Current edition approved Sept. 10, 1995. Published November 1995.

<sup>2</sup> Annual Book of ASTM Standards, Vol 01.03.

<sup>3</sup> Annual Book of ASTM Standards, Vol 01.05.

<sup>4</sup> Annual Book of ASTM Standards, Vol 03.02.

<sup>5</sup> Annual Book of ASTM Standards, Vol 02.03.

<sup>6</sup> Annual Book of ASTM Standards, Vol 10.01.

<sup>7</sup> Annual Book of ASTM Standards, Vol 06.01.

<sup>8</sup> Available from International Organization for Standards (ISO), 1 Rue de Varembe, Case Postale 56, 20 Geneve, Suisse 1211.

<sup>9</sup> Available from International Electrotechnical Commission (IEC), 3 Rue de Varembe, 20 Geneve, Suisse 1211.

<sup>10</sup> Available from European Committee for Standardization (CEN), Rue Brederoede 2, B 1000 Bruxelles.

<sup>11</sup> Available from German Institute for Standardization (DIN), Burggrafenstrasse 6, 1000 Berlin 30.

4.1.2 Dimensions of sheet (thickness (texture included), width, and length). See Tables 1-5 and Section 9 for preferred sizes and tolerances.

4.1.3 ASTM designation and date of issue.

4.1.4 Name and type of material.

4.1.5 Surface condition of the nontextured surface. See Specification A 480/A 480M or DIN 17441 Table 8.

4.1.6 Textured identification reference number. See Table 6.

4.1.7 Type and thickness of protective liner, if required by the purchaser.

4.1.8 Marking requirements. Reference: Practices A 700.

NOTE 1—A typical ordering description is as follows: 500 sheets, 1.00 by 1200 by 2500 mm; ASTM Specification 176, Type 430; Surface Finish Texture ID: S-F-O, 6-1, 3-6-170-3; 100 sheet maximum/skid, textured side up. Each skid marked with purchase order number, applicable ASTM standard, and date of shipment.

**5. Materials and Manufacture**

5.1 The textured side or sides of the sheet shall be produced in such a manner that guarantees repeatability of the pattern over time. See 6.2.

5.2 Manufacture process of textured material under this specification shall follow industry practices.

**6. Texture of Sheet**

6.1 The texture of any sheet delivered under this specification shall meet the provisions outlined in Table 6 and Section 13.

6.2 The customer shall either provide a control-sample (300 mm by 400 mm) or designate a control-sample from a chosen textured material to ensure accurate repetition in appearance of like products. See Section 13.

**7. Chemical Composition**

7.1 The heat chemical composition shall be reported to the purchaser, or his representative, and shall conform to the requirements specified in the applicable ASTM standard of the steel type selected for texturing.

7.2 Methods and practices relating to chemical analysis required by this specification shall be in accordance with Test Methods, Practices, and Terminology A 751.

**TABLE 1 Permissible Deviations in Thickness<sup>A</sup>**

Preferred Nominal Thickness	Applicable Thickness		Permissible Thickness Variations for Nominal Sheet Widths $\geq 10 \leq 1600$
	$\geq$	$\leq$	
0.40	0.4	0.5	0.04
0.50; 0.60	0.5	0.7	0.05
0.70; 0.80; 0.90; 1.00	0.7	1.1	0.06
1.20	1.1	1.5	0.08
1.50; 2.00	1.5	2.5	0.1
2.50; 3.00	2.5	3.5	0.12
3.50; 4.00	3.5	4.5	0.14
4.50; 5.00; 6.00	4.5	6.0	0.15

<sup>A</sup> In reference to preferred sheet thicknesses. Dimensions stated are in millimetres.

**TABLE 2 Permissible Deviations for Nominal Widths<sup>A</sup>**

Nominal Thickness	Permissible Deviation at Nominal Width					
	$\geq$	$\leq$	$\leq 100$	$\geq 100$ to $\leq 300$	$\geq 300$ to $\leq 700$	$\geq 700$ to $\leq 1600$
0.40	1.00	0.5	0.8	1.0	1.5	1.5
1.00	1.75	0.7	1.0	1.5	1.5	1.5
1.75	3.00	1.0	1.5	1.5	2.0	2.0
3.00	6.00	...	...	2.0	2.0	2.0

<sup>A</sup> Dimensions stated are in millimetres.

**TABLE 3 Permissible Deviations for Nominal Length<sup>A</sup>**

Nominal "L"	Permissible Deviation for Nominal Length
$\leq 2000$	5
$> 2000$	$0.0025 \times \text{Length}$

<sup>A</sup> Dimensions stated are in millimetres.

**TABLE 4 Permissible Deviations on Flatness<sup>A</sup>**

Nominal Thickness	Total Deviation, %		
	Relating to Length D/L	Relating to Width D/W	
0.40	2.00	0.4	0.5
2.00	4.00	0.3	0.4
4.00	6.00	0.1	0.4

<sup>A</sup> Dimensions stated are in millimetres.

**TABLE 5 Permissible Deviations on Squareness<sup>A</sup>**

Nominal Length	Squareness Tolerances at Nominal Width Ratio of AA/BB Dimension			
	$\geq$	$\leq$	$\leq 1000$	$\geq 1000$ to $\leq 1600$
...	2000	3000	6	7
2000	3000	3500	7	7
3000	3500	5000	7	8
3500	5000	6000	8	10
5000	6000		12	12

<sup>A</sup> Dimensions stated are in millimetres.

**8. Other Requirements**

8.1 If requested by the purchaser, physical (electrical and optical) and mechanical (tensile, yield, and elongation) property requirements shall be reported to the purchaser based on a lot size as specified in 8.2.

8.2 A lot shall consist of all sheets of the same thickness made from the same coil. In case the material cannot be identified by coil, a lot shall consist of no more than 5000 kg (approximately 5 tons) of sheets of the same thickness.

**8.3 Electrical Requirements:**

8.3.1 The specific resistivity of the material measured at 20°C to be reported in: ohms-mm<sup>2</sup>/m ( $\mu\Omega$ -cm).

8.3.2 The surface resistivity of the material measured at 20°C to be reported in: milliohms. Refer to Test Methods D 257.

8.4 *Optical Requirements*—The textured surface of the material selected under this specification shall meet the inspection requirements (see 13.2) based on a visual sample comparison or a 6:1 art master pattern comparison, or both.

8.5 *Mechanical Requirements*—The mechanical properties, tensile strength, yield strength, and elongation of the material

**TABLE 6 Textured Reference Identification**

Pattern orientation	Note 1
Pattern appearance	Note 2
Height of pattern	Note 3
Size of pattern	Note 4
Type of pattern	Note 5
Pattern repetition configuration	Note 6
Pattern effect on far side of sheet	Note 7
Example of typical ordering description: <b>S-F-O,6-1,3-6-170-3</b>	
Note 1:	S (Straight) Pattern oriented with flow line of rolling process.
	A (Angular) Pattern oriented 45° to flow line of rolling process.
	O (Other) Optional pattern orientation.
Note 2:	F (Fine) If the number of pattern repetitions under Note 6 exceeds 100.
	C (Coarse) If the number of pattern repetitions under Note 6 is less than 100.
Note 3:	Height of pattern in millimetres.
Note 4:	Size of individual pattern. (Largest individual pattern dimension in millimetres; length, width, diagonal, and so forth.)
Note 5:	Type of pattern:
	No. 0 round      No. 7 trapezoidal      No. 14 arrow
	No. 1 square      No. 8 lines      No. 15 snowflake
	No. 2 rectangular      No. 9 points      No. 16 teardrop
	No. 3 triangular      No. 10 letters      No. 17 combination
	No. 4 hex      No. 11 numbers      No. 18 shapeless
	No. 5 octal      No. 12 bricks      No. 19 irregular shape
	No. 6 oblong      No. 13 star      No. 20 others not defined
Note 6:	Number of largest individual pattern repetitions within a 20-mm × 20-mm area of the stainless steel sheet. (Partial pattern repetition included.)
Note 7:	A two-sided pattern under this specification displays the same pattern on both sides of the sheet. This pattern is usually reserved for material thicknesses of 2.5 mm and thicker.
	No. 1 Two-sided pattern.
	No. 2 One-sided pattern. No visible marks from an one-sided pattern, when viewed with the unaided eye from a distance of 1 m.
	No. 3 One-sided pattern. Shadings and reflections as a result from the pattern process on the opposite side of the sheet shall be acceptable.
	No. 4 One-sided pattern. Measurable deformation, caused by the pattern on the opposite side of the sheet shall be acceptable.

selected for texturing shall be reported in values specified in 12.5 of this specification.

**9. Dimensions, Mass, and Permissible Variations**

9.1 Unless noted in the purchase order, the stated tolerance conditions in Tables 1-5 are deemed to be acceptable.

9.2 Table 1 lists the tolerance for sheet-thickness relevant to the preferred thickness-sizes of textured sheets in this specification.

9.3 Table 2 lists the tolerance for sheet widths relevant to the preferred width-sizes of textured sheets in this specification.

9.4 Table 3 lists the tolerance for sheet lengths relevant to the preferred length-sizes in this specification.

9.5 Table 4 lists the permissible tolerance for sheet flatness relevant to the preferred flatness tolerances in this specification as a ratio of: deviation “D” to length “L” and width “W” of textured sheet. (See 10.5.)

9.6 Table 5 lists the maximum permissible difference between the diagonal dimensions “AA” and “BB” of the textured sheet. (See 10.6 and Fig. 1.)

9.7 The maximum permissible deviation of the edge camber “D” for textured sheets is 0.2 % of the nominal length of the sheet. (See 10.6)

**10. Measurement**

10.1 Unless otherwise stated, the measurement of the geometrical requirements shall be based on the definition outlined in Section 10.

10.2 *Thickness*—The thickness (texture included) may be measured at any point located more than 20 mm from the edges.

10.3 *Width*—The width is measured perpendicularly to the longitudinal axis of the product.

10.4 *Length*—The length is measured along one of the sides of the sheet or cut length.

10.5 *Flatness*—The measurement of the flatness deviation (pockets) is made according to the pictorial representation “A” and “B”, see Fig. 2. The sheet is lying on a flat surface with the concave side upward.

10.6 *Edge Camber*—The edge camber is the greatest deviation of a side edge from a straight line, the measurement being taken on the concave side with a straight edge (see Fig. 3).


**11. Workmanship**

11.1 Textured sheets shall be uniform in quality and condition and free of injurious defects, that due to their nature or severity, may detrimentally affect the suitability for the service intended.

**12. General Requirements for Delivery**

12.1 Unless otherwise specified in the purchase order, the materials furnished under this specification shall conform to applicable requirements of the current edition of Specification A 480/A 480M or, if applicable, to DIN 17441.

12.2 If requested by the purchaser, material shall be delivered with a protective liner of either polyvinyl (PVC) or polyethylene (PE) on the textured side of the sheet. However, if a protective liner is being specified it must not be detrimentally affected by ultraviolet (UV) or temperature exposure, or both, up to 70°C. Its removal from the sheet stock must be

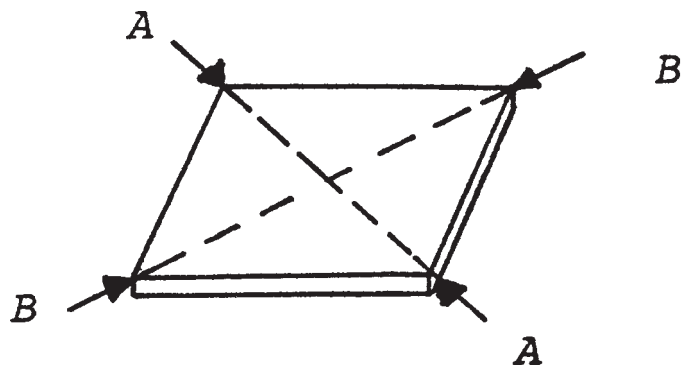

**FIG. 1 Squareness**