

---

---

**Mechanical joining of sheet  
materials — Destructive testing of  
joints — Specimen dimensions and  
procedure for mechanized peel testing  
of single joints**

*Assemblage mécanique de tôles — Essais destructifs des assemblages  
— Dimensions des échantillons et procédure pour l'essai de pelage  
mécanisé des assemblages simples*

(<https://standards.iteh.ai>)  
Document Preview

ISO 23598:2021

<https://standards.iteh.ai/catalog/standards/iso/f46ad3c8-e4e6-4f21-8e0a-82729daa421e/iso-23598-2021>



iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

ISO 23598:2021

<https://standards.iteh.ai/catalog/standards/iso/f46ad3c8-e4e6-4f21-8e0a-82729daa421e/iso-23598-2021>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Test pieces and test specimens</b> .....	<b>3</b>
<b>5 Preparation of mechanized peel test specimens</b> .....	<b>4</b>
5.1 General.....	4
5.2 Bending procedure for preparation of peel test specimens.....	5
5.3 Dimensions and accuracy of bent radius.....	6
<b>6 Testing procedure and test equipment</b> .....	<b>6</b>
<b>7 Type of failure mode</b> .....	<b>8</b>
<b>8 Re-test</b> .....	<b>8</b>
<b>9 Test report</b> .....	<b>8</b>
<b>Annex A (normative) Type of joint failure in mechanized peel testing</b> .....	<b>10</b>
<b>Annex B (informative) Examples of bending tools</b> .....	<b>13</b>
<b>Annex C (informative) Determination of bending centre position with the press brake system</b> .....	<b>15</b>
<b>Bibliography</b> .....	<b>16</b>

ITeH Standards  
 (https://standards.iteh.ai)  
 Document Preview

ISO 23598:2021

<https://standards.iteh.ai/catalog/standards/iso/f46ad3c8-e4e6-4f21-8e0a-82729daa421e/iso-23598-2021>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 6, *Resistance welding and allied mechanical joining*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

Official interpretations of ISO/TC 44 documents, where they exist, are available from this page: <https://committee.iso.org/sites/tc44/home/interpretation.html>.

# Mechanical joining of sheet materials — Destructive testing of joints — Specimen dimensions and procedure for mechanized peel testing of single joints

## 1 Scope

This document specifies the geometry of test specimens and the testing procedure for mechanized peel testing of single mechanical joints on single-lap test specimens up to a single sheet thickness of 4,5 mm.

The term “sheet”, as used in this document, includes extrusions and cast materials.

The purpose of the mechanized peel tests is to determine the mechanical characteristics and the failure modes of the joints made with different joining methods.

This document does not apply to civil engineering applications such as metal buildings and steel constructions which are covered by other application standards.

NOTE For mechanized peel testing of resistance spot, seam and embossed projection welds, see ISO 14270

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 23598:2021

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### mechanized peel strength

##### MPS

$F_{\max}$

maximum peel force (3.2) obtained from mechanized peel testing

### 3.2

#### peel force

$F$

force/load which is applied to the test specimen during mechanized peel testing

### 3.3

#### slippage force

$F_{sl}$

peel force (3.2)/load at which slippage occurs if the phenomenon is observed during testing

### 3.4 specimen deformation

$s$   
crosshead displacement during testing

### 3.5 specimen deformation at maximum load

$s_{F_{\max}}$   
specimen deformation (3.4) at which the maximum peel force (3.2)/load  $F_{\max}$  is recorded

Note 1 to entry: See [Figure 4](#) and [Figure 5](#)

### 3.6 specimen deformation at 0,3 $F_{\max}$

$s_{0,3F_{\max}}$   
specimen deformation (3.4) at which 0,3 $F_{\max}$  is recorded

Note 1 to entry: See [Figure 4](#) and [Figure 5](#)

### 3.7 specimen deformation at fracture

$s_{\text{fracture}}$   
specimen deformation (3.4) of at which fracture occurs

Note 1 to entry: See [Figure 4](#) and [Figure 5](#)

### 3.8 dissipated energy

$W$   
amount of energy dissipated until a displacement point under the load-crosshead displacement curve  
[SOURCE: ISO 12161:2006, 3.4.1]

### 3.9 dissipated energy up to $F_{\max}$

$W_{F_{\max}}$   
dissipated energy or work calculated by integrating the area under the crosshead displacement curve up to the point at which maximum peel load (MPS point) is recorded

$$W_{F_{\max}} = \int_0^{s_{F_{\max}}} F \, ds$$

### 3.10 dissipated energy up to 0,3 $F_{\max}$

$W_{0,3F_{\max}}$   
dissipated energy or work calculated by integrating the area under the crosshead displacement curve up to the point where the peel force drops to 30 % of the MPS value,  $F_{\max}$

$$W_{0,3F_{\max}} = \int_0^{s_{0,3F_{\max}}} F \, ds$$

Note 1 to entry: See [Clause 6](#)

### 3.11 dissipated energy up to fracture

$W_{\text{fracture}}$

dissipated energy calculated by integrating the crosshead displacement curve up to the point at which fracture occurs

$$W_{\text{fracture}} = \int_0^{s_{\text{fracture}}} F \, ds$$

#### 4 Test pieces and test specimens

[Table 1](#) and [Figure 1](#) give the dimensions and form of test coupons and test specimens for mechanized peel testing, and the location of mechanical joint. The positional accuracy of the mechanical joints on the test specimen shall be  $\pm 1$  mm in every direction.

**Table 1 — Test specimen dimensions and joint position**

Dimensions in millimetres

Thickness <i>t</i>	Flange length <i>a</i>	Specimen width <i>b</i>	Coupon length <sup>a</sup> <i>l<sub>s</sub></i>	Free length between clamps <sup>a</sup> <i>l<sub>f</sub></i>	Edge distance <i>e</i>
0,5 < <i>t</i> ≤ 4,5	50	50	100	30	25
			≥160	105	

<sup>a</sup> The shorter coupon length (before joining) is preferred but a longer specimen can be needed based on joining process limitations or for comparison with results from testing in accordance with ISO 14270.


The test specimen for mechanical joints shall be produced as a single joint specimen as shown in [Figure 1](#) b), which is made of two coupons shown in [Figure 1](#) a), and then the mechanized peel test specimen shall be mounted on a tensile test machine as shown in [Figure 1](#) c).

In the case of unequal sheet thicknesses, the test specimen dimensions shall be based on the thinner sheet. Mechanized peel testing shall be made by the procedure specified in [Clause 5](#) and [Clause 6](#).

The tolerances on the dimensions shall be in accordance with [Table 2](#).

ISO 23598:2021

<https://standards.iteh.ai/catalog/standards/iso/f46ad3c8-e4e6-4f21-8e0a-82729daa421e/iso-23598-2021>

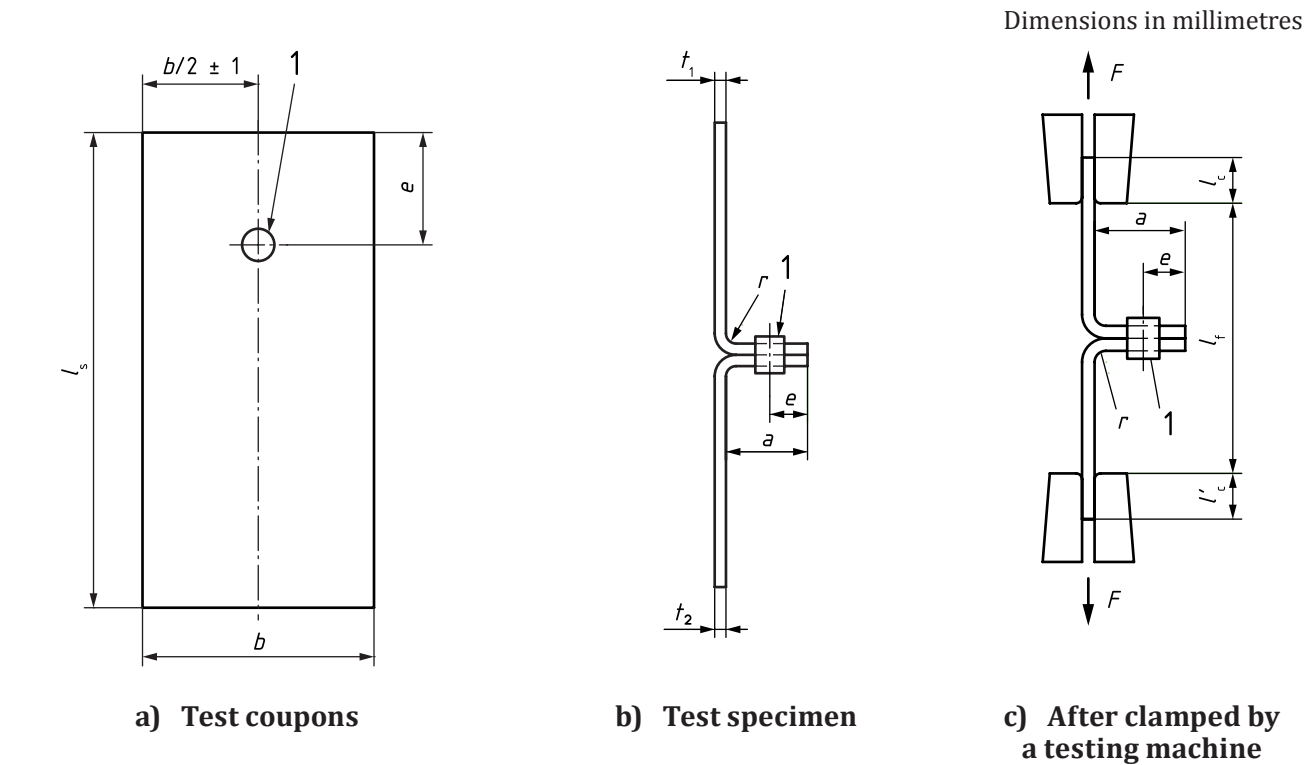

Key

- |             |                            |   |                       |
|-------------|----------------------------|---|-----------------------|
| 1           | joint/fastener             | a | flange length         |
| $l_s$       | coupon length              | r | bending radius        |
| $l_f$       | free length between clamps | b | coupon/specimen width |
| $l_c, l'_c$ | clamping length            | e | edge distance         |
| F           | applied force (load)       |   |                       |

Figure 1 — Test coupons, test specimens and the clamping state for mechanized peel testing

Table 2 — Tolerances on dimensions for mechanized peel test specimens

Dimensions in millimetres					
Flange length	Coupon/ specimen width	Edge distance	Coupon length	Free length be- tween clamps	Bend radius
a	b	e	$l_s$	$l_f$	r
+1,0 0	+1 0	+0,5 0	0 -1	0 -1	$\pm 0,5t^a$
<sup>a</sup> t is the sheet thickness of each coupon.					

5 Preparation of mechanized peel test specimens

5.1 General

The mechanized peel test specimens for mechanical joints are recommended to be made in the following sequence, so that the test specimens can be tested using a tensile test machine;

Bending → Mechanical joining → Mechanized peel testing



The sequence is called “joining-after-bending process”.


NOTE In resistance spot welding, the bending-after-welding process (Joining → Bending → Mechanized peel testing) can be used, but in the case of mechanical joining, some fasteners cannot be tested using this sequence as the fastener interferes with the clamping face for bending after joining, or the clamping device can influence the joint part properties.

## 5.2 Bending procedure for preparation of peel test specimens

The test coupons shall be bent before mechanical joining as shown in [Figure 2](#).

The recommended set-up conditions of jigs for bending with a press brake are shown in [B.1](#).


NOTE When setting the value  $l_b = a$  as shown in [Figure 2](#), the maximum error in the flange length is less than  $\pm 0,5$  mm if  $r = 2t$  and  $t \leq 4,5$  mm (see detail in [Annex C](#)).

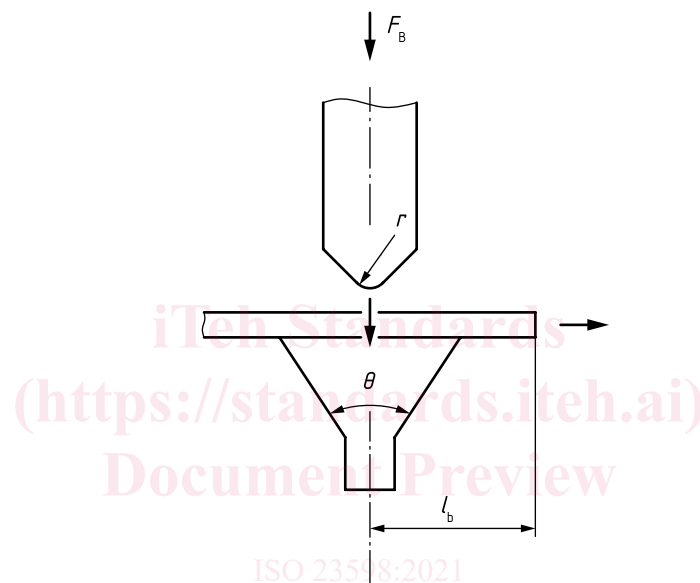

### Key

$F_B$	bending force	$r$	radius of bent corner/bend radius
$l_b$	centre of bending (= $a$ , flange length, see <a href="#">Figure 1</a> )	$\theta$	angle

**Figure 2 — Bending process with a press brake for test coupons**

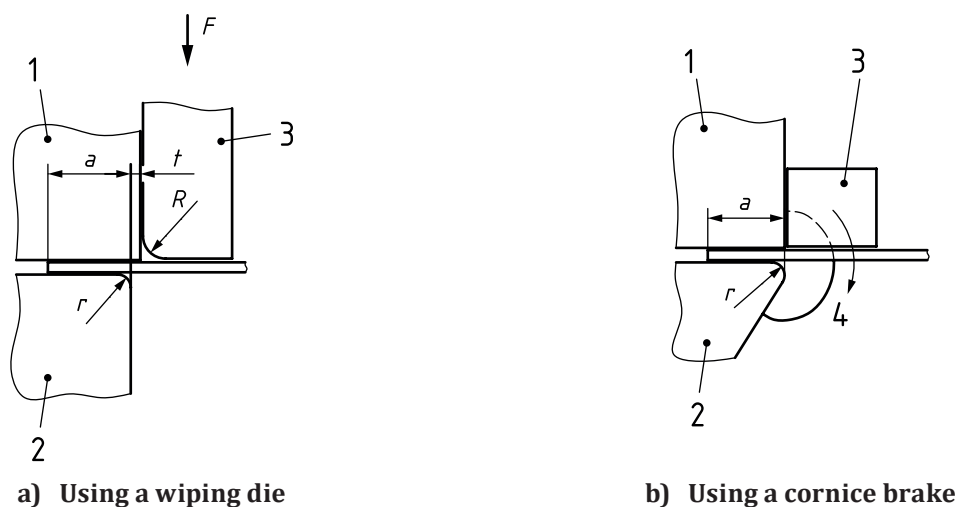**Key**

1	upper jaw	$F$	force
2	lower jaw	$r$	radius of bent corner
3	die	$R$	edge radius of die
4	rotating	$a$	flange length

**Figure 3 — Examples of edge bending**

A mechanized press brake system is generally recommended for the bending although a manual press brake can be used to bend test coupons for soft and thinner test pieces. Other bending tools shown in Figure 3 are also applicable to make the test coupons. The wiping die and cornice brake system can be used. An example of edge bending is shown in Annex B.

### 5.3 Dimensions and accuracy of bent radius

The value of the inner radius,  $r$ , shall be set so that no large and deep cracking occurs during bending on the inner or outer surfaces of the bent corner. The radius value tested shall be recorded. The inner radius  $r$ , equal to approximately  $2t$  ( $t$ , plate thickness) is recommended. Tolerances shall be in accordance with Table 2.

If any cracks are visible, with up to  $\times 5$  magnification, after bending in accordance with 5.2, new test specimens/coupons with larger inner radii shall be made. The value of the inner radius shall be increased until no cracking occurs on the outer side of the bend.

## 6 Testing procedure and test equipment

The test specimen is clamped in a tensile testing machine which satisfies the requirements of ISO 7500-1, such that the clamps are at the required distance from one another as shown in Figure 1 c). Force and crosshead displacement shall be measured simultaneously during testing, and the measuring accuracy shall be  $\pm 1\%$ . All tests shall be performed at room temperature until the joint fails.

If a special clamping device is used, the shape and size shall be specified in a joining procedure specification (JPS) document, and recorded.

The crosshead displacement rate of the testing machine shall be equal to 10 mm/min or less, and shall be kept constant during testing.