

DRAFT INTERNATIONAL STANDARD

ISO/DIS 6002

ISO/TC 153

Secretariat: AFNOR

Voting begins on:
2020-01-29

Voting terminates on:
2020-04-22

Industrial valves - Bolted bonnet steel gate valves

Robinetterie industrielle - Robinets-vannes en acier à chapeau boulonné

ICS: 23.060.30

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/9df502e7-6402-40df-99ea-e4ea66414e3e/iso-dis-6002>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.



Reference number
ISO/DIS 6002:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/9df502e7-6402-40df-99ea-e4ea66414e3e/iso-dis-6002>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Pressure/temperature ratings	3
5 Design	3
5.1 Body wall thickness.....	3
5.2 Body dimensions.....	4
5.2.1 Flanges.....	4
5.2.2 Weld ends.....	5
5.3 Gate.....	6
5.4 Stem.....	8
5.5 Auxiliary connections.....	8
5.6 Closure test.....	11
5.7 Operation.....	12
6 Materials	12
6.1 Materials other than trim materials.....	12
6.2 Trim.....	13
7 Testing and inspection	13
8 Marking	14
8.1 Legibility.....	14
8.2 Body markings.....	14
8.3 Ring joints marking.....	14
8.4 Identification plate marking.....	14
Bibliography	15

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 153, *Valves*.

This second edition cancels and replaces the first edition (ISO 6002:1992), which has been technically revised.

The main changes compared to the previous edition are as follows:

- in the whole text, deletion of PN 20 and PN 50, addition of PN 63 and inclusion of nominal pipe sizes NPS and Class designations;
- update of the normative references in [Clause 2](#);
- addition of definitions for DN, NPS, PN and Class;
- revision of [Figure 1](#) identifying valves terms and [Figure 6](#) for butt-welding for auxiliary connections;
- addition of requirements for gate in [5.3](#) and stem in [5.4](#);
- addition of requirements for closure test in [5.6](#);
- deletion of former [Table 1](#) on body wall thickness, deletion of former [Table 3](#) on end-to-end dimensions for butt-weld end valves and deletion of former [5.4](#) on envelope dimensions;
- revision of [Table 8](#) on component materials;
- update of [Clause 7](#) on testing and inspection and [Clause 8](#) on marking.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The purpose of this document is the establishment of the basic requirements and recommendations for flanged or butt-weld end steel gate valves of bolted bonnet construction.

It is not the purpose to replace ISO 10434 or any other international Standard.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/9df502e7-6402-40df-99ea-e4ea66414e3e/iso-dis-6002>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Full standard:
<https://standards.iteh.ai/catalog/standards/sist/9df502e7-6402-40df-99ea-e4ea66414e3e/iso-dis-6002>

Industrial valves - Bolted bonnet steel gate valves

1 Scope

This document specifies the requirements for bolted bonnet steel gate valves having the following features:

- bolted bonnet;
- outside screw and yoke;
- inside screw (alternative for PN 10, PN 16, PN 25 and PN 40 only);
- single or double obturator;
- wedge or parallel seating;
- with or without non-metallic obturator or seat seals;
- flanged or butt-welding ends.

It covers valves of the nominal sizes DN:

- 10; 15; 20; 25; 32; 40; 50; 65; 80; 100; 125; 150; 200; 250; 300; 350; 400; 450; 500; 600; 700; 800; 900; 1 000;

corresponding to nominal pipe sizes NPS:

- 3/8; 1/2; 3/4; 1; 1 1/4; 1 1/2; 2; 2 1/2; 3; 4; 5; 6; 8; 10; 12; 14; 16; 18; 20; 24; 28; 32; 36; 40;

and applies to valves of the following pressure designations:

- PN 10; 16; 25; 40; 63; 100;
- Class 150; 300; 600.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4991, *Steel castings for pressure purposes*

ISO 5208, *Industrial valves — Pressure testing of metallic valves*

ISO 5210, *Industrial valves — Multi-turn valve actuator attachments*

ISO 5752:1982, *Metal valves for use in flanged pipe systems — Face-to-face and centre-to-face dimensions*

ISO 7005-1, *Pipe flanges — Part 1: Steel flanges for industrial and general service piping systems*

ISO 9327 (series), *Steel forgings and rolled or forged bars for pressure purposes*

ISO 9328-1, *Steel flat products for pressure purposes — Technical delivery conditions — Part 1: General requirements*

ISO 9328-2, *Steel flat products for pressure purposes — Technical delivery conditions — Part 2: Non-alloy and alloy steels with specified elevated temperature properties*

ISO/DIS 6002:2020(E)

ISO 9328-3, *Steel flat products for pressure purposes — Technical delivery conditions — Part 3: Weldable fine grain steels, normalized*

ISO 9328-4, *Steel flat products for pressure purposes — Technical delivery conditions — Part 4: Nickel-alloy steels with specified low temperature properties*

ISO 9328-5, *Steel flat products for pressure purposes — Technical delivery conditions — Part 5: Weldable fine grain steels, thermomechanically rolled*

ISO 14737, *Carbon and low alloy cast steels for general applications*

EN 1092-1, *Flanges and their joints — Circular flanges for pipes, valves, fittings and accessories, PN designated — Part 1: Steel flanges*

EN 12982, *Industrial valves — End-to-end and centre-to-end dimensions for butt welding end valves*

EN 12516-1, *Industrial valves — Shell design strength — Part 1: Tabulation method for steel valve shells*

EN 12516-2, *Industrial valves — Shell design strength — Part 2: Calculation method for steel valve shells*

ASME B16.5, *Pipe Flanges and Flanged Fittings: NPS 1/2 through NPS 24 Metric/Inch Standard*

ASME B16.10, *Face-to-Face and End-to-End Dimensions of Valves*

ASME B16.34, *Valves Flanged, Threaded, and Welding End*

ASME B16.47, *Large Diameter Steel Flanges: NPS 26 through NPS 60 Metric/Inch Standard*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

nominal size DN or NPS

alphanumeric designation of size for components of a pipework system, which is used for reference purposes, comprising the letters DN or NPS followed by a dimensionless number indirectly related to the physical size, in millimetres, of the bore or outside diameter of the end connections

Note 1 to entry: The number following the letters DN or NPS does not represent a measurable value and is not used for calculation purposes except where specified in the relevant standard.

Note 2 to entry: See ISO 6708 and ASME B16.34.

3.2

PN or Class

alphanumeric designation for pressure-temperature rating that is common for components used in a piping system, used for reference purposes, comprising the letters "PN" or "Class" followed by a dimensionless number indirectly related to the pressure retaining capability as a function of temperature of the component

Note 1 to entry: The number following the letters PN or Class does not represent a measurable value and is not used for calculation purposes except where specified in the relevant standard. There is no definitive correlation that links PN designations to Class designations.

Note 2 to entry: See ISO 7268 and ASME B16.34.

4 Pressure/temperature ratings

4.1 The pressure/temperature ratings shall be in accordance with EN 12516-1 for PN-designated valves and in accordance with ASME B16.34 for Class-designated valves.

4.2 The temperature shown for a corresponding pressure rating is the temperature of the pressure-containing shell of the valve. In general, this temperature is the same as that of the contained fluid. The use of a pressure rating corresponding to a temperature other than that of the contained fluid is the responsibility of the user.

4.3 For temperatures below the lowest temperature listed in the pressure/temperature rating tables, the working pressure shall be no greater than the lowest listed temperature. The use of valves at lower temperatures is the responsibility of the user. Consideration should be given to the loss of ductility and impact strength of many materials at low temperature.

5 Design

5.1 Body wall thickness

5.1.1 The terms used in 5.1 are illustrated in Figure 1. d is the inside diameter given in Table 1.

5.1.2 The minimum body wall thickness, t_m at the time of manufacture, shall be in accordance with:

- EN 12516-1 or EN 12516-2 for PN-designated valves,
- ASME B16.34 or EN 12516-1 for Class-designated valves.

Exceptions are given in 5.1.3 to 5.1.5.

Additional metal thickness needed for assembly stresses, closing stresses, stress concentrations and shapes other than circular shall be determined by the manufacturers, since these factors vary widely.

5.1.3 The weld preparation in butt-welding end valves (see 5.2.2.2) shall not reduce the body wall thickness to less than the values specified in 5.1.2 within a region closer to the outside surface of the body neck than t_m measured along the run direction.

The transition to the weld preparation shall be gradual and the section shall be essentially circular through the entire length of the transition. Sharp discontinuities or abrupt changes in section in areas that infringe into the transition shall be avoided, except that test collars or bands, either welded or integral, are allowed.

In no case shall the thickness be less than $0,77 t_m$ at a distance of $2 t_m$ from the weld end.


5.1.4 The valve body neck shall maintain the minimum body wall thickness t_m as specified in 5.1.2 within the distance $1,1 \sqrt{dt_m}$ measured from the outside of the body run along the neck direction, where d is the nominal inside diameter as defined in 5.2.1.3.

Beyond the distance $1,1 \sqrt{dt_m}$ from the outside of the body run, straight circular sections of body necks with inside diameter d' shall be provided with a minimum local wall thickness of t' where t' is determined, by interpolation if necessary, as the value of t_m which would correspond to a value of d equal to $2d'/3$, using the applicable nominal pressure rating.

For any case where $d' > 1,5 d$, the newly determined minimum wall thickness for the body neck will be greater than the basic value t_m . In such cases, this greater wall thickness shall be provided for all parts of the body neck having a diameter greater than $1,5 d_0$.

5.1.5 Local areas having less than minimum wall thickness are acceptable provided that all of the following limitations are satisfied:

- a) The area of less than minimum thickness can be enclosed by a circle whose diameter is no greater than $0,35 \sqrt{dt_m}$.
- b) Measured thickness is no less than $0,75 t_m$.
- c) Enclosure circles are separated from each other by an edge-to-edge distance of no less than $1,75 \sqrt{dt_m}$.

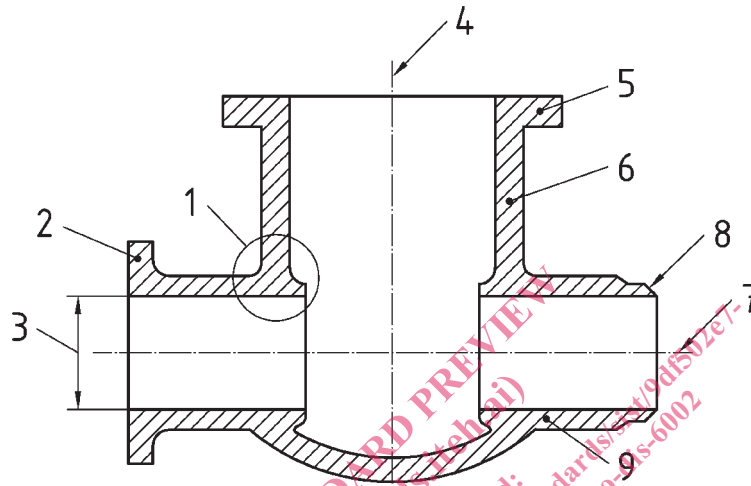

Key

- | | | | |
|---|------------------------------------|---|------------------|
| 1 | junction of body run and body neck | 6 | body neck |
| 2 | body end flange | 7 | axis of body run |
| 3 | body end port inside diameter | 8 | butt-welding end |
| 4 | axis of body neck | 9 | body run |
| 5 | body/bonnet flange | | |

Figure 1 — Identification of terms

5.2 Body dimensions

5.2.1 Flanges

5.2.1.1 Body end flanges shall comply with the requirements of ASME B16.34 for Class-designated valves and EN 1092-1 for PN-designated valves. Raised face end flanges shall be provided unless otherwise specified by the purchaser.

5.2.1.2 Face-to-face dimensions for flanged end valves shall be in accordance with ISO 5752.

5.2.1.3 End flanges shall be cast or forged integral with the body except that flanges may be attached by welding by a qualified welding operator using a qualified welding procedure, provided that all such flanges on valves DN 50 and larger are butt-welded. Any heat treatment necessary to ensure that the material is suitable for the full range of service temperatures shall be performed.