

ISO/TC 38

Secretariat: JISC

Voting begins on:
2021-01-25

Voting terminates on:
2021-03-21

Fibre ropes — Polypropylene split film, monofilament and multifilament (PP2) and polypropylene high-tenacity multifilament (PP3) — 3-, 4-, 8- and 12-strand ropes

Cordages en fibres — Film fibrillé, monofilament et multifilament de polypropylène (PP2) et multifilament de polypropylène haute ténacité (PP3) — Cordages à 3, 4, 8 et 12 torons

[ISO/FDIS 1346](https://standards.iteh.ai/catalog/standards/sist/77db564a-fd48-4b75-a929-248efa057e65/iso-fdis-1346)

<https://standards.iteh.ai/catalog/standards/sist/77db564a-fd48-4b75-a929-248efa057e65/iso-fdis-1346>

ISO/CEN PARALLEL PROCESSING

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 1346:2021(E)

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/FDIS 1346

<https://standards.iteh.ai/catalog/standards/sist/77db564a-fd48-4b75-a929-248efa057e65/iso-fdis-1346>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Designation	1
5 General requirements	2
6 Physical properties	3
7 Marking	7

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/FDIS 1346

<https://standards.iteh.ai/catalog/standards/sist/77db564a-fd48-4b75-a929-248efa057e65/iso-fdis-1346>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 38, *Textiles*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 248, *Textiles and textile products*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This fifth edition cancels and replaces the fourth edition (ISO 1346:2012), which has been technically revised.

The main changes compared to the previous edition are as follows:

- in the Scope, a statement specifying that the document does not cover all variations in strength or product performance has been added;
- in [Clause 3](#), the term "minimum breaking strength" has been added;
- in [Table 1](#), [Table 2](#) and [Table 3](#), the tolerances in linear density have been modified.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Fibre ropes — Polypropylene split film, monofilament and multifilament (PP2) and polypropylene high-tenacity multifilament (PP3) — 3-, 4-, 8- and 12-strand ropes

1 Scope

This document specifies requirements for 3-strand hawser-laid and 4-strand shroud-laid ropes, 8-strand braided ropes and 12-strand braided ropes for general service made of polypropylene, and gives rules for their designation.

This document does not cover all variations in strength or product performance. The rope manufacturer is consulted to ensure the intended design meets the requirements of the application

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1968, *Fibre ropes and cordage — Vocabulary*

ISO 2307, *Fibre ropes — Determination of certain physical and mechanical properties*

ISO 9554, *Fibre ropes — General specifications*

<https://standards.iteh.ai/catalog/standards/sist/77db564a-fd48-4b75-a929-248efa057e65/iso-fdis-1346>

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1968 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

minimum breaking strength

MBS

force a fibre rope shall at least achieve when tested following a recognized procedure/test method

Note 1 to entry: The MBS is set by each manufacturer, as per their own internal statistical methods based on breaking tests. In ISO 9554:2019, Annex D, two statistical methods are given that can be used to determine the MBS.

[SOURCE: ISO 9554:2019, 3.2]

4 Designation

Fibre ropes shall be designated by

- the words “fibre rope”,
- the number of this document, i.e. ISO 1346,
- the construction or type of rope (see [Clause 5](#)),

- the reference number of the rope,
- the material from which the rope is made:
 - 1) PP2: polypropylene split film, monofilament and multifilament,
 - 2) PP3: polypropylene high-tenacity multifilament.
- The rope fibres shall be protected against deterioration due to sunlight (UV). See ISO 9554

EXAMPLE

Designation of an 8-strand braided rope (type L) with a linear density of 1 630 ktex, corresponding to the reference number 60 and made of polypropylene monofilament (PP2):

Fibre rope ISO 1346 - L - 60 - PP2 protected (UV)

5 General requirements

5.1 Polypropylene ropes shall be made in one of the following constructions:

- type A: 3-strand hawser-laid rope (see [Figure 1](#));
- type B: 4-strand shroud-laid rope (see [Figure 2](#));
- type L: 8-strand braided rope (see [Figure 3](#));
- type T: 12-strand braided rope (see [Figure 4](#)).

iteh STANDARD PREVIEW
(standards.iteh.ai)
ISO/FDIS 1346:2021(E)
<https://standards.iteh.ai/catalog/standards/iso/1346-2021/248-4b75-a929-248efa057e65/iso-1346-2021>



Figure 1 — Shape of a 3-strand hawser-laid rope (type A)

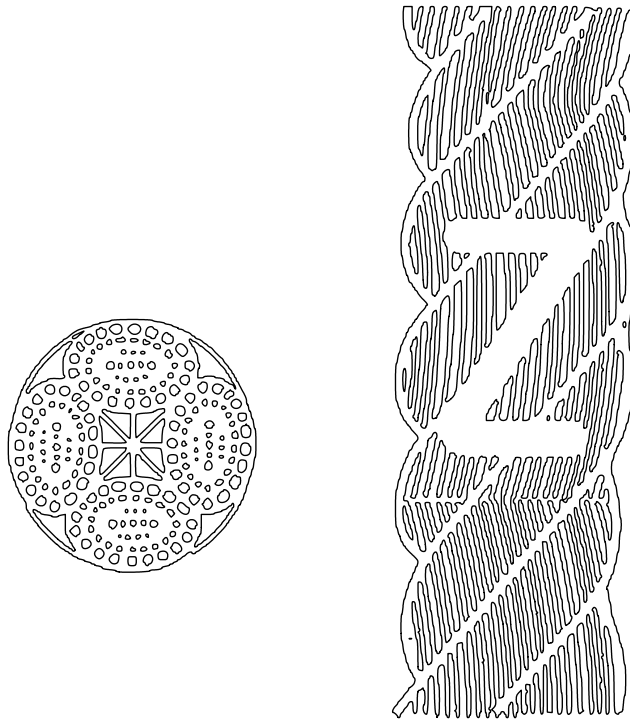


Figure 2 — Shape of a 4-strand shroud-laid rope (type B)



Figure 3 — Shape of an 8-strand braided rope (type L)

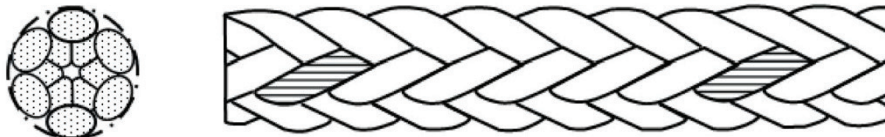


Figure 4 — Shape of a 12-strand braided rope (type T)

5.2 Construction, manufacture, lay, labelling, packaging, invoicing and delivery lengths shall be in accordance with ISO 9554.

6 Physical properties

Linear density and minimum breaking strength shall be in accordance with [Table 1](#), [Table 2](#) and [Table 3](#).

Regarding [Table 1](#), [Table 2](#) and [Table 3](#), the following applies.

- The reference number corresponds to the approximate diameter, in millimetres.
- The linear density, in kilotex, corresponds to the net mass per length of rope, expressed in grams per metre or in kilograms per thousand metres.
- The linear density is under reference tension and is measured as specified in ISO 2307

- The breaking strengths quoted in these tables relate to new dry and wet ropes.
- A force determined by the test methods specified in ISO 2307 is not necessarily an accurate indication of the force at which that rope might break in other circumstances and situations. The type and quality of the termination rate of force application, prior conditioning and previous force applications to the rope can significantly influence the breaking strength. A rope bent around a post, capstan, pulley or sheave could break a significantly lower force. A knot or other distortion in a rope will significantly reduce the breaking strength.

Table 1 — Linear density and minimum breaking strength (MBS) of 3-strand hawser-laid polypropylene ropes, type A

Reference Number	Linear density		Minimum breaking strength kN				
	Nominal ktex	Tolerance %	Split/Mono/Multi PP2 Multi PP2		High-tenacity Multi PP3 Multi PP3		
			Unspliced ropes	Ropes with eye-spliced terminations	Unspliced ropes	Ropes with eye-spliced terminations	
4	7,23	±10	2,80	2,52	3,15	2,84	
4,5	9,15		3,55	3,20	4,00	3,60	
5	11,3		4,25	3,83	4,75	4,28	
6	16,3		6,00	5,40	6,70	6,03	
8	28,9		10,0	9,00	11,8	10,6	
9	36,6		12,5	11,3	14,0	12,6	
10	45,2		15	13,5	17,0	15,3	
12	65,1		±8	21,2	19,1	25,0	22,5
14	88,6			28,0	25,2	33,5	30,2
16	116			37,5	33,8	42,5	38,3
18	146	45,0		40,5	53,0	47,8	
20	181	56,0		50,4	63,0	56,7	
22	219	67,0		60,3	75,0	67,5	
24	260	80,0		72,0	90,0	81,0	
26	306	90,0		81,0	106	95,4	
28	354	106		95,4	118	106	
30	407	118		106	132	119	
32	463	132		119	150	135	
36	586	170		153	190	171	

Table 1 (continued)

Reference Number	Linear density		Minimum breaking strength kN			
	Nominal ktex	Tolerance %	Split/Mono/Multi PP2 Multi PP2		High-tenacity Multi PP3 Multi PP3	
			Unspliced ropes	Ropes with eye-spliced terminations	Unspliced ropes	Ropes with eye-spliced terminations
40	723	±5	200	180	236	212
44	875		250	225	280	252
48	1 040		280	252	335	302
52	1 220		335	302	375	338
56	1 420		375	338	425	383
60	1 630		425	383	500	450
64	1 850		500	450	560	504
72	2 340		600	540	710	639
80	2 890		750	675	850	765
88	3 500		900	810	1 000	900
96	4 170		1 060	954	1 180	1 062
104	4 890		1 250	1 125	1 400	1 260
112	5 670		1 400	1 260	1 600	1 440
120	6 510		1 600	1 440	1 800	1 620
128	7 410		1 800	1 620	2 000	1 800
136	8 360		2 000	1 800	2 240	2 016
144	9 370	2 240	2 016	2 500	2 250	
160	11 600	2 800	2 520	3 000	2 700	