
**Acoustics — Determination of airflow
resistance —**

**Part 2:
Alternating airflow method**

*Acoustique — Détermination de la résistance à l'écoulement de l'air —
Partie 2: Méthode avec écoulement d'air alternatif*

iteh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO 9053-2:2020

<https://standards.iteh.ai/catalog/standards/iso/7cdcb2b9-842c-472c-b547-8dd39154142b/iso-9053-2-2020>



iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO 9053-2:2020

<https://standards.iteh.ai/catalog/standards/iso/7cdcb2b9-842c-472c-b547-8dd39154142b/iso-9053-2-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols	3
5 Principle	5
6 Equipment	6
6.1 General.....	6
6.2 Device for producing the alternating airflow	6
6.3 Sound measuring device.....	7
6.4 Vessel and measurement cell.....	7
6.5 Device for measuring the static pressure	8
6.6 Device for measuring the frequency of the piston	8
7 Test specimens	8
7.1 Homogeneity of test specimen.....	8
7.2 Shape	8
7.3 Dimensions.....	8
7.3.1 Lateral dimensions.....	8
7.3.2 Thickness.....	9
7.4 Number of test specimens.....	9
8 Test procedure	9
9 Uncertainty	10
10 Test report	11
Annex A (normative) Effective ratio of specific heats for air	12
Annex B (informative) Acoustic model of the flow	15
Annex C (informative) Calculation of uncertainty	17
Annex D (informative) Airflow resistance of perforated support	19
Bibliography	20

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 43, *Acoustics*, Subcommittee SC 2, *Building acoustics*.

This first edition of ISO 9053-2, together with ISO 9053-1:2018, cancels and replaces ISO 9053:1991, which has been technically revised.

The main changes compared to the previous edition are as follows:

- the former method B in ISO 9053:1991 has been transferred to this document;
- the requirement to the dimensions of the test specimen have been updated;
- a correction for heat conduction has been added.

A list of all parts in the ISO 9053 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Acoustics — Determination of airflow resistance —

Part 2: Alternating airflow method

1 Scope

This document specifies an alternating airflow method for the determination of the airflow resistance^{[5], [6]} of porous materials for acoustical applications.

Determination of the airflow resistance based on static flow is described in ISO 9053-1.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO/IEC Guide 98-3, *Uncertainty of measurement — Part 3: Guide to the expression of uncertainty in measurement (GUM:1995)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <https://www.iso.org/obp>

— IEC Electropedia: available at <http://www.electropedia.org/>

3.1

airflow resistance

R

quantity defined by

$$R = \frac{\Delta p}{q_v}$$

where

Δp is the RMS air pressure difference, across the test specimen, due to the alternating airflow, in pascals;

q_v is the RMS volumetric airflow rate, passing through the test specimen, in cubic metres per second.

Note 1 to entry: Airflow resistance is expressed in pascals seconds per cubic metre.

3.2 specific airflow resistance

R_s
quantity defined by

$$R_s = R \cdot A$$

where

- R is the airflow resistance of the test specimen, in pascals seconds per cubic metre;
- A is the cross-section area of the test specimen, perpendicular to the direction of flow, in square metres.

Note 1 to entry: Specific airflow resistance is expressed in pascals seconds per metre.

3.3 airflow resistivity

σ
quantity defined by the following formula if the material is considered as being homogeneous

$$\sigma = \frac{R_s}{d}$$

where

- R_s is the specific airflow resistance of the test specimen, in pascals seconds per metre;
- d is the thickness of the test specimen, in the direction of flow, in metres.

Note 1 to entry: Airflow resistivity is expressed in pascals seconds per square metre.

3.4 airflow velocity

v
quantity defined by

$$v = \frac{q_v}{A}$$

where

- q_v is the RMS volumetric airflow rate, passing through the test specimen, in cubic metres per second;
- A is the cross-sectional area of the test specimen, perpendicular to the direction of flow, in square metres.

Note 1 to entry: Airflow velocity is expressed in metres per second.

3.5

sound pressure level

L_p

ten times the logarithm to the base 10 of the ratio of the time average of the square of the sound pressure, $p(t)$, during a stated time interval of duration, T (starting at t_1 and ending at t_2), to the square of a reference value, p_0 :

$$L_p = 10 \lg \left(\frac{\frac{1}{T} \int_{t_1}^{t_2} p^2(t) dt}{p_0^2} \right) \text{dB}$$

where the reference value, p_0 , is 20 μPa

Note 1 to entry: The sound pressure level is expressed in decibels.

4 Symbols

A	cross-section area of the test specimen, in square metres;
A_p	cross sectional area of the piston, in square metres;
b	thickness of the thermal boundary layer, in metres;
C_p	specific heat capacity at constant pressure, in joules per kilogram and degree kelvin;
c_0	speed of sound, in metres per second;
d	thickness of the test specimen, in the direction of flow, in metres;
f	frequency of the piston movement, in hertz;
h	amplitude of the stroke of the piston, in metres;
h_s	amplitude of the stroke of the piston when the measurement cell with the test specimen is mounted, in metres;
h_t	amplitude of the stroke of the piston when the air cavity is closed by the airtight termination, in metres;
j	$\sqrt{-1}$
k_a	thermal conductivity, in joules per meter, second and degree kelvin;
L_p	sound pressure level, in decibels;
$L_{p,b}$	background sound pressure level, in decibels;
$L_{p,s}$	sound pressure level in the air cavity when the measurement cell with the test specimen is mounted, in decibels;
$L_{p,t}$	sound pressure level in the air cavity with the airtight termination, in decibels;
l_h	characteristic thermal diffusion length, in metres;
N	acoustic compliance, in cubic metres per pascal;
P_s	static pressure, in pascals;

p	sound pressure, in pascals;
p_s	sound pressure when the test cell with the test specimen is mounted, in pascals;
p_t	sound pressure when the air cavity is closed by the airtight termination, in pascals;
p_0	sound pressure reference value, 20 μPa ;
q_s	rms value of the volume flow when the test cell with the test specimen is mounted, in cubic metres per second;
q_t	rms value of the volume flow when the air cavity is closed by the airtight termination, in cubic metres per second;
q_v	rms volumetric airflow rate, passing through the test specimen, in cubic metres per second;
R	airflow resistance of the test specimen, in pascals seconds per cubic metre;
R_s	specific airflow resistance of the test specimen, in pascals seconds per metre;
r	ratio between the stroke amplitudes;
r_r	radius of the perforations in the specimen support (Annex D), in metres;
S	total area, in square metres;
U	expanded uncertainty;
u	standard uncertainty;
V	volume of the air cavity with the airtight termination, in cubic metres;
v	airflow velocity, in metres per second;
v_s	rms-value of the airflow velocity through the test specimen, in metres per second;
y	thickness of the support, in metres;
Z_a	acoustic impedance of the cavity, in pascals seconds per cubic metres;
Δp	rms air pressure difference, across the test specimen, due to the alternating airflow, in pascals;
ϕ	perforation rate;
η	dynamic viscosity of air, in pascals seconds;
κ	ratio of specific heats for air;
κ'	effective ratio of specific heats for air;
λ	wavelength, in metres;
ρ_0	density of air, in kilograms per cubic metre;
σ	airflow resistivity of the test specimen, in pascals seconds per square metre;
ω	circular frequency, $2 \cdot \pi \cdot f$, in per second.

5 Principle


An alternating volume flow with a low frequency, f , for example of 2 Hz, is generated by a piston or similar device (see Figure 1 and Figure 2) moving sinusoidally. This volume flow acts on an air cavity that is either closed by an airtight termination or terminated by the test specimen mounted in a measurement cell. The sound pressure level is measured in the air cavity for both cases.

The pressure inside the cavity is the outside atmospheric pressure modulated by the alternating flow generated by the piston. The microphone mounted inside the cavity therefore measures the pressure difference across the specimen when the test cell with the specimen is mounted.

When the air cavity is closed, the volume flow creates a sound pressure in the air cavity that can be calculated from the piston movement, the dimensional information of the cavity and the atmospheric air pressure.

When the measurement cell is mounted, the main part of the generated volume flow passes through the test specimen and a lower sound pressure is observed in the air cavity. The difference between the sound pressure levels when the vessel is closed and when the test cell is mounted is a direct function of the airflow resistivity of the test specimen. By the measurement of the sound pressure differences, the airflow resistance for the test specimen can be computed.


It can be practical to use different piston stroke lengths for the closed vessel and when the measurement cell is mounted.

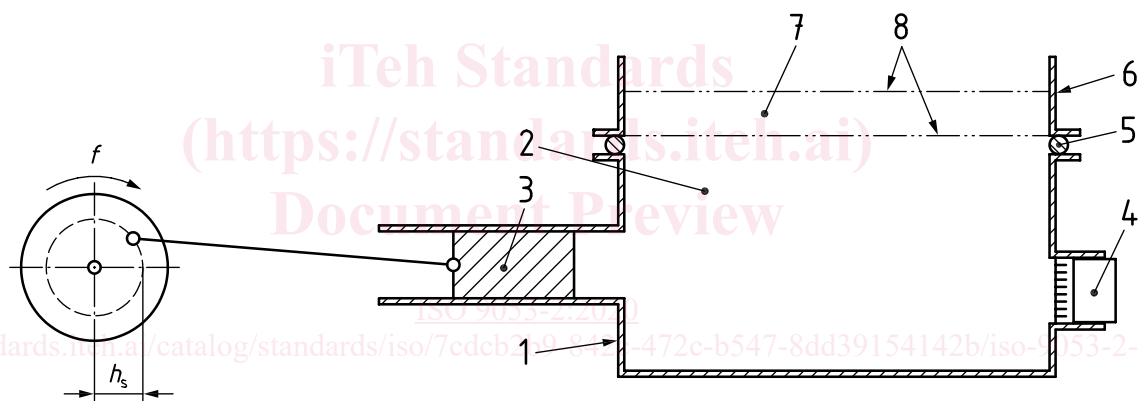

Key

- | | |
|-----------------|--------------------------------------|
| 1 vessel | 2 air cavity |
| 3 piston | 4 microphone |
| 5 seal | 6 measurement cell |
| 7 test specimen | 8 optional support for test specimen |

Figure 1 — Basic principle, termination with the test specimen

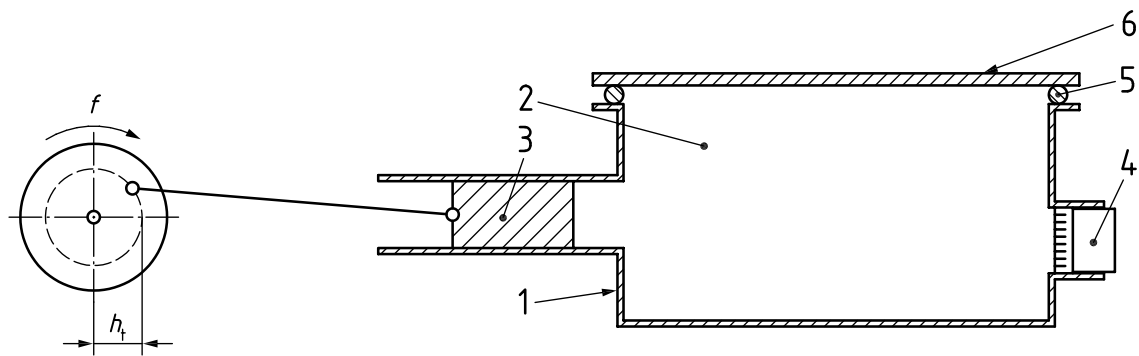**Key**

- | | | | |
|---|--------|---|----------------------|
| 1 | vessel | 2 | air cavity |
| 3 | piston | 4 | microphone |
| 5 | seal | 6 | airtight termination |

Figure 2 — Basic principle, termination with an airtight seal

NOTE For materials with a visco-inertial transition frequency below 100 Hz, the method described in ISO 9053-1 using a static flow can give a different result. Examples of such materials are: a) fibre materials with large fibres, such as some metal or plant fibres, b) foams with low porosity but big pores, such as some metal foams, c) granular materials with large grains and low porosity, such as road pavements.

6 Equipment

6.1 General

The equipment shall consist of:

- a) a device for producing the alternating airflow (see 6.2);
- b) a sound level meter or an alternative device for measuring the sound pressure level in a narrow frequency band (e.g. a fractional-octave band) around the frequency of the piston (see 6.3);
- c) a vessel (see 6.4)
 - containing the air cavity,
 - allowing connections to the microphone and the source of the alternating airflow, and
 - including an airtight termination and a measurement cell;
- d) a device for measuring the static pressure (see 6.5);
- e) a device for measuring the frequency of the piston (see 6.6);
- f) a device for measuring the thickness of the test specimen when it is positioned for the test.

6.2 Device for producing the alternating airflow

The alternating airflow shall be produced by a sinusoidally moving piston. The frequency of the piston movement, f , shall be in the range of 1 Hz to 4 Hz and known with sufficient accuracy (see Annex C).