This document is not an ASTM standard and is intended only to provide the user of an ASTM standard an indication of what changes have been made to the previous version. Because it may not be technically possible to adequately depict all changes accurately, ASTM recommends that users consult prior editions as appropriate. In all cases only the current version of the standard as published by ASTM is to be considered the official document.



Designation: D5635-04a Designation: D5635/D5635M - 11

# Standard Test Method for Dynamic Puncture Resistance of Roofing Membrane Specimens<sup>1</sup>

This standard is issued under the fixed designation D5635/D5635M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\varepsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the evaluation of the maximum dynamic puncture load that roofing membrane samples can withstand, without allowing the passage of water, when subjected to impact from a rigid object having a sharp edge.

1.2 This laboratory test can be conducted at any desired temperature using membrane samples manufactured in a factory or prepared in a laboratory.

1.3 Roof membrane specimens to which the test method is applicable include bituminous built-up, polymer-modified bitumens, vulcanized rubbers, non-vulcanized polymeric, and thermoplastic materials.

1.3.1 The applicability of this test method to these membrane specimens includes their use in vegetative roof systems.

1.4 This test method is not applicable to aggregate-surfaced membrane specimens; however, it is applicable to specimens having factory-applied granules.

1.5The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only. 1.5 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.6 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

## 2. Referenced Documents

2.1 ASTM Standards:<sup>2</sup>

C578 Specification for Rigid, Cellular Polystyrene Thermal Insulation D1079 Terminology Relating to Roofing and Waterproofing

#### 3. Terminology

<u>astm D5635/D5635M-11</u>

it ps://standards.iteh.ai/catalog/standards/sist/6db4e591-bd58-4a0c-acec-73fc85453fe1/astm-d5635-d5635m-11 3.1 Definitions:

3.1.1 For definitions of terms used in this test method, refer to Terminology D1079.

## 4. Summary of Test Method

4.1 The roofing membrane test specimen, set on a thermal insulation substrate, is subjected to a predetermined dynamic impact load created by a rigid falling puncture head. The head falls through a quarter-circle trajectory from a vertical position to horizontal position under gravitational acceleration.

4.2 The puncture energy is increased from 5 to 50 J (119[119 to 1190 ft-pdl)ft.pdl] in 2.5 J (59.4 ft-pdl)[59.4 ft-pdl] increments until puncture of the membrane specimen occurs or until the maximum energy is reached.

4.3 Puncture of the test specimen is assessed by visual examination and verified by conducting a watertightness test.

### 5. Principle of the Test Method

5.1 The energy at impact is equated to the potential energy of the raised puncture head as follows:

E = mgH

(1)

Copyright © ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States.

<sup>&</sup>lt;sup>1</sup> This test method is under the jurisdiction of ASTM Committee D08 on Roofing and Waterproofing and is the direct responsibility of Subcommittee D08.20 on Roofing Membrane Systems.

Current edition approved July 1, 2004. Feb. 15, 2011. Published July 2004. May 2011. Originally approved in 1994. Last previous edition approved in 2004 as D5635 – 04a. DOI: 10.1520/D5635-04A.10.1520/D5635\_D5635M-11.

<sup>&</sup>lt;sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

## D5635/D5635M – 11

where:

m = mass of the puncture head (in kg or lbm),

 $g = \text{gravitational acceleration (in m/s<sup>2</sup> or ft/s<sup>2</sup>), and$ 

H = height through which the puncture head falls (in metres or feet).

In this test method, the height is fixed at 0.51 m (1.67 ft).[1.67 ft]. With gravitational acceleration being equal to 9.8 m/s<sup>2</sup> ( $32 \text{ ft/s}^{[32 \text{ ft/s}^2]}$ ),], the impact energy is, thus, equal to the following:

$$E = 5 \cdot m \tag{2}$$

where: m = kg.

or  

$$E = 53.4 \cdot \mathrm{m}$$
 (3)

where:

m = 1bm.

Increasing the mass of the puncture head from 1 to 10 kg (2.2[2.2 to 22 lbm)[lbm] in increments of 0.5 kg (1.1 lbm)[1.1 lbm] increases the puncture energy from 5 to 50 J (119[119 to 1190 ft-pdl)ft-pdl] in increments of 2.5 J (59.4 ft-pdl). [59.4 ft-pdl].

NOTE 1-A counter weight placed on the falling arm opposite to the axis of rotation eliminates the need to include the mass of the arm in the determination of the impact energy.

#### 6. Significance and Use

6.1 An important factor affecting the performance of membrane roofing systems is their ability to resist dynamic puncture loads. This test method provides a means to assess dynamic puncture resistance.

6.2 This test method can be used to compare the dynamic puncture resistance of a single type of membrane as a function of a variety of insulation substrates or, conversely, to compare the resistance of a number of membrane specimens set on a single type of insulation.

6.3 The effect of temperature on puncture resistance can be studied by conducting the test under controlled conditions using such equipment as an environmental chamber, oven, or freezer.

6.4 The test method can be useful in developing performance criteria for membrane roofing systems.

6.5 The test method can be useful in developing classifications of dynamic puncture resistance of membrane roofing systems.

6.6 While it is considered that the results obtained by this laboratory test can afford a measure of the dynamic puncture resistance of membrane roofing systems in the field, (provided that service loads and temperature conditions are known) no direct correlation has yet been established.

6.7 This test method can be useful for evaluating the dynamic puncture resistance of membranes used in vegetative roof systems.

## 7. Apparatus

7.1 *Dynamic Puncture Device*—The dynamic puncture device consists primarily of a heavy base, a falling arm, and puncture head (see Fig. 1).

7.1.1 The falling arm is attached to the base so that it can rotate freely (for example, using ball bearings) from a vertical to horizontal position. The length of the arm is sufficiently long so that the puncture head can be secured to it at a distance that is  $0.51 \text{ m} (1.67 \text{ ft}), [1.67 \text{ ft}], \pm 0.5 \%$ , from the point of rotation at the base.

7.1.2 The shape and dimensions of a typical puncture head are given in Fig. 2. When mounted on the arm, the face of the puncture head is parallel to axis of rotation. Several heads of different mass may be needed. Alternatively, a means for adding weights to a given puncture head to increase its mass can be used. The head and additional weights shall constitute a continuous series of mass from 1 to 10 kg (2.2[2.2] to 22 lbm)[bm] in 0.5 kg (1.1 lbm)[1.1 lbm] increments. The mass of the puncture head shall be within  $\pm 0.5$  % of that selected.

NOTE 2—It is suggested that the puncture head be fabricated from 1018 mild steel to minimize risk of damage during its use. No matter the metal from which the puncture head is made, users of the test device should periodically examine the puncture head to check that damage has not occurred during use.

7.1.3 A counter weight, equivalent to the mass of the falling arm, is placed on the arm on the side of the axis of rotation opposite to that holding the puncture head. The presence of the counter weight eliminates the need to include the mass of the arm in the determination of the puncture energy. Alternatively, if a counter weight is not used, then the mass of the arm shall be included in the determination of the impact energy.

7.1.4 The device shall incorporate a mechanism that allows the puncture head to be kept stationary in an upright position, forming an angle from the vertical not exceeding  $5^{\circ}$ . This mechanism shall allow release of the arm so that it falls freely without any additional motion imposed.


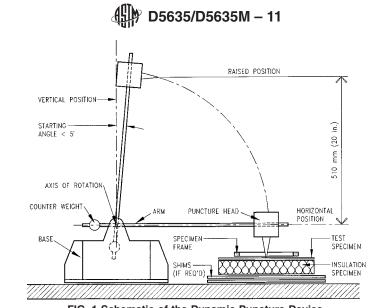


FIG. 1 Schematic of the Dynamic Puncture Device

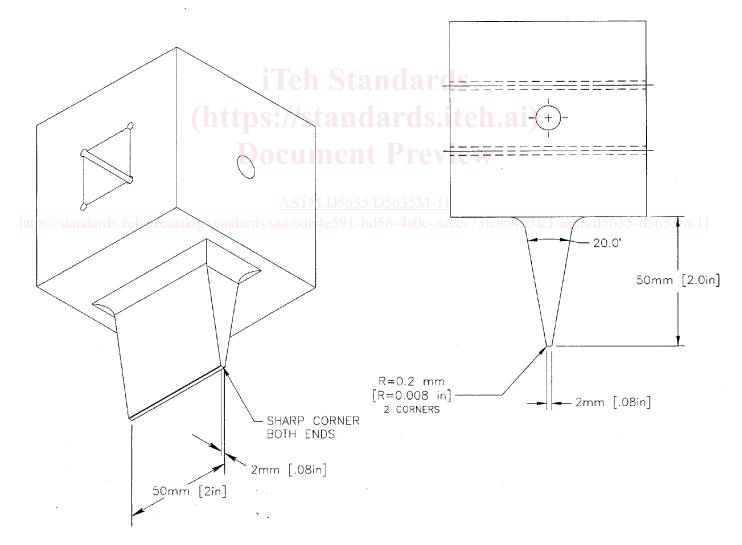

NOTE 1—Dimensions are in millimetres. FIG. 2 Shape and Dimensions of Puncture Head