



Designation: B963 – 11

# Standard Test Methods for Oil Content, Oil-Impregnation Efficiency, and Interconnected Porosity of Sintered Powder Metallurgy (PM) Products Using Archimedes' Principle<sup>1</sup>

This standard is issued under the fixed designation B963; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This standard describes three related test methods that cover the measurement of physical properties of oil-impregnated powder metallurgy products.

1.1.1 Determination of the volume percent of oil contained in the material.

1.1.2 Determination of the efficiency of the oil-impregnation process.

1.1.3 Determination of the percent interconnected porosity by oil impregnation.

1.2 The values stated in SI units are to be regarded as the standard. The values in parentheses are converted in accordance with IEEE/ASTM SI 10 and are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards*:<sup>2</sup>

[B243 Terminology of Powder Metallurgy](#)

[D1217 Test Method for Density and Relative Density \(Specific Gravity\) of Liquids by Bingham Pycnometer](#)

[D1298 Test Method for Density, Relative Density \(Specific Gravity\), or API Gravity of Crude Petroleum and Liquid Petroleum Products by Hydrometer Method](#)

2.2 *IEEE/ASTM Standard*:

[SI 10 American National Standard for Use of the International System of Units \(SI\): The Modern Metric System](#)

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Products and are the direct responsibility of Subcommittee B09.04 on Bearings.

Current edition approved May 1, 2011. Published May 2011. Last previous edition approved in 2008 as B963–08. DOI: 10.1520/B0963-11.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

## 3. Terminology

3.1 Definitions of powder metallurgy (PM) terms can be found in Terminology B243. Additional descriptive material is available in the Related Material section of Vol. 02.05 of the *Annual Book of ASTM Standards*.

## 4. Summary of Test Method

4.1 The part or test specimen is first weighed in air. It is then oil impregnated to fill the surface-connected porosity and the specimen is reweighed. The test specimen is then weighed when immersed in water and its volume calculated based on Archimedes' principle. The oil is then removed and the specimen is reweighed.

4.2 The *oil content* of an oil-impregnated part or test specimen is then calculated as a percentage of the volume of the specimen. This may be done for the as-received and the fully oil-impregnated specimen.

4.3 The *oil-impregnation efficiency* is calculated by dividing the as-received oil content by the fully impregnated oil content and expressing the result as a percentage.

4.4 The volume percentage of *interconnected porosity* (as measured by oil impregnation) is then calculated based on the amount of oil in the fully oil-impregnated specimen.

## 5. Significance and Use

5.1 Oil content values are generally contained in specifications for oil-impregnated PM bearings.

5.2 The oil-impregnation efficiency provides an indication of how well the as-received parts had been impregnated.

5.3 The desired self-lubricating performance of PM bearings requires a minimum amount of interconnected porosity and satisfactory oil impregnation of the interconnected porosity. A minimum oil content is specified.

5.4 The results from these test methods may be used for quality control or compliance purposes.

## 6. Apparatus

6.1 *Analytical Balance*—Precision single-pan balance that will permit readings within 0.01 % of the test specimen mass. See Table 1.

TABLE 1 Balance Sensitivity

Mass, g	Balance Sensitivity, g
less than 10	0.0001
10 to less than 100	0.001
100 to less than 1000	0.01
1000 to less than 10 000	0.1

6.2 *Water Container*—A glass beaker or other suitable transparent container should be used to contain the water.

NOTE 1—A transparent container makes it easier to see air bubbles adhering to the test specimen and specimen support when immersed in water.

NOTE 2—For the most precise determination, the water container should be of a size that the level of the water does not rise more than 2.5 mm (0.10 in.) when the test specimen is lowered into the water.

6.3 *Water*—Distilled or deionized water to which 0.05 to 0.1 volume percent of a wetting agent has been added to reduce the effects of surface tension.

NOTE 3—Degassing the water by evacuation, boiling, or ultrasonic agitation helps to prevent air bubbles from collecting on the test specimen and support when immersed in water.

6.4 *Test Specimen Support for Weighing in Water*—Two typical arrangements are shown in Fig. 1. The suspension wire may be twisted around the test specimen or the test specimen may be supported in a wire basket that is attached to the suspension wire. For either arrangement, a single corrosion-resistant wire—for example, austenitic stainless steel, copper,

or nichrome—shall be used for the basket and suspension wire. The maximum recommended diameter of suspension wire to be used for various mass ranges is shown in Table 2.

NOTE 4—For the most precise determinations, it is important that the mass and volume of all supporting wires immersed in water be minimized.

6.5 *Oil for Oil-Impregnation*—The same type of oil that was used to impregnate the parts originally.

6.5.1 If parts are not already impregnated, oil with a viscosity of  $20 \times 10^{-6}$  to  $65 \times 10^{-6}$  m<sup>2</sup>/s (20 to 65 cSt or 100 to 300 SSU) at 38 °C (100 °F) has been found to be suitable.

6.6 *Vacuum Impregnation Apparatus*—Equipment for impregnation of the part or test specimen with oil.


6.7 *Thermometer*—A thermometer with an accuracy of 0.5 °C (1 °F) to measure the temperature of the water.

6.8 *Soxhlet Apparatus*—Glass laboratory unit consisting of a condenser, extractor, filter, flask with a suitable solvent for the oil such as petroleum ether, and a heating mantle.

## 7. Preparation of Test Specimens

7.1 The mass of the test specimen shall be a minimum of 1.0 g. For small parts, several parts may be combined to reach the minimum mass.

7.2 Thoroughly wipe clean all surfaces of the test specimen to remove any adhering foreign materials such as dirt or oxide scale.

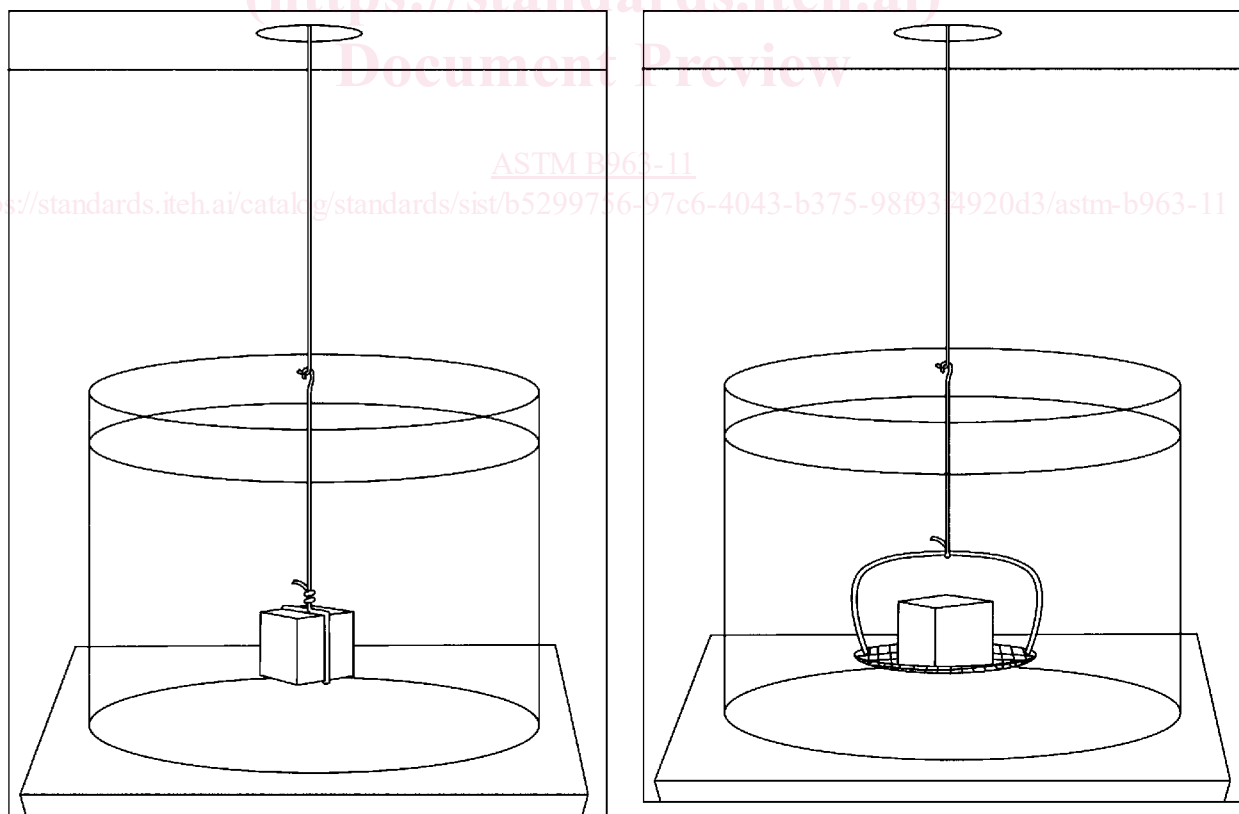

a. Twisted wire arrangement

b. Basket support arrangement

FIG. 1 Methods for Holding the Test Specimen When Weighing in Water