



Designation: ~~D1264-03 (Reapproved 2008)~~ Designation: D1264 – 11

Standard Test Method for Determining the Water Washout Characteristics of Lubricating Greases¹

This standard is issued under the fixed designation D1264; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

~~1.1 This test method covers the evaluation of the resistance of a lubricating grease to washout by water from a bearing, when tested at 38 and 79°C (100 and 175°F) under the prescribed laboratory conditions. It is not to be considered the equivalent of service evaluation tests. This test method may not be suitable for some greases containing highly volatile components.*~~

1.1 This test method covers the evaluation of the resistance of a lubricating grease to washout by water from a bearing, when tested at 38 and 79°C (100 and 175°F) under the prescribed laboratory conditions. It is not to be considered the equivalent of service evaluation tests. This test method may not be suitable for some greases containing highly volatile components. Precision and bias was determined using grease ranging from NLGI 3 to 0 grades in the research report (see Section 10).

1.2 The values state in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For specific warning statements, see 6.3.

2. Referenced Documents

2.1 *ASTM Adjuncts:*

Standard Ball Bearing²

D2PP, Version 4.43, Determination of Precision and Bias Data for Use in Test Methods for Petroleum Products³

3. Summary of Test Method

3.1 The grease is packed into a ball bearing, the bearing is then inserted in a housing with specified clearances, and rotated at 600 ± 30 rpm. Water, controlled at the specified test temperature, impinges on the bearing housing at a rate of 5 ± 0.5 mL/s. The amount of grease washed out in 60 ± 1 min is a measure of the resistance of the grease to water washout.

4. Significance and Use

4.1 This test method estimates the resistance of greases to water washout from ball bearings under conditions of the test. No correlation with field service has been established.

5. Apparatus

5.1 *Ball Bearing*, ASTM test bearing size 6204 (see ADJD3336).²

5.2 *Bearing Housing and Shield* with dimensions as shown in Fig. 1.

5.3 *Reservoir, Bearing-Housing Mount, Circulating Pump, and Drive Motor*, similar or equivalent to those shown in Fig. 1.

5.4 *Heating Source*, to maintain the water temperature at $79 \pm 1.7^\circ\text{C}$ ($175 \pm 3^\circ\text{F}$), to maintain the water temperature at $38^\circ\text{C} \pm 1.7^\circ\text{C}$ ($100^\circ\text{F} \pm 3^\circ\text{F}$) or $79^\circ\text{C} \pm 1.7^\circ\text{C}$ ($174^\circ\text{F} \pm 3^\circ\text{F}$).

NOTE 1—Suitable temperature control may be obtained by the use of immersion heaters, steam coils, or infrared heat lamps, in conjunction with transformers or thermostats.

¹ This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products and Lubricants and is the direct responsibility of Subcommittee D02.G0.06 on Functional Tests - Contamination.


~~Current edition approved Dec. 1, 2008. Published February 2009. Originally approved in 1953. Last previous edition approved in 2003 as D1264-03^{ε1}. DOI: 10.1520/D1264-03R08.~~

Current edition approved May 1, 2011. Published May 2011. Originally approved in 1953. Last previous edition approved in 2008 as D1264-03(2008). DOI: 10.1520/D1264-11.


² Available from ASTM International Headquarters. Order Adjunct No. ADJD3336. Original adjunct produced in 1984.

³ ADJD6300 is no longer available.

*A Summary of Changes section appears at the end of this standard.

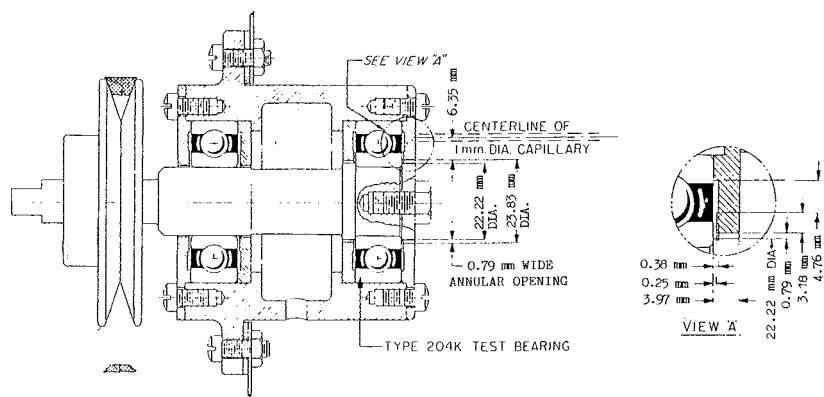

TYPICAL CROSS SECTION
THRUST BEARING ASSEMBLY

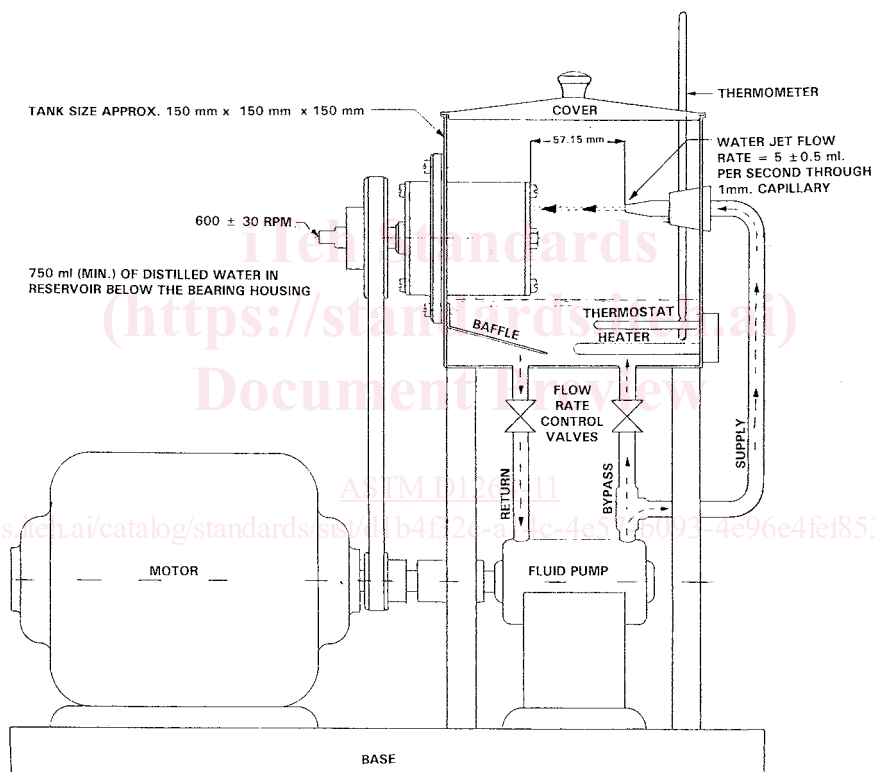

in.	mm	in.	mm	°F	°C
0.010	0.25	0.875	22.22	100 ± 5	37.8 ± 3
0.010	0.25	0.875	22.22	100 ± 3	38 ± 1.7
0.015	0.38	0.938	23.81	175 ± 3	79.4 ± 2
0.015	0.38	0.938	23.81	174 ± 3	79 ± 1.7
0.031	0.79	2 1/4	57.1		
1/8	3.18	6	152		
5/32	3.97				
3/16	4.76				
1/4	6.35				

FIG. 1 Water Washout Characteristics of Lubricating Grease Apparatus

5.5 Thermometer or Thermocouple, to determine the temperature of the water reservoir.

6. Materials and Reagents

6.1 Purity of Reagents—Reagent grade chemicals shall be used in all tests. Unless otherwise indicated, it is intended that all reagents shall conform to the specifications of the committee on Analytical Reagents of the American Chemical Society, where