



~~Designation: D2244-09b~~ Designation: D2244 – 11

Standard Practice for Calculation of Color Tolerances and Color Differences from Instrumentally Measured Color Coordinates¹

This standard is issued under the fixed designation D2244; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

INTRODUCTION

This practice originally resulted from the consolidation of a number of separately published methods for the instrumental evaluation of color differences. As revised in 1979, it included four color spaces in which color-scale values could be measured by instruments, many of which were obsolete, and the color differences calculated by ten equations for different color scales. The sections on apparatus, calibration standards and methods, and measurement procedures served little purpose in the light of modern color-measurement technology. The revision published in 1993 omitted these sections, and limited the color spaces and color-difference equations considered, to the three most widely used in the paint and related coatings industry. A previous revision added two new color tolerance equations and put two of the color difference equations from the 1993 version in an informative appendix for historical purposes.

1. Scope*

1.1 This practice covers the calculation, from instrumentally measured color coordinates based on daylight illumination, of color tolerances and small color differences between opaque specimens such as painted panels, plastic plaques, or textile swatches. Where it is suspected that the specimens may be metameric, that is, possess different spectral curves though visually alike in color, Practice D4086 should be used to verify instrumental results. The tolerances and differences determined by these procedures are expressed in terms of approximately uniform visual color perception in CIE 1976 CIELAB opponent-color space (1),² CMC tolerance units (2), CIE94 tolerance units (3), the DIN99 color difference formula given in DIN 6176 (4), or the new CIEDE2000 color difference units (5).

1.2 For product specification, the purchaser and the seller shall agree upon the permissible color tolerance between test specimen and reference and the procedure for calculating the color tolerance. Each material and condition of use may require specific color tolerances because other appearance factors, (for example, specimen proximity, gloss, and texture), may affect the correlation between the magnitude of a measured color difference and its commercial acceptability.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory requirements prior to use.*

2. Referenced Documents

2.1 ASTM Standards:³

- D1729 Practice for Visual Appraisal of Colors and Color Differences of Diffusely-Illuminated Opaque Materials
- D4086 Practice for Visual Evaluation of Metamerism
- E284 Terminology of Appearance
- E308 Practice for Computing the Colors of Objects by Using the CIE System
- E805 Practice for Identification of Instrumental Methods of Color or Color-Difference Measurement of Materials

¹ This practice is under the jurisdiction of ASTM Committee E12 on Color and Appearance and is the direct responsibility of Subcommittee E12.04 on Color and Appearance Analysis.

Current edition approved Dec. 1, 2009; 2011. Published February 2010; June 2011. Originally approved in 1964. Last previous edition approved in 2009 as D2244 – 09ab. DOI: 10.1520/D2244-09B-10.1520/D2244-11.

² The boldface numbers in parentheses refer to the list of references at the end of this standard.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard.

E1164 Practice for Obtaining Spectrometric Data for Object-Color Evaluation

2.2 Other Standards:

DIN 6176 Farbmetrische, Bestimmung von Farbabständen bei Körperfarben nach der DIN99-Formel ⁴

3. Terminology

3.1 Terms and definitions in Terminology E284 are applicable to this practice.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *colorimetric spectrometer, n*—spectrometer, one component of which is a dispersive element (such as a prism, grating or interference filter or wedge or tunable or discrete series of monochromatic sources), that is normally capable of producing as output colorimetric data (such as tristimulus values and derived color coordinates or indices of appearance attributes). Additionally, the colorimetric spectrometer may also be able to report the underlying spectral data from which the colorimetric data were derived.

3.2.1.1 *Discussion*—At one time, UV-VIS analytical spectrophotometers were used for colorimetric measurements. Today, while instruments intended for use in color measurements share many common components, UV-VIS analytical spectrophotometers are designed to optimize their use in chemometric quantitative analysis, which requires very precise spectral position and very narrow bandpass and moderate baseline stability. Colorimetric spectrometers are designed to optimize their use as digital simulations of the visual colorimeter or as the source of spectral and colorimetric information for computer-assisted color matching systems. Digital colorimetry allows more tolerance on the spectral scale and spectral bandwidth but demand much more stability in the radiometric scale.

3.2.2 *color tolerance equation, n*—a mathematical expression, derived from acceptability judgments, which distorts the metric of color space based on the coordinates in that color space, of a reference color, for the purpose of single number shade passing.

3.2.2.1 *Discussion*—The color tolerance equation computes a pass/fail value based on which of the pair of specimens is assigned the designation “standard.” Thus, inter-changing the reference and test specimens will result in a change in the predicted level of acceptance between the specimens while the perceived difference is unchanged. A color difference equation quantifies distance in a color space using the metric of that space. Inter-changing the reference and test specimens does not change either the perceived or predicted color differences.

4. Summary of Practice

4.1 The differences in color between a reference and a test specimen are determined from measurements made by use of a spectral based or filter based colorimeter. Reflectance readings from spectral instruments are converted by computations to color-scale values in accordance with Practice E308, or these color-scale values may be read directly from instruments that automatically make the computations. Color-difference units are computed, from these color-scale values, and approximate the perceived color differences between the reference and the test specimen.

5. Significance and Use

5.1 The original CIE color scales based on tristimulus values X , Y , Z and chromaticity coordinates x , y are not uniform visually. Each subsequent color scale based on CIE values has had weighting factors applied to provide some degree of uniformity so that color differences in various regions of color space will be more nearly comparable. On the other hand, color differences obtained for the same specimens evaluated in different color-scale systems are not likely to be identical. To avoid confusion, color differences among specimens or the associated tolerances should be compared only when they are obtained for the same color-scale system. There is no simple factor that can be used to convert accurately color differences or color tolerances in one system to difference or tolerance units in another system for all colors of specimens.

5.2 For uniformity of practice, the CIE recommended in 1976 the use of two color metrics. The CIELAB metric, with its associated color-difference equation, has found wide acceptance in the coatings, plastics, textiles and related industries. While the CIELAB equation has not completely replaced the use of Hunter L_H , a_H , b_H , this older scale is no longer recommended for other than legacy users, and is therefore included in an Appendix for historical purposes. The CIELAB color-difference equation is also not recommended in this practice for use in describing small and moderate color differences (differences with magnitude less than 5.0 ΔE^*_{ab} units). The four more recently defined equations, documented here, are highly recommended for use with color-differences in the range of 0.0 to 5.0 ΔE^*_{ab} units.

5.3 Users of color tolerance equations have found that, in each system, summation of three, vector color-difference components into a single scalar value is very useful for determining whether a specimen color is within a specified tolerance from a standard. However, for control of color in production, it may be necessary to know not only the magnitude of the departure from standard but also the direction of this departure. It is possible to include information on the direction of a small color difference by listing the three instrumentally determined components of the color difference.

5.4 Selection of color tolerances based on instrumental values should be carefully correlated with a visual appraisal of the acceptability of differences in hue, lightness, and saturation obtained by using Practice D1729. The three tolerance equations given here have been tested extensively against such data for textiles and plastics and have been shown to agree with the visual

⁴ Available from Beuth Verlag GmbH, 10772, Berlin, Germany, <http://www.beuth.de/>.

evaluations to within the experimental uncertainty of the visual judgments. That implies that the equations themselves misclassify a color difference with a frequency no greater than that of the most experienced visual color matcher.

5.5 While color difference equations and color tolerance equations are routinely applied to a wide range of illuminants, they have been derived or optimized, or both, for use under daylight illumination. Good correlation with the visual judgments may not be obtained when the calculations are made with other illuminants. Use of a tolerance equation for other than daylight conditions will require visual confirmation of the level of metamerism in accordance with Practice D4086.

6. Description of Color-Difference and Color-Tolerance Equations

6.1 *CIE 1931 and 1964 Color Spaces*—The daylight colors of opaque specimens are represented by points in a space formed by three rectangular axes representing the lightness scale Y and chromaticity scales x and y , where:

$$x = \frac{X}{X + Y + Z} \quad (1)$$

$$y = \frac{Y}{X + Y + Z} \quad (2)$$

where X , Y , and Z are tristimulus values for either the 1931 CIE standard observer (2° observer) or the 1964 CIE standard observer (10° observer) and standard illuminant D_{65} , or other phase of daylight. These scales do not provide a perceptually uniform color space. Consequently, color differences are seldom if ever computed directly from differences in x , y , and Y .

6.2 *CIE 1976 $L^* a^* b^*$ Uniform Color Space and Color-Difference Equation (1, 6)*—This is an approximately uniform color space based on nonlinear expansion of the tristimulus values and taking differences to produce three opponent axes that approximate the percepts of lightness-darkness, redness-greenness and yellowness-blueness. It is produced by plotting in rectangular coordinates the quantities L^* , a^* , b^* , calculated as follows:

$$L^* = 116f(Q_Y) - 16 \quad (3)$$

$$a^* = 500 [f(Q_X) - f(Q_Y)] \quad (4)$$

$$b^* = 200 [f(Q_Y) - f(Q_Z)] \quad (5)$$

where

$$Q_X = (X/X_n); Q_Y = (Y/Y_n); Q_Z = (Z/Z_n)$$

and

$$f(Q_i) = Q_i^{1/3} \text{ if } Q_i > (6/29)^3$$

else

$$f(Q_i) = (841/108)Q_i + 4/29 \text{ if } Q_i \leq (6/29)^3$$

Here, i varies as X , Y , and Z .

The tristimulus values X_n , Y_n , Z_n define the color of the nominally white object-color stimulus. Usually, the white object-color stimulus is given by the spectral radiant power of one of the CIE standard illuminants, for example, C , D_{65} or another phase of daylight, reflected into the observer's eye by the perfect reflecting diffuser. Under these conditions, X_n , Y_n , Z_n are the tristimulus values of the standard illuminant with Y_n equal to 100.

6.2.1 The total color-difference ΔE^*_{ab} between two colors each given in terms of L^* , a^* , b^* is calculated as follows:

$$\Delta E^*_{ab} = \sqrt{(\Delta L^*)^2 + (\Delta a^*)^2 + (\Delta b^*)^2} \quad (6)$$

NOTE 1—The color space defined above is called the CIE 1976 $L^* a^* b^*$ space and the color-difference equation the CIE 1976 $L^* a^* b^*$ color-difference formula. The abbreviation CIELAB (with all letters capitalized) is recommended.

6.2.2 The magnitude, ΔE^*_{ab} , gives no indication of the character of the difference since it does not indicate the relative quantity and direction of hue, chroma, and lightness differences.

6.2.3 The direction of the color difference is described by the magnitude and algebraic signs of the components ΔL^* , Δa^* , and Δb^* :

$$\Delta L^* = L^*_B - L^*_S \quad (7)$$

$$\Delta a^* = a^*_B - a^*_S \quad (8)$$

$$\Delta b^* = b^*_B - b^*_S \quad (9)$$

where L^*_S , a^*_S , and b^*_S refer to the reference or standard, and L^*_B , a^*_B , and b^*_B refer to the test specimen or batch. The signs of the components ΔL^* , Δa^* , and Δb^* have the following approximate meanings (7):

$$+ \Delta L^* = \text{lighter} \quad (10)$$

$$- \Delta L^* = \text{darker} \quad (11)$$

$$+ \Delta a^* = \text{redder (less green)} \quad (12)$$

$-\Delta a^*$ = greener (less red) (13)

$+\Delta b^*$ = yellow (less blue) (14)

$-\Delta b^*$ = bluer (less yellow) (15)

6.2.4 For judging the direction of the color difference between two colors, it is useful to calculate hue angles h_{ab} and CIE 1976 metric chroma C^*_{ab} according to the following pseudocode: ~~If $b^* \neq 0$, then~~

(16) if $b^* = 0$ then

h_{ab}

D2244-11_20

else

$h_{ab} = 180 - (180 / \pi) \arctan(a^*/b^*) - 90 \text{ sign}(b^*)$

end if.

Here *sign* is a function that returns the sign of the argument, and *arctan* is the inverse tangent function returning angles in units of radians. The units of h_{ab} calculated by the above are degrees counter-clockwise from the positive a^* axis. The function *sign* is expected to return a minus one for negative values of the argument, a zero when the argument is zero, and a positive one for positive values of the argument.

(17) $C^*_{ab} = (a^*)^2 + (b^*)^2$

Differences in hue angle h_{ab} between the test specimen and reference can be correlated with differences in their visually perceived hue, except for very dark colors (8). Differences in chroma $\Delta C^*_{ab} = ([C^*_{ab}]_{batch} - [C^*_{ab}]_{standard})$ can similarly be correlated with differences in visually perceived chroma.

6.2.5 For judging the relative contributions of lightness differences, chroma differences, and hue differences between two colors, it is useful to calculate the CIE 1976 Metric Hue Difference ΔH^*_{ab} between the colors as follows:


 (https://standards.iteh.ai)
 Document Preview

ASTM D2244-11

<https://standards.iteh.ai/catalog/standards/sist/327adf13-acbd-4d39-9cec-a39275b438f4/astm-d2244-11>

where

$$\text{if } a^*_S b^*_B > a^*_B b^*_S \quad (19)$$

$$\text{if } a^*_S b^*_B > a^*_B b^*_S \quad (19)$$

When then

$$s = 1$$

else

$$s = -1$$

end if.

When ΔE^*_{ab} is calculated as in 6.2.1 and ΔC^*_{ab} is calculated as in 6.2.4, then

$$(20) \quad \Delta E^*_{ab} = [(\Delta L^*)^2 + (\Delta C^*)^2 + (\Delta H^*)^2]^{0.5}$$

contains terms showing the relative contributions of lightness differences ΔL^*_{ab} , chroma differences ΔC^*_{ab} , and hue differences ΔH^*_{ab} .

6.3 CMC Color Tolerance Equation—The Colour Measurement Committee of the Society of Dyers and Colourists undertook a task to improve upon the results of the JPC79 tolerance equation (2) developed at J & P Coates thread company in the United Kingdom. It was a combination of the CIELAB equation and local optimization based on the position of the standard used to derive the FMC-2 equation. It was based on the more intuitive perceptual variables of lightness, chroma and hue instead of the lightness, redness/greenness and yellowness/blueness of the older equation. It is intended to be used as a single-number shade-passing equation. There should not be a need to break the equation down into perceptual components—the CIELAB components of the model do that already. Fig. 1 (12) shows the CIELAB chromaticness plane (a^* , b^*) with a large number of CMC ellipsoids plotted on that plane. The figure clearly shows the change in area of the ellipses with increases in CIELAB metric chroma C^*_{ab} and with respect to changes in CIELAB metric hue angle h^*_{ab} . The CMC components and single number tolerances are computed as follows:

$$(21) \quad \Delta E_{CMC}(l : c) = (\Delta L^* l \cdot SL)^2 + (\Delta C^* c \cdot Sc)^2 + (\Delta H^* SH)^2$$

The parameters (l , c) are to compensate for systematic bias or parametric effects such as texture and sample separation. The most common values are (2:1) for textiles and plastics that are molded to simulate a woven material, implying that lightness differences carry half the importance of chroma and hue differences **D2244-11 28**

The CMC equation is sometimes used with a commercial factor. See Appendix X3 for more information on use of commercial factors in color tolerance equations. The most common values are (2:1) for textiles and plastics that are molded to simulate a woven material, implying that lightness differences carry half the importance of chroma and hue differences (13). The values (1:1), often assumed to represent a just perceptible difference, should be applied to materials that require very critical tolerances or have glossy surfaces. For specimens that are matte, randomly rough, or mildly textured, values intermediate between (1:1) and (2:1) can be

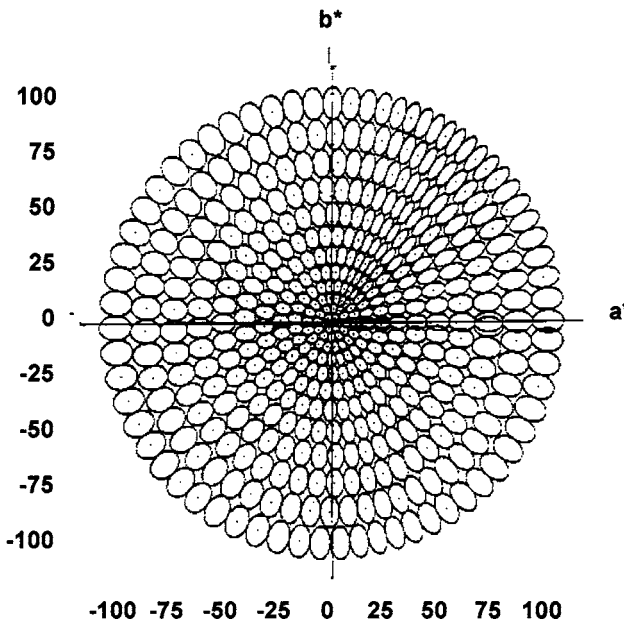


FIG. 1 CMC Ellipse Distribution in the CIELAB (a^* , b^*) Plane

used, with the value (1.3:1) being reported most frequently. The parameter cf is a commercial factor (**15**), used to adjust the total volume of the tolerance region so that accept/reject decisions can be made on the basis of a unit value of the tolerance. The color dependent functions are defined as:

$$S_L = 0.511, \quad \text{for } L^* < 16$$

$$S_C = \frac{0.0638 \cdot C^*}{(1 + 0.0131 \cdot C^*)} + 0.638$$

$$S_H = S_C(T \cdot f + 1 - f)$$

where

$$f = \left\{ \frac{(C^*)^4}{(C^*)^4 + 1900} \right\}^{\frac{1}{2}}$$

$$T = 0.56 + 0.2 \cos(h + 168^\circ), \quad \text{if } 164^\circ < h < 345^\circ$$

else

$$T = 0.36 + 0.4 \cos(h + 35^\circ)$$

All angles are given in degrees but will generally need to be converted to radians for processing on a digital computer. In Eq 22, the values of L^* , C^* , and h are taken to be those of the standard specimen.

6.4 *CIE94 Color Tolerance Equation (3)*—The development of this color tolerance equation was prompted by the success of the CMC tolerance equation. It was derived primarily from visual observations of automotive paints on steel panels. Like the CMC equation, it is based on the CIELAB color metric and uses the position of the standard in CIELAB color space to derive a set of analytical functions that modify the spacing of the CIELAB space in the region around the standard. Its weighting functions are much simpler than those of the CMC equation. CIE94 tolerances are computed as follows:

$$(23) \quad \Delta E^*_{94} = (\Delta L^* k_{LS} L)^2 + (\Delta C^* k_{CSC})^2 + (\Delta H^* k_{HSH})$$

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ASTM D2244-11](#)

<https://standards.itih.ai/catalog/standards/sist/327adf13-acbd-4d39-9cec-a39275b438f4/astm-d2244-11>