

INTERNATIONAL
STANDARD

ISO
23930

First edition
2023-01

**Fibre-reinforced plastic composites —
Full-section compressive test for
pultruded profiles**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 23930:2023

<https://standards.iteh.ai/catalog/standards/sist/bf8a0147-706e-4b64-8386-736da0d69f5e/iso-23930-2023>



Reference number
ISO 23930:2023(E)

© ISO 2023

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 23930:2023

<https://standards.iteh.ai/catalog/standards/sist/bf8a0147-706e-4b64-8386-736da0d69f5e/iso-23930-2023>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	3
5.1 Test machine.....	3
5.2 Compression platens.....	3
5.3 Strain indicator.....	3
6 Specimens	4
6.1 Geometry.....	4
6.2 Preparation of specimens.....	4
6.3 Number of test specimens.....	4
6.4 Sampling of test specimens.....	4
6.5 Conditioning atmosphere.....	4
7 Test procedure	5
7.1 Test atmosphere.....	5
7.2 Measurement of initial dimensions of test specimen.....	5
7.3 Test speed.....	5
8 Calculation and expression results	5
8.1 General.....	5
8.2 Full-section compressive strength.....	6
8.3 Strain.....	6
8.4 Full-section compressive modulus.....	6
8.4.1 General.....	6
8.4.2 Chord slope.....	6
8.4.3 Regression slope.....	6
8.5 Failure mode.....	7
9 Test report	7
Annex A (informative) Calculation method of slenderness ratio and width-thickness ratio	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

ISO 23930:2023

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Previous attempts to determine compressive properties of pultruded FRP have been hampered by experimental difficulty of clamping and different boundary conditions between test specimen and actual specimen.

The procedure presented in this document uses the full-section compressive test to determine the compressive properties of pultruded FRP. This test is convenient and able to evaluate the mechanical properties of the full-section. The result of this test, despite being lower than that of the coupon test, can better represent the properties across the full-section and thus, is recommended to be used in the strength design of pultruded FRP compressive members.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 23930:2023](https://standards.iteh.ai/catalog/standards/sist/bf8a0147-706e-4b64-8386-736da0d69f5e/iso-23930-2023)

<https://standards.iteh.ai/catalog/standards/sist/bf8a0147-706e-4b64-8386-736da0d69f5e/iso-23930-2023>

Fibre-reinforced plastic composites — Full-section compressive test for pultruded profiles

1 Scope

This document specifies a method for determining the compressive properties in the pultruded fibre reinforced plastic (FRP) using full-section compressive tests.

It is applicable to pultruded FRP profiles. The scope is not limited to types of fibres and resins.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 9513, *Metallic materials — Calibration of extensometer systems used in uniaxial testing*

ISO 16012, *Plastics — Determination of linear dimensions of test specimens*

ISO 21920-2, *Geometrical product specifications (GPS) — Surface texture: Profile — Part 2 Terms, definitions and surface texture parameters*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

full-section compressive stress compressive stress

σ

compressive force divided by initial cross-sectional area perpendicular to the loading direction

Note 1 to entry: Full-section compressive stress is expressed in megapascals (MPa).

3.2

full-section compressive strength compressive strength

σ_c

maximum compressive force divided by initial cross-sectional area perpendicular to the loading direction

Note 1 to entry: Full-section compressive strength is expressed in megapascals (MPa).

3.3
compressive strength at x% compressive strain

σ_x
stress at which the strain, ϵ , reaches the specified value x% expressed as a percentage

Note 1 to entry: Full-section compressive strength at x% compressive strain is expressed in megapascals (MPa).

3.4
compressive strain

ϵ
deformation divided by the initial length parallel to the loading direction, in most cases measured by strain indicator

Note 1 to entry: Compressive strain is expressed as a percentage.

3.5
full-section compressive modulus
compressive modulus

E_c
full-section compressive stress divided by compressive strain

Note 1 to entry: Full-section compressive modulus is expressed in megapascals (MPa).

3.6
radius of gyration

r
square root of second moment of area divided by total cross-sectional area

Note 1 to entry: Radius of gyration is expressed in millimetre (mm).

3.7
length

h
length of specimen

Note 1 to entry: Length is expressed in millimetre (mm).

3.8
gauge length

h_0
gauge length of specimen

Note 1 to entry: Gauge length is expressed in millimetre (mm).

3.9
slenderness ratio

λ
length divided by radius of gyration

3.10
width-thickness ratio

β
plate width divided by thickness, while plate width is the larger measurement of plate in longitudinal and transverse orientation

4 Principle

The test is a method for evaluating full-section compressive properties of pultruded FRP. The compressive test is carried out using a universal test machine. Compressive stress is measured from applied force. Compressive strain is measured directly on the specimen via gauges or extensometers.

5 Apparatus

5.1 Test machine

The test machine shall be in accordance with ISO 7500-1 and ISO 9513. The force measurement system shall comply with Class 1 as defined in ISO 7500-1. The test machine shall have a measuring system of crosshead displacement. See [Figure 1](#).

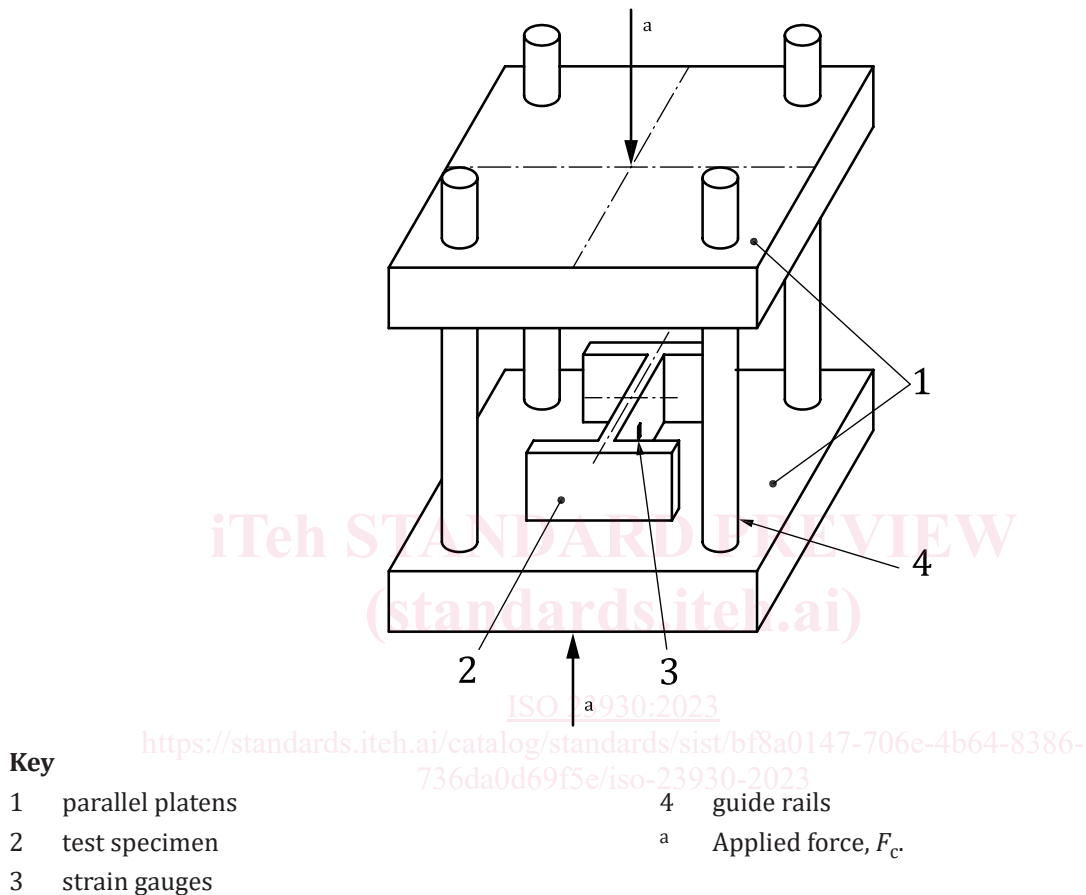


Figure 1 — Schematic illustration of test

5.2 Compression platens

Two parallel platens, well guided to avoid lateral movements and of 5 mm larger size more than the specimen to be tested, shall be used. One compression platen shall be rigidly mounted, while the other platen shall remain parallel during the test. The minimum hardness of the compression platens shall be 700 HV 0,2. The maximum surface roughness of the compression platens shall be 6,3 μm , measured in accordance with ISO 21920-2.

5.3 Strain indicator

If compressive modulus is required, strain gauges shall be used. The grid length of strain gauges shall be longer than 3 mm and adapted to the size of the fibre structure of the material being tested. Strain gauges shall have appropriate electrical resistance. The accuracy of k-factor shall be 1 % of the relevant value or better. According to the cross section of tested specimen, strain gauges shall be attached in different locations, see [Figure 2](#).

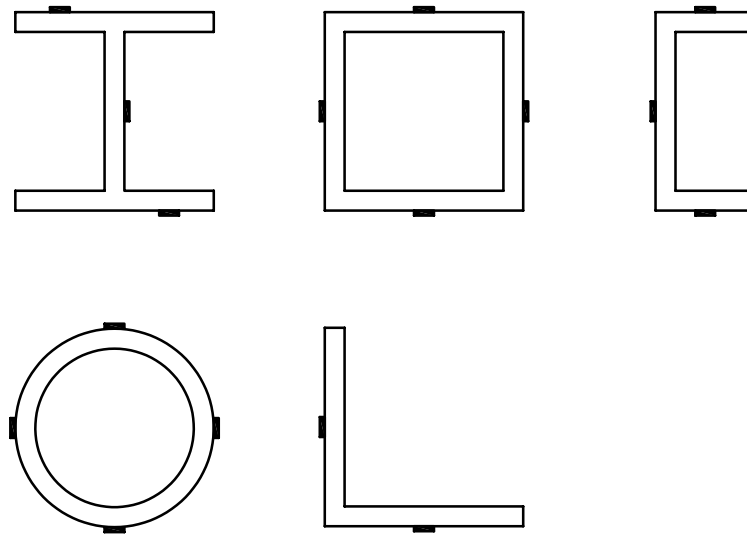


Figure 2 — Strain gauge locations of different sections

6 Specimens

6.1 Geometry

Cross-section shape includes, but is not limited to, I-section, L-section, C-section, rectangular section and circular section. The cross-section shape and geometry shall be recorded in the test report.

The slenderness ratio shall be less than 3. The width-thickness ratio of the free side plate shall be less than 5, and the width-thickness ratio of the plates without free edges shall be less than 8. The width-thickness ratio of the non-double symmetrical section shall be less than 5. The length of the test specimen is the minimum length controlled by the mentioned slenderness ratio.

The length of the test specimen is irrelevant to the width-thickness ratio.

The areas in contact with the platens shall be parallel, and perpendicular to the load direction. The errors of parallelism shall be less than 0,5 mm. Cut surfaces shall have any burrs removed.

6.2 Preparation of specimens

Specimens can be reinforced in ends by steel plates or aluminium plates to prevent local damage. The plates shall be bonded to specimens using a suitable adhesive. The reinforcing length shall less than 1/3 of specimen length.

6.3 Number of test specimens

The number of test specimens shall be no less than three, and a minimum of five is recommended.

6.4 Sampling of test specimens

The test specimens shall be sampled from pultruded FRP profiles by the suitable machining techniques to minimise damage, for instance using a diamond grit coated blade, water jet, etc. Under no circumstances shall the material properties be affected by the cutting procedure.

6.5 Conditioning atmosphere

The conditioning atmosphere shall be in accordance with ISO 291 Class 2.