



Designation: D5493 – 06(Reapproved 2011)

Standard Test Method for Permittivity of Geotextiles Under Load¹

This standard is issued under the fixed designation D5493; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of the water permittivity behavior of geotextiles in a direction normal to the plane of the geotextile when subjected to specific normal compressive loads.

1.2 Use of this test method is limited to geotextiles. This test method is not intended for application with geotextile-related products such as geogrids, geonets, geomembranes, and other geocomposites.

1.3 The values stated in SI units are to be regarded as the standard. The inch-pound units given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D123 Terminology Relating to Textiles

D653 Terminology Relating to Soil, Rock, and Contained Fluids

D4354 Practice for Sampling of Geosynthetics and Rolled Erosion Control Products(RECPs) for Testing

D4439 Terminology for Geosynthetics

D4491 Test Methods for Water Permeability of Geotextiles by Permittivity

D4716 Test Method for Determining the (In-plane) Flow Rate per Unit Width and Hydraulic Transmissivity of a Geosynthetic Using a Constant Head

E11 Specification for Woven Wire Test Sieve Cloth and Test Sieves

¹ This test method is under the jurisdiction of ASTM Committee D35 on Geosynthetics and is the direct responsibility of Subcommittee D35.03 on Permeability and Filtration.

Current edition approved June 1, 2011. Published July 2011. Originally approved in 1993. Last previous edition approved in 2006 as D5493 – 06. DOI: 10.1520/D5493-06R11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3. Terminology

3.1 *Definitions:*

3.1.1 *geotextile, n*—any permeable textile material used with foundation, soil, rock, earth, or any other geotechnical engineering related material as an integral part of a manmade project, structure, or system (see Terminology D4439).

3.1.2 *hydraulic gradient, i, n*—the loss of hydraulic head per unit distance of flow, dh/dL (see Test Method D4716).

3.1.3 *permittivity, (ψ), (T^{-1}), n*—of geotextiles, the volumetric flow rate of water per unit cross-sectional area per unit head under laminar flow conditions, in the normal direction through a geotextile (see Terminology D4439).

3.2 For the definitions of other terms relating to geotextiles, refer to Terminology D4439. For the definitions of textile terms, refer to Terminology D123. For the definitions of coefficient of permeability, refer to Terminology D653.

4. Summary of Test Method

4.1 This test method provides a procedure for measuring the water flow, in the normal direction through a known cross section of a single layer of a geotextile at predetermined constant hydraulic heads over a range of applied normal compressive stresses.

4.2 The permittivity of a geotextile, ψ , can be determined by measuring the flow rate of water, in the normal direction, through a known cross section of a geotextile at predetermined constant water heads.

4.3 Water flow through geotextiles can be laminar, transient, or turbulent, and therefore permittivity cannot be taken as a constant.

5. Significance and Use

5.1 The thickness of a geotextile decreases with increase in the normal compressive stress. This decrease in thickness may result in the partial closing or the opening of the voids of geotextile depending on its initial structure and the boundary conditions.

5.2 This test method measures the permittivity due to a change of void structure of a geotextile as a result of an applied compressive stress.

6. Apparatus

6.1 The apparatus is a constant head permeameter. General guidance on the hydraulic design of a constant head permeameter can be found in Test Method D4491.

6.2 The components installed around the test specimen are designed in such a way that a normal load can be applied uniformly on the entire flow surface without restraining significantly the flow rate. The permittivity of the apparatus, calculated using the calibration curve established in section 10, shall be at least 10 times greater than the permittivity of the test specimen under the hydraulic conditions prevailing during a given test. However, the central deflection of the loading mechanism on the plane of the geotextile shall not exceed 0.025 mm while subjected to the maximum normal load applied during the test.

6.3 The recommended apparatus configuration is shown in Fig. 1:

6.3.1 An optimum flow diameter has been found to be 50 mm to minimize hydraulic side effects while ensuring an optimum rigidity of the loading mechanism.

6.3.2 A wire meshes, 1.0 mm in opening, complying with Specification E11 is installed as the contact surface on both sides of the test specimen.

6.3.3 Two rigid metallic plate with the geometry shown on Figure 2 act as a structural component on both sides of the wire meshes. The lower one is supported by the apparatus, while the upper one can move freely but is adjusted to the diameter of the flow channel.

6.3.4 The upper metallic plate is connected to a device capable of applying the requested normal load on the test specimen (dead loads, air piston or any suitable device). The mechanical connection between the upper metallic plate and

the loading mechanism consists of four rods, 3 mm in diameter, distributed on a circle approximately 30 mm in diameter.

6.3.5 A dial indicator can be connected to the loading mechanism to monitor the specimen thickness during the test.

7. Sampling

7.1 *Lot Sample*—As a lot sample for acceptance testing, take at random the number of rolls of geotextile directed in an applicable material specification and the supplier (for example Practice D4354) or other agreement between the purchaser and the supplier. Consider rolls of geotextile to be the primary sampling units. If the specification requires sampling during manufacture, select the rolls for the lot sample at uniformly spaced time intervals throughout the production period.

NOTE 1—An adequate specification or other agreement between the purchaser and the supplier requires taking into account the variability between rolls of geotextile and between specimens from a swatch from a roll of geotextile so as to provide a sampling plan with a meaningful producer's risk, consumer's risk, acceptable quality level, and limiting quality level.

7.2 *Laboratory Sample*—Consider the units in the lot sample as the units in the laboratory sample. Take a sample that will exclude material from the outer wrap of the roll or the inner wrap around the core unless the sample is taken at the production site, at which point the inner and outer wrap material may be used.

8. Test Water Preparation

8.1 De-air the test water to provide reproducible test results.

8.2 De-air the water used for saturation.

8.3 De-air the water under a vacuum of 710 mm (28 in.) of mercury (Hg) for the period of time to bring the dissolved oxygen content down to a maximum of 6 ppm.

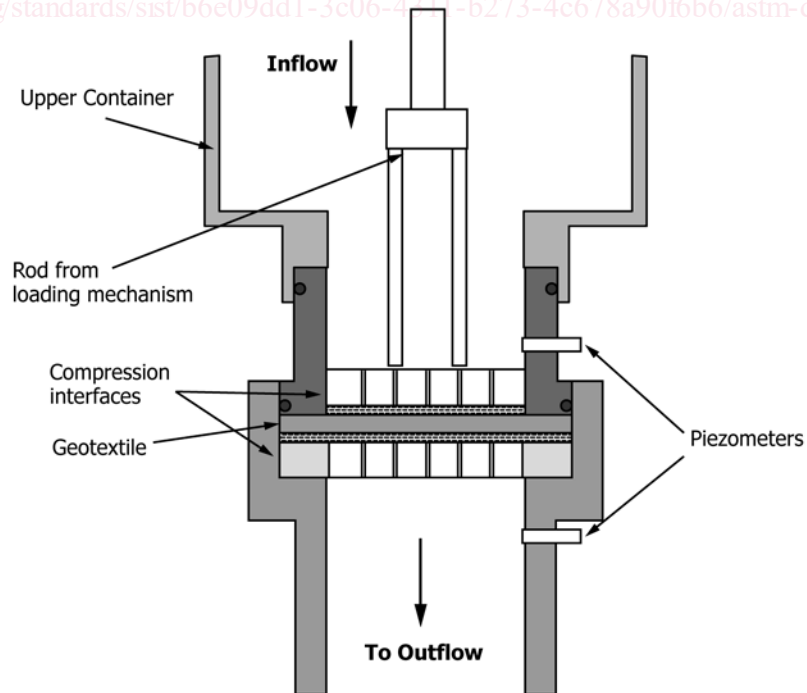


FIG. 1 Specimen Holder and Loading Mechanism