

ISO/TC 45/SC 2

Secretariat: JISC

Voting begins on:
2020-12-18

Voting terminates on:
2021-02-12

Rubber, vulcanized or thermoplastic — Determination of dynamic properties —

Part 3: Glass transition temperature (T_g)

iTeh STANDARD PREVIEW
(standards.iteh.ai)
*Caoutchouc vulcanisé ou thermoplastique — Détermination des
propriétés dynamiques —
Partie 3: Température de transition vitreuse (T_g)*

[ISO/FDIS 4664-3](https://standards.iteh.ai/catalog/standards/sist/8d1778ba-742e-4675-9ae3-ecf632f79744/iso-fdis-4664-3)

<https://standards.iteh.ai/catalog/standards/sist/8d1778ba-742e-4675-9ae3-ecf632f79744/iso-fdis-4664-3>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 4664-3:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/FDIS 4664-3

<https://standards.iteh.ai/catalog/standards/sist/8d1778ba-742e-4675-9ae3-ecf632f79744/iso-fdis-4664-3>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	1
5.1 General	1
5.2 Force capability and measurement	2
5.3 Cycling capability	2
5.4 Damping measuring device	2
5.5 Test chamber	2
5.6 Grips	2
5.7 Measurement of test piece dimensions	2
6 Test piece	2
6.1 Preparation	2
6.2 Dimensions	2
7 Number of test pieces	3
8 Conditioning	3
9 Procedure	4
9.1 Measurement of the test piece dimensions	4
9.2 Measurement of properties	4
9.3 Test conditions	4
9.3.1 Strain	4
9.3.2 Frequency	4
9.3.3 Temperature	4
9.4 Clamping and testing	4
10 Expression of results	4
10.1 General	4
10.2 Calculation of $\tan \delta$	5
11 Determination of glass transition temperature, T_g	5
12 Precision	5
13 Test report	6
Annex A (informative) Temperature dependence of dynamic properties of vulcanized rubber	7
Annex B (informative) Precision results from an interlaboratory test programme	9
Bibliography	11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

A list of all parts in the ISO 4664 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Elastomers are viscoelastic in nature hence their response to dynamic stress is a combination of elastic and viscous response. Glass transition temperature, T_g , is the temperature at which an amorphous or semi crystalline polymer transforms from a rubbery viscous state to a brittle glass-like state. It is always lower than the melting temperature.

This document is based on a force induced vibration test from which the stiffness can be determined, (see [Annex A](#)) and modulus and $\tan \delta$ can be calculated. $\tan \delta$ is the ratio of viscous modulus to the elastic modulus. $\tan \delta$ is plotted against temperature and the glass transition temperature is taken as the peak in the curve.

The measured value of T_g depends on the experimental conditions and the mode of deformation. Measurement of T_g in dynamic mode is more sensitive to the temperature dependent physical properties of the material and is relevant to understanding its service temperature.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/FDIS 4664-3](#)

<https://standards.iteh.ai/catalog/standards/sist/8d1778ba-742e-4675-9ae3-ecf632f79744/iso-fdis-4664-3>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO/FDIS 4664-3

<https://standards.iteh.ai/catalog/standards/sist/8d1778ba-742e-4675-9ae3-ecf632f79744/iso-fdis-4664-3>

Rubber, vulcanized or thermoplastic — Determination of dynamic properties —

Part 3: Glass transition temperature (T_g)

1 Scope

This document specifies a method for determining the glass transition temperature, T_g , of vulcanized rubbers in the hardness range from 30 IRHD to 80 IRHD. The dynamic properties are measured via temperature sweep in sinusoidal deformation at a defined strain and frequency and T_g is determined from the peak in the $\tan \delta$ versus temperature curve. Glass transition temperature, T_g , determined in this way serves the purpose of a guideline to the service temperature of the material.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4664-1:2011, *Rubber, vulcanized or thermoplastic — Determination of dynamic properties — Part 1: General guidance*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4664-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

Test pieces are subjected to a temperature scan in a closed chamber at a constant strain and frequency using a dynamic mechanical analyser and the temperature of maximum $\tan \delta$ taken as the glass transition.

5 Apparatus

5.1 General

The test machine used shall comply with the requirements of ISO 4664-1. Care shall be taken to avoid resonance under operating conditions.

5.2 Force capability and measurement

The force measuring device shall have an adequate range for the materials to be tested and the test pieces and deformations used. It shall enable the peak force to be read to an accuracy of $\pm 1,0$ %.

5.3 Cycling capability

The test machine shall be able to operate at a defined frequency and with the required dynamic displacement amplitude. The deformation cycles shall be in the form of a continuous wave train of sinusoidal shape with less than 10 % harmonic content.

NOTE "Harmonic content" indicates that there is no deviation/deformation of the sine curve due to equipment contribution, sample effect or any other factors.

5.4 Damping measuring device

The test machine shall be fitted with a device to enable the loss factor of the material under test to be determined to an accuracy of ± 5 % or $\pm 0,02$ in $\tan \delta$ whichever is the smaller.

5.5 Test chamber

The test chamber shall be closed and thermostatically controlled to within $\pm 0,3$ °C of the programmed test temperature. Care shall be taken to reduce heat conduction from the test piece through the test piece holders to the outside environment of the chamber. A means of measuring the actual temperature around the sample should be provided. Accurate temperature control is of great importance, owing to the temperature dependent properties of rubber.

5.6 Grips

Grips shall be used for clamping the test pieces in the equipment such that no slippage occurs during testing.

5.7 Measurement of test piece dimensions

Instruments to measure test piece dimensions shall be in accordance with ISO 23529.

6 Test piece

6.1 Preparation

The standard method for test piece preparation shall be direct moulding for cylinders and cut from the moulded sheet for strips or elements dedicated to the preparation of shear test pieces. If required, test pieces may be prepared from a finished article by cutting and buffing as described in ISO 23529. If the test piece is prepared from finished product, it should be free of surface irregularities, fabric layers, etc.

6.2 Dimensions

The test piece for tests in compression shall be a cylinder of 10 mm height and 10 mm diameter. Test pieces with different heights and diameters are acceptable as long as the slenderness ratio of the test piece is greater than 1.

The preferred test piece for tests in tension shall be a strip of 25 mm length, 10 mm width and $2,0 \text{ mm} \pm 0,2 \text{ mm}$ thickness. The test length shall be $10 \text{ mm} \pm 1,0 \text{ mm}$ with the remainder of the strip in the grips. Test pieces with different lengths, widths, thicknesses and test lengths are acceptable as long as they are in accordance with ISO 4664-1:2011, Table 2.

The test piece for tests in shear shall be of sandwich construction containing two parallel rubber elements, the thickness of the test piece shall be at least 4 times less than the diameter. The preferred thickness of the elements is 2,00 mm. In no case shall the thickness of the elements be less than 1,8 mm or more than 2,3 mm. The rubber elements shall be firmly attached to metal cylinders having diameter of 10 mm and height of 10 mm which will be held in the grip. [Figure 1](#) provides an example of sample preparation tool and the grip.

Bonding to metal components is best done during the curing operation starting from uncured compound. When test pieces are cut from finished product, bonding with a suitable cold-setting adhesive (e.g. Loctite 407TM¹⁾ thermal adhesive) may be used.

For shear mode analysis, all the elements in the prepared, bonded test pieces shall be aligned to the centre of axis of the metal cylinders.

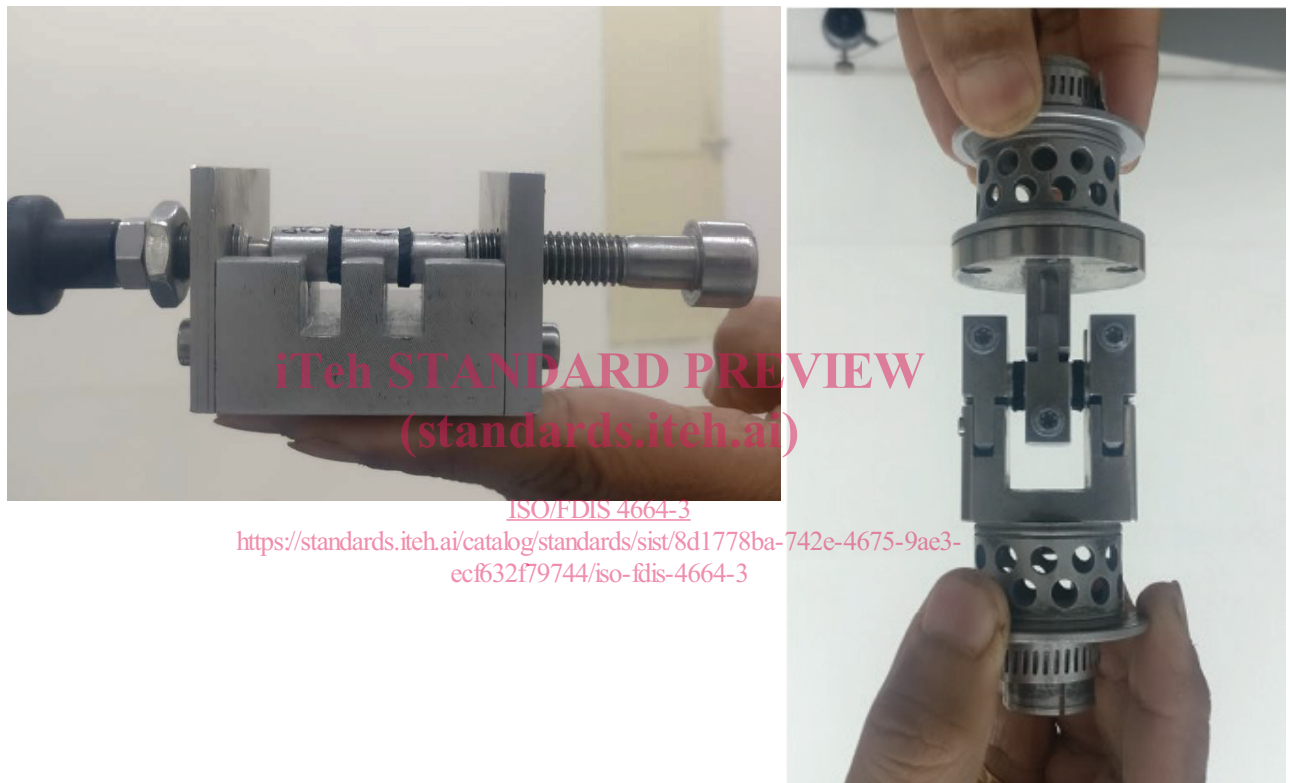


Figure 1 — Example of shear sample preparation tool and corresponding grip

7 Number of test pieces

A minimum of three test pieces shall be used.

8 Conditioning

The time interval between vulcanization and testing shall be in accordance with ISO 23529. Samples and test pieces shall be protected from light as completely as possible during the interval between vulcanization and testing.

Test pieces shall be conditioned for not less than 3 h before testing at one of the standard laboratory temperatures specified in ISO 23529.

1) Loctite 407TM is an example of a suitable product. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.