

# INTERNATIONAL STANDARD

ISO  
**7270-1**

Second edition  
2020-02

---

---

## Rubber — Analysis by pyrolytic gas-chromatographic methods —

### Part 1: Identification of polymers (single polymers and polymer blends)

iTech Standards  
Caoutchouc — Méthodes d'analyse par pyrolyse et chromatographie  
en phase gazeuse —  
(<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>)  
Document Preview

[ISO 7270-1:2020](#)

<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>



Reference number  
ISO 7270-1:2020(E)

© ISO 2020

**iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview**

[ISO 7270-1:2020](#)

<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

	Page
<b>Foreword</b>	<b>iv</b>
<b>1 Scope</b>	<b>1</b>
<b>2 Normative references</b>	<b>1</b>
<b>3 Terms and definitions</b>	<b>1</b>
<b>4 Principle</b>	<b>2</b>
<b>5 Single polymers and blends</b>	<b>2</b>
5.1 General	2
5.2 Group M	2
5.3 Group O	2
5.4 Group Q	2
5.5 Group R	2
5.6 Blends	3
<b>6 Reagents</b>	<b>3</b>
<b>7 Apparatus</b>	<b>3</b>
7.1 Extraction apparatus	3
7.2 Pyrolysis/chromatography system	3
7.2.1 General	3
7.2.2 Pyrolysis device	4
7.2.3 Gas chromatograph	4
7.2.4 Chromatographic columns	4
7.2.5 Data-handling equipment	4
<b>8 Procedure</b>	<b>4</b>
<b>9 Interpretation of results</b>	<b>5</b>
<b>10 Test report</b>	<b>5</b>

ISO 7270-1:2020

<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>

## **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This second edition cancels and replaces the first edition (ISO 7270-1:2003), of which it constitutes a minor revision. It also incorporates the Amendment ISO 7270-1:2003/Amd.1:2010.

[https://standards.iteh.ai/catalog/standards/iso/03222b5d\\_1b6d4667-9125-d845abdc765d/iso-7270-1-2020](https://standards.iteh.ai/catalog/standards/iso/03222b5d_1b6d4667-9125-d845abdc765d/iso-7270-1-2020)  
The main changes compared to the previous edition are as follows:

- normative references have been updated in [Clause 2](#).

A list of all parts in the ISO 7270 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Rubber — Analysis by pyrolytic gas-chromatographic methods —

## Part 1: Identification of polymers (single polymers and polymer blends)

**WARNING 1 — Persons using this document should be familiar with normal laboratory practice. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to determine the applicability of any other restrictions.**

**WARNING 2 — Certain procedures specified in this document might involve the use or generation of substances, or the generation of waste, that could constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.**

### 1 Scope

This document specifies a method for the identification of polymers, or blends of polymers, in raw rubbers and in vulcanized or unvulcanized compounds from pyrograms (pyrolysis-gas chromatographic patterns) obtained under the same conditions. This allows qualitative identification of single rubbers or blends, with exceptions discussed below. This document is not intended for quantitative analysis.

The method applies first and foremost to single polymers. When the pyrogram indicates a characteristic hydrocarbon, the method is also applicable to blends. For details, see [Clause 5](#). The method can be also applicable to other types of polymer when verified by the analyst in each particular case.

<https://standards.iec.ch/IEC/ISO/IEC%207270-1:2020> NOTE The use of this document pre-supposes sufficient working knowledge of the principles and techniques of gas chromatography to enable the analyst to carry out the operations described and to interpret the results correctly.

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1407:2011, *Rubber — Determination of solvent extract*

ISO 1629:2013, *Rubber and latices — Nomenclature*

### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

## 4 Principle

**4.1** Raw or vulcanized rubbers and/or their blends are pyrolysed and the pyrolysis products are subjected to gas-chromatographic analysis under predefined conditions. The chromatograms produced are referred to as pyrograms.

**4.2** Pyrograms are interpreted by comparison with reference pyrograms produced from the same rubbers and/or blends, prepared and analysed under the same conditions.

## 5 Single polymers and blends

### 5.1 General

The rubbers in the following listing are grouped in accordance with ISO 1629:2013.

### 5.2 Group M

- a) Chlorinated polyethylene (CM) and chlorosulfonated polyethylene (CSM).

NOTE 1 The pyrogram will not differentiate between these chlorinated polyethylenes.

- b) Ethylene-propylene copolymers (EPMs) and ethylene-propylene-diene terpolymers (EPDMs).

NOTE 2 The pyrogram can differentiate terpolymers from copolymers when the pyrogram indicates characteristic "diene" monomer pyrolysis products.

- c) Acrylic rubbers (ACMs).

### 5.3 Group O

## Document Preview

Epichlorohydrin rubbers [homopolymer (CO), copolymer (ECO) and terpolymers].

NOTE 1 The pyrogram will not differentiate between these various types of epichlorohydrin polymer.

### 5.4 Group Q

Polysiloxanes.

### 5.5 Group R

- a) Polybutadiene (BR).

NOTE 1 The pyrogram will not differentiate between polymers containing different proportions of isomers.

- b) Polychloroprene (CR).

NOTE 2 The pyrogram will not differentiate between the various types of polychloroprene rubber, or polychloroprene rubber from other types of chlorinated rubber.

- c) Isobutene-isoprene copolymer (IIR).

NOTE 3 The pyrogram will not differentiate butyl rubber from its halogenated forms or from isobutene.

- d) Polyisoprene (NR or IR).

NOTE 4 The pyrogram will not differentiate natural from synthetic polyisoprenes.

- e) Acrylonitrile-butadiene copolymer (NBR).

NOTE 5 In some cases, NBR can be differentiated from hydrogenated acrylonitrile-butadiene copolymer (HNBR). The pyrogram will not differentiate a single NBR from an NBR/BR blend or a blend of various types of NBR.

- f) Styrene-butadiene copolymer (SBR).

NOTE 6 In some cases, block polymers can be differentiated from random polymers. The pyrogram will not differentiate a single SBR from an SBR/BR blend or a blend of various types of SBR.

## 5.6 Blends

With the exception of blends containing both styrene-butadiene copolymer and polybutadiene, the method enables blends of the following polymers to be identified:

- a) polyisoprene (NR or IR);
- b) polybutadiene (BR);
- c) isobutene-isoprene copolymers (IIRs);
- d) styrene-butadiene copolymers (SBRs).

## 6 Reagents

All reagents shall be of analytical grade.

### 6.1 Solvents for extraction purposes

The following solvents are suitable (see 8.2):

#### 6.1.1 Acetone.

#### 6.1.2 Methanol.

[ISO 7270-1:2020](#)

<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>

#### 6.1.3 Methyl ethyl ketone.

### 6.2 Carrier gas.

#### 6.2.1 Nitrogen.

#### 6.2.2 Helium.

6.3 Gas for flame-ionization detector: hydrogen plus purified compressed air.

## 7 Apparatus

### 7.1 Extraction apparatus

As specified in ISO 1407.

### 7.2 Pyrolysis/chromatography system

#### 7.2.1 General

The apparatus utilized to obtain pyrograms consists of four parts: the pyrolysis device, the gas chromatograph, the gas-chromatographic column and the data-handling equipment.

## 7.2.2 Pyrolysis device

The following types of electrically heated pyrolysis device are suitable:

**7.2.2.1 Micro-furnace**, with quartz tubes in which the test portion is pyrolysed.

**7.2.2.2 Curie-point pyrolyser**, with a holder (pyrolysis probe) containing ferromagnetic material which surrounds the test portion and is heated to the Curie-point temperature to pyrolyse the test portion.

**7.2.2.3 Platinum-filament pyrolyser**, with a holder (pyrolysis probe) containing a platinum filament which surrounds the test portion and is heated to pyrolyse the test portion.

## 7.2.3 Gas chromatograph

A wide variety of chromatographs using either a flame-ionization detector (FID) or a thermal conductivity detector (TCD) are suitable for use in this document.

Selective detectors such as electron capture detector (ECD), flame photometric detector (FPD), flame thermionic detector (FTD), atomic emission detector (AED) can give useful information. For identification of pyrolysis products, a mass spectrometer detector can be utilized.

## 7.2.4 Chromatographic columns

A variety of column lengths and diameters and stationary and liquid phases are suitable for use in this document, the main requirement being good resolution of the volatile pyrolysis products.

NOTE 1 Capillary columns with good separation efficiency are suitable, but not essential.

NOTE 2 Capillary columns containing non-polar polydimethylsiloxanes and partially modified (diphenyl-, cyanopropylphenyl- or other) semi-polar silicones are suitable.

NOTE 3 Usually, capillary columns require little evaluation, while it often is necessary to evaluate many conditions for polar and non-polar packed columns. ISO 7270-1:2020  
03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020

The conditions chosen will depend on the column used. Typical operating conditions for the gas chromatograph with both polar and non-polar columns can be found in [Tables 1 to 5](#). Typical pyrograms obtained can be found in [Figures 1 to 44](#).

## 7.2.5 Data-handling equipment

A recorder, an integrator or a computer data-analysis system may be used.

# 8 Procedure

**8.1** Accurate comparison of the pyrogram of an unknown polymer with the reference is only possible under the same conditions.

**8.2** Extraction of test samples is recommended to remove additives which may interfere with the chromatographic separation. For oil-extended materials, extraction of the extender oil is essential otherwise this oil may cause serious interference in the pyrogram. Carry out the extraction following the general principles of either method A or method B in ISO 1407:2011. The chosen solvent shall not affect the polymer and shall remove as much of the additives as possible. After extraction, dry the test sample, as residual solvent may cause interference with the pyrolysis products (see [9.4](#)).

**8.3** Take a test portion of mass appropriate to the apparatus used. Generally, this will be between 0,1 mg to 5 mg. For good reproducibility, the size of the test portion should be as small as practicable.

**8.4** Place the test portion in the pyrolysis device and pyrolyse. An appropriate pyrolysis temperature is 400 °C to 800 °C for a micro-furnace or Curie-point pyrolyser, and 800 °C to 1 200 °C for a platinum-filament pyrolyser.

**8.5** Record the pyrogram for comparison with the pyrogram of a known polymer or polymer blend obtained under the same conditions.

## 9 Interpretation of results

**9.1** Each polymer will be characterized by the retention times of its main peaks. Some polymers produce characteristic hydrocarbons and their identification is relatively easy. Examples of this type are as follows:

- a) polyisoprene, which yields mainly isoprene and dipentene (isoprene dimer);
- b) styrene-butadiene copolymers, which yield mainly butadiene, 4 vinyl-1 cyclohexene (butadiene dimer) and styrene;
- c) polybutadiene, which yields mainly butadiene and 4 vinyl-1 cyclohexene (butadiene dimer);
- d) isobutene-isoprene copolymers, which yield mainly isobutene.

**9.2** Some polymers do not yield characteristic hydrocarbons, and careful inspection of the pyrogram is required. Supplementary tests, such as those for halogen and nitrogen, may be an aid to more definite identification.

**9.3** The characteristic hydrocarbons in the unknown polymer are identified by comparison of retention times for a known blend of polymer, or by direct injection of the pure hydrocarbon into the chromatograph. Results may be tabulated for ready reference.

**9.4** The analyst should be aware of additives which may not be extractable and which may or may not affect the chromatographic pattern.

## 10 Test report

The test report shall contain the following information:

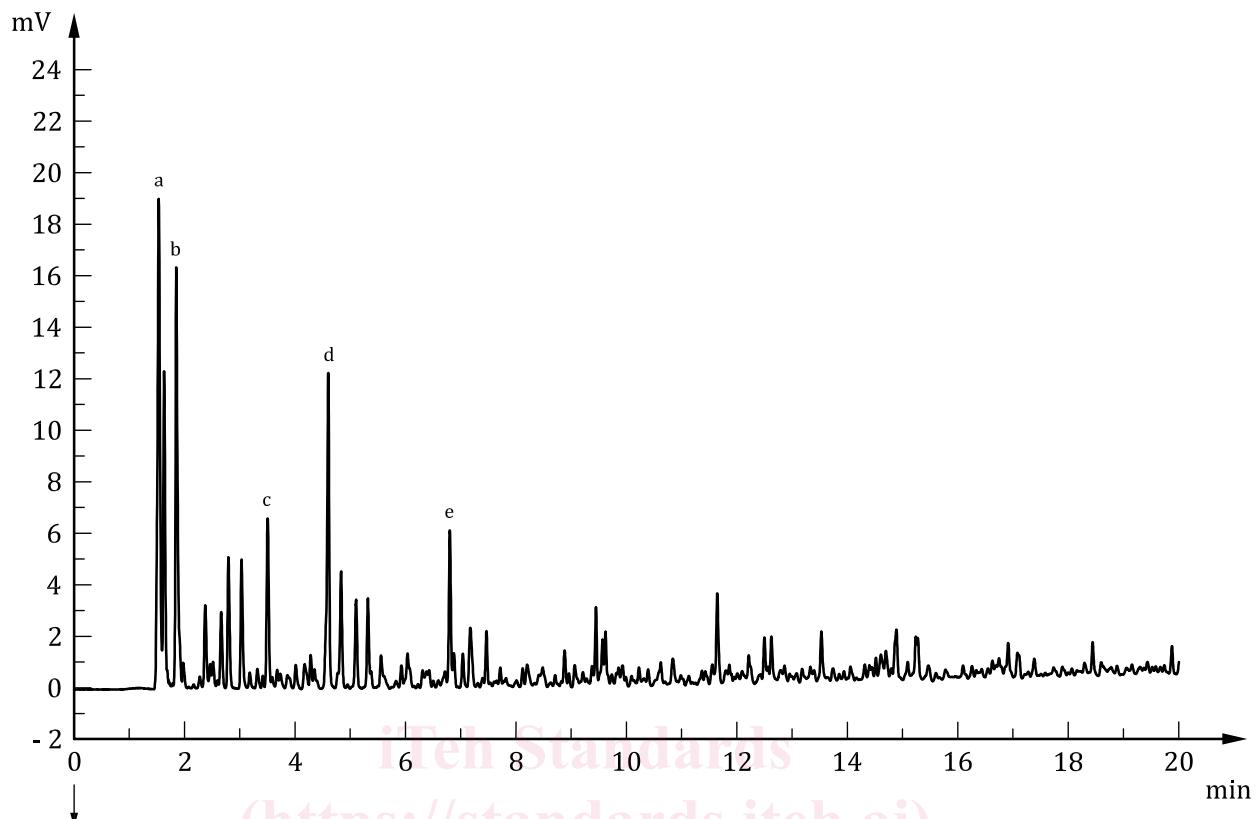
- a) all details necessary for full identification of the sample analysed;
- b) the type of pyrolysis device used;
- c) the pyrolysis temperature;
- d) the gas-chromatographic conditions used;
- e) the data-handling equipment used;
- f) the polymer or polymer blend found in the sample.

**Table 1 — List of pyrograms contained in this document**

Group	Rubber (example)	Number of figure			
		Micro-furnace	Curie point	Micro-furnace	Curie point
		Semi-polar capillary column	Semi-polar capillary column	Polar packed column	Non-polar packed column
<b>Group M</b>					
CM	Chlorinated polyethylene	1	—	—	—
CSM	Chlorosulfonated polyethylene	2	16	—	33
EPM	Ethylene-propylene copolymer	3	—	—	—
EPDM	Ethylene-propylene-diene terpolymer	4	17	—	34
ACM	Acrylic rubber	5	18	28	35
<b>Group O</b>					
CO	Epichlorohydrin rubber	6	19	—	36
<b>Group Q</b>					
	Polysiloxanes	7	20	—	37
<b>Group R</b>					
BR	Polybutadiene	8	21	—	38
CR	Polychloroprene	9	22	29	39
IIR	Isobutene-isoprene copolymer	10	23	—	40
	Halogenated isobutene-isoprene copolymer	11	—	—	—
NR or IR	Polyisoprene	12	24	30	41
NBR	Acrylonitrile-butadiene copolymer	13	25	31	42
HNBR	Hydrogenated acrylonitrile-butadiene copolymer	14	26	—	43
SBR	Styrene-butadiene copolymer	15	27	29	44

**Table 2 — Recommended operating conditions for micro-furnace pyrolysis followed by chromatography with a capillary column**

<b>Pyrolysis</b>	
Device	Micro-furnace
Pyrolysis temperature	600 °C
<b>Gas-chromatographic column</b>	
Liquid phase	5 % diphenylpolysiloxane Ultra ALLOY-5
Film thickness	1,0 µm
Column diameter	0,25 mm ID
Column length	30 m
<b>Chromatographic conditions</b>	
Carrier gas	Helium
Injector temperature	320 °C
Type of detector	FID
Detector temperature	350 °C
<b>Temperature programme</b>	
Isothermal for 2 min at 50 °C then 10 °C/min from 50 °C to 280 °C then isothermal for 10 min at 280 °C	

**Key**

a Retention time: 1,53.

b Retention time: 1,85.

c Retention time: 3,50.


[ISO 7270-1:2020](#)

<https://standards.iteh.ai> rds/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020

d Retention time: 4,60 (benzene).

e Retention time: 6,80 (toluene).

**Figure 1 — Chlorinated polyethylene (CM)**

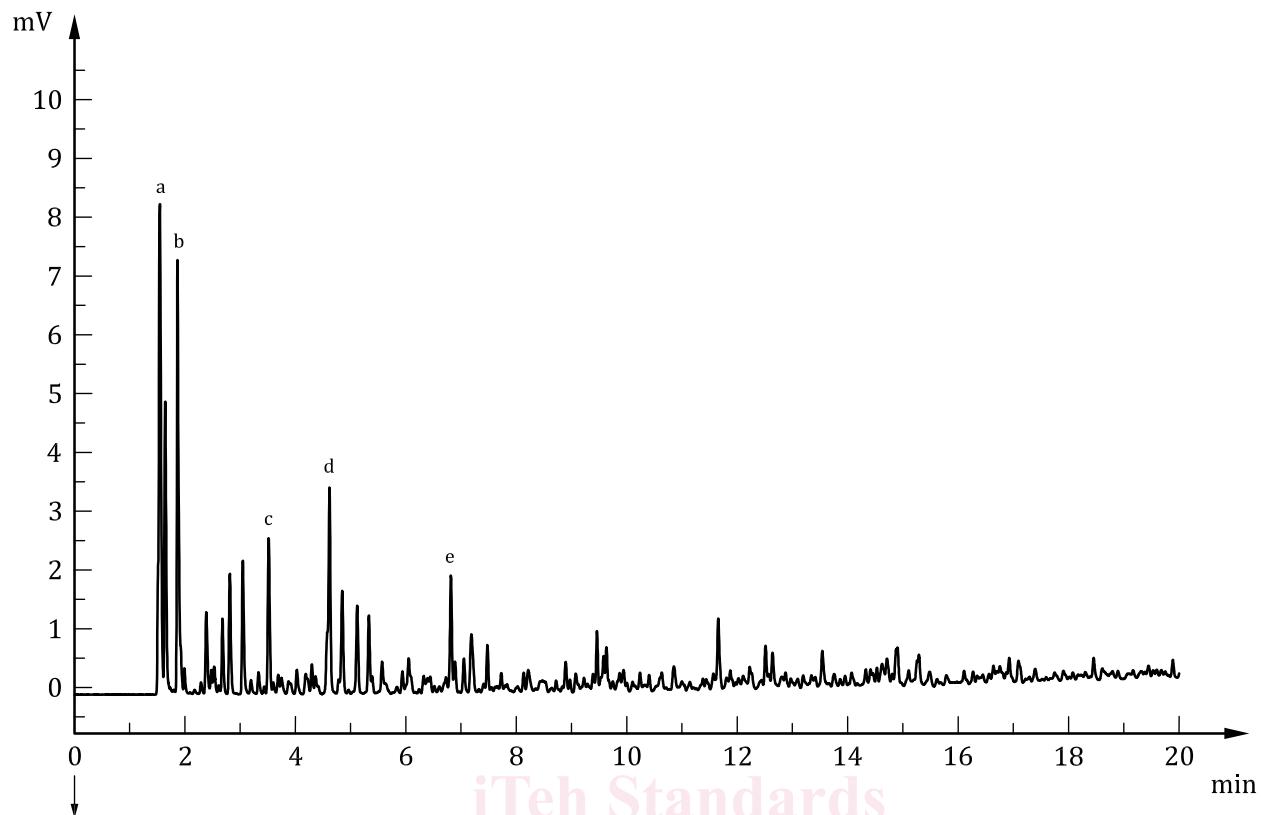


**Key**

- a Retention time: 1,55.
- b Retention time: 1,87.
- c Retention time: 3,52.
- d Retention time: 4,62 (benzene).
- e Retention time: 6,82 (toluene).

[ISO 7270-1:2020](#)


<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845abdc765d/iso-7270-1-2020>

**Figure 2 — Chlorosulfonated polyethylene (CSM)**

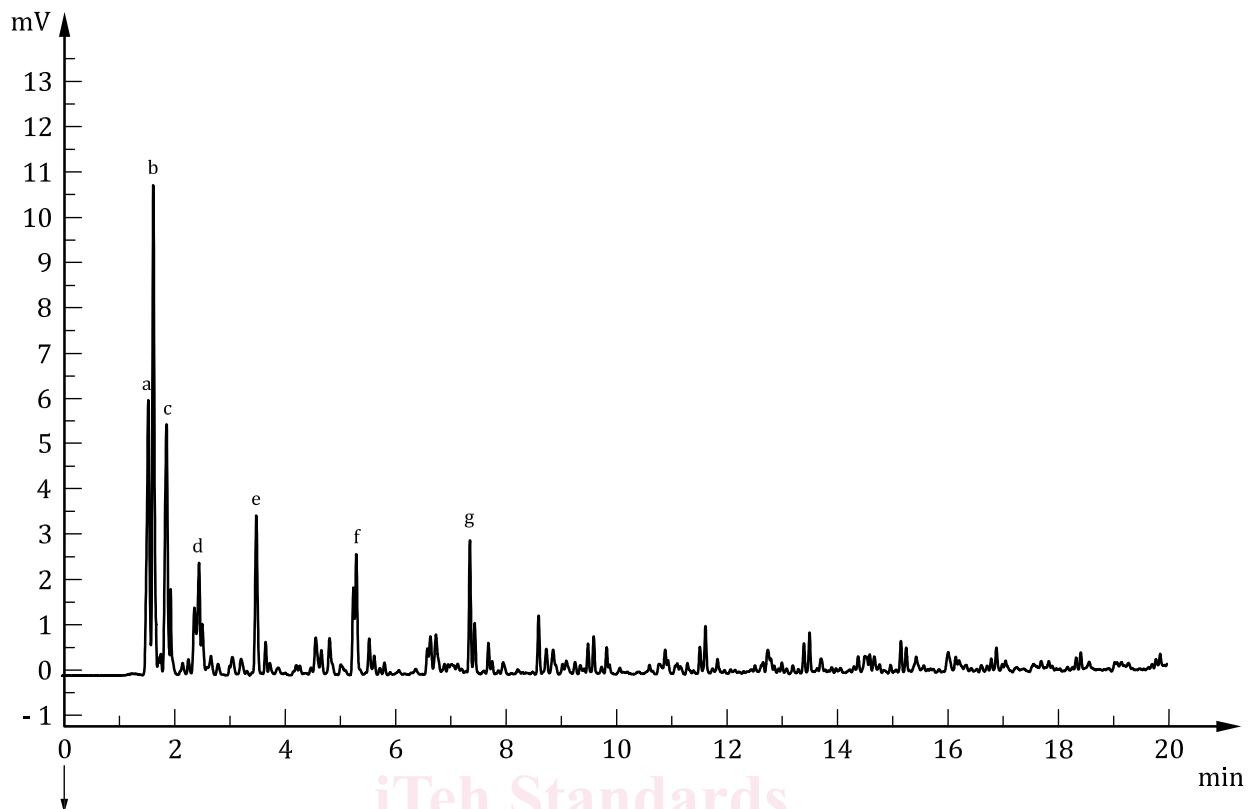**Key**

- |   |                                 |   |                                 |
|---|---------------------------------|---|---------------------------------|
| a | Retention time: 1,56.           | e | Retention time: 3,52 ( $C_6$ ). |
| b | Retention time: 1,65.           | f | Retention time: 5,33 ( $C_7$ ). |
| c | Retention time: 1,89 ( $C_4$ ). | g | Retention time: 7,38 ( $C_8$ ). |
| d | Retention time: 2,40 ( $C_5$ ). |   |                                 |

[Figure 3 — Ethylene-propylene copolymer \(EPM\)](https://standards.iteh.ai/catalog/figure-3-ethylen-propylene-copolymer-epm)

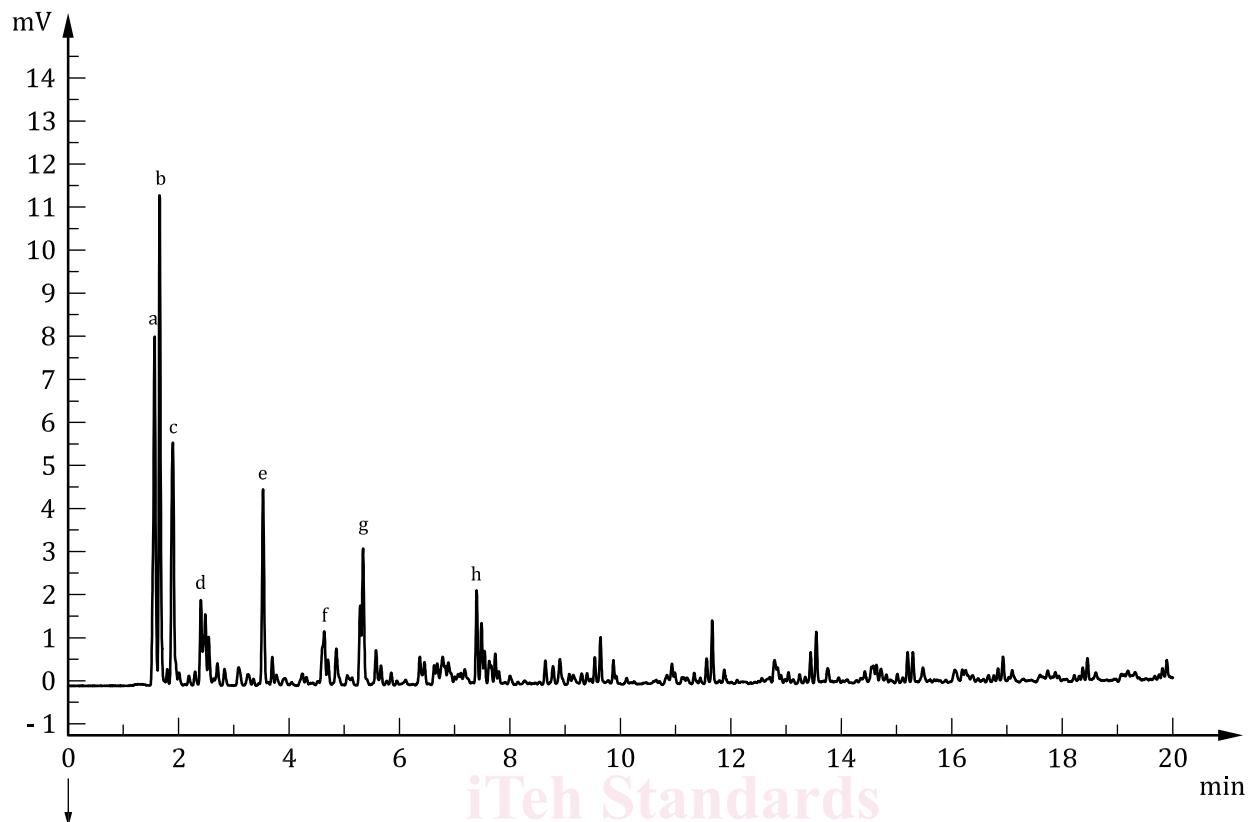

**Key**

- |  |  |
|--|--|
| a      Retention time: 1,57.           | e      Retention time: 3,53 ( $C_6$ ). |
| b      Retention time: 1,66.           | f      Retention time: 4,64.           |
| c      Retention time: 1,90 ( $C_4$ ). | g      Retention time: 5,34 ( $C_7$ ). |
| d      Retention time: 2,40 ( $C_5$ ). | h      Retention time: 7,40 ( $C_8$ ). |

<https://standards.iteh.ai/catalog/standards/iso/03322b5d-1bad-4667-9125-d845bdc765d/iso-7270-1-2020>  
**Figure 4 — Ethylene-propylene-diene terpolymer (EPDM)**