

---

---

**Plastics — Plasticized poly(vinyl chloride) (PVC-P) moulding and extrusion materials —**

**Part 1:  
Designation system and basis for specifications**

iTeh STANDARD PREVIEW

*Plastiques — Matériaux à base de poly(chlorure de vinyle) plastifié (PVC-P) pour moulage et extrusion —*

*Partie 1: Système de désignation et base de spécifications*

<https://standards.iteh.ai/catalog/standards/sist/01606e03-be06-4a88-b33c-82a65658f5cb/iso-24023-1-2020>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 24023-1:2020

<https://standards.iteh.ai/catalog/standards/sist/01606e03-be06-4a88-b33c-82a65658f5cb/iso-24023-1-2020>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>2</b>
<b>4 Designation and specification system .....</b>	<b>2</b>
4.1 General .....	2
4.2 Data block 1 .....	2
4.3 Data block 2 .....	3
4.4 Data block 3 .....	3
4.5 Data block 4 .....	3
4.5.1 General .....	3
4.5.2 Shore hardness .....	4
4.5.3 Density .....	4
4.5.4 Torsional-stiffness temperature at 300 MPa .....	4
4.6 Data block 5 .....	4
<b>5 Examples of designations .....</b>	<b>5</b>
5.1 Designation only .....	5
5.2 Designation transformed into a specification .....	6

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 24023-1:2020

<https://standards.iteh.ai/catalog/standards/sist/01606e03-be06-4a88-b33c-82a65658f5cb/iso-24023-1-2020>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastic materials*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 249, *Plastics*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This first edition of ISO 24023-1 cancels and replaces ISO 2898-1:1996, which has been technically revised.

The main changes compared to the previous edition are as follows:

- the positions of Data block 2 and Data block 4 of the old designation system has been changed.

A list of all parts in the ISO 24023 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Plastics — Plasticized poly(vinyl chloride) (PVC-P) moulding and extrusion materials —

## Part 1: Designation system and basis for specifications

### 1 Scope

**1.1** This document establishes a system of designation for plasticized PVC thermoplastic material which can be used as the basis for specifications.

**1.2** The types of PVC-U plastics are differentiated from each other by a classification system based on appropriate levels of the designatory properties

- a) Shore hardness,
- b) density,
- c) torsional-stiffness temperature at 300 MPa,

and on information about physical form, intended application and/or method of processing, important properties, additives, colorants.

**1.3** This document is applicable to all plasticized compositions of homopolymers and copolymers that contain at least a mass percentage of 50 % of vinyl chloride. It is also applicable to plasticized compositions containing chlorinated poly (vinyl chloride) and to plasticized compositions containing blends of one or more of the above-mentioned polymers, provided that the total amount of these polymers represents at least a mass percentage of 50 % of the polymer content of the composition.

This document applies to materials ready for normal use in the form of powder (dry blends), granules or pellets and to materials unmodified or modified by colorants, additives, fillers, etc. It does not apply to cellular plastics or to paste compositions (plastisols).

**1.4** This document does not intend to imply that materials having the same designation give the same performance. It does not provide engineering data, performance data or data on processing conditions which might be required to specify a material for a particular application and/or method of processing.

If additional properties are required, they are, if suitable, determined using the test methods specified in ISO 24023-2.

**1.5** In order to specify a thermoplastic material for a particular application or to ensure reproducible processing, additional requirements can be given in data block 5 (see 4.1).

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1043-1, *Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics*

ISO 24023-2, *Plastics — Plasticized poly (vinyl chloride) (PVC-P) moulding and extrusion materials — Part 2: Preparation of test specimens and determination of properties*

### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

## 4 Designation and specification system

### 4.1 General

The designation and specification system for thermoplastics is based on the following standardized pattern.

Designation						
Description block (optional)	Identity block					
	International Standard Number block	Individual-item block				
		Data block 1	Data block 2	Data block 3	Data block 4	Data block 5

The designation consists of an optional description block, reading “Thermoplastics”, and an identity block comprising the International Standard number and an individual-item block. For unambiguous coding, the individual-item block is subdivided into 5 data blocks comprising the following information.

- Data block 1: Identification of the plastic by its symbol PVC-P in accordance with ISO 1043-1 (see 4.2).
- Data block 2: Fillers or reinforcing materials and their nominal content (not included in this document, see 4.3).
- Data block 3: Position 1: Intended application or method of processing (see 4.4).  
Positions 2 to 8: Important properties, additives and supplementary information (see 4.4).
- Data block 4: Designatory properties (see 4.5).
- Data block 5: For the purpose of alternative specifications, a fifth data block may be added containing additional information.

The first character of the individual-item block shall be a hyphen. The data blocks shall be separated from each other by commas.

If a data block is not used, this shall be indicated by doubling the separation sign, i.e. by two commas (,,).

### 4.2 Data block 1

In this data block, after the hyphen, plasticized poly (vinyl chloride) plastics are identified by the symbol “PVC-P”, in accordance with ISO 1043-1.

### 4.3 Data block 2

Not included in this document.

### 4.4 Data block 3

In this data block, information about intended application and/or method of processing is given in position 1 and information about important properties, additives and colour in positions 2 to 8. The code-letters used are specified in [Table 1](#).

If information is presented in positions 2 to 8 and no specific information is given in position 1, the letter X shall be inserted in position 1.

**Table 1 — Code-letters used in data block 3**

Code-letter	Position 1	Code-letter	Positions 2 to 8
B	Blow moulding	B	Antiblocking
C	Calendering	C	Coloured
		D	Powder dry blend
E	Extrusion	E	Expandable
F	Extrusion of films	F	Special burning characteristics
G	General use	G	Granules
H	Coating	H	Heat ageing stabilized
J	Cable and wire insulating		
K	Cable and wire sheathing		
		L	Light or weather stabilized
M	Injection moulding	N	Natural (no colour added)
		P	Impact modified
Q	Compression moulding		
R	Rotational moulding	R	Mould release agent
S	Sintering	S	Lubricated
T	Tape manufacture	T	Transparent
V	Thermoforming		
X	No indication		
		Y	Increased electrical conductivity
		Z	Antistatic

### 4.5 Data block 4

#### 4.5.1 General

In this data block, the Shore hardness is represented by a 2-figure code-number (see [4.5.2](#)), the range of density by a 2-figure code-number (see [4.5.3](#)) and the range of torsional-stiffness temperature at 300 MPa by a 2-figure code-number (see [4.5.4](#)). The code-numbers are separated from each other by hyphens.

If a property value falls on or near a range limit, the manufacturer shall state which range will designate the material. If subsequent individual test values lie on, or on either side of, the limit, because of manufacturing tolerances, the designation is not affected.

NOTE Not all combinations of the values of designatory properties are provided in currently available polymers.

4.5.2 Shore hardness

The Shore A or D hardness shall be determined in accordance with ISO 24023-2.

The value of the Shore hardness is represented by a 2-figure code-number as specified in Table 2. The scale used is indicated by a single code-letter (A or D) immediately preceding the code-number indicating the hardness value.

Table 2 — Code-numbers used for designatory properties in data block 4

Shore hardness	Density		Torsional-stiffness temperature at 300 MPa	
	Code-number	Range g/cm <sup>3</sup>	Code-number	Range °C
The Shore hardness is designated by the letter A or D followed by the hardness value, for example, A82 for a measured Shore A value of 82.  A tolerance of ± 3 is permitted.  Use the D scale when the A scale value exceeds 85.	15	≤ 1,17	00	≥ -5
	20	> 1,17 but ≤ 1,22	10	< -5 but ≥ -15
	25	> 1,22 but ≤ 1,27	20	< -15 but ≥ -25
	30	> 1,27 but ≤ 1,32	30	< -25 but ≥ -35
	35	> 1,32 but ≤ 1,37	40	< -35 but ≥ -45
	40	> 1,37 but ≤ 1,42	50	< -45 but ≥ -55
	45	> 1,42 but ≤ 1,47	60	< -55
	50	> 1,47 but ≤ 1,52		
	55	> 1,52 but ≤ 1,57		
	60	> 1,57 but ≤ 1,62		
	65	> 1,62 but ≤ 1,67		
	70	> 1,67 but ≤ 1,72		
	75	> 1,72 but ≤ 1,77		
	80	> 1,77 but ≤ 1,82		
	85	> 1,82 but ≤ 1,87		
	90	> 1,87 but ≤ 1,92		
	95	> 1,92		

4.5.3 Density

The density shall be determined in accordance with ISO 24023-2.

The possible values of density are divided into 17 ranges, each represented by a 2-figure code-number as specified in Table 2.

4.5.4 Torsional-stiffness temperature at 300 MPa

The torsional-stiffness temperature at 300 MPa shall be determined in accordance with ISO 24023-2.

The possible values of torsional-stiffness temperature at 300 MPa are divided into 7 ranges, each represented by a 2-figure code-number as specified in Table 2.

4.6 Data block 5


Indication of additional requirements in this optional data block is a way of transforming the designation of a material into a specification for a particular application. This may be done, for example, by reference to a suitable national standard or to a standard-like, generally established specification.



## 5 Examples of designations

### 5.1 Designation only

A plasticized poly (vinyl chloride) thermoplastic material (PVC-P), intended for cable and wire sheathing (K), in the form of a granular material (G), natural and not coloured (N), with a Shore A hardness of 82 (A82), a density of 1,24 g/cm<sup>3</sup> (25) and a torsional-stiffness temperature at 300 MPa of -31 °C (30), would be designated:

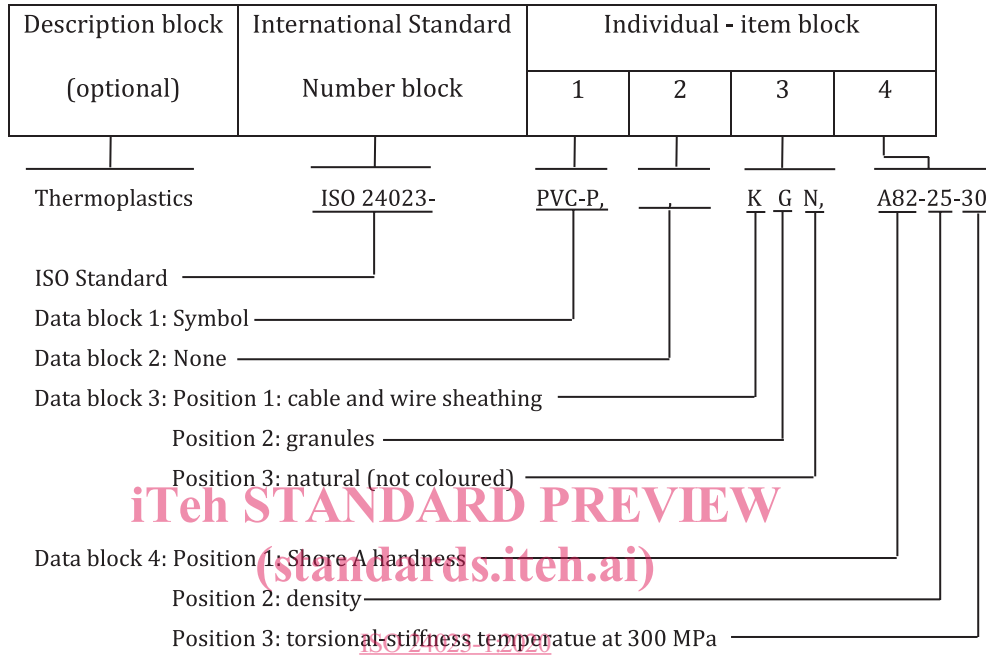

**Designation:** (Thermoplastics) ISO 24023-PVC-P,, KGN, A82-25-30