

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
24020

ISO/TC 156

Secretariat: SAC

Voting begins on:
2021-10-20

Voting terminates on:
2021-12-15

**Corrosion of metals and alloys —
Standard test method for particle-
free erosion corrosion of metallic
materials by jet-in-slit**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/FDIS 24020](https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020)

<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 24020:2021(E)

© ISO 2021

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/FDIS 24020

<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principles.....	1
4.1 Schematic of jet-in-slit test.....	1
4.2 Hydrodynamic conditions on the specimen.....	2
4.3 Typical damage pattern.....	3
4.4 Material and solution.....	3
5 Apparatus.....	4
5.1 Nozzle and specimen.....	4
5.2 Test chamber.....	5
5.3 Test solution circuit.....	6
6 Test conditions and procedure.....	7
7 Test report.....	8
Annex A (informative) Recommended practice for copper alloys by jet-in-slit test.....	9
Bibliography.....	11

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/FDIS 24020](https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020)

<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Particle-free erosion corrosion is a major problem in metallic materials of industries handling liquids flowing rapidly which are corrosive. Specifically, the metallic materials include copper, copper alloys and steels, and the liquids are various types of liquids such as seawater, tap water, industrial water, chemical water (e.g. acid and alkali aqueous solution), waste water. Particle-free erosion corrosion usually leads to rapid metal loss with possibly catastrophic consequences. In order to prevent, either mitigate or control, or both, the problems, it is important to determine the particle-free erosion corrosion behaviour of materials for plant construction. This can be achieved by standardization of the test methods which can reproduce the specific mode of corrosion in those materials. This test method can be applied to various types of metallic materials by choosing appropriate test solutions and conditions.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO/FDIS 24020](https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020)

<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/FDIS 24020

<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccb215e42d/iso-fdis-24020>

Corrosion of metals and alloys — Standard test method for particle-free erosion corrosion of metallic materials by jet-in-slit

1 Scope

This document specifies a test method for particle-free erosion corrosion of metallic materials by use of jet-in-slit which is flow induced corrosion in single phase flowing liquids. The test method can be used for ranking materials performance, selecting candidate materials and testing the effects of corrosion inhibitors.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 8044, *Corrosion of metals and alloys — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 8044 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

erosion

progressive loss of original material from a solid surface due to mechanical interaction between that surface and a fluid, a multicomponent fluid, or an impinging liquid or solid particles

Note 1 to entry: For more details, see Reference [1].

3.2

erosion corrosion

process involving conjoint corrosion and *erosion* (3.1)

3.3


particle-free erosion corrosion

erosion corrosion (3.2) of metallic materials in single phase flowing liquids free of solid particles and gas bubbles

4 Principles

4.1 Schematic of jet-in-slit test

The schematic of jet-in-slit test can be seen in [Figure 1](#). Two circular discs with the same dimensions are set face-to-face to form a narrow gap (slit) between them. A bore hole is drilled-through at the centre of the upper disc to make a nozzle. A jet of test solution from the nozzle impinges at a right angle to the specimen and then to flow in radial direction through the slit.

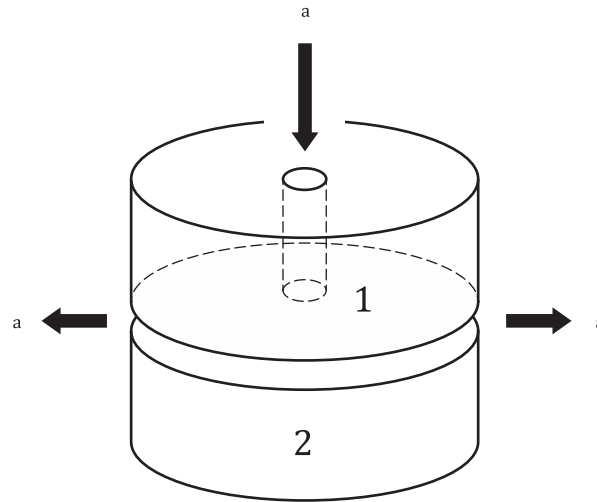

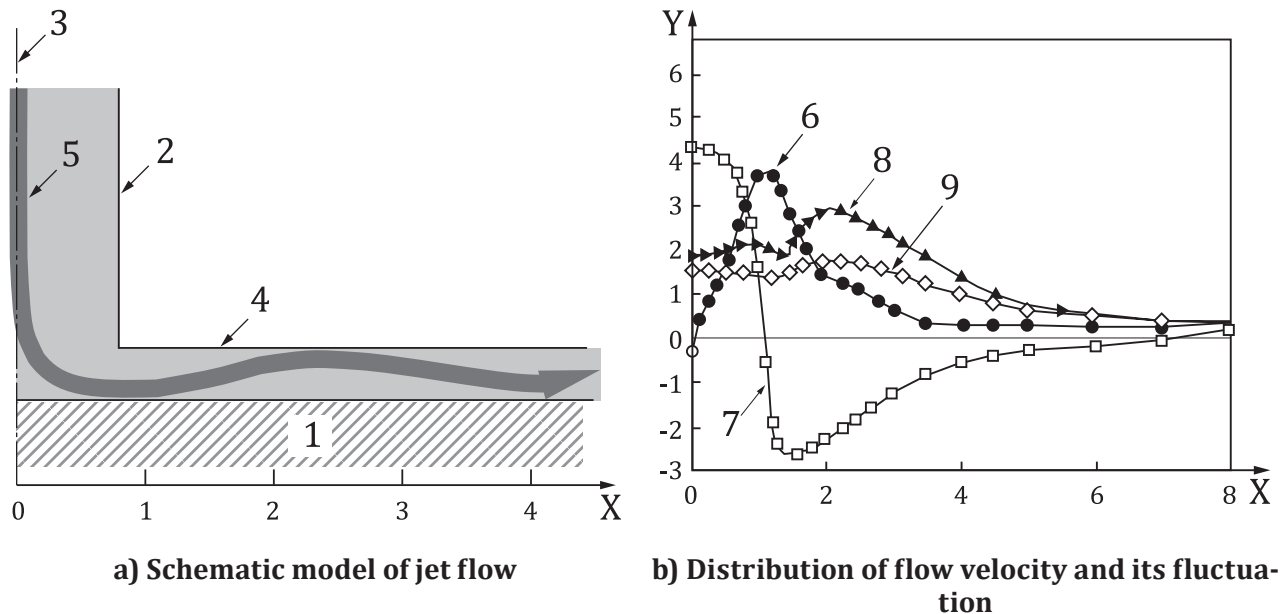
- Key**
- 1 nozzle
 - 2 specimen
 - a Solution flow.

Figure 1 — Schematic of jet-in-slit test

iTeh STANDARD PREVIEW
(standards.iteh.ai)

4.2 Hydrodynamic conditions on the specimen

The hydrodynamic conditions of jet flow on the specimen surface in the nozzle and slit are shown in [Figure 2 a\)](#) and [b\)](#)^[2]. The vertical flow velocity, (see [Figure 2](#), Key 7) is highest at the centre (see [Figure 2](#), Key 3) of the nozzle ([Figure 2](#), Key 2), or the specimen ([Figure 2](#), Key 1), but is reciprocally the highest (reverse direction) at the location approximately 1,5 mm from the centre, in the jet flow (see [Figure 2](#), Key 5). The flow rebounds after impinging on the specimen surface and causes boundary layers peeling followed by flow fluctuation. The shear stress caused by fluid running over the surface of specimen is proportional to the velocity gradient normal to the surface, and it is usually higher at higher flow velocity, as same as the shear stress in jet in impingement testing^[3]. The horizontal flow velocity ([Figure 2](#), Key 6) shows a maximum at the location approximately 1 mm from the centre and gradually lowered as the circumference is approached. The fluctuation of horizontal (see [Figure 2](#), Key 8) and vertical (see [Figure 2](#), Key 9) flow velocities are highest at the location approximately 2 mm from the centre. In general, the fluctuation of flow velocity represents the intensity of turbulence in fluid flow.

**Key**

X distance from the centre of the specimen / mm

Y flow velocity / ms^{-1}

1 specimen (16 mm in diameter)

2 nozzle (1,6 mm in diameter)

3 centre of nozzle and specimen

4 slit (0,4 mm in width)


5 schematic model of jet flow

6 horizontal flow velocity (\rightarrow)7 vertical flow velocity (\downarrow)8 horizontal flow velocity fluctuation (\leftrightarrow)9 vertical flow velocity fluctuation (\updownarrow)**Figure 2 — Hydrodynamic condition of jet flow in nozzle and slit****4.3 Typical damage pattern**

A typical damage pattern after jet-in slit test is shown in [Figure 3](#)^[4]. Damage ring 1 is formed by the separation of corrosion product film by the highly vertical and horizontal velocity, i.e. shear stress (see [Figure 2](#), Key 3 and Key 4), whereas damage ring 2 is due to that by turbulence in the flow (see [Figure 2](#), Key 5 and Key 6).

4.4 Material and solution

This document can be applied to various types of metallic materials by choosing appropriate test solutions and conditions. For copper and copper alloys, the solution examples are in seawater or industrial water environments. This test method has already been put to practical use in the industry. For steels and steel alloys, the solution examples are in various boiler water environments. This test method has been validated in the laboratory ^{[5],[6]}.

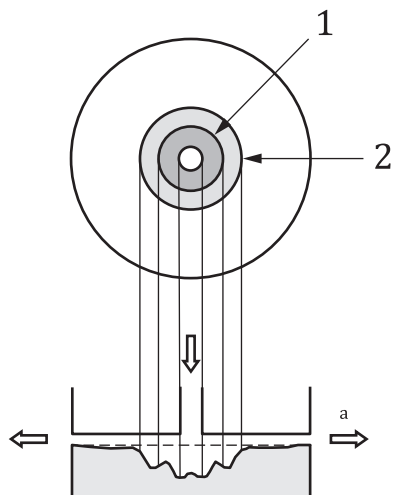

Key

- 1 inner damage ring
- 2 outer damage ring
- a Solution flow.

Figure 3 — Surface and cross-section of a pure copper specimen after jet-in-slit test in 12,7 g (CuCl₂ · 2H₂O) /1 cupric chloride (II) solution^[4]

iTech STANDARD PREVIEW
(standards.iteh.ai)

5 Apparatus

5.1 Nozzle and specimen

ISO/FDIS 24020
<https://standards.iteh.ai/catalog/standards/sist/6360630f-a6d4-411c-8f67-1dccc215e42d/iso-fdis-24020>

The required size and arrangement of nozzle and specimen is shown in Figure 4. The specimen shall be set coaxially with nozzle. The meeting surfaces of nozzle and specimen shall be finished with JIS P600^[Z] or finer abrasive cloth or paper after machining. The surfaces shall be polished to a maximum surface roughness of 0,8 μm. The circular edges of the specimen shall be smooth, but the chamfer or radius shall not exceed 0,15 mm.

NOTE The number of JIS P600^[Z] corresponds to ISO P600^[8].