



Designation: ~~D 7488–10~~ Designation: D7488 – 11

Standard Test Method for Open Time of Latex Paints¹

This standard is issued under the fixed designation D7488; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope

1.1 This test method covers a procedure to determine the length of time a latex paint remains “wet” or “open” enough to allow for brush-in and repair.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D3924 [Specification for Environment for Conditioning and Testing Paint, Varnish, Lacquer, and Related Materials](#)

D5068 [Practice for Preparation of Paint Brushes for Evaluation](#)

D5301 [Practice for Physical Characterization of Paint Brushes](#)

E177 [Practice for Use of the Terms Precision and Bias in ASTM Test Methods](#)

E691 [Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

3. Terminology

3.1 *Definitions:*

3.1.1 *open time, n*—the length of time a coating remains wet or open enough to allow for brush-in without the edges of the first coat becoming visible and allowing for repair within the previously painted area.

4. Summary of Test Method

4.1 Since environmental conditions such as temperature, humidity and air flow can result in variable results, it is recommended that this test method be performed in a constant temperature / humidity room ($23 \pm 2^\circ\text{C}$ ($73.5 \pm 3.5^\circ\text{F}$)) / $50 \pm 5\%$ relative humidity. Test paints are applied to the center of a sealed chart with a 76 microns (3 mil) wet film thickness. X marks are made immediately. The number of X marks will depend on how many can fit on one drawdown (see Fig. 1). The test paint is then applied in perpendicular sections, brushing each section across the initial painted section. The perpendicular sections are repeated at agreed upon time intervals. After drying, wet edge is recorded as the last time the test paint could be brushed into the initial painted section without the edges of the first coat being visible. The time at which the X marks become visible is also noted.

5. Significance and Use

5.1 Latex paints dry very quickly which often causes difficulty in final appearance of painted areas, especially paints formulated below 100g/L VOC where lower amounts of solvents are in the formulated latex paint. This method is a means of determining the time available before a test paint cannot be worked into a previously painted area.

6. Apparatus

6.1 *Constant Temperature/Humidity Room* ($23 \pm 2^\circ\text{C}$ ($73.5 \pm 3.5^\circ\text{F}$)) / $50 \pm 5\%$ relative humidity in accordance with Specification D3924.

6.2 *Contrasting Sealed Chart* (that is, black sealed chart for white paints or white sealed chart for tinted paints), typically 30 by 60 cm (1 by 2 ft.).

¹ This test method is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.42 on Architectural Coatings.

Current edition approved Dec. 1, 2010. Published February 2011. DOI: 10.1520/D7488-10.

Current edition approved July 1, 2011. Published August 2011. Originally approved in 2010. Last previous edition approved in 2010 as D7488-10. DOI: 10.1520/D7488-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

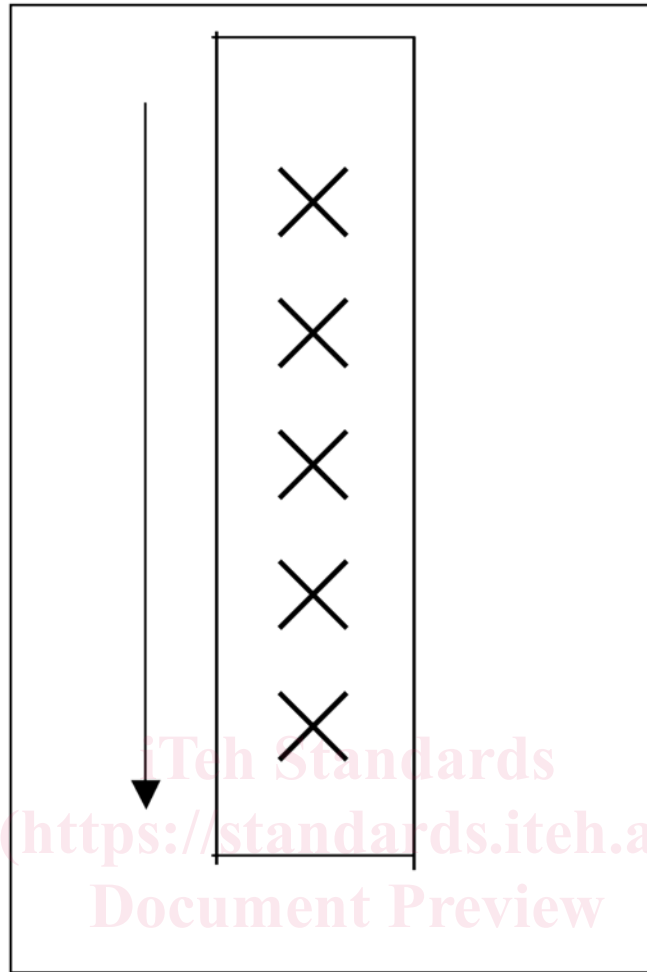


FIG. 1 Illustration 11

<https://standards.iteh.ai/catalog/standards/sist/e1cb3cfc-4b1e-4737-97b2-7dd04a507b96/astm-d7488-11>

6.3 *Glass Plate*, 30 by 60 cm (1 by 2 ft.) or vacuum plate.

6.3.1 If using a glass plate, tape to secure sealed chart to glass plate.

6.4 *Good Quality Brush*, 50 mm (2 in.) wide with straight edge, polyester bristles in accordance with Practice D5301.

6.5 *Timer or Clock* to record time intervals.

6.6 *Film Applicator*, capable of applying a film with a width of 7.5 cm (3 in.) and approximate wet film thickness of 75 microns (3 mil).

7. Procedure

~~7.1 Condition the brush in accordance with Practice~~

7.1 Condition the brush in with the test paint accordance with Practice D5068.

7.2 Tape the edges of the chart to a smooth glass plate or use a vacuum plate.

7.3 Along the length of the panel, drawdown 76 microns (3 mil) wet film thickness of the test paint (see Fig. 1). The drawdown must be free of ridges, craters, or other imperfections.

7.4 Start the timer or record the time.

7.5 Immediately make X marks approximately in 4 cm (1½ in.) wide and 4 cm (1½ in.) long in four to five different areas on the drawdown, as shown in Fig. 1.

NOTE 1—The wide curved end of a wooden tongue blade/paint brush or the end of a tongue depressor/metal spatula has been found suitable for this purpose.³ Depending on the type of instrument used to make the X mark, ensure that the X marks are consistent in size down the chart and throughout your testing.

³ Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:D01-1154.

³ It is suggested that you wrap the brush in a disposable plastic wrap between timed intervals to prevent the paint from drying on the brush.