



Designation: D6549 – 06(Reapproved 2011)

## Standard Test Method for Determination of Cooling Characteristics of Quenchants by Cooling Curve Analysis with Agitation (Drayton Unit)<sup>1</sup>

This standard is issued under the fixed designation D6549; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the equipment and the procedure for evaluation of quenching characteristics of a quenching fluid by cooling rate determination.

1.2 This test method is designed to evaluate quenching fluids with agitation, using the Drayton Agitation Unit.

1.3 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>2</sup>

E220 Test Method for Calibration of Thermocouples By Comparison Techniques

E230 Specification and Temperature-Electromotive Force (EMF) Tables for Standardized Thermocouples

#### 2.2 SAE Standards:<sup>3</sup>

AMS 5665 Nickel Alloy Corrosion and Heat Resistant Bars, Forgings and Rings

#### 2.3 Other Standards:<sup>4</sup>

Wolfson Engineering Group Specification Laboratory Tests for Assessing the Cooling Curve Characteristics of Industrial Quenching Media

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee D02.L0.06 on Non-Lubricating Process Fluids.

Current edition approved May 1, 2011. Published August 2011. Originally approved in 2000. Last previous edition approved in 2006 as D6549–06. DOI: 10.1520/D6549-06R11.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096-0001, http://www.sae.org.

<sup>4</sup> Available from Wolfson Heat Treatment Centre, Federation House, Vyse St., Birmingham, B18 6LT, UK. http://www.sea.org.uk/whtc.

#### 2.4 ASTM Adjuncts:<sup>5</sup>

ADJD6300 D2PP, Determination of Precision and Bias Data for Use in Test Methods for Petroleum Products and Lubricants

### 3. Terminology

#### 3.1 Definitions of Terms Specific to This Standard:

3.1.1 *aqueous polymer quenchant*—an aqueous polymer quenchant is an aqueous solution containing a water soluble polymer, typically including poly(alkylene glycol), poly(ethyl oxazoline), poly(sodium acrylate), and poly(vinyl pyrrolidone) (1, 2, 3).<sup>6</sup> The quenchant solution also typically contains additives for corrosion and foam control, if needed. Quench severity of aqueous polymer quenchants is dependent on concentration and molecular weight of the specific polymer being evaluated, quenchant temperature, and agitation rate as shown in Fig. 1, Fig. 2, and Fig. 3, respectively.

3.1.2 *cooling curve*—the cooling curve is a graphical representation of the cooling time ( $t$ ) versus temperature ( $T$ ) response of the probe (see 7.3). An example is illustrated in Fig. 4.

3.1.3 *cooling curve analysis*—the process of quantifying the cooling characteristics of a quenchant based on the temperature versus time profile obtained by cooling a preheated metal probe assembly (see Fig. 4) under standard conditions (1-7).

3.1.4 *cooling rate curve*—the cooling rate curve is a graphical representation of first derivative of the cooling curve, the rate of temperature change ( $dT/dt$ ) versus temperature. An example is illustrated in Fig. 4.

3.1.5 *quenchant*—a quenching medium may be either a liquid or a gas. Gasses that are used as quenchants include air, nitrogen, argon, and hydrogen and, with the exception of air, which is used at atmospheric pressure, are used under pressure. Liquid quenchants include water, brine (most commonly dilute aqueous solutions of sodium chloride or sodium hydroxide), oil, molten salt, molten metal, and aqueous solutions of water soluble polymers. Water, brine, oil, and aqueous polymer quenchants are generally used with agitation.

<sup>5</sup> No longer available from ASTM International Headquarters.

<sup>6</sup> The boldface numbers in parentheses refer to the list of references at the end of this standard.

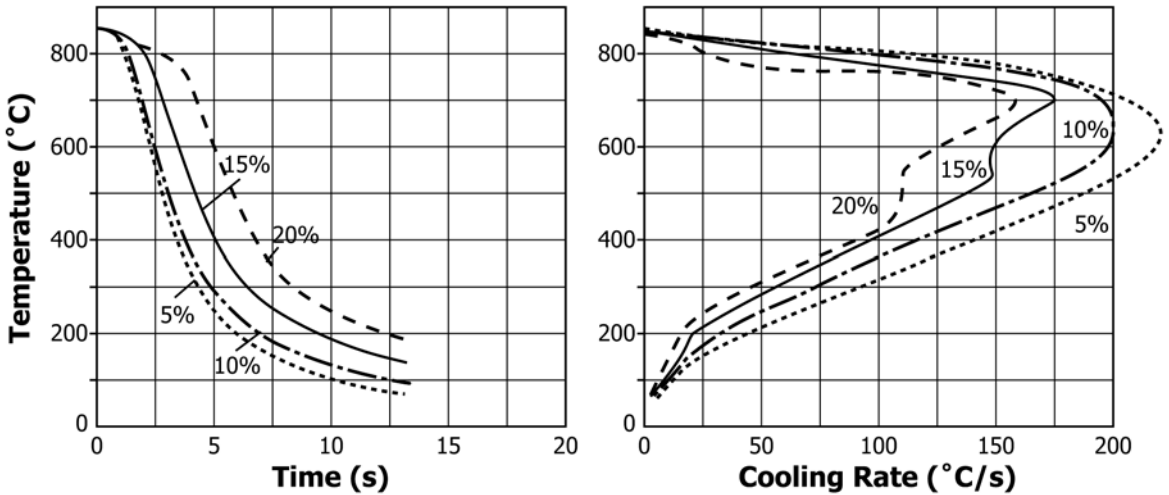


FIG. 1 Effect of Quenchant Concentration on Cooling Curve Performance for a Poly(Alkylene Glycol) Quenchant at 30°C and 0.5 m/s

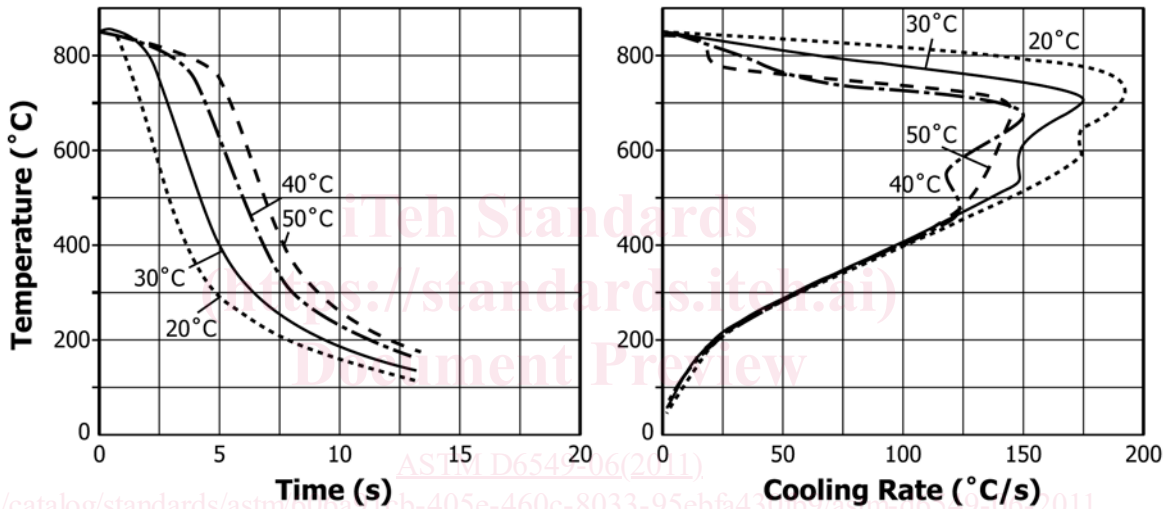


FIG. 2 Effect of Bath Temperature Variation on Cooling Curve Performance for 15 % Aqueous Solution of Poly(Alkylene Glycol) Quenchant at 0.5 m/s

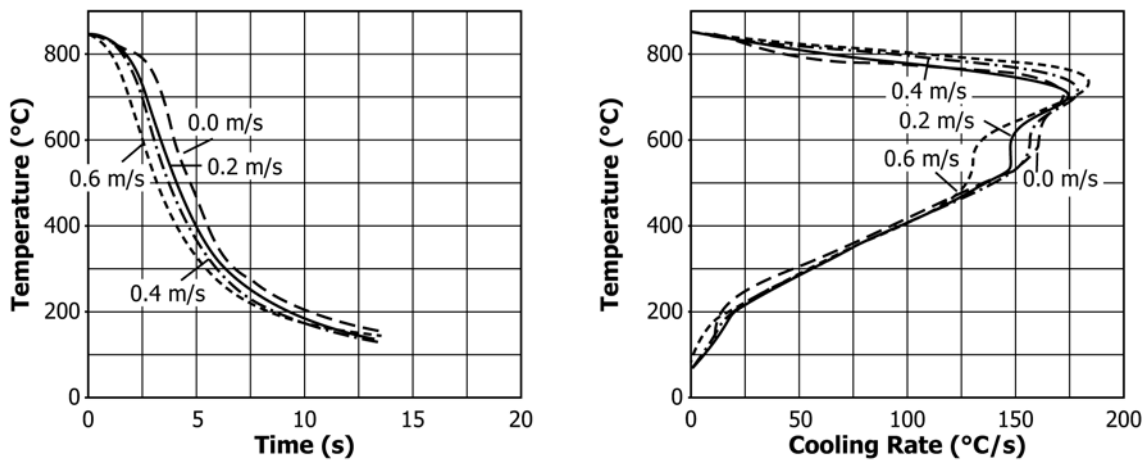


FIG. 3 Effect of Agitation Rate Variation on Cooling Curve Performance for a 15 % Aqueous Poly(Alkylene Glycol) Quenchant Solution at 30°C

3.1.6 *quench severity*—the ability of a quenching medium to extract heat from a hot metal (8).