
**Fine bubble technology — Cleaning
applications —**

Part 1:

**Test method for cleaning salt (NaCl)-
stained surfaces**

iTEH Standards *Technologie des fines bulles — Applications de nettoyage —
Partie 1: Méthode d'essai pour le nettoyage de surfaces dégradées par
le sel (NaCl)*
Document Preview

[ISO/TS 21256-1:2020](#)

<https://standards.iteh.ai/catalog/standards/iso/9f09989d-a925-409e-8db0-f9a4199c18e1/iso-ts-21256-1-2020>



Reference number
ISO/TS 21256-1:2020(E)

© ISO 2020

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/TS 21256-1:2020](https://standards.iteh.ai/catalog/standards/iso/9f09989d-a925-409e-8db0-f9a4199c18e1/iso-ts-21256-1-2020)

<https://standards.iteh.ai/catalog/standards/iso/9f09989d-a925-409e-8db0-f9a4199c18e1/iso-ts-21256-1-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle of cleaning performance test	1
5 Test apparatus for cleaning test	2
5.1 High-pressure water jet	2
5.1.1 Test conditions	2
5.1.2 Characteristics of the high-pressure water jet	2
5.2 Measuring instrument	3
6 Salt-stained steel test plate for cleaning performance test	3
7 Procedure	3
7.1 General	3
7.2 Measurement before cleaning the surface of the steel test plate	3
7.3 Cleaning method of the surface of the steel test plate	4
7.4 Measurement of salt stains after cleaning the surface of the steel test plate	5
8 Calculation method of salt stain removal	6
8.1 Calculation method of salt removal ratio	6
8.2 Calculation method of salt removal quantity	6
9 Test report	6
Annex A (informative) Surface salinity meter	8
Annex B (informative) Example of evaluation results for cleaning of steel bridge girder edges	9
Annex C (informative) Example of test result table	11
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 281, *Fine bubble technology*.

A list of all parts in the ISO 21256 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

<https://standards.iteh.ai/catalog/standards/iso/9109989d-a925-409e-8d00-19a4199c18e1/iso-ts-21256-1-2020>

Introduction

Salt and materials derived from other pollution sources are known to coat surfaces of exterior of steel structures over time. Highway bridges and other steel structures are particularly vulnerable to anti icing salts or ocean spray. It is necessary that this contamination be removed in order to prevent growth of corrosion and to preserve the life time of the structure. Maintenance is conducted at times of inspection, possibly via the erection of suitable scaffolding and platforms and therefore a rapid efficient cleaning mechanism is essential.

High-pressure water sprays are commonly used for the cleaning method due to their hydrodynamic power. The method requires the operator long term engagement to dangerous operation in inhospitable environment.

It has been shown recently that cleaning process is much more effective and quicker once the water used for the high-pressure spray is augmented with the addition of ultrafine bubbles (UFB) and that markets of ultrafine bubble water or its generating systems are growing rapidly.

This document is intended to provide users of such products and systems with objective information on the cleaning performance of ultrafine bubble water and to facilitate the improvement of ultrafine bubble waters and their generating systems.

The test procedure correlates the ultrafine bubble enhanced performance with the presence of ultrafine bubbles under standardized conditions based on the most commonly used criteria such as hydrodynamic characteristics of high-pressure water spray, quality of raw water before mixing with ultrafine bubbles, quality of salt stain, quality and dimension of coating and substrate of test steel material and testing environmental conditions.

In this document, the presence of ultrafine bubbles is evaluated by measuring their sizes and number concentrations. The performance of the method is assessed by measuring the change in removal of salt from the test sample surface due to application of the ultrafine bubble water relative to that of plain water as control. Example application of the test procedure demonstrates the test results on various steel bridges long exposed to environments of express ways.

This document is intended to be used as a guidance for conducting tests and gathering more data to develop an International Standard.

Fine bubble technology — Cleaning applications —

Part 1: Test method for cleaning salt (NaCl)-stained surfaces

1 Scope

This document describes the test method to evaluate the cleaning performance of ultrafine bubble water when used in high-pressure water jet to wash out salt-stained steel surfaces.

The evaluation is carried out by measuring comparative removal of salt stain from the surface of a test plate with the ultrafine bubble water to that with control water.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 20480-1, *Fine bubble technology — General principles for usage and measurement of fine bubbles — Part 1: Terminology* (<https://standards.iteh.ai>)

ISO 20480-2, *Fine bubble technology — General principles for usage and measurement of fine bubbles — Part 2: Categorization of the attributes of fine bubbles* (<https://standards.iteh.ai>)

3 Terms and definitions

[ISO/TS 21256-1:2020](https://standards.iteh.ai)

For the purposes of this document, the terms and definitions given in ISO 20480-1, ISO 20480-2 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

high-pressure water jet

equipment that forces water out of a small orifice at high speed

3.2

control water

blank water

water used as reference in comparative test on the ultrafine bubble water

4 Principle of cleaning performance test

Cleaning of salt stains is performed using water containing ultrafine bubbles that are uniformly distributed in the water medium.

The characteristics to define the ultrafine bubble water are the diameter and the density distribution of ultrafine bubbles.

The performance of the cleaning test is dependent in principle on the characteristics of the ultrafine bubble water and the hydrodynamic performance of the high-pressure water jet as well as the characteristic of the salt stains and the test environment.

In the test method, the characteristics of the high-pressure water jet, the salt stains and the test environment are fixed, while the ultrafine bubble characteristics are modified to assess how ultrafine bubbles can enhance performance.

The change in performance is assessed by measuring the density of salt stains after removal by high-pressure water jet using ultrafine bubble water and control water.

5 Test apparatus for cleaning test


5.1 High-pressure water jet

5.1.1 Test conditions

A high-pressure water jet is used to carry out the cleaning test, as shown in [Figure 1](#).

The test conditions are as follows:

- high-pressure water jet nozzle: inner diameter 6 mm at outlet;
- water temperature: 15 °C to 25 °C.

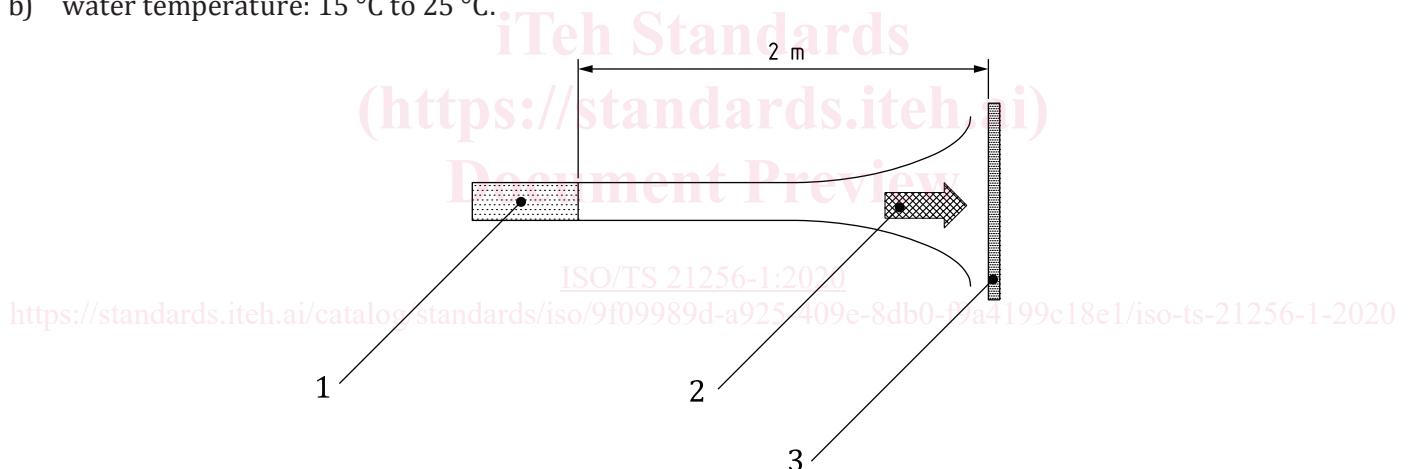

Key

- nozzle of high-pressure water jet
- water flow
- steel test plate

Figure 1 — Salt removal method using a high-pressure water jet

5.1.2 Characteristics of the high-pressure water jet

The characteristics of the high-pressure water jet should be as follows.

- The high-pressure cleaning machine should have an outlet pressure from 5 MPa to 9 MPa and the amount of outlet cleaning liquid should range from 300 l/h to 400 l/h. The cleaning width on the target should be stable, between 250 mm and 300 mm at a distance of 2 m from the outlet gate.
- Ultrafine bubble water should be continuously supplied to the high-pressure water jet during the cleaning test.

5.2 Measuring instrument

After removal, the adherent salt stains on the test plate shall be measured using a surface salinity meter to perform density measurements.

The following conditions apply:

- a) the surface salinity density is measured based on the electrical conductivity data after conversion (see ISO 8502-9^[4]);
- b) precision should be $\pm 1\%$ (for a temperature between $0\text{ }^{\circ}\text{C}$ and $50\text{ }^{\circ}\text{C}$).

[Annex A](#) shows an example of surface salinity meter, according to ISO 8502-9.

6 Salt-stained steel test plate for cleaning performance test

The salt-stained steel test plate shall have the following features:

- a) flat plate with simple configuration;
- b) plate made of steel of carbon steel grade;
- c) with dimensions $530\text{ mm} \times 530\text{ mm}$ and thickness 10 mm .

7 Procedure

iTeh Standards

7.1 General


<https://standards.iteh.ai>

The salt density is measured before and after cleaning the surface of the steel test plate. The test shall be very carefully conducted from the beginning to the end as it is a destructive test.

7.2 Measurement before cleaning the surface of the steel test plate

https://standards.iteh.ai/catalog/standard/iso/0000801-025400-8450-0-4109-18s1/iso_ts_21256-1-2020
Salt density shall be measured before cleaning the surface of the steel test plate in accordance with the following procedure.

- a) Four even-numbered points on the surface of the steel test plate are measured with the surface salinity meter. See [Figure 2](#).

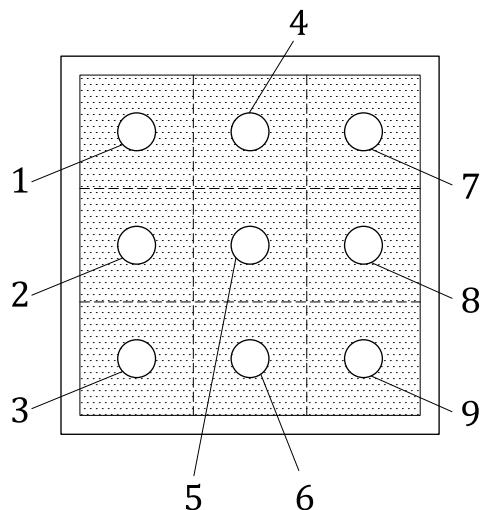**Key**

1	not measured initially	6	$\rho_{\text{initial-6}}$
2	$\rho_{\text{initial-2}}$	7	not measured initially
3	not measured initially	8	$\rho_{\text{initial-8}}$
4	$\rho_{\text{initial-4}}$	9	not measured initially
5	not measured initially		

Figure 2 — Initial measuring points before cleaning

b) The initial salt density average is calculated using [Formula \(1\)](#):

$$\rho_{\text{initial}} = (\rho_{\text{initial-2}} + \rho_{\text{initial-4}} + \rho_{\text{initial-6}} + \rho_{\text{initial-8}})/4 \quad (1)$$

where ρ_{initial} is the initial adherent average value before cleaning (mg/m²).

<https://standards.iteh.ai/catalog/standards/iso/909989d-a925-409e-8db0-f9a4199c18e1/iso-ts-21256-1-2020>

7.3 Cleaning method of the surface of the steel test plate

[Figure 3](#) shows an outline of the test method. When reproducibility of manual operation, for cleaning the surface, is significantly deteriorated, introduction of automatic operation is recommended.

- A distance of 2 m is kept between the outlet gate of the high-pressure water jet and the surface of the steel test plate.
- The steel test plate is tightly fixed and the cleaning liquid of the high-pressure water jet is outlet at right angle to the surface of the steel test plate.
- The high-pressure water jet is reciprocally moved like a round-trip starting from "a", going through "b", "c" and "d" and returning to "a" as shown in [Figure 3](#). The number of repetitions is arbitrary, but 20 times are enough.
- Time needed for the nozzle to make a reciprocal move is approximately 1 s.
- To compare removal quantities, cleaning liquid with or without ultrafine bubbles is applied for the cleaning test.