
**Urine-absorbing aids for
incontinence — Polyacrylate
superabsorbent powders —**

Part 2:

**Test method for determination of
the amount of residual acrylate
monomers**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

*Aides pour absorption d'urine — Méthodes d'essai pour caractériser
les matériaux absorbants à base de polymères —*

Partie 2: Détermination de la quantité de monomères résiduels

PROOF / ÉPREUVE



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/PRF 17190-2

<https://standards.iteh.ai/catalog/standards/sist/d486317a-9c79-42b8-9fd9-225f7b3a8dd6/iso-prf-17190-2>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	2
5 Reagents and materials.....	2
5.1 Water.....	2
5.2 Sodium chloride solution.....	2
5.3 Phosphoric acid.....	2
5.4 Phosphoric acid solution.....	2
5.5 Acetonitrile.....	2
5.6 Acrylic acid.....	2
6 Apparatus.....	3
7 Calibration.....	4
8 Conditioning.....	4
9 Sampling.....	4
10 Procedure.....	5
11 Calculation.....	6
11.1 Calibration curve.....	6
11.2 Amount of residual monomers.....	6
12 Report.....	7
13 Precision.....	7
Annex A (informative) Notes on chromatographical testing.....	8
Bibliography.....	10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 173, *Assistive products*, Subcommittee SC 3, *Aids for ostomy and incontinence*.

This second edition cancels and replaces the first edition (ISO 17190-2:2001), which has been technically revised. The main changes compared to the previous edition are as follows:

- full text review and new laboratory analysis with statistical evaluation.

A list of all parts in the ISO 17190 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Urine-absorbing aids for incontinence — Polyacrylate superabsorbent powders —

Part 2:

Test method for determination of the amount of residual acrylate monomers

WARNING — This document does not claim to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this document to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. It is expected that the person performing this test has been fully trained in all aspects of this procedure.

1 Scope

This document provides a test method for determining the sum of residual monomeric sodium acrylate and acrylic acid present in polyacrylate superabsorbent powders as acrylic acid.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

amount of residual monomers

sum of residual monomeric sodium acrylate and acrylic acid

3.2

sample

product or portion of a product taken from a production lot for testing purposes and identifiable and traceable back to its origin

3.3

specimen

specific portion of the identified *sample* (3.2) upon which a test is performed

4 Principle

Residual monomeric sodium acrylate and acrylic acid are extracted from the polyacrylate superabsorbent powders and the amount determined as residual acrylate monomer by HPLC.

The method described here uses a simple 1 g in 200 ml dilution factor. However, it is equally valid to use different masses and volumes as long as the mass:volume dilution ratio is the same and suitable experimental validation is performed.

5 Reagents and materials

Use only reagents of recognized analytical grade, unless otherwise specified.

5.1 Water.

Grade 1 water according to ISO 3696, for the standard solutions for the calibration and Grade 3 water according to ISO 3696, with the exception that the conductivity can be as high as 30 $\mu\text{S}/\text{cm}$, for the saline solution.

5.2 Sodium chloride solution.

5.2.1 0,9 % mass fraction of sodium chloride solution in water. Weigh $(9,00 \pm 0,01)$ g of sodium chloride into a 1 l beaker and add $(991,0 \pm 0,1)$ g of deionized water (grade 3). Stir until dissolved.

5.2.2 The conductivity of the solution should be checked prior to each use using properly calibrated measuring equipment. The expected conductivity of a 0,9 % saline solution is of the order of 1600 S/m (depending on temperature). Each testing lab shall determine the correct conductivity for the conditions obtaining in the lab. It is also recommended that the temperature of the solution be maintained at (23 ± 2) °C for the duration of the test. As this matches the required laboratory temperature it is not necessary to record the solution temperature.

5.3 Phosphoric acid.

Concentrated $c(\text{H}_3\text{PO}_4) = 85$ % by mass, of HPLC grade or better.

5.4 Phosphoric acid solution.

$c(\text{H}_3\text{PO}_4) = 0,1$ % by mass (1 g/l or 0,0087 mol/l). Dilute concentrated H_3PO_4 to volume with deionized water (grade 1). Stir until dissolved.

5.5 Acetonitrile.

HPLC grade or better.

5.6 Acrylic acid.

Greater than 99,5 % purity.

Acrylic acid degrades over time owing to slow polymerization, particularly dimerization, and water uptake. It is important to obtain acrylic acid that meets the purity required for this test method. It is not recommended to obtain the reference substance from a laboratory chemicals distributor as the purity of this material from such a source is likely to be defined inaccurately.

6 Apparatus

6.1 Analytical balance, capable of weighing a mass of $(100,000 \pm 0,001)$ g of polymer powder in combination with the mass of the weighing vessel or laboratory paper employed.

6.2 Analytical balance, capable of weighing a mass of $(9,00 \pm 0,01)$ g of sodium chloride in combination with the mass of the weighing vessel or laboratory paper employed.

6.3 Analytical balance, capable of weighing a mass of $(1000,00 \pm 1,00)$ g of sodium chloride solution in combination with the mass of the vessel employed.

6.4 Graduated 250 ml tall form beaker, to give better separation of gel and saline.

6.5 Grade A 100 ml graduated measuring cylinder, accurate to 0,5 %.

6.6 Grade A volumetric flasks 100 ml and 1 l.

6.7 Magnetic stirrer and stirring bar. Cylindrical stirring bars can be unstable when used on a multipoint magnetic stirring block. The mixture of magnetic fluxes can cause the bar to freeze periodically. Both cylindrical and star-shaped stirrers can tear the gel. It is recommended to use a cross-centred circular bar (see [Figure 1](#)), which provides more stable stirring and minimum tearing of the gel. It is also important to make sure that the cross is properly centred in the circle. Cheaply made versions can be off-centre and this increases variability in the test.



Figure 1 — Cowie double crosshead stir bar (typical dimensions: $20 < d < 25$ mm, $12 < h < 18$ mm)

6.8 Metal spatula, to accommodate 1,0 g of superabsorbent powder.

6.9 Filters – 0,45 µm pore size PTFE filters.

6.10 HPLC injection system, allowing injection volumes between 10 µl and 100 µl of analyte solution, accurate to ± 1 %.

6.11 HPLC pump, capable of delivering flows with a maximum back-pressure variability of ± 10 %.

6.12 C18 column, with suitable packing material. For example, 5 µm particle size, 100 mm length x 4,6 mm internal diameter (ID), fitted with a guard column.

6.13 Guard column with suitable packing material. For example, 5 µm particle size, 10 mm length x 4,6 mm internal diameter (ID).

6.14 UV detector for HPLC, capable of making measurements at a wavelength of 210 nm.

6.15 Standard Solutions for Calibration.

Use grade 1 ultra-pure water.

6.15.1 Solution S1 [pcal(S1) = 1 000 mg/l].

Weigh (0,1000 g ± 0,0005) g, of acrylic acid into the 100 ml volumetric flask labelled S1. Make up to the mark with ultra-pure water. This contains 1 000 mg/l acrylic acid. Using this solution, prepare the dilutions as follows:

6.15.2 Solution S2 [pcal(S2) = 100 mg/l].

Pipette 10 ml from S1 into the 100 ml volumetric flask labelled S2 and make up to the mark with ultra-pure water. This contains 100 mg/l acrylic acid.

6.15.3 Solution S3 [pcal (S3) = 1 mg/l].

Pipette 1 ml from S2 into the 100 ml volumetric flask labelled S3 and make up to the mark with ultra-pure water.

6.15.4 Solution S4 [pcal (S4) = 2 mg/l].

Pipette 2 ml from S2 into the 100 ml volumetric flask labelled S4 and make up to the mark with ultra-pure water.

6.15.5 Solution S5 [pcal (S5) = 3 mg/l].

Pipette 3 ml from S2 into the 100 ml volumetric flask labelled S5 and make up to the mark with ultra-pure water.

6.15.6 Solution S6 [pcal (S6) = 4 mg/l].

Pipette 4 ml from S2 into the 100 ml volumetric flask labelled S6 and make up to the mark with ultra-pure water.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/d486317a-9c79-42b8-9fd9-225f7b3a8dd6/iso-prf-17190-2>

7 Calibration

7.1 Analyze the standard solutions S3 to S6 in duplicate. Average the peak area obtained for each level (Ai).

7.2 If the difference between the duplicate peak areas for S3 to S6 is less than 5 %, use the average value for the calibration curve. If the difference of any of the duplicate analyses exceeds 5 % of the average, repeat the calibration in duplicate. If the differences continue to exceed 5 %, identify and eliminate the source of error.

8 Conditioning

Samples shall be delivered in a closed container, to prevent absorption of atmospheric moisture. Allow the closed container to equilibrate to the laboratory conditions. The preferred test conditions are (23 ± 2) °C and (45 ± 15) % relative humidity. If these conditions are not available, test at ambient conditions and report the temperature and relative humidity. Measure these laboratory conditions in accordance with ISO 187.

9 Sampling

WARNING — Powder Handling: The German Commission for the Investigation of Health Hazards of Chemical Compounds in the Work Area (MAK Commission) has provided a guideline value for long-term exposure to the respirable portion of superabsorbent polyacrylate dust of 0,05 mg.m-3. The respirable portion is defined as those particles of less than 10 µm diameter.

Commercial superabsorbent polymers typically contain less than 0,1 % of such particles. Precautions should be taken to avoid routine exposure to atmospheric respirable particles above this guideline.

9.1 Before taking a test portion out of the container to run the test, rotate the container five to ten times in a three-dimensional figure of eight motion (see [Figure 2](#)), so as to obtain a homogeneous product. For that matter, sample bottles should not be filled more than 80 % of their nominal capacity.

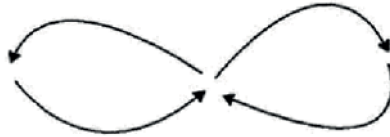


Figure 2 — Sense of motion of the container

9.2 Make sure the test portion is substantially free of lumps of size greater than 1 mm in diameter before proceeding with testing. Lumps can pierce the screen and disqualify the equipment and the test.

10 Procedure

WARNING — - Concentrated acids and bases shall be handled with care. Safety protection, including gloves and face shields, shall be worn. Concentrated hydrochloric acid shall be handled under a fume hood.

(standards.iteh.ai)

10.1 Accurately add $(200,0 \pm 0,1)$ ml of saline solution to a 250 ml glass beaker using the measuring cylinder.

ISO/PRF 17190-2

[https://standards.iteh.ai/catalog/standards/sist/d486317a-9c79-42b8-9fd9-](https://standards.iteh.ai/catalog/standards/sist/d486317a-9c79-42b8-9fd9-225f7b3181d6/iso-prf-17190-2)

10.2 Place a clean, dry weighing vessel or laboratory paper onto a balance and tare the balance.

10.3 Add $(1,000 \pm 0,005)$ g of a test portion of polyacrylate superabsorbent powder test sample to the weighing vessel or laboratory paper and tare the balance again.

Transfer the sample portion from the sample bottle to the weighing vessel or laboratory paper in one spatula portion. Discard any excess material on the spatula. Do not return it to the sample bottle. Keep the sample container closed as much as possible during this process.

10.4 Evenly distribute the test portion into the beaker containing the $(200,0 \pm 0,1)$ ml of saline.

10.5 Place the weighing vessel or laboratory paper back on the balance. The negative weight displayed is the mass of the sample transferred. Record this as M_{sam} .

10.6 Cover the beaker with a Petri dish lid or seal with paraffin film and stir the solution at a rate of (250 ± 50) r.min⁻¹ for 1 hour.

10.7 After 1 hour, stop stirring the solutions and allow the polymer to settle for 5 minutes.

10.8 Filter a portion of the supernatant through a $0,45 \mu\text{m}$ PTFE filter and use this for the HPLC analysis, using the chromatographic conditions as indicated in [Table 1](#).