
INTERNATIONAL STANDARD



2846

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Set of printing inks for offset printing – Colorimetric characteristics

Gamme d'encre primaires pour l'impression offset – Caractéristiques colorimétriques

First edition – 1975-07-01

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 2846:1975

<https://standards.iteh.ai/catalog/standards/sist/988d97d0-4b38-4cbf-b56e-437ca7ab6ee8/iso-2846-1975>

UDC 667.5

Ref. No. ISO 2846-1975 (E)

Descriptors: offset printing, colour printing, printing inks, colour, colorimetric characteristics, specifications, tests, spectrophotometric analysis.

Price based on 5 pages

FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO Member Bodies). The work of developing International Standards is carried out through ISO Technical Committees. Every Member Body interested in a subject for which a Technical Committee has been set up has the right to be represented on that Committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the Technical Committees are circulated to the Member Bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 2846 was drawn up by Technical Committee ISO/TC 130, *Graphic technology*, and circulated to the Member Bodies in September 1972.

TECH STANDARD PREVIEW
(standards.iteh.ai)

It has been approved by the Member Bodies of the following countries :

Czechoslovakia	Ireland	Sweden
Egypt, Arab Rep. of	New Zealand	Switzerland
Finland	Poland	Thailand
France	Romania	Turkey
Germany	South Africa, Rep. of	United Kingdom
India	Spain	

The Member Body of the following country expressed disapproval of the document on technical grounds :

Austria

Set of printing inks for offset printing – Colorimetric characteristics

0 INTRODUCTION

This International Standard is in technical conformity with CEI specification 13-67 of the European Committee of the Paint and Printing Ink Manufacturers' Association defining a "European set of primary colours for offset printing".

1 SCOPE AND FIELD OF APPLICATION

This International Standard extends the set of primary inks for letterpress printing given in ISO 2845 to include primary inks intended for three- or four-colour printing by the offset process, in defined order of printed colour and describes the control method.

It will enable :

- a) photolithographers and photo-engravers to make colour separations for offset printing based on an identical scale so that, irrespective of their different origin, various subjects for colour printing may be assembled on the same montage.
- b) lithographic and other printers to obtain printing inks which, when they are applied in the following conditions and to standard reference paper, can produce results complying with the specifications of this International Standard.

NOTE – This International Standard does not apply to fluorescent inks. Pigments are not covered by this International Standard thereby avoiding prejudice to future development in pigment production.

2 REFERENCES

ISO 2834, *Printing inks – Preparation of standard prints for determination of resistance to physical and chemical agents.*

ISO 2835, *Prints and printing inks – Assessment of light fastness.*

ISO 2837, *Prints and printing inks – Assessment of resistance to solvents.*

ISO 2845, *Set of printing inks for letterpress printing – Colorimetric characteristics.*

3 DEFINITIONS

For the purpose of this International Standard the following definitions apply :

3.1 reference inks : Yellow, magenta and cyan inks from which primary and secondary colours are obtained conforming to the set defined in this International Standard when printed on reference paper and with the reference ink film thickness given in 3.3.

3.2 standard set : A complete series of primary inks intended for three- or four-colour printing of which the colorimetric characteristics comply with the specifications of this International Standard.

3.3 reference film thickness of ink : Thickness of a printed film when printed solid on reference paper, of which the value is between 0,7 and 1,1 μm .

3.4 reference paper : Coated paper as specified in ISO 2834.

3.5 primary colours : Colours of individual prints from yellow, magenta and cyan inks produced under standard conditions, and of which the colorimetric definitions correspond to the numerical values given in 4.2.

3.6 secondary colours : Colours obtained by overprinting primary colours two at a time :

yellow + magenta,

yellow + cyan,

magenta + cyan,

in the conditions specified in this International Standard and with the colorimetric definitions corresponding to the numerical values shown in 4.2. The order of the overprinting of the primary colours is not – subject to specification to the contrary – laid down, but it must be stated in the test report.

4 TEST METHOD

4.1 Principle

Each colour in the set obtained by printing (or overprinting) reference inks under the conditions specified in 5.2 is assessed according to its visual appearance by the values of the colorimetric steps established from measurements made in accordance with the spectrophotometric methods of colorimetry.

Reference inks are printed solid, either alone (primary colours) or overprinted (secondary colours) at the reference thickness and on reference paper.

NOTE — The colours chosen are those which offer the best possible lightfastness (see ISO 2835) and resistance to solvents (see ISO 2837) in order that prints may be varnished.

4.2 Colorimetric characteristics and tolerances

The table below gives the numerical values of the colorimetric characteristics of the specified primary and secondary colours.

Tristimulus coefficients *X*, *Y* and *Z* have been established in accordance with the recommendations of the 1931 meeting of the CIE¹⁾. They are determined for Illuminant C.

Numerical values of the uniform colour space coefficients *U**, *V**, and *W** derived from the above and the colour difference ΔE_{CIE} are calculated according to the 1964 CIE recommendations (CIE vocabulary — definition 45-15-185).

The chromaticity co-ordinates *x*, *y* and the luminance *Y* have been calculated and rounded from fixed values *U**, *V** and *W**.

4.3 Preparation of test specimens

4.3.1 Primary colours

In order to check whether a set of offset primary colours conforms to this International Standard, prepare on reference paper a series of test specimens with ink film thicknesses which are within the range of the reference film thickness, printed solid in accordance with the letterpress system and at a reproducible speed on equipment for testing printability. The quantity of ink applied is checked by weighing the printing plates both before and after printing.

The thickness of the film prepared, expressed in micrometres, is equal to the quotient of the quantity of ink applied, expressed in grams per square metre, by the value of the density of the ink used, expressed in grams per cubic centimetre.

4.3.2 Secondary colours

In order to check whether a range of secondary colours intended for offset printing conforms to this International Standard, a series of overprint test specimens on reference paper will have to be prepared by means of a process similar to that described in 4.3.1.

Such overprints should only be prepared on test specimens of which the thoroughly dry, primary colour print has been prepared with an ink film thickness which comes within the range of reference film thicknesses and which has colorimetric characteristics, the values of which offer minimum ΔE_{CIE} colour differences in relation to the values given in 4.2.

Various tests carried out on test specimens of primary colours also make it possible to determine the quantity of the ink necessary for overprints of secondary colours.

4.4 Colorimetric evaluation of the test specimens

The prints (or overprints) when completely dry are spectrophotometrically measured in accordance with the recommendations of the CIE²⁾, placing them on a pile of at least five unprinted sheets of the reference paper before assessment.

The spectrophotometric curve is plotted using a spectrophotometer with 45/0 geometry, in other words with the incident light at 45° to the specimen and measurement at right angles to it. The percentage spectral reflectance is expressed relative to a reference surface of pure magnesium oxide, freshly prepared and obtained by gradually depositing small quantities of vaporized magnesium oxide until an increase in reflectance is no longer obtained between successive deposits (at least 0,5 mm thickness).

Calculations from the spectrophotometric curves are made for illuminant C, either from ordinates at 10 nm intervals by multiplication with the appropriate normality coefficients, or using the 30 selected ordinates method for this illuminant. This gives the tristimulus coefficients *X*, *Y* and *Z*.

Primary and secondary colours	Chromaticity co-ordinates		Luminance	Uniform colour space coefficients CIE 1964			Tolerance
	<i>x</i>	<i>y</i>	<i>Y</i>	<i>U*</i>	<i>V*</i>	<i>W*</i>	ΔE_{CIE}
Yellow	0,437	0,494	77,8	19,1	70,9	89,7	2,3
Magenta	0,464	0,232	17,1	112,0	- 12,7	47,4	5,0
Cyan	0,153	0,196	21,9	- 54,5	- 50,9	52,9	3,0
Yellow + magenta	0,613	0,324	16,3	139,8	21,8	46,4	7,3
Yellow + cyan	0,194	0,526	16,5	- 69,1	28,1	46,7	5,3
Magenta + cyan	0,179	0,101	2,8	- 3,6	- 35,4	18,1	8,0

The plate attached to this International Standard, made with reference inks, gives an idea of the prints obtainable.

1) International Commission on Illumination.
 2) Colorimetry document from the CIE (July 1969 — *Official Recommendations of the CIE*).

4.5 Expression of results

The colour difference ΔE_{CIE} is given by the formula

$$\Delta E_{CIE} = [(U_2^* - U_1^*)^2 + (V_2^* - V_1^*)^2 + (W_2^* - W_1^*)^2]^{1/2}$$

In this formula U_2^* , V_2^* and W_2^* are the values given in the table in 4.2 and U_1^* , V_1^* and W_1^* are the corresponding values for the test specimens under examination.

The ΔE_{CIE} colour difference values calculated for primary and secondary colours shall be compared with the tolerances given in the table in 4.2.

A set of inks will be considered to comply with this International Standard, therefore constituting a "standard set", if :

- a) for each of the primary colours, there can be found at least two thicknesses the ΔE_{CIE} values of which are less than the corresponding tolerances, and provided that these thicknesses differ from each other by at least $0,1 \mu\text{m}$ and are both less than $1,1 \mu\text{m}$;
- b) additionally, the ΔE_{CIE} colour difference values of secondary colours are within the corresponding tolerances shown in the table in 4.2.

4.6 Test report

Quoting this International Standard, state the ΔE_{CIE} values for primary colours and for secondary colours. State the overprinting order for the secondary colours together with any unusual features likely to have affected the results.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
ISO 2846:1975
<https://standards.iteh.ai/catalog/standards/sist/98d97d0-4b38-4cbf-b56e-437ca7ab6ee8/iso-2846-1975>

5 OTHER TEST METHOD

This method is designed to test conformity of a specimen with the standard values of colorimetric characteristics without recourse on each occasion to the elaborate scientific equipment and expertise required when using the method specified in 4.4. In case of dispute the method specified in 4.4 is to be used.

5.1 Principle

Colour and colour strength shall be determined by visual comparison of a dry print with a dry print of the master standard ink made on the same paper at the same time under similar conditions of printing and film thickness. The comparison shall be made with film thicknesses between $0,7 \mu\text{m}$ and $1,1 \mu\text{m}$ and prepared as specified in 5.3. The film thickness of a print may vary between 70 % and 110 % of the film thickness of the master standard.

The specimens shall produce a good commercial match to the standard print when examined by a trained observer as specified by the Experts Committee E 1.3.1 of the CIE (illuminant D 6 500).

NOTES

- 1 Prints should not be regarded as "dry" until at least 24 h after printing.
- 2 In practice the error introduced by comparing under north skylight or colour-matching fluorescent tubes as specified by the CIE (see above) is usually negligible.

5.2 Colorimetric characteristics and tolerances

A master standard ink shall be prepared for each primary colour, yellow, magenta and cyan, such that they give colorimetric characteristics within the given tolerances as shown in 4.2.

The test specimens for this work shall be prepared according to the specifications in 4.3, but the film thickness of the reference specimen shall be $1,0 \mu\text{m}$. The measurement of characteristics shall be made in accordance with 4.4.

Such master standard inks must receive approval from a recognized institution competent to carry out this standardization and to certify that such master standards are in conformity with the colorimetric data (see 4.2).

NOTE – The National Research Associations for the printing trades would normally offer such services. P.I.R.A. (U.K.) are able to give information on the availability of such master standards.

5.3 Preparation of reference prints

Reference prints shall be made using a suitable proofing press, the printing plate being weighed before and after printing, and the film thickness applied calculated from the difference in mass, the print area, and a knowledge of the relative density of the ink used. If, for instance, an ink of relative density 1 is used, and if 1 g of ink is transferred per square metre of printing surface, the ink film thickness will be deemed to be $1 \mu\text{m}$. Overprinting shall be done wet on dry.

5.4 Transparency

The transparency of inks conforming to this International Standard shall be not less than those of the respective master standard inks when dry prints, made by the method described in 5.3 on paper printed with a black bar 10 to 15 mm wide, are visually compared. The area printed with each coloured ink shall extend on either side over the black bar a distance at least equal to its width.

5.5 Light fastness

The light fastness of inks conforming to this International Standard shall be not less than that of the respective master standard ink when dry prints on the same paper, under the same conditions of printing and with the same weight and colour strength, are compared by an exposure test as specified in ISO 2835. The exposure shall be continued until a just perceptible change in reference standard 4 of the grey scale is observed.

5.6 Solvent resistance

The solvent resistance of inks conforming to this International Standard shall be not less than that of the respective master standard inks when dry prints, made by the method described in 5.3, on the same paper, under the same conditions of printing are tested in accordance with ISO 2837.

ANNEX

CALCULATION FORMULAE FOR THE DIFFERENT COLORIMETRIC CHARACTERISTICS

A.1 Calculation formulae for the different colorimetric characteristics are :

$$W^* = 25 Y^{1/3} - 17 \quad \text{with } 0 < Y < 100$$

$$U^* = 13 W^* (u - u_0)$$

$$V^* = 13 W^* (v - v_0)$$

where

$$u = \frac{4 X}{X + 15 Y + 3 Z}$$

$$v = \frac{6 Y}{X + 15 Y + 3 Z}$$

A.2 Where illuminant C is adopted as an achromatic colour, the u_0 and v_0 values of this light source are :

$$u_0 = 0,200 9$$

$$v_0 = 0,307 3$$

iTeh STANDARD PREVIEW
(standards.iteh.ai)




ISO 2846:1975

<https://standards.iteh.ai/catalog/standards/sist/988d97d0-4b38-4cbf-b56e-437ca7ab6ee8/iso-2846-1975>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 2846:1975

<https://standards.iteh.ai/catalog/standards/sist/988d97d0-4b38-4cbf-b56e-437ca7ab6ee8/iso-2846-1975>

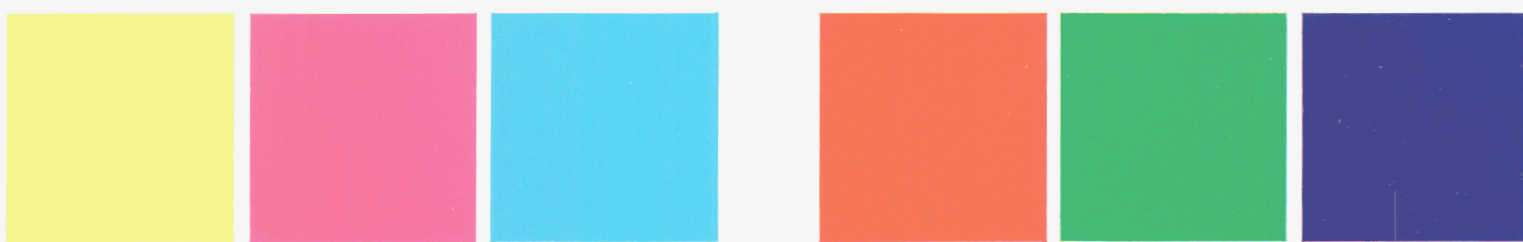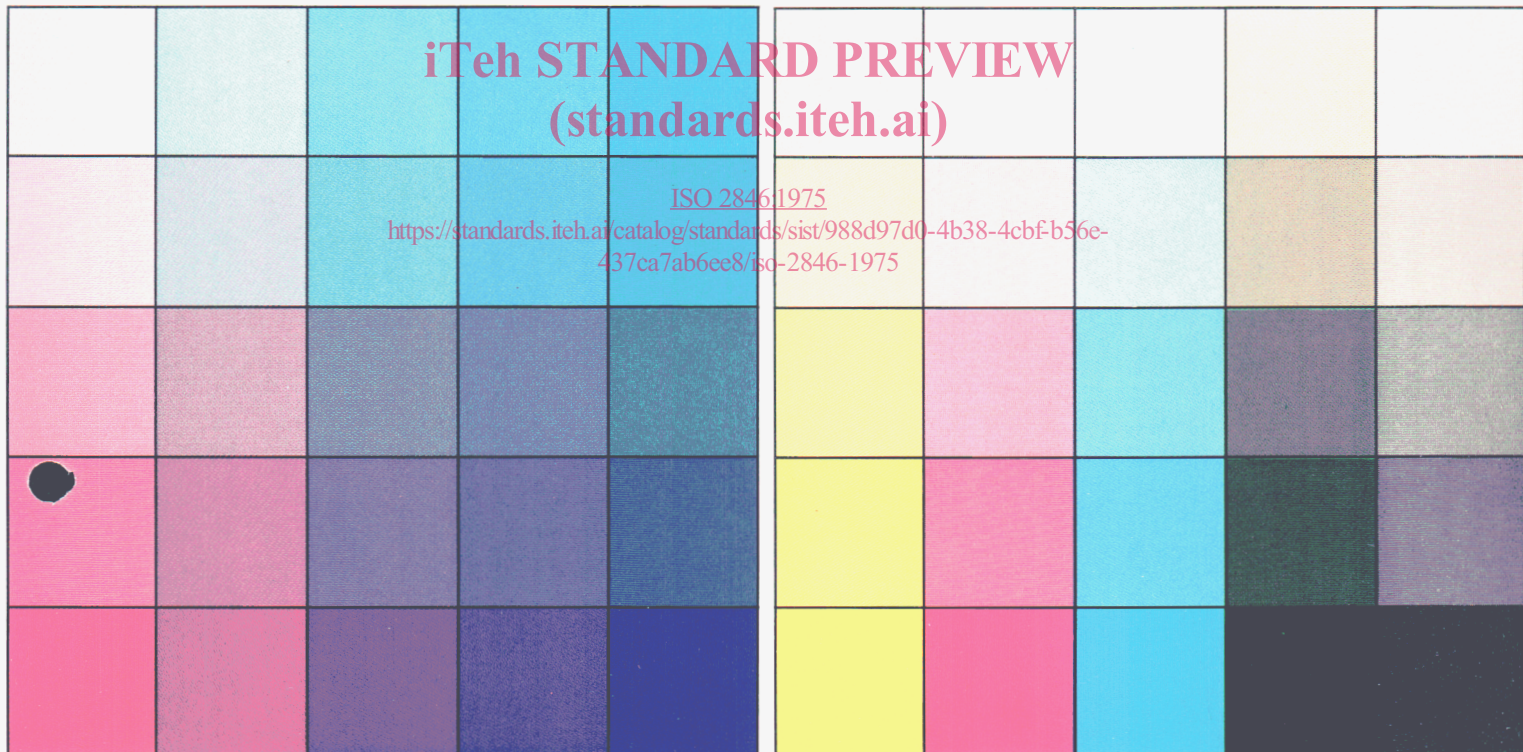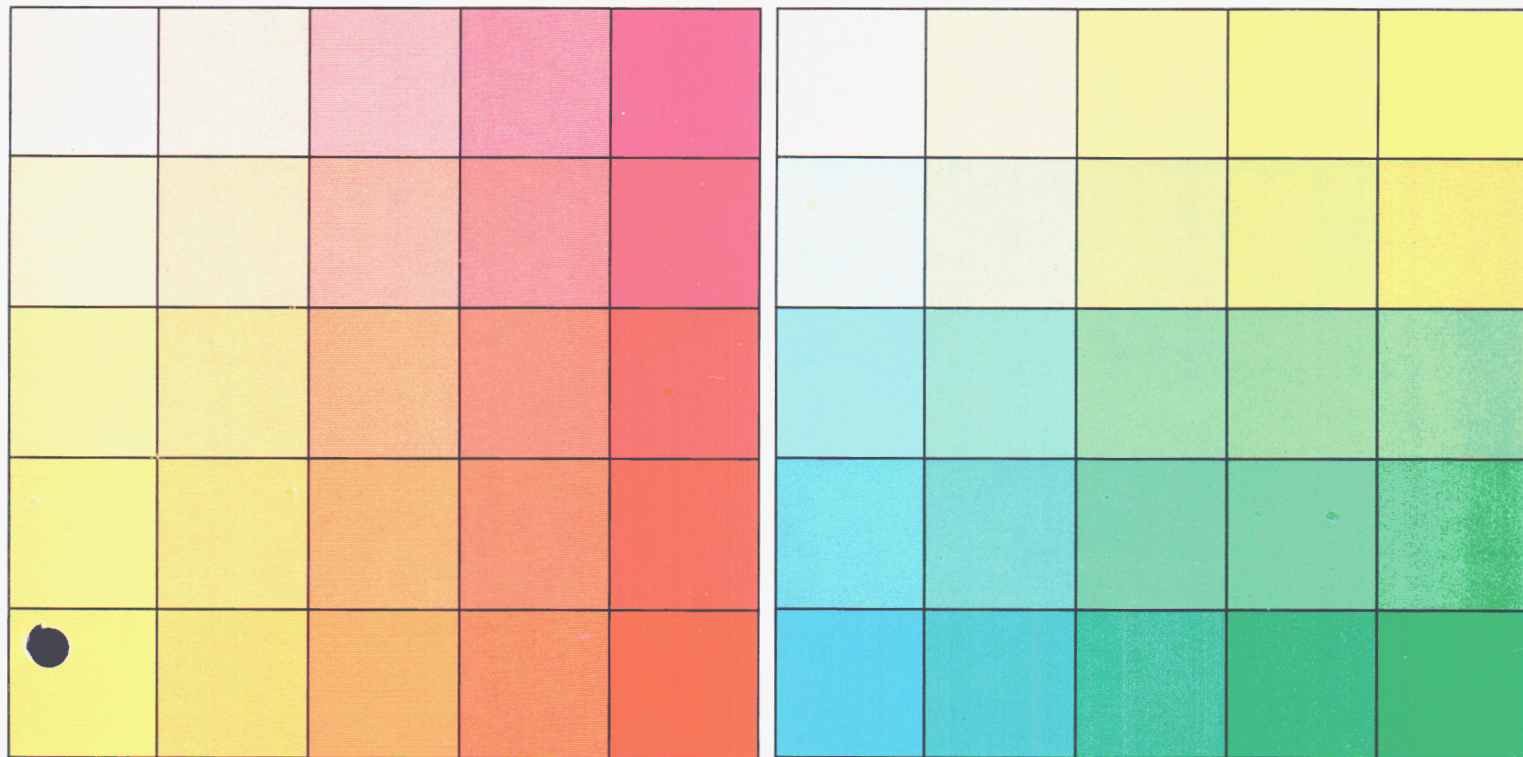

This print is an illustration only and must not be used for reference purposes.