



Designation: ~~A327-91 (Reapproved 2006)~~ Designation: A327/A327M - 11

Standard Test Methods for Impact Testing of Cast Irons¹

This standard is issued under the fixed designation A327/A327M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 These test methods for impact testing cover the details of apparatus, test specimens and procedures for cast iron, including gray iron, white iron, malleable iron, ductile iron, and austempered ductile iron, but not including chilled rolls or rolls with white iron skins.

~~1.2 The values stated in inch-pound units are to be regarded as the standard. A companion standard, A327M, lists values in SI units.~~

1.2 Units—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

A327M Test Methods for Impact Testing of Cast Irons (Metric)

E23 Test Methods for Notched Bar Impact Testing of Metallic Materials

TEST METHOD A—ROUND BAR CHARPY-TYPE IMPACT TEST FOR GRAY AND WHITE IRONS

3. Scope

3.1 The Charpy-type impact test shall be employed for testing gray and white irons.

4. Apparatus

4.1 The single-blow Charpy impact test for gray and white irons shall be carried out in a pendulum-type impact machine with a capacity of at least 150 J [110 ft · lbf] as used for the simple beam test for steel described in Test Methods E23.

5. Test Specimens

5.1 The test specimens shall have a plain cylindrical form, machined or ground to a smooth finish and shall conform to the following dimensions:

	Type A Type A	Type M Type M
Diameter	1.125 ± 0.002 in.	0.787 ± 0.001 in.
Diameter	28.572 ± 0.050 mm	20.00 ± 0.03 mm
	[1.125 ± 0.002 in.]	[0.787 ± 0.001 in.]
Length	8.0 ± 0.5 in.	4.73 ± 0.08 in.
Length	200 ± 13 mm	120 ± 2 mm
	[8.0 ± 0.5 in.]	[4.73 ± 0.08 in.]
Span	6.00 ± 0.03 in.	3.937 ± 0.020 in.

¹ These test methods are under the jurisdiction of ASTM Committee A04 on Iron Castings and are the direct responsibility of Subcommittee A04.21 on Testing. Current edition approved Feb. 1, 2006. Published February 2006. Originally approved in 1950. Last previous edition approved in 1997 as A327-91(1997). DOI: 10.1520/A0327-91R06.

Current edition approved Oct. 15, 2011. Published December 2011. Originally approved in 1950. Last previous edition approved in 2006 as A327-91 (2006). DOI: 10.1520/A0327_A0327M-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

Span

152.0 ± 0.7 mm
[6.00 ± 0.03 in.]

100.0 ± 0.5 mm
[3.937 ± 0.020 in.]

6. Procedure

6.1 Test the bars on the spans indicated in the tabular data of 5.1. In all other respects, the test shall conform to the appropriate requirements of Test Methods E23.

6.2 Make the test at room temperature.

6.3 Characterization of the fracture toughness of any cast iron should be based upon testing at least three specimens.

NOTE 1—Care should be taken to examine broken specimens for indication of anvil interference which will give erroneous results.

7. Report

7.1 The results shall be reported as ____ J [ft · lbf] cast iron Charpy impact with ____ mm [in.] diameter bar.

TEST METHOD B—STANDARD CHARPY-TYPE IMPACT TEST FOR MALLEABLE AND DUCTILE IRONS


8. Scope

8.1 Either the standard notched or unnotched Charpy impact test shall be employed in testing of malleable or ductile irons. Selection of the type bar is dependent upon the specific material to be evaluated as defined in Section 9.

8.2 Both types of charpy bars have been designated to characterize the fracture toughness of irons. The unnotched Charpy bar, when tested, will produce substantially higher energy values than the notch bar type. The unnotched bar is therefore specified for testing irons that have low fracture toughness characteristics.

9. Charpy Test Bar Type

9.1 Unless specified otherwise, the notched bar type specimens in Fig. 1 or Fig. 2 (for pipe type products) shall be employed. Exceptions are defined in 9.2 and 9.3.

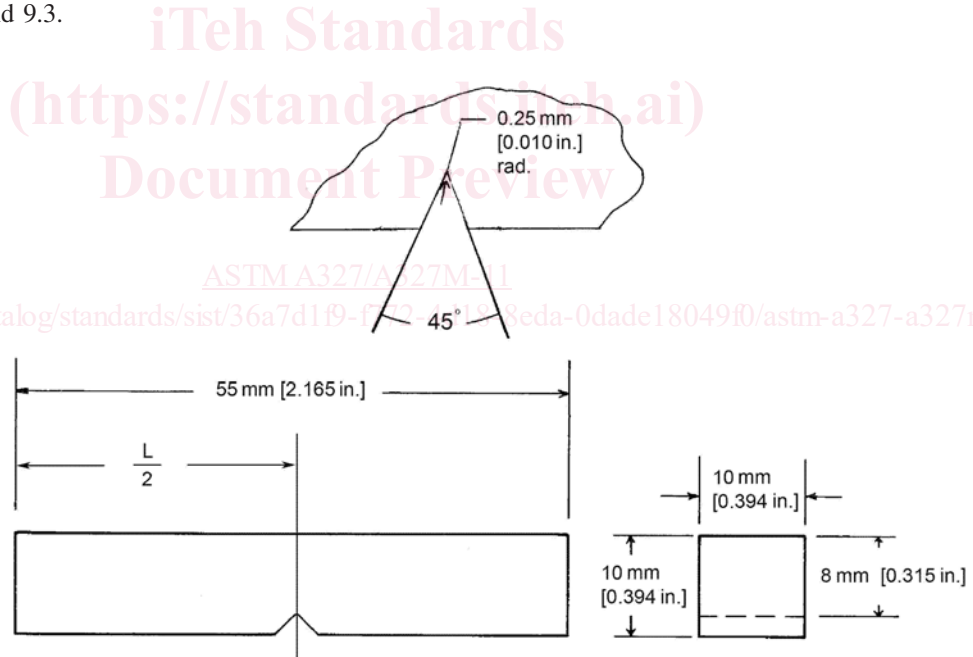

NOTE—Permissible variations shall be as follows:

Adjacent sides shall be at	$90^\circ \pm 10$ min
Cross section dimensions	± 0.03 mm [±0.001 in.]
Length of specimen, <i>L</i>	$\pm 0, -2.5$ mm [±0, -0.100 in.]
Angle of notch	$\pm 1^\circ$
Radius of notch	± 0.03 mm [±0.001 in.]
Dimension to bottom of notch	± 0.03 mm [±0.001 in.]
Distance to notch, $\frac{1}{2}$	± 1 mm [±0.040 in.]

FIG. 1 Standard Vee Notch Charpy Bar Impact Test Specimen