
**Guidelines for the determination
of the long-term strength of
geosynthetics for soil reinforcement**

*Lignes directrices pour la détermination de la résistance à long terme
des géosynthétiques pour le renforcement du sol*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/TS 20432:2022

<https://standards.iteh.ai/catalog/standards/sist/928a3a14-1d58-44dc-a5fe-860ee64c26dd/iso-ts-20432-2022>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/TS 20432:2022

<https://standards.iteh.ai/catalog/standards/sist/928a3a14-1d58-44dc-a5fe-860ee64c26dd/iso-ts-20432-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms, definitions, abbreviated terms and symbols.....	1
3.1 Terms and definitions.....	1
3.2 Abbreviated terms.....	2
3.3 Symbols.....	3
4 Design procedure.....	4
4.1 General.....	4
4.2 Design lifetime.....	4
4.3 Causes of degradation.....	5
4.4 Design temperature.....	5
5 Determination of long-term creep strain.....	5
5.1 General.....	5
5.2 Extrapolation.....	6
5.3 Time-temperature superposition methods.....	6
5.4 Isochronous curves.....	7
5.5 Weathering, chemical and biological effects.....	7
6 Determination of long-term strength.....	8
6.1 Tensile strength.....	8
6.2 Reduction factors.....	8
6.3 Modes of degradation.....	8
7 Creep rupture.....	9
7.1 General.....	9
7.2 Measurement of creep rupture: conventional method.....	10
7.3 Curve fitting (conventional method).....	11
7.4 Curve fitting for time-temperature block shifting of rupture curves.....	13
7.5 Strain shifting and the stepped isothermal method.....	14
7.6 Extrapolation and definition of reduction factor or lifetime.....	15
7.7 Residual strength.....	16
7.8 Reporting of results.....	16
7.9 Procedure in the absence of sufficient data.....	16
8 Installation damage.....	17
8.1 General.....	17
8.2 Data recommended.....	17
8.3 Calculation of reduction factor.....	18
8.4 Procedure in the absence of direct data.....	18
8.4.1 General.....	18
8.4.2 Interpolation from measurements with different soils.....	18
8.4.3 Interpolation between products of the same product line.....	19
8.4.4 Laboratory damage tests.....	19
9 Weathering, chemical and biological degradation.....	19
9.1 General.....	19
9.2 Data recommended for assessment.....	20
9.3 Weathering.....	20
9.4 Chemical degradation.....	21
9.4.1 Causes of chemical degradation.....	21
9.4.2 Evidence from service experience.....	21
9.4.3 Accelerated chemical degradation tests.....	22
9.4.4 Oxidation of polyolefins.....	26
9.4.5 Hydrolysis of polyesters.....	27

9.4.6	Procedure in the absence of sufficient data	29
9.5	Biological degradation.....	29
10	Determination of long-term strength	29
10.1	Factor of safety f_s	29
10.2	Design for residual strength	30
11	Reporting.....	30
	Bibliography.....	31

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/TS 20432:2022

<https://standards.iteh.ai/catalog/standards/sist/928a3a14-1d58-44dc-a5fe-860ee64c26dd/iso-ts-20432-2022>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 221, *Geosynthetics*.

This first edition of ISO/TS 20432 cancels and replaces ISO/TR 20432:2007, which has been technically revised. It also incorporates the Technical Corrigendum ISO/TR 20432:2007/Cor 1:2008.

The main changes are as follows:

- Subclause 7.4 has been modified to further detail and clarify the fitting of linear regression curves to time-temperature block shifted creep-rupture test results.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Guidelines for the determination of the long-term strength of geosynthetics for soil reinforcement

1 Scope

This document provides guidelines for the determination of the long-term strength of geosynthetics for soil reinforcement.

This document describes a method of deriving reduction factors for geosynthetic soil-reinforcement materials to account for creep and creep rupture, installation damage and weathering, and chemical and biological degradation. It is intended to provide a link between the test data and the codes for construction with reinforced soil.

The geosynthetics covered in this document include those whose primary purpose is reinforcement, such as geogrids, woven geotextiles and strips, where the reinforcing component is made from polyester (polyethylene terephthalate), polypropylene, high density polyethylene, polyvinyl alcohol, aramids and polyamides 6 and 6,6. This document does not cover the strength of joints or welds between geosynthetics, nor whether these might be more or less durable than the basic material. Nor does it apply to geomembranes, for example, in landfills. It does not cover the effects of dynamic loading. It does not consider any change in mechanical properties due to soil temperatures below 0 °C, nor the effect of frozen soil. The document does not cover uncertainty in the design of the reinforced soil structure, nor the human or economic consequences of failure.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 10318-1, *Geosynthetics — Part 1: Terms and definitions*

3 Terms, definitions, abbreviated terms and symbols

3.1 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 10318-1 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1.1

long-term strength

load which, if applied continuously to the geosynthetic during the service lifetime, is predicted to lead to rupture at the end of that lifetime

3.1.2

reduction factor

factor (≥ 1) by which the tensile strength is divided to take into account particular service conditions in order to derive the long-term strength

Note 1 to entry: In Europe, the term 'partial factor' is used.

3.1.3

characteristic strength

95 % (two-sided) lower confidence limit for the tensile strength of the geosynthetic, approximately equal to the mean strength less two standard deviations

Note 1 to entry: This should be assured by the manufacturer's own quality assurance scheme or by independent assessment.

3.1.4

block shifting

procedure by which a set of data relating applied load to the logarithm of time to rupture, all measured at a single temperature, are shifted along the log time axis by a single factor to coincide with a second set measured at a second temperature

3.1.5

product line

series of products manufactured using the same polymer, in which the polymer for all products in the line comes from the same source, the manufacturing process is the same for all products in the line, and the only difference is in the product mass per area or number of fibres contained in each reinforcement element

3.2 Abbreviated terms

CEG	carboxyl end group
DSC	differential scanning calorimetry
HALS	hindered amine light stabilizers
HDPE	high density polyethylene
HPOIT	high pressure oxidation induction time
LCL	lower confidence limit
MARV	minimum average roll value
OIT	oxidation induction time
PA	polyamide
PET	polyethylene terephthalate
PP	polypropylene
PTFE	polytetrafluoroethylene
PVA	polyvinyl alcohol
SIM	stepped isothermal method
TTS	time-temperature shifting

3.3 Symbols

A_i	time-temperature shift factor
b_a	gradient of Arrhenius graph
d_{50}	mean granular size of fill
d_{90}	granular size of fill for 90 % pass (10 % retention)
f_s	factor of safety
G, H	parameters used in the validation of temperature shift linearity (see 7.4)
m	gradient of line fitted to creep rupture points (log time against load); inverse of gradient of conventional plot of load against log time.
M_n	number averaged molecular weight
n	number of creep rupture or Arrhenius points
P	applied load
R_1	ratio representing the uncertainty due to extrapolation
R_2	ratio representing the uncertainty in strength derived from Arrhenius testing
$f_{R,CH}$	reduction factor to allow for chemical and biological effects
$f_{R,CR}$	reduction factor to allow for the effect of sustained static load
$f_{R,ID}$	reduction factor to allow for the effect of mechanical damage
$f_{R,W}$	reduction factor to allow for weathering
S_{sq}	sum of squares of difference of log (time to rupture) and straight line fit
S_{xx}, S_{xy}, S_{yy}	sums of squares as defined in derivation of regression lines in 9.4.3
σ_0	standard deviation used in calculation of LCL
t	time, expressed in hours
t_{90}	time to 90 % retained strength
t_D	design life
t_{deg}	degradation time during oxidation
t_{ind}	induction time during oxidation
t_{LCL}	LCL of time to a defined retained strength at the service temperature
t_{max}	longest observed time to creep rupture, expressed in hours
t_{n-2}	Student's t for $n - 2$ degrees of freedom and a stated probability
t_R	time to rupture, expressed in hours
t_s	time to a defined retained strength at the service temperature

T	load per width
T_B	batch tensile strength (per width)
T_{char}	characteristic strength (per width) (see 6.1)
T_x	unfactored long-term strength (see 9.4.3)
T_D	long-term strength per width (including factor of safety)
T_{DR}	residual strength
θ_j	temperature of accelerated creep test
θ_k	absolute temperature
T_{LCL}	LCL of T_{char} due to chemical degradation
θ_s	service temperature
x	abscissa: on a creep rupture graph the logarithm of time, in hours
\bar{x}	mean value of x
x_i	abscissa of an individual creep rupture point
x_p	predicted time to rupture
y	ordinate: on a creep rupture graph, applied load expressed as a percentage of tensile strength, or a function of applied load
y_0	value of y at 1 h ($\lg t = 0$)
\bar{y}	mean value of y
y_i	ordinate of an individual creep rupture point
y_0	value of y at time 0, derived from the line fitted to creep rupture points

4 Design procedure

4.1 General

The design of reinforced soil structures generally requires consideration of the following two issues:

- a) the maximum strain in the reinforcement during the design lifetime;
- b) the minimum strength of the reinforcement that could lead to rupture during the design lifetime.

In civil engineering design, these two issues are referred to as the serviceability and ultimate limit state respectively. Both factors depend on time and can be degraded by the environment to which the reinforcement is exposed.

4.2 Design lifetime

A design lifetime, t_D , is defined for the reinforced soil structure. For civil engineering structures this is typically 50 years to 100 years. These durations are too long for direct measurements to be made in advance of construction. Reduction factors have therefore to be determined by extrapolation of short-term data aided, where necessary, by tests at elevated temperatures to accelerate the processes of creep or degradation.

4.3 Causes of degradation

Strain and strength may be changed due to the effects of the following:

- mechanical damage caused during installation;
- sustained static (or dynamic) load;
- elevated temperature;
- weathering while the material is exposed to light;
- chemical effects of natural or contaminated soil.

4.4 Design temperature

The design temperature should have been defined for the application in hand. In the absence of a defined temperature or of site specific in-soil temperature data, the design temperature should be taken as the temperature which is halfway between the average yearly air temperature and the normal daily air temperature for the hottest month at the site. If this information is not available, 20 °C should be used as the default value.

Many geosynthetic tests are performed at a standard temperature of (20 ± 2) °C. If the design temperature differs, appropriate adjustments should be made to the measured properties.


This document does not cover the effects of temperatures below 0 °C (see [Clause 1](#)).

5 Determination of long-term creep strain

5.1 General

The design specification may set a limit on the total strain over the service lifetime of the geosynthetic, or on the strain generated between the end of construction and the service lifetime. In the second case, the time at “end of construction” should be defined, as shown in [Figure 1](#). When plotted against $\lg t$, even a one-year construction period should have negligible influence on the creep strain curve beyond 10 years.

Levels of creep strain encountered in the primary creep regime (creep rate decreasing with time) are thought not to adversely affect strength properties of geosynthetic reinforcement materials.

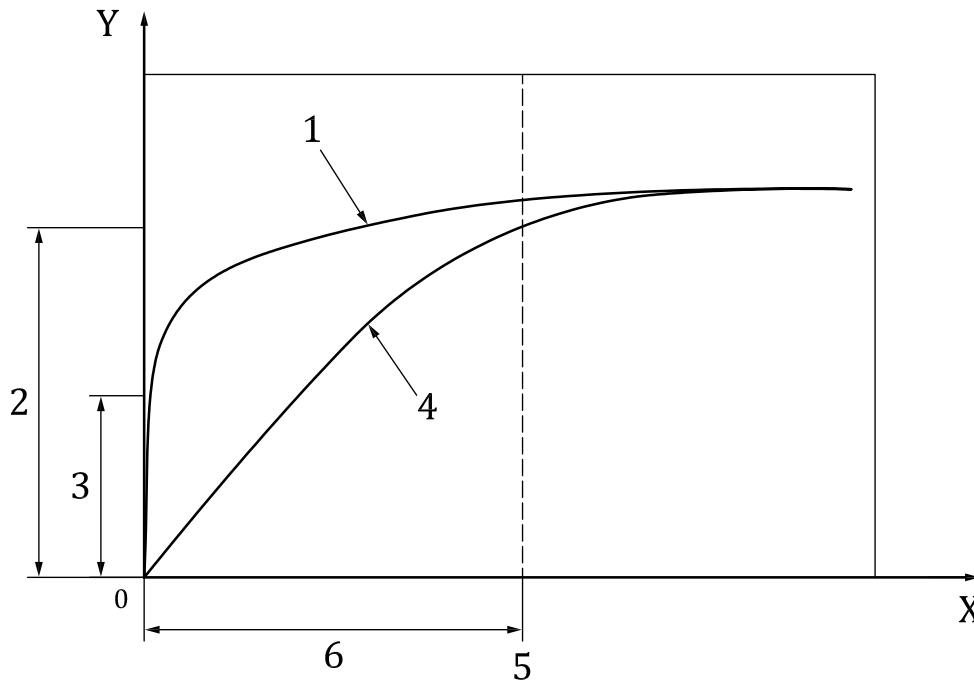

Key

- | | | | |
|---|--------------------------|---|--|
| X | time | 3 | load ramp period in creep test |
| Y | strain | 4 | loading and creep of reinforcement in wall |
| 1 | laboratory creep test | 5 | new time = 0 for post construction creep |
| 2 | load ramp period on wall | 6 | wall construction time |

Figure 1 — Conceptual illustration for comparing the creep measured in walls to laboratory creep data

<https://standards.iteh.ai/catalog/standards/sist/928a3a14-1d58-44dc-a5fe-860ee64c26dd/iso-ts-20432-2022>

5.2 Extrapolation

Creep strain should be measured according to ISO 13431 and plotted as strain against the $\lg t$. It may then be extrapolated to the design lifetime. Extrapolation may be by graphical or curve-fitting procedures, in which the formulae applied should be as simple as is necessary to provide a reasonable fit to the data, for example, power laws. The use of polynomial functions is discouraged since they can lead to unrealistic values when extrapolated.

5.3 Time-temperature superposition methods

Time-temperature superposition methods may be used to assist with extending the creep curves. Creep curves are measured under the same load at different temperatures, with intervals generally not exceeding 10 °C, and plotted on the same diagram as strain against $\lg t$. The lowest temperature is taken as the reference temperature. The creep curves at the higher temperatures are then shifted along the time axis until they form one continuous “master” curve, i.e. the predicted long-term creep curve for the reference temperature. The shift factors, i.e. the amounts (in units equivalent to $\lg t$) by which each curve is shifted, should be plotted against temperature where they should form a straight line or smooth curve. The cautions given in 7.6 should be noted.

Experience has shown the strains on loading are variable. Since the increase in strain with time is small, this variability can lead to wide variability in time-temperature shifting (TTS). The stepped isothermal method (SIM) described in 7.5 avoids this problem by using a single specimen, increasing the temperature in steps, and then shifting the sections of creep curve measured at the various temperatures to form one continuous master curve.

If a more accurate measure of initial strain is required, five replicates are recommended at each load. Some of these can be of short duration (e.g. 1 000 s). At a series of loads, fewer replicates at each load will suffice if the data are pooled using regression techniques. One approach is to use regression analysis to develop an isochronous load versus strain curve at 0,1 h. The creep curve should then be shifted vertically to pass through the mean strain measured after 0,1 h.

If the lowest test temperature is below the design temperature, the shift factor corresponding to the design temperature should be read off the plot of shift factor against temperature. The time-scale of the master curve should then be adjusted by this factor.

5.4 Isochronous curves

From the creep curve corresponding to each load, read off the strains for specified durations, typically 1 h, 10 h, 100 h, etc., and including the design lifetime. Set up a diagram of load against strain. For each duration, plot the points of load against strain for the corresponding durations (see Figure 2). These are called isochronous curves. Where a maximum strain is permitted over the design lifetime, or between the end of construction (e.g. 100 h) and the design lifetime, it is possible to read off the corresponding loads from these curves. Where the strain is measured from zero, note that in geosynthetics strains are measured from a set preload (defined in ISO 10319 and ISO 13431 as 1 % of the tensile strength) and that some woven and particularly non-woven materials may exhibit considerable irreversible strains below this initial loading. See Reference [2] for additional details on creep strain characterization.

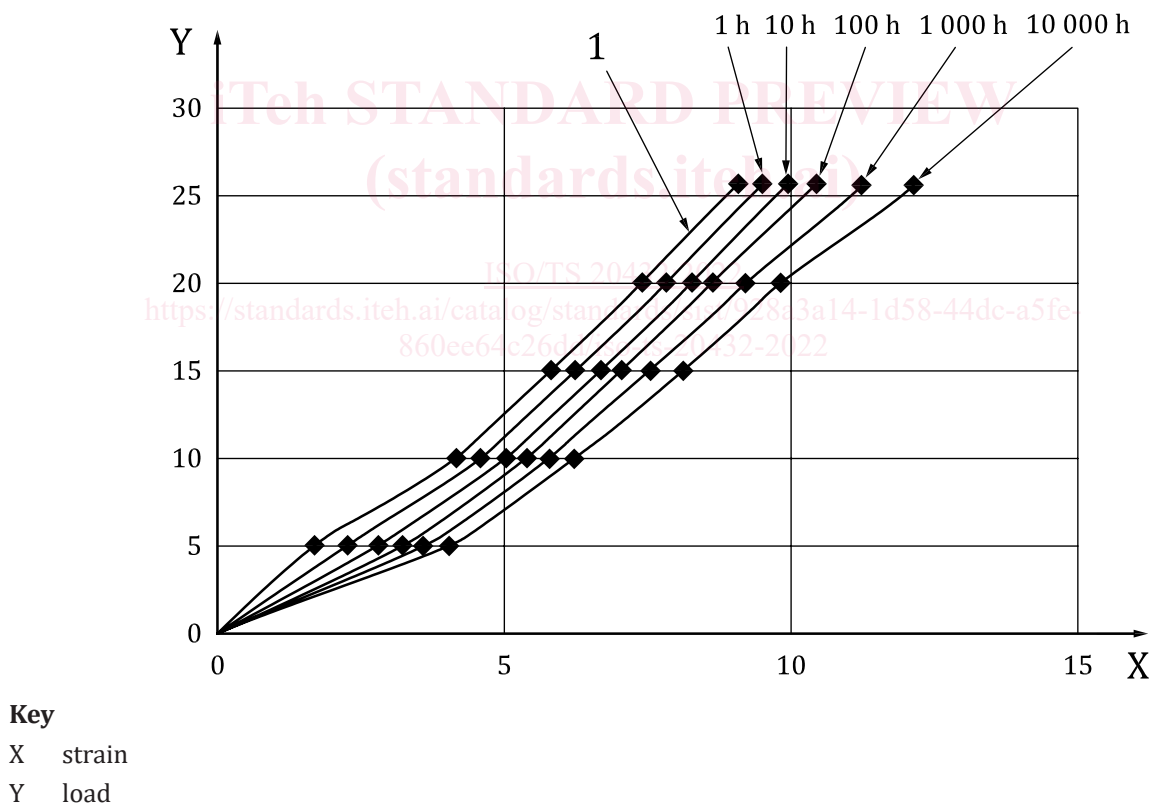


Figure 2 — Isochronous diagram

5.5 Weathering, chemical and biological effects

Creep strain is generally insensitive to limited weathering, chemical and biological effects. In addition, creep strains are in general not affected by installation damage, unless the damage is severe, or unless the load level applied is very near the creep limit of the undamaged material. In most cases, the load level applied is well below the creep limit of the material. See Reference [3] for additional details on this issue. Thus, no further adjustment is generally required beyond the effect of temperature.