

Designation: B213 - 11

# StandardTest Methods for Flow Rate of Metal Powders Using the Hall Flowmeter Funnel<sup>1</sup>

This standard is issued under the fixed designation B213; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\varepsilon$ ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

### 1. Scope\*

- 1.1 This test method covers the determination of a flow rate, by the use of the Hall Flowmeter funnel of metal powders and powder mixtures. It is suitable only for those powders that will flow unaided through the Hall Flowmeter funnel.
- 1.2 With the exception of the values for density and the mass used to determine density, for which the use of the gram per cubic centimeter (g/cm³) and gram (g) units is the long-standing industry practice, the values in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only, and are not considered standard.
- 1.3 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

## 2. Referenced Documents

2.1 ASTM Standards:<sup>2</sup>

**B215** Practices for Sampling Metal Powders

**B243** Terminology of Powder Metallurgy

B855 Test Method for Volumetric Flow Rate of Metal Powders Using the Arnold Meter and Hall Flowmeter Funnel

B964 Test Methods for Flow Rate of Metal Powders Using the Carney Funnel

## 3. Terminology

- 3.1 *Definitions* —Definitions of powder metallurgy terms can be found in Terminology B243.
  - 3.2 Definitions of Terms Specific to This Standard:
- 3.2.1 Hall flow rate  $(FR_H)$ , n—the time required for a metal powder sample of specified mass to flow through the orifice in a Hall Flowmeter funnel according to a specified procedure.

# 4. Summary of Test Method

4.1 A weighed mass (50.0 g) of metal powder is timed as it flows through the calibrated orifice of a Hall Flowmeter funnel.


## 5. Significance and Use

- 5.1 The rate and uniformity of die cavity filling are related to flow properties, which thus influence production rates and uniformity of compacted parts.
- 5.2 The ability of a powder to flow is a function of interparticle friction. As interparticle friction increases, flow is slowed. Fine powders may not flow. Some powders, often fine powders and lubricated powder mixtures, may not flow through the Hall Flowmeter funnel. Nevertheless, if a larger orifice is provided, such as in the Carney Flowmeter funnel of Test Method B964, a meaningful flow rate may be determined, providing specific information for certain applications.
- 5.3 Test Method B213, using the Hall Flowmeter funnel, is the preferred method for determining the flowability of metal powders and powder mixtures. The Carney Flowmeter funnel of Method B964 should only be used when powder will not flow through the Hall Flowmeter funnel.
- 5.4 Humidity and moisture content influence flow rate. Wet or moist powders may not flow.
- 5.5 These test methods are based on flow of a specified mass of powder. If flow of a specific volume of powder is preferred, Test Method B855 may be used for powders that flow readily through the Hall Flowmeter funnel.
- 5.6 This test method may be part of the purchase agreement between powder manufacturers and powder metallurgy (PM)

<sup>&</sup>lt;sup>1</sup> This test method is under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Productsand is the direct responsibility of B09.02 on Base Metal Powders.

Current edition approved Nov. 15, 2011. Published December 2011. Originally approved in 1946. Last previous edition approved in 2003 as B213 – 03. DOI: 10.1520/B0213-11.

<sup>&</sup>lt;sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

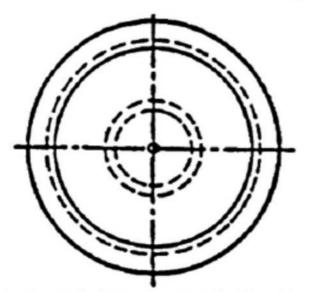

16 microinch (0.4 x 10-6 m) finish or better

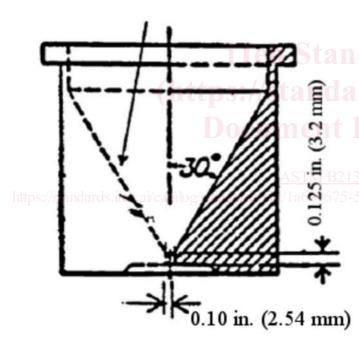


FIG. 1 Hall Flowmeter Funnel

part producers, or it can be an internal quality control test by either the producer or the end user.

## 6. Apparatus

6.1 *Powder Flowmeter Funnel*<sup>3</sup>—A flowmeter funnel (Fig. 1) having a calibrated orifice of 0.10 in. (2.54 mm) in diameter.

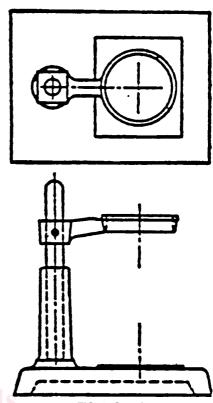


FIG. 2 Stand

- 6.2 The dimensions shown for the flowmeter funnel, including the orifice, are not to be considered controlling factors. Calibration with emery, as specified in Section 9, determines the working flow rate of the funnel.
- 6.3 Stand<sup>3</sup>—A stand (Fig. 2) to support the powder flow-meter funnel.
- 6.4 *Workbench*—A level, vibration free table or workbench to support the powder flowmeter stand.
- 6.5 *Timing Device*—A stopwatch or other suitable device capable of measuring to the nearest 0.1 s.
- 6.6 *Chinese Emery*<sup>3</sup>—An emery powder used to calibrate the flowmeter funnel.
- 6.7 *Balance*—A balance readable to 0.01 g suitable for weighing at least 50.0 g to the nearest 0.1 g.

## 7. Sampling

- 7.1 A test sample of powder sufficient to run the desired number of flow tests shall be obtained in accordance with Practice B215.
- 7.2 Individual test portions, each of approximately the required mass, shall be obtained from the test sample in accordance with Practice B215.

## 8. Preparation of Apparatus

- 8.1 Clean the funnel with clean dry toweling paper.
- 8.2 Clean the funnel orifice with a clean dry pipe cleaner.

 $<sup>^{\</sup>rm 3}$  The flow meter funnel, stand, and Chinese emery are available from Acu Powder International, LLC.