
**Textiles — Smart textiles — Test
method for sheet resistance of
conductive textiles using non-contact
type**

*Textiles — Textiles intelligents — Méthode d'essai de mesurage de la
résistance superficielle de textiles conducteurs au moyen d'un capteur
de type sans contact*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 24584:2022

<https://standards.iteh.ai/catalog/standards/sist/6373d694-f435-4e46-907a-d6d2aaf4e661/iso-24584-2022>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 24584:2022
<https://standards.iteh.ai/catalog/standards/sist/6373d694-f435-4e46-907a-d6d2aaf4e661/iso-24584-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	4
5 Apparatus	4
5.1 Apparatus for eddy current measurement.....	4
5.1.1 Eddy current instrument, which is part of an eddy current testing system.....	4
5.1.2 Eddy current sensor probe.....	4
5.1.3 Device or external software which calculates the sheet resistance from eddy current signal based on the underlying calibration.....	4
5.2 Measurement stage.....	4
5.3 Pressure plate.....	5
5.4 Stopwatch.....	6
6 Sampling and preparation of test specimen	6
7 Calibration	6
8 Test procedure	6
8.1 Measurement points.....	6
8.2 Method A: Standard procedure.....	7
8.3 Method B: Deviating procedure applying pressure to the test specimen using a pressure plate.....	8
9 Test report	8
Annex A (informative) Example of a pattern for cutting test specimens from a laboratory sample	9
Annex B (informative) Example of test results and procedure	10
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 38, *Textiles*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 248, *Textiles and textile products*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Conductive fabrics are an important component in the design and manufacture of smart textiles. On the one hand, it is possible to use the non-destructive method for measuring the sheet resistance of fabrics of different construction and thickness described in this document for quality control of the fabrics. On the other hand, it is also suitable for quantitatively determining the sheet resistance of the conductive fabric, which is needed for the design and manufacture of electronic (smart) textile products.

The eddy current method is a method applied for the characterization of electrical properties such as sheet resistance, conductivity and local magnetization. Typically, an alternating electromagnetic field (primary field) is inducing eddy currents in the flat electrically conductive sample of interest. According to Lenz' law, the induced eddy currents generate a secondary electromagnetic field which is opposed to the primary field. The interaction of the primary field with the secondary field is a function of the sheet resistance of the present conductive layers. This principle is applied to electrically characterize layers without establishing an electrical contact. Generally, there are variants of measurements in physical contact and without physical contact of an electrically isolated eddy current sensor. The non-contacting mode allows investigating specimen without any mechanical impact as a potential source of damage or artefacts. It is possible to implement the primary field induction and the resulting field measurement at different positions. The industry is using various probe types and sizes for eddy current testing (see ISO 12718 and ISO 15549).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 24584:2022

<https://standards.iteh.ai/catalog/standards/sist/6373d694-f435-4e46-907a-d6d2aaf4e661/iso-24584-2022>

Textiles — Smart textiles — Test method for sheet resistance of conductive textiles using non-contact type

1 Scope

This document describes the measurement for the determination of the sheet resistance of conductive textile structures or conductive structures by using eddy current technology in reflection mode setup/arrangement.

It is applicable to conductive textile structures or conductive structures intended for application in/to textiles in the form of sheets (woven fabric, knitted fabric, nonwoven, coated fabric) where the area is formed by intersecting surfaces having conductive textile material.

It is also applicable to multilayer structures containing both insulating and conductive layers.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology database for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

textile material

material made of textile fibres and intended to be used, as such or in conjunction with other textile or nontextile items, for the production of textile products

Note 1 to entry: textile material refers to linear textile materials (textile yarns) as well as flat textile material (e.g. knitted, woven and nonwoven fabric).

3.2

conductive textile material

textile material (3.1) intended to carry electric current

3.3

conductive fabric

fabric having electrical conductivity

Note 1 to entry: Possible applications for conductive fabrics are as signal line, power transmission line, or electromagnetic shield.

Note 2 to entry: Fabrics are for example of woven, knitted or nonwoven construction.

Note 3 to entry: Highly conductive materials like silver or copper have values for the specific resistance around $10^{-8} \Omega \text{ m}$. Conductive fabrics do not reach these low resistance values yet.

[SOURCE: IEC 63203-101-1:2021, 3.18, modified — The examples have been moved to Note 2 to entry, Note 3 to entry has been added.]

3.4

woven fabric

fabric produced by interlacing (by weaving on a loom or a weaving machine) a set of warp threads and a set of weft threads normally at right angles to each other

[SOURCE: ISO 3572:1976, 2.1]

3.5

conductive woven fabric

woven fabric (3.4) which has contact points at interlacing with conductive material over its entire surface

Note 1 to entry: See [Figure 1](#).

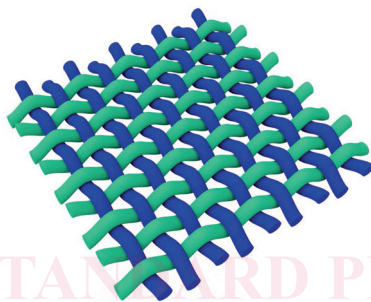


Figure 1 — Conductive woven fabric

3.6

knitted fabric

generic name applied to textile fabric in which at least one system of threads is formed into knitted loops and the knitted loops are intermeshed into stitches

[SOURCE: ISO 8388:1998, 3.0.1]

3.7

conductive knitted fabric

knitted fabric which has contact points at interlacing with conductive material over its entire surface

Note 1 to entry: See [Figure 2](#).

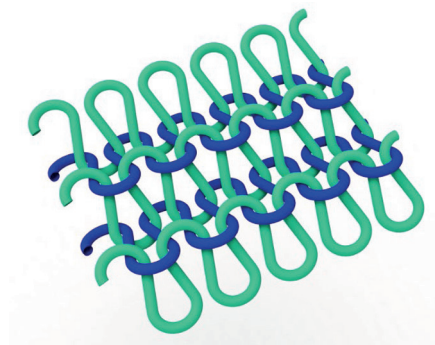


Figure 2 — Conductive knitted fabric

3.8**nonwoven**

engineered fibrous assembly, primarily planar, which has been given a designed level of structural integrity by physical and/or chemical means, excluding weaving, knitting or papermaking

[SOURCE: ISO 9092:2019, 3.1.1]

3.9**conductive nonwoven**

nonwoven (3.8) fabric which has contact points at interlacing with conductive material over its entire surface

Note 1 to entry: See [Figure 3](#).

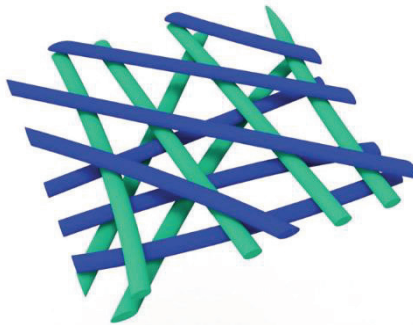


Figure 3 — Conductive nonwoven

3.10**fabric coating**

coating applied to a fabric by impregnation or as a toplayer, consisting of substances such as lacquer, varnish, rubber, or polymers

3.11**conductive fabric coating**

fabric coated with conductive material such as liquid or paste

3.12**sheet resistance**

electrical resistance of a thin film material measured across the opposite ends of a square area

Note 1 to entry: The unit of sheet resistance is expressed in ohms (Ω). However, for the purpose of this procedure, it represents the unit of ohms per square (Ω/\square) with the thickness of the film.

[SOURCE: IEC 62899-202-3:2019, 3.1]

3.13**eddy current**

electric current induced in a conductive material by a varying magnetic field

[SOURCE: ISO 12718:2019, 3.1.12, modified to use the term in singular]

3.14**sensor probe**

eddy current (3.13) transducer physical device containing excitation elements and receiving elements

[SOURCE: ISO 12718:2019, 3.3.40, adapted from the definition of 'probe' with 'sensor' added to the term]

3.15**non-contact type**

measurement method without contact between *sensor probe* (3.14) and sample

3.16

insulating material

insulant

material used to prevent electric conduction between conductive elements

Note 1 to entry: In the field of electromagnetism the term “insulant” is also used as a synonym for “insulating medium”.

[SOURCE: IEC 60050-151:2001/AMD3:2019]

3.17

sensor gap

distance between test specimen and *sensor probe* (3.14)

3.18

calibration

correlation in-between *eddy current* (3.13) signal and physical parameter (sheet resistance)

4 Principle

The purpose of this test method is to measure the sheet resistance of a conductive fabric, such as conductive woven fabric, conductive knitted fabric, conductive nonwoven, conductive fabric coating. During the measurement, the test specimen is placed flat on the measurement stage, i.e. without wrinkles and not being under tension. If it is not possible to measure the sheet resistances of a fabric in the standard procedure, for example due to it having a rough surface, a high thickness or it being bulky, a pre-defined pressure shall be applied to the test specimen during the measurement using a pressure plate. The sheet resistance is determined through an eddy current measurement using a non-contact sensor probe.

5 Apparatus

5.1 Apparatus for eddy current measurement

The following apparatus shall be used.

5.1.1 Eddy current instrument, which is part of an eddy current testing system.

NOTE Generally, this consists of a generator, an amplifier, a demodulator and a display unit.

5.1.2 Eddy current sensor probe.

5.1.3 Device or external software which calculates the sheet resistance from eddy current signal based on the underlying calibration.


5.2 Measurement stage

The surface of the sensor probe shall not touch the specimen directly and a constant distance shall be maintained.

NOTE The eddy current produced by the specimen varies with the distance between the sensor probe and the test specimen.

The sensor probe and the surface of the measurement stage shall be installed perpendicular to each other. After calibration the sensor gap shall remain fixed. The measurement stage shall be made of insulating material and shall have a thickness of 50 mm to prevent affecting the test result.

[Figure 4](#) below shows the two possible test equipment configurations, as [Figure 4 a\)](#) and [Figure 4 b\)](#).

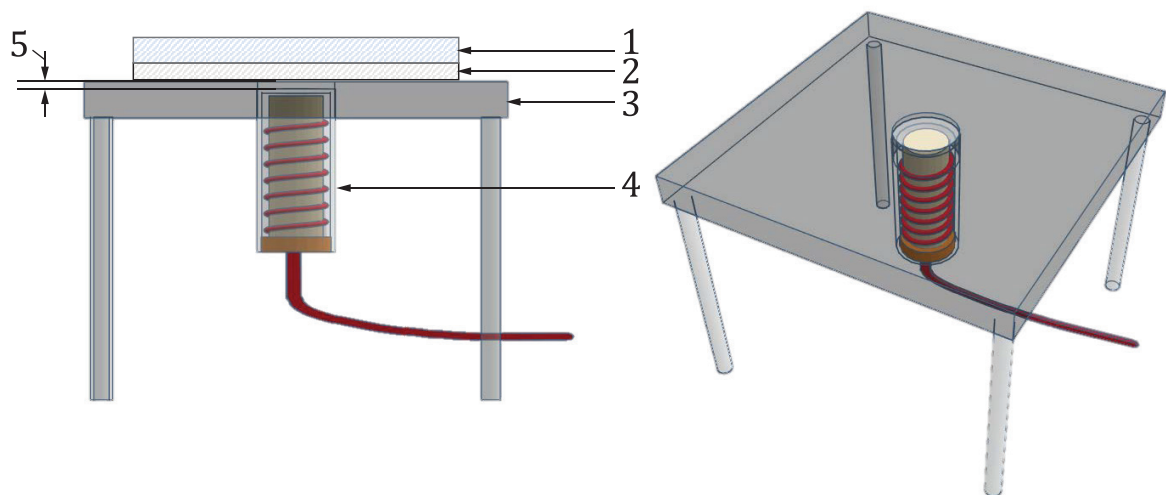

a) Type 1, portable sensor probe, fixed in the measurement stage



b) Type 2, fixed sensor probe (permanently integrated into the measurement stage)

Key

- 1 pressure plate
- 2 test specimen
- 3 measurement stage
- 4 sensor probe
- 5 sensor gap

Figure 4 — Test equipment configuration

5.3 Pressure plate

The pressure plate shall be made of insulating material and shall be placed over the test specimen as to apply an even pressure over the complete surface area of the test specimen such that the fabric is flattened but the structure is not distorted from its normal configuration.

It is recommended to have a range of pressure plate masses or a means of applying a variable pressure, dependent on the type of fabric under test.