INTERNATIONAL STANDARD

ISO 15792-1

Second edition 2020-08

Welding consumables — Test methods —

Part 1:

Preparation of all-weld metal test pieces and specimens in steel, nickel and nickel alloys

iTeh STANDARD PREVIEW

Produits consommables pour le soudage — Méthodes d'essai —

Partie 1: Préparation des pièces d'essai et des éprouvettes de métal fondu hors dilution pour le soudage de l'acier, du nickel et des alliages

https://standards.iteh.decnickelstandards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15792-1:2020 https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland

Con	ntents	Page
Forev	word	iv
Intro	oduction	v
1	Scope	1
2	Normative references	
3	Terms and definitions	
4	General requirements	1
5	Test plate material	1
6	Preparation of test piece	2
7	Welding conditions	2
8	Heat treatment	3
9	Position of test specimens and test specimen dimensions	3
Bibli	ography	4

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15792-1:2020 https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html. (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 44, Welding and allied processes, Subcommittee SC 3, Welding consumables, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 121, Welding and allied processes, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Official interpretations of ISO/TC 44 documents, where they exist, are available from this page: https://committee.iso.org/sites/tc44/home/interpretation.html.

This second edition cancels and replaces the first edition (ISO 15792-1:2000), which has been technically revised. It also incorporates the Amendment ISO 15792-1:2000/Amd 1:2011. The main changes compared to the previous edition are as follows:

- the title and scope of this document have been changed;
- Clause 10 and Clause 11 have been deleted consequently;
- in <u>Clause 1</u>, pass has been changed to run for consistency with other standards;
- tolerances have been added to Table 1.

Introduction

It should be noted that the mechanical properties of all-weld metal test specimens used to classify welding consumables can vary from those obtained in production joints because of differences in welding procedure such as electrode diameter, width of weave, welding position and material composition.

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15792-1:2020 https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15792-1:2020 https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020

Welding consumables — Test methods —

Part 1:

Preparation of all-weld metal test pieces and specimens in steel, nickel and nickel alloys

1 Scope

This document specifies the preparation of test pieces and specimens for all-weld metal tests in steel, nickel and nickel alloys.

The test pieces and specimens are used to determine the mechanical properties of all-weld metal where required by consumable classification standards or for other purposes, in arc welding of steel, nickel and nickel alloys.

This document is not applicable to single- or two-run welding or fillet welding. For these cases, ISO 15792-2 and ISO 15792-3 apply.

2 Normative references TANDARD PREVIEW

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-ISO 5178, Destructive tests on welds in metallic materials (2000) Longitudinal tensile test on weld metal in fusion welded joints

ISO 9016:2012, Destructive tests on welds in metallic materials — Impact tests — Test specimen location, notch orientation and examination

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at https://www.iso.org/obp
- IEC Electropedia: available at http://www.electropedia.org/

4 General requirements

Welding consumables to be tested shall be representative of the manufacturer's products to be classified or tested. Test pieces shall be prepared as described below.

5 Test plate material

The material to be used for the test piece shall be compatible with the weld metal provided by the welding consumable tested. Alternatively, the groove edges and the backing strip shall be built up with at least two layers using the welding consumable being tested.

Preparation of test piece

The test piece shall be prepared in the form of a single V-groove on a backing strip. The backing strip shall be tack welded to the test piece on the reverse side (see Figure 1 and Table 1).

The plates of the test piece shall be pre-set or restrained in such a way that a sufficiently flat test piece is produced for extraction of specimens. The welded test piece shall not be straightened.

The type of test piece defines the dimensions, see <u>Table 1</u>. The type selected for classification purpose is specified in the relevant consumable standard.

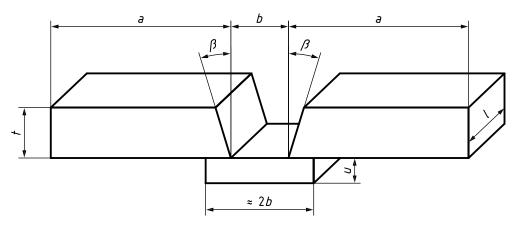


Figure 1 — Test piece dimensions VIF.W

(standards.iteh.ai)
Table 1 — Type and dimensions of the test piece

https://gtandards.itah.ai/aats

<u>ISO 15792-1:2020</u>	Dimensions in millimetres
alackstandards kist/500ah04f a76d_45f	2 2202
and social relations in the second se	2-a07a-

Туре	t			96fb1bd6	672/iso-15	792-1-2020	degree	1
1.0	12		≥80	10				
1.1	12		≥90	12				
1.2	16		≥100	14				
1.3	20	+1.0	≥125	16	+1.0	>6	10 +2.5	>150
1.4	25	+1,0 -1,0	≥125	20	+1,0 -0	≥6	10 +2,5	≥150
1.5	30		≥200	25				
1.6	20		≥150	20				
1.7	25		≥150	24				

Welding conditions

The test piece shall be welded in the flat position except for consumables which are designed exclusively for welding in another position, in which case that position shall be used for welding. Welding shall be started after applying any preheating requirements given in the consumable classification standard being used. The interpass temperature shall also be in accordance with the consumable classification standard.

The preheat and interpass temperatures shall be measured using temperature indicator crayons, surface thermometers or thermocouples, for example in accordance with ISO 13916.

The welding conditions used, such as current, voltage, travel speed, weld run sequence, weld bead size, shall be in accordance with the limits specified in the consumable classification standard being used.

8 Heat treatment

All heat treatments required for the weld metal, except hydrogen removal treatment, shall be carried out on the test piece, or on sections thereof with a machining allowance.

Heat treatments shall be as specified in the welding consumable classification standard being used.

Hydrogen removal treatment may be carried out on the test piece for tensile testing before or after final machining. The test piece may be held at a temperature not exceeding 250 °C for up to 16 h.

9 Position of test specimens and test specimen dimensions

<u>Figures 2</u> and <u>3</u> respectively show the position of the tensile test specimen and of the notched impact specimens. The test pieces shall be divided by cutting (machining) or by thermal cutting. In the case of thermal cutting, machining allowances of 10 mm at least on either side shall be provided for the subsequent machining of the specimens.

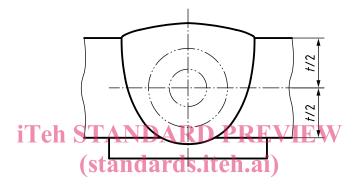


Figure 2 — Position of the tensile specimen in the test piece

https://standards.iteh.ai/catalog/standards/sist/500eb04f-e76d-45f2-ae9a-b96fb1bd6e72/iso-15792-1-2020




Figure 3 — Position of the notched bar impact specimen in the test pieces

The tensile test specimens shall be in accordance with ISO 5178. Apart from type 1.0 and 1.1 test pieces, for which the diameter shall be 8 mm, the specimens shall have a diameter of 10 mm in the gauge length.

The impact specimens shall be in accordance with the designation VWT 0/b in ISO 9016:2012. The position of the impact specimen shall be at the midline of the plate thickness.

The size of impact specimens shall be $10 \text{ mm} \times 10 \text{ mm}$.