
Two-electrode method using acetic acid to measure pitting potential of aluminium and aluminium alloys in chloride solutions

Méthode à deux électrodes utilisant l'acide acétique pour mesurer le potentiel de piqûre de l'aluminium et des alliages d'aluminium dans des solutions de chlorure

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 3079:2022

<https://standards.iteh.ai/catalog/standards/sist/aa4c08fe-620c-411d-8e30-4b6bc9afbde0/iso-3079-2022>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 3079:2022

<https://standards.iteh.ai/catalog/standards/sist/aa4c08fe-620c-411d-8e30-4b6bc9afbde0/iso-3079-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Field of application	1
5 Comparison with conventional methods	1
5.1 Anodic polarization curve measurement.....	1
5.2 Corrosion potential.....	2
6 General principles	2
7 Apparatus	3
7.1 Potentiometer.....	3
7.2 Working electrode.....	3
7.3 Reference electrode.....	3
7.4 Stirrer.....	3
8 Specimen	4
9 Test procedure	4
9.1 Solution.....	4
9.2 Test set-up.....	5
9.3 Evaluation.....	6
10 Test report	6
Bibliography	8

ISO 3079:2022
<https://standards.iteh.ai/catalog/standards/sist/aa4c08fe-620c-411d-8e30-4b6bc9afbde0/iso-3079-2022>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Aluminium and aluminium alloys show excellent corrosion resistance in near-neutral environments as a result of the formation of an oxide or hydroxide film on their surface, thereby achieving passivation. However, if the environment contains the chloride ion, the passive film will be broken, and localized corrosion, such as pitting corrosion, can occur. Aluminium-clad material is used to prevent localized corrosion by galvanic protection. In this method, the underlying core aluminium is protected by a sacrificial layer whose pitting potential is lower than that of the core aluminium. Therefore, in order to estimate the performance of galvanic protection, it is important to obtain the pitting potential.

Although anodic polarization curve measurement is one method for obtaining the pitting potential, the method described in the test method in this document has several advantages in that it causes less specimen damage, has a shorter measurement time and smaller specimen area, multiple measurements are possible, and a two-electrode system is used. In an anodic polarization curve measurement, the specimen is severely corroded due to excessive polarization. The method described in this document causes less specimen corrosion, as the degree of polarization is small because the potential is maintained near the pitting potential. This makes it possible to conduct repeated etching and measurements with the same specimen, which is particularly useful for measurement of the depth profile of the pitting potential in thin clad materials. As a method for measuring the corrosion potential of aluminium alloys, ASTM G69 was established in 1997. ASTM G69 is widely used, substantially to obtain the pitting potential without the anodic polarization curve measurement. In ASTM G69, 1 M (a mass fraction of 5,85 %) of sodium chloride is used as the solution and hydrogen peroxide is used as the oxidant. The test method in this document, where a sodium chloride mass fraction of 5 % is used as the solution and acetic acid is used as the oxidant, also has advantages over ASTM G69. In particular, it causes less specimen damage and has a more stable oxidant with a buffer action.

(standards.iteh.ai)

ISO 3079:2022

<https://standards.iteh.ai/catalog/standards/sist/aa4c08fe-620c-411d-8e30-4b6bc9afbde0/iso-3079-2022>

Two-electrode method using acetic acid to measure pitting potential of aluminium and aluminium alloys in chloride solutions

1 Scope

This document specifies a test method for the measurement of the pitting potential of aluminium and aluminium alloys in sodium chloride solution of a mass fraction of 5 %, with a fixed concentration of acetic acid as the oxidant, using a two-electrode system. This document provides a simple method for ranking aluminium alloys and is especially useful for evaluating galvanic protection performance of thin clad materials because the test method causes little specimen damage.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <https://www.iso.org/obp>

— IEC Electropedia: available at <https://www.electropedia.org/>

4 Field of application

This test method can be used to estimate the corrosion resistance of aluminium alloys in chloride environments, the galvanic corrosion between an aluminium alloy and other metals, and the galvanic protection of aluminium products. In particular, it is useful for estimating the galvanic protection performance of aluminium-clad materials used in heat exchangers in the automotive and air-conditioning fields.

5 Comparison with conventional methods

5.1 Anodic polarization curve measurement


This test method has several advantages compared to the anodic polarization curve measurement, including less specimen damage, a shorter measurement time and smaller specimen area, the possibility of multiple measurements, and the use of a two-electrode system. In an anodic polarization curve measurement, the specimen is severely corroded due to excessive polarization. The method described here causes less specimen corrosion, as the degree of polarization is small because the potential is maintained near the pitting potential. This makes it possible to perform repeated measurements with the same specimen, which is particularly useful for the measurement of the pitting potential at intervals of around 10 μm .

5.2 Corrosion potential

ASTM G69 provides a method for measuring the corrosion potential of aluminium alloys and is widely used to obtain the pitting potential without an anodic polarization curve measurement. In ASTM G69, 1 M of sodium chloride is used as the solution and hydrogen peroxide is used as the oxidant.

6 General principles

In this test method, acetic acid is added to the sodium chloride solution of a mass fraction of 5 % as an oxidant at a concentration in which the corrosion potential is always above the pitting potential of the range of aluminium alloys investigated. On the basis that the current pitting of these alloys increases without much change in potential (see Figure 1), the corrosion potential at which the cathodic reduction of protons intersects the anodic curve reflects the pitting potential of the alloy (to a reasonable approximation). This assumes that there is no effect of the alloy on the cathodic current if the latter is activation controlled. Thus, a simple measurement of the corrosion potential using a working and reference electrode provides a measure of the pitting potential.

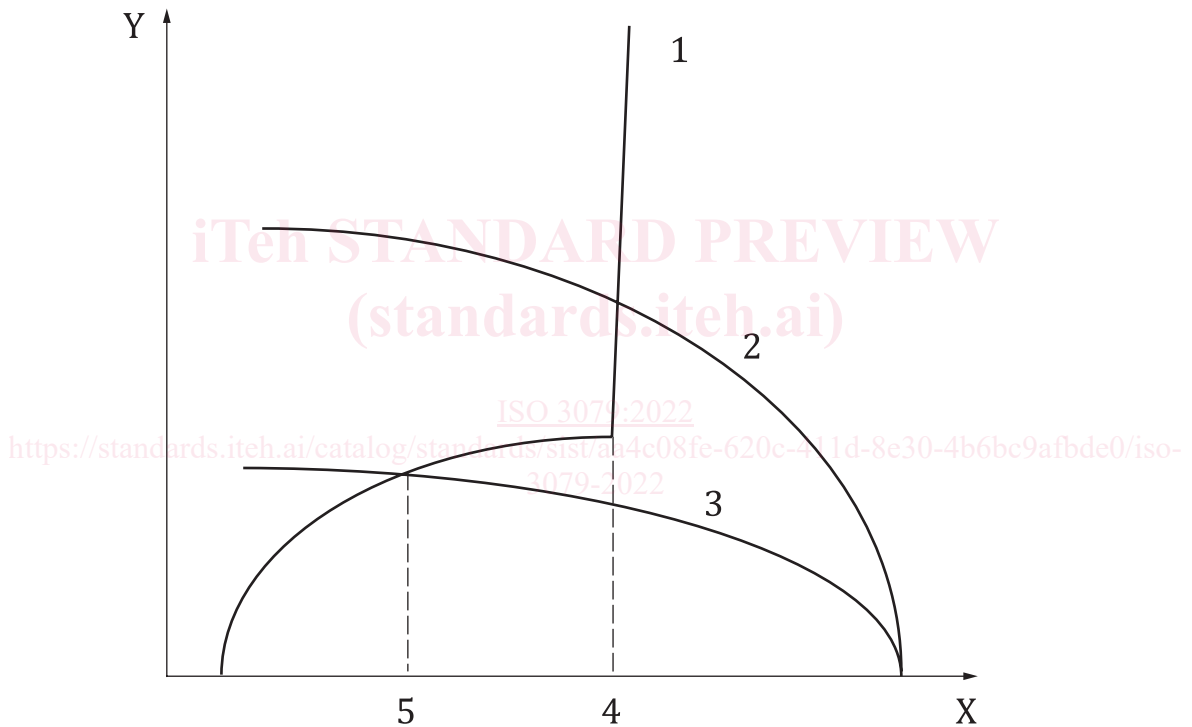

- Key**
- X electrode potential
 - Y current density
 - 1 anodic polarization curve in sodium chloride with and without acetic acid
 - 2 cathodic polarization curve in sodium chloride with acetic acid
 - 3 cathodic polarization curve in sodium chloride without acetic acid
 - 4 corrosion potential = pitting potential
 - 5 corrosion potential < pitting potential

Figure 1 — Effect of acetic acid on corrosion potential

In pitting tests by a conventional anodic polarization measurement, the potential is commonly driven to values significantly above the pitting potential and the specimen can be severely corroded. The method described in this document causes less specimen corrosion, as the degree of polarization is small because the potential is maintained near the pitting potential.

ASTM G69 also describes a method for measuring the corrosion potential of aluminium alloys, in 1 M of sodium chloride, using a two-electrode system but with H_2O_2 as the oxidant. The test method in this document provides advantages over ASTM G69. In particular, it causes less specimen damage and has a more stable oxidant with a buffer action.

7 Apparatus

The measuring apparatus shall be a combination of the following. [Figure 2](#) provides an example of a test apparatus.

7.1 Potentiometer

An internal resistance of potentiometer shall be larger than $10^9 \Omega$.

7.2 Working electrode


The working electrode should be taken from the test material with the test area of 1 cm^2 . The other area shall be masked by or embedded in an inert material such as resin.

7.3 Reference electrode

The reference electrode should be a saturated silver/silver chloride electrode (SSE). Other reference electrodes, i.e. saturated calomel electrode (SCE), can be used. The potentials of these electrodes relative to the standard hydrogen electrode at 25°C are given in ISO 17474.

7.4 Stirrer

The stirrer and stirrer bar are used to stir the solution at a speed of at least 60 rpm. Stirring is important for stable measurement of the corrosion potential, as in measurements of pitting potential, because stirring accelerates the cathodic reaction by acetic acid and reduces local differences in the solution between the anode site and cathode site. 3079-2022

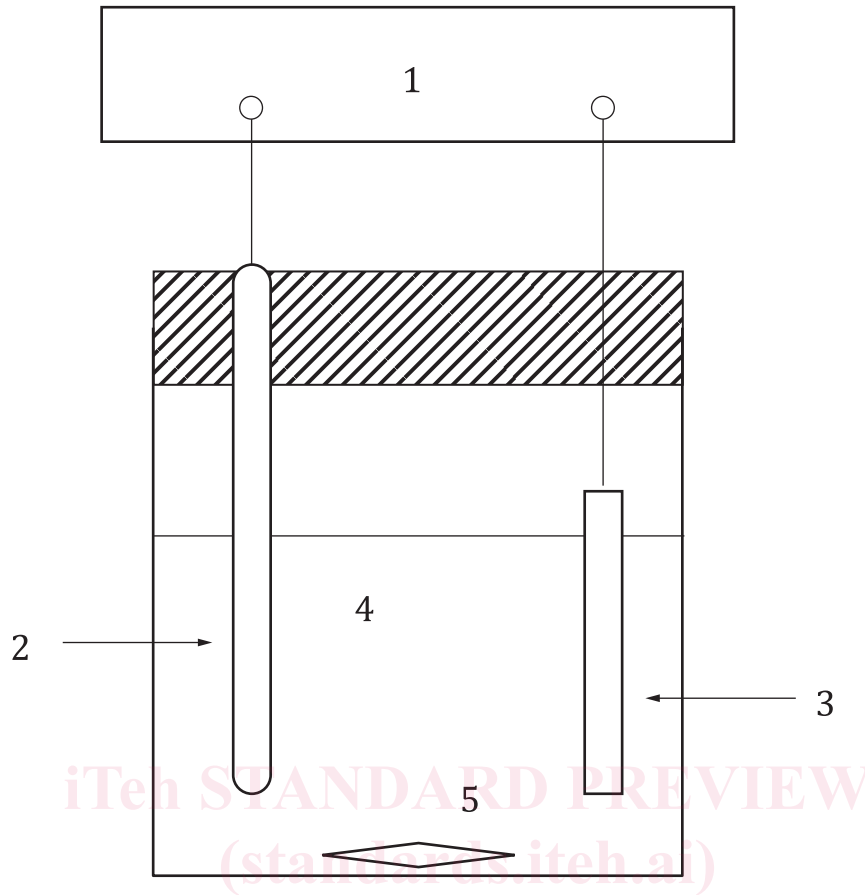

Key

- 1 potentiometer
- 2 reference electrode
- 3 working electrode
- 4 solution
- 5 stirrer bar

Figure 2 — Example of test apparatus

8 Specimen

The specimen shall be taken from a test material with the test area of 1 cm². The other area of the specimen shall be masked by or embedded in an inert material such as resin. There is a possibility of a crevice attack in the resin. The aluminium and resin should be closely attached so that there is no gap between them.

9 Test procedure

9.1 Solution

The solution shall be prepared using reagent-grade chemicals and high purity water. The solution is prepared by creating an aqueous solution with a sodium chloride and glacial acetic acid or diluted acetic acid. The ratio of the volume of the solution to the test area of the specimens shall be at least 100 ml/cm². The chloride ion concentration, which strongly influences the value of pitting potential, is adjusted with a sodium chloride mass fraction of 5 %. To determine the appropriate concentration of acetic acid, immerse the specimen and the reference electrode and connect them via a potentiometer in a sodium