

SLOVENSKI STANDARD oSIST prEN ISO 13997:2024

01-september-2024

Varovalna obleka - Mehanske lastnosti - Ugotavljanje odpornosti proti urezu z ostrimi predmeti (ISO/FDIS 13997:2024)

Protective clothing - Mechanical properties - Determination of resistance to cutting by sharp objects (ISO/FDIS 13997:2024)

Schutzkleidung - Mechanische Eigenschaften - Bestimmung des Widerstandes gegen Schnitte mit scharfen Gegenständen (ISO/FDIS 13997:2024)

Vêtements de protection - Propriétés mécaniques - Détermination de la résistance à la coupure par des objets tranchants (ISO/FDIS 13997:2024)

Ta slovenski standard je istoveten z: prEN ISO 13997

ICS:

13.340.10 Varovalna obleka Protective clothing

oSIST prEN ISO 13997:2024 en,fr,de

oSIST prEN ISO 13997:2024

iTeh Standards (https://standards.iteh.ai) Document Preview

oSIST prEN ISO 13997:2024

https://standards.iteh.ai/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-2024



FINAL DRAFT International Standard

Protective clothing — Mechanical properties — Determination of resistance to cutting by sharp objects

Vêtements de protection — Propriétés mécaniques — Détermination de la résistance à la coupure par des objets tranchants

ISO/FDIS 13997

ISO/TC 94/SC 13

Secretariat: SNV

Voting begins on: **2024-06-26**

Voting terminates on: 2024-09-18

Document Preview

oSIST prEN ISO 13997:2024

https://standards.iteh.ai/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-2024

ISO/CEN PARALLEL PROCESSING

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

iTeh Standards (https://standards.iteh.ai) Document Preview

oSIST prEN ISO 13997:2024

https://standards.iteh.ai/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-2024



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland

Foreword Introduction 1 Scope 2 Normative reference 3 Terms and definitions 4 Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus 5.2.1 Rigid framework	iv
1 Scope 2 Normative reference 3 Terms and definitions 4 Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
Normative reference Terms and definitions Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning Test method 5.1 Principle 5.2 Test apparatus	v
Normative reference Terms and definitions Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning Test method 5.1 Principle 5.2 Test apparatus	1
3 Terms and definitions 4 Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
4 Sampling 4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
4.1 General 4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
4.2 Textiles and other materials 4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
4.3 Gloves 4.4 Conditioning 5 Test method 5.1 Principle 5.2 Test apparatus	
4.4 Conditioning	
5 Test method 5.1 Principle 5.2 Test apparatus	
5.1 Principle 5.2 Test apparatus	
5.2 Test apparatus	
1 1	
5.2.2 Force application system	
5.2.3 Specimen holder mount	
5.2.4 Specimen holder	
5.2.5 Specimen securing clamp	
5.2.6 Blades	7
5.2.7 Blade holder	
5.2.8 Cutting-motion system	
5.2.9 Cut-stroke length measurement system	
5.3 Calibration	9
5.3.1 Beam balancing procedure	
5.3.2 Cutting speed adjustment	
5.3.3 Validation of blades	
5.4.1 Specimen mounting	
5.4.2 Test procedure for measuring the cutting stroke length	
5.4.3 Test procedure for determining the calculated cutting force	-pren-iso-1399712
5.4.4 Calculations	
6 Test report	12
Annex A (informative) Inter-laboratory test data analysis	14
Annex B (normative) Calculated cutting force determination	16
Annex C (normative) Testing of the calibration material (see <u>5.3.3.1</u>)	
Bibliography	

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 94, *Personal safety* — *Personal protective equipment*, Subcommittee SC 13, *Protective clothing*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 162, *Protective clothing including hand arm protection and lifejackets*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 13997:2023), of which it constitutes a minor revision. do itel al/catalog/standards/sist/37ba8d08-6e21-4e10-8701-6b26214ddd5e/osist-pren-iso-13997-2024

The main changes are as follows:

- Figure 7 a) was replaced;
- Footnote 2 to Figure 7 title was moved;
- the Excel file that can be downloaded using the link in the note to <u>Table B.2</u> was replaced (there was a correction because in few specific cases the Excel didn't work as planned)

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Although textiles, composites, leather, rubbers and reinforced materials may resist cutting by sharp edges in different ways, a test method for evaluating the resistance to cut of materials in protective clothing needs to be applicable to all materials. The test described in this document provides a method that allows calculations of the downwards (normal) force required to cause a blade drawn across the sample for a fixed distance to cut through the specimen.

The performance of protective clothing materials may be classified using the numerical values obtained from this test.

iTeh Standards (https://standards.iteh.ai) Document Preview

oSIST prEN ISO 13997:2024

https://standards.iteh.ai/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-202

oSIST prEN ISO 13997:2024

iTeh Standards (https://standards.iteh.ai) Document Preview

oSIST prEN ISO 13997:2024

https://standards.iteh.ai/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-2024

Protective clothing — Mechanical properties — Determination of resistance to cutting by sharp objects

1 Scope

This document specifies a tomodynamometer cut test method and related calculations, for use on materials and assemblies designed for protective clothing, including gloves. The test determines resistance to cutting by sharp edges, such as knives, sheet metal parts, swarf, glass, bladed tools and castings.

When this document is cited as a test method in a material or product requirement standard, that standard contains the necessary information to permit the application of this document to the particular product.

This test does not provide data on the resistance to penetration by pointed objects such as needles and thorns, or the point of sharp-edged blades. The test described in this document is not considered suitable for testing materials made from chain mail and metal plates. The text of this document does not include provisions for the safeguard of the operator.

2 Normative reference

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 34-1, Rubber, vulcanized or thermoplastic — Determination of tear strength — Part 1: Trouser, angle and crescent test pieces

ISO 37, Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties

ISO 48-4, Rubber, vulcanized or thermoplastic — Determination of hardness — Part 4: Indentation hardness by durometer method (Shore hardness)

ISO 2781, Rubber, vulcanized or thermoplastic — Determination of density

ISO 11610, Protective clothing — Vocabulary

ISO 23388:2018, Protective gloves against mechanical risks

ISO 23529, Rubber — General procedures for preparing and conditioning test pieces for physical test methods

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11610 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at https://www.iso.org/obp
- IEC Electropedia: available at https://www.electropedia.org/

3.1

cut-through

event which has occurred when the blade edge first contacts the conducting material below the test specimen

3.2

cutting force

calculated force that would be required to be applied to a blade of standard sharpness to cut through a material in a blade stroke of length 20 mm

3.3

cutting stroke length

distance the cutting-edge travels before *cut-through* (3.1) occurs

4 Sampling

4.1 General

Unless otherwise specified, specimen dimensions should not be less than 25 mm by 100 mm as this allows for several cuts on the same sample (see $\underline{5.2.4}$ and $\underline{5.2.5}$). If this specimen size is not possible, the smallest specimen on which single cuts are made shall not be less than 25 mm by 25 mm.

NOTE The test requires at least 15 cuts therefore at least two specimens are necessary.

4.2 Textiles and other materials


Specimens shall be taken from regions of the sample product representative of the range of construction present in protective areas or as defined in product requirement standard. In the case of an irregular design, the test specimen shall be taken from the area where the least protection is expected.

Specimens from textile materials shall be prepared so that test cuts are made at an angle of $(45 \pm 5)^{\circ}$ to the warp and weft direction as defined in <u>Figure 1</u>. Only one result (cutting force, see <u>5.4.4.2</u>) shall be reported.

Materials that have no clear orientation shall be tested in two directions at 90° to each other and both cutting forces (see <u>5.4.4.2</u>) shall be reported and the final result is the lowest one.

If the material is known to have homogenous properties in all directions, only one result (cutting force see <u>5.4.4.2</u>) needs to be reported.

NOTE Materials that have no clear orientation are for example, unoriented materials, or those in which the machine direction either does not exist or is uncertain such as some non-woven.

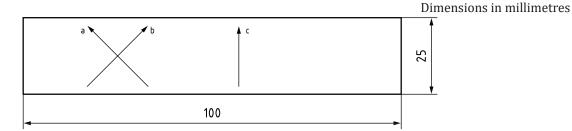

- ^a Warp or longitudinal direction.
- b Weft or transversal direction.
- c Cut test direction.

Figure 1 — Control specimen dimensions and cut direction for garments

4.3 Gloves

For gloves, take the specimen from the palm area cut on the bias such that the size of the specimen is adequate but at an angle as close as possible to 45° as shown in Figure 2.


In the case of an irregular design of the palm, the test specimen shall be taken from the palm area where the least protection is expected.

If reinforcement(s) does not uniformly cover the palm area, either the specimen shall be taken without reinforcement or the specimen shall be provided without reinforcement.

If cut protection is claimed for back of the hand or cuff and the materials are different from the palm, they shall be tested and reported.

NOTE There is no tolerance to the angle for the glove as this depends on the size of the glove and its construction to take the correct angle that best represents a 45° angle.

Dimensions in millimetres

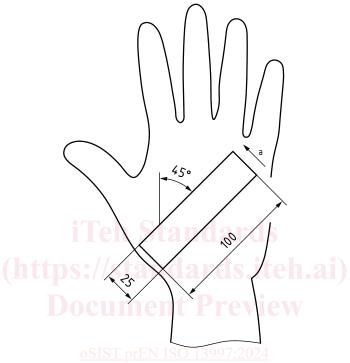

nttps://standards.iteh.aj/catalog/standards/sist/37ba8d08-6e21-4ef0-8701-6b26214ddd5e/osist-pren-iso-13997-2024

^a Cut test direction.

Figure 2 — Glove sample and cut direction

4.4 Conditioning

Specimens shall be conditioned as defined in product requirement standard or in the following conditioning atmosphere:

— Temperature (23 ± 2) °C and relative Humidity (50 ± 5) %.

Alternatively, the following conditioning should be used, and shall be reported in the test report.

— Temperature (20 ± 2) °C and relative Humidity (65 ± 5) %.

The period of conditioning is at least 24 h. Testing shall be carried out in the conditioning environment or within 30 min of withdrawing the specimens from the conditioning environment.