

FINAL  
DRAFT

INTERNATIONAL  
STANDARD

ISO/FDIS  
3444

ISO/TC 105

Secretariat: SAC

Voting begins on:  
**2023-01-26**

Voting terminates on:  
**2023-03-23**

---

---

## Stainless-steel wire ropes

*Câbles en acier inoxydables*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/FDIS 3444

<https://standards.iteh.ai/catalog/standards/sist/0d77fb51-7e2e-4ef0-ae2e-572f23e1490e/iso-fdis-3444>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number  
ISO/FDIS 3444:2023(E)

© ISO 2023

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/FDIS 3444

<https://standards.iteh.ai/catalog/standards/sist/0d77fb51-7e2e-4ef0-ae2e-572f23e1490e/iso-fdis-3444>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references.....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>1</b>
<b>4 Ordering information.....</b>	<b>2</b>
<b>5 Requirements.....</b>	<b>2</b>
5.1 Materials.....	2
5.1.1 Stainless steel.....	2
5.1.2 Wire.....	2
5.1.3 Core.....	3
5.2 Rope manufacture.....	3
5.2.1 General.....	3
5.2.2 Wire joints.....	3
5.2.3 Lubrication.....	4
5.2.4 Rope construction.....	4
5.3 Designation and classification.....	4
5.3.1 Designation.....	4
5.3.2 Classification.....	5
5.4 Dimensions.....	5
5.4.1 Diameter.....	5
5.4.2 Out-of-roundness.....	5
5.4.3 Rope length.....	5
5.4.4 Lay length.....	6
5.5 Mechanical properties.....	6
5.5.1 Breaking force.....	6
5.5.2 Elongation.....	6
5.5.3 Bend fatigue property.....	6
5.6 Other requirements.....	6
<b>6 Inspection.....</b>	<b>7</b>
6.1 General.....	7
6.2 Test methods.....	7
6.2.1 Chemical composition test.....	7
6.2.2 Wrapping test of wire.....	7
6.2.3 Test on rope for diameter.....	7
6.2.4 Inspection of internal stresses.....	8
6.2.5 Straightness inspection.....	8
6.2.6 Tensile test.....	8
6.2.7 Bend fatigue test.....	8
6.2.8 Inspection of surface quality.....	9
6.3 Sampling and acceptance criteria.....	9
<b>7 Delivery conditions.....</b>	<b>9</b>
7.1 General.....	9
7.2 Certificate.....	9
7.3 Packaging and marking.....	10
7.3.1 Packaging.....	10
7.3.2 Marking.....	10
<b>Annex A (informative) Construction examples of stainless-steel wire ropes.....</b>	<b>11</b>
<b>Annex B (normative) Minimum breaking forces for the ropes.....</b>	<b>13</b>
<b>Bibliography.....</b>	<b>18</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 105, *Steel wire ropes*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Stainless-steel wire ropes

## 1 Scope

This document specifies requirements for manufacture, classification, test methods, packaging, marking and issuing of a certificate for stainless-steel wire ropes.

It is applicable to stainless-steel wire ropes (hereafter referred to as ropes) for instruments, mechanical transmission, cable, sling, shock absorber vibration, yacht, architecture and structure.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2020-2, *Aerospace — Preformed flexible steel wire rope for aircraft controls — Part 2: Technical specification*

ISO 3108, *Steel wire ropes — Test method — Determination of measured breaking force*

ISO 7802, *Metallic materials — Wire — Wrapping test*

ISO 15510, *Stainless steels — Chemical composition*

ISO 17893, *Steel wire ropes — Vocabulary, designation and classification*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 17893 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 3.1

#### **stainless steel**

steel with at least 10,5 % (mass fraction) Cr and maximum 1,2 % (mass fraction) C

[SOURCE: ISO 15510:2014, 3.1, modified — Note 1 to entry removed.]

### 3.2

#### **surface status**

#### 3.2.1

##### **cleanliness**

freedom from visible residue such as lubricating grease, powder and oil

#### 3.2.2

##### **lubricated**

coated with grease, rust-proof oil or fatigue oil

**3.3  
lot**

series of ropes manufactured under basically the same time period and consistent conditions, and which have the same construction and diameter

**4 Ordering information**

The contract in accordance with this document shall at least include the following main contents:

- a) number of this document (ISO 3444);
- b) product name, if relevant;
- c) construction (designation);
- d) nominal rope diameter;
- e) minimum breaking force;
- f) type of core, if relevant;
- g) lay type and direction;
- h) delivery surface status (cleanliness, lubricated, or other requirements);
- i) quantity (length, weight);
- j) steel name;
- k) other specific requirements including detection methods, physical and chemical properties.

**5 Requirements**

**5.1 Materials**

**5.1.1 Stainless steel**

Stainless steel shall conform to ISO 15510. Steel names can be agreed by the purchaser and the manufacturer.

**5.1.2 Wire**

**5.1.2.1 Tolerance on diameter**

The tolerance on the nominal wire diameter shall be in accordance with the values given in [Table 1](#).

Table 1 — Tolerance on wire diameter

Nominal wire diameter, $\delta$ [mm]	Tolerance on diameter [mm]
$\delta < 0,10$	$\pm 0,005$
$0,10 \leq \delta < 0,20$	$\pm 0,008$
$0,20 \leq \delta < 0,40$	$\pm 0,010$
$0,40 \leq \delta < 1,00$	$\pm 0,015$
$1,00 \leq \delta < 1,60$	$\pm 0,025$
$1,60 \leq \delta < 3,70$	$\pm 0,030$
$3,70 \leq \delta < 6,00$	$\pm 0,040$
$\delta \geq 6,00$	$\pm 0,045$

### 5.1.2.2 Tensile-strength grade

The tensile-strength grades of wires shall make the ropes meet the minimum breaking force given in this document or the requirements of the purchaser.

### 5.1.2.3 Wrapping test

Before rope making, wires shall not be broken when performing the wrapping test in accordance with [6.2.2](#).

### 5.1.2.4 Wire finish

The finish of the wires shall not have cracks, ring and other defects that may affect the use.

### 5.1.3 Core

Cores of ropes shall normally be of steel (WSC or IWRC) or fibre (NFC or SFC). In addition, solid polymer (SPC) may also be supplied.

The purchaser should specify any other particular core type requirements. In the centre strand, the centre wire of rope can be properly bolded to ensure adequate support.

## 5.2 Rope manufacture

### 5.2.1 General

The completed ropes shall be evenly laid, tight, smooth, and free from loose wires, distorted strands and other irregularities. The surface status of ropes can be agreed by the purchaser and manufacturer.

### 5.2.2 Wire joints

**5.2.2.1** For single-layer ropes, the minimum distance between wire joints within one strand should be  $50 \times$  rope diameter ( $d$ ). Wires over 0,4 mm in diameter shall have their ends joined by welding. Wires having up to and including a 0,4 mm diameter shall be joined by welding or by ends being inserted in the strand's formation. Partial crossing of the wires at the inserted ends is allowed, but the wire ends shall be sealed inside the strands and not be exposed.

**5.2.2.2** For spiral strand ropes, the distance between two wire joints shall not be less than 50 m. For the finished spiral strand ropes, the joint in any length shall not exceed one and the welding position of each wire shall be obviously marked on the ropes. Flash butt welding or upset butt welding shall be

used for wire joints. Weld joints should not break during assembly and spooling and need to be ground, to prevent from consequence on diameter.

**5.2.3 Lubrication**

**5.2.3.1** Ropes can be coated with a small amount of neutral grease. For ropes with fibre cores and solid polymer cores, the amount of lubrication and type of rope lubricant shall be agreed by the purchaser and manufacturer.

**5.2.3.2** After the purchaser’s approval, the remaining grease on the surface of ropes for medical equipment, decoration and fitness equipment can be cleaned.

**5.2.3.3** For ropes for automobile, control, aeronautical use and other safety-related purposes, the remaining grease on the surface should be retained.

**5.2.4 Rope construction**


See [Annex A](#) for the construction examples of the ropes. Other rope constructions can be stated by the manufacturer.

**5.3 Designation and classification**

**5.3.1 Designation**

Ropes shall be ordered in accordance with this document and be designated as follows.

[Figure 1](#) gives the designation of single-layer rope.

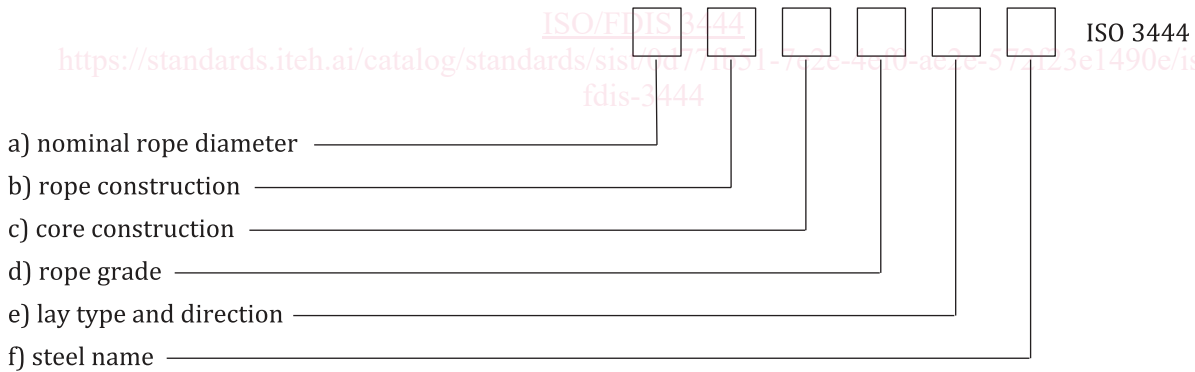

**Figure 1 — Designation of single-layer rope**


NOTE 1 Rope grades that classified to Grade A and Grade B for single-layer ropes are given in [Table 3](#).

EXAMPLE 1 A rope with a nominal rope diameter of 2 mm, rope construction of 6×7-WSC, rope grade of Grade A, right ordinary lay (sZ) and steel name of X3CrNiMo17-12-3 is designated:

2 6×7-WSC A sZ X3CrNiMo17-12-3 ISO 3444.

[Figure 2](#) gives the designation of spiral strand rope.



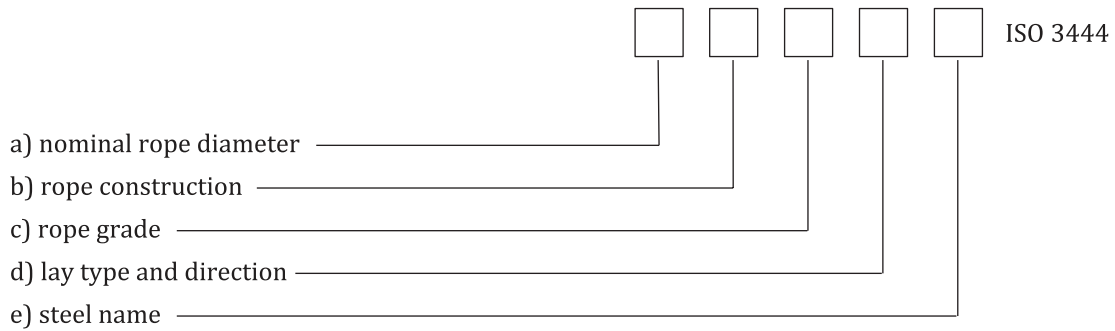

**Figure 2 — Designation of spiral strand rope**

NOTE 2 Rope grades for spiral strand ropes are classified to 1150 and 1500.

EXAMPLE 2 A rope with a nominal rope diameter of 6 mm, rope construction of 1 × 7, rope grade of 1500, left lay (S) and steel name of X5CrNi18–10 is designated:

6 1×7 1500 S X5CrNi18–10 ISO 3444.

### 5.3.2 Classification

The rope classes for single-layer ropes and spiral strand ropes shall be in accordance with ISO 17893.

## 5.4 Dimensions

### 5.4.1 Diameter

The rope diameter shall be within the tolerances given in [Table 2](#). The other tolerance requirements shall be agreed by the purchaser and the manufacturer.

**Table 2 — Tolerance on rope diameter**

Nominal rope diameter, <i>d</i> [mm]	Tolerance as percentage of nominal diameter
$d < 2$	+10 0
$2 \leq d < 4$	+8 0
$4 \leq d < 6$	+7 0
$6 \leq d < 8$	+6 0
$d \geq 8$	+5 0

### 5.4.2 Out-of-roundness

The out-of-roundness of rope shall not be more than half the tolerance on nominal rope diameter.

### 5.4.3 Rope length

Rope length shall be specified in the ordering information. Otherwise it shall be determined by the manufacturer.

#### 5.4.4 Lay length

5.4.4.1 Lay length of single-layer rope shall be no more than  $8 \times$  rope diameter.

5.4.4.2 Lay length of spiral strand rope shall be no more than  $14 \times$  rope diameter, unless otherwise agreed with the purchaser.

### 5.5 Mechanical properties

#### 5.5.1 Breaking force

5.5.1.1 For single-layer ropes, according to different steel names, there are two classes Grade A and Grade B as in [Table 3](#). The minimum breaking forces for single-layer ropes shall be either as given in [Table B.3](#) and [Table B.4](#) in [Annex B](#) or as stated by the manufacturer.

**Table 3 — Classes according to different steel names**

Class	Steel names
Grade A	X9CrNi18-9
	X5CrNi18-10
	X10CrNi18-8
Grade B	X5CrNiMo17-12-2
	X2CrNiMo17-12-2
	X4CrNi18-12
	X15CrNiSi25-21

5.5.1.2 For spiral strand ropes, the minimum breaking forces for rope grades 1150 and 1500 shall be as given in [Table B.5](#) in [Annex B](#). Other rope grades shall be agreed between the purchaser and the manufacturer.

5.5.1.3 For the determination of minimum breaking forces of rope diameters not listed in [Table B.3](#) to [Table B.5](#), calculations in accordance with [Formula \(B.1\)](#) can be used or agreed by the purchaser and manufacturer.

#### 5.5.2 Elongation

5.5.2.1 Special requirements, such as the permanent elongation and elastic elongation of single-layer ropes, can be specified in accordance with the ordering information between the purchaser and manufacturer.

5.5.2.2 The permanent elongation of spiral strand ropes shall not be more than 1,50 %.

#### 5.5.3 Bend fatigue property

If the purchaser has requirements for bend fatigue property of the ropes, the test conditions and specific requirements of bend fatigue property shall be agreed by the purchaser and the manufacturer.

### 5.6 Other requirements

Other technical requirements shall be agreed between the purchaser and manufacturer.

## 6 Inspection

### 6.1 General

The inspection shall be carried out by the manufacturer.

### 6.2 Test methods

#### 6.2.1 Chemical composition test

**6.2.1.1** In case it is requested when ordering, the rope manufacturer should choose a suitable chemical analysis method to conduct the test after purchasing stainless steel. In cases of dispute, the analysis shall be carried out by a laboratory approved by the two parties. In these cases, the reference method of analysis shall be agreed upon, and where possible the method of analysis should be taken from ISO/TR 9769.

**6.2.1.2** The main chemical composition of alloying elements for ropes, such as Cr and Ni, shall be analysed. The alloying elements to be tested shall be agreed and specified in the ordering information. The detection elements to be tested of the common steel names are shown in [Table 4](#).

**Table 4 — Steel name and necessary detection elements**

Steel name	Necessary detection elements
X9CrNi18-9 X5CrNi18-10 X10CrNi18-8 X4CrNi18-12	Cr, Ni
X5CrNiMo17-12-2 X2CrNiMo17-12-2	Cr, Ni, Mo
X15CrNiSi25-21	Cr, Ni, Si

#### 6.2.2 Wrapping test of wire

When coiled for 8 turns around a mandrel of equal diameter to the wire, the wire shall not break, and the test shall be carried out in accordance with ISO 7802.

#### 6.2.3 Test on rope for diameter

**6.2.3.1** For a rope diameter  $\leq 2$  mm, the minimum scale value of the measuring instrument shall be  $\leq 0,01$  mm. For a rope diameter over 2 mm, the minimum scale value of the measuring instrument shall be  $\leq 0,02$  mm.

**6.2.3.2** For a rope diameter  $\leq 5$  mm, the measuring equipment shall extend over at least two adjacent strands. Diameter measurements shall be taken on a straight portion of rope under no tension, at two positions spaced at least 1 m apart. At each position, two measurements, at  $90^\circ$  apart, of the circumscribed circle diameter shall be taken. The average of these four measurements shall be the measured in actual diameter.

**6.2.3.3** For a rope diameter over 5 mm, diameter measurements shall be taken on a straight portion of rope under no tension, at two positions spaced at least 10 m apart. At each position, two measurements, at  $90^\circ$  apart, of the circumscribed circle diameter shall be taken. The average of these four measurements shall be the measured in actual diameter.