

DRAFT INTERNATIONAL STANDARD

ISO/DIS 2076

ISO/TC 38

Secretariat: JISC

Voting begins on:
2021-01-20

Voting terminates on:
2021-04-14

Textiles — Man-made fibres — Generic names

Textiles — Fibres chimiques — Noms génériques

ICS: 59.060.20; 01.040.59

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/DIS 2076

<https://standards.iteh.ai/catalog/standards/sist/0cbbcad-c-d59a-4476-b153-7ef3d3199838/iso-dis-2076>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 2076:2021(E)

© ISO 2021

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/DIS 2076

<https://standards.iteh.ai/catalog/standards/sist/0cbbcadc-d59a-4476-b153-7ef3d3199838/iso-dis-2076>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 General	1
4.1 Introduction	1
4.2 Generic name (e.g. acetate)	1
4.3 Other denominations	2
4.4 Abbreviated terms (e.g. CA)	2
4.5 Distinguishing attributes	2
4.6 Chemical formulae	2
5 Generic names	2
6 Designation of the bicomponent fibres	13
Annex A (informative) Rules related to the creation of a generic name	14
Annex B (informative) Fibres made of several components	16
Annex C (informative) Modified fibres	18
Annex D (informative) Index of generic names in English and in French	19
Annex E (informative) Index of codes in alphabetical order with English and French equivalents	21
Annex F (informative) Regional and national requirements related to generic names	22
Bibliography	25

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2. www.iso.org/directives

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received. www.iso.org/patents

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 38, *Textiles*.

This seventh edition cancels and replaces the sixth edition (ISO 2076:2013), which has been technically revised. The main changes compared to the previous edition are as follows:

- [Clause 2](#) (Normative references) has been added;
- in [Table 1](#), the definition of protein (5.28) has been modified, chitosan (5.36), polyacrylate (5.37) as well as their respective definition have been added;
- in [Table D.1](#), chitosan and polyacrylate have been added;
- in [Table F.2](#), protein (EU denomination) has been added.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The objective of this document is to propose a generic name of fibre (a generic name is unique by nature) within the framework of the ISO standardization for the textile products. It has been elaborated in order to present a compilation of generic names and the rules to create a new generic name for new fibres.

It is intended to be the reference for the ISO 1833 series^[2] and the Technical Report ISO/TR 11827^[3].

It could be a reference within the framework of the globalization as compilation of the generic names of man-made fibres is important for the global distribution of textile products due to national regulations for the declaration of fibre content and care labelling. It could be an answer to a universal need for the standardization of generic names that would foster easy movement of textiles across borders to facilitate trade, for example, for companies which might have plants in multiple countries and have innovations and business activities covering research and development in fibre-producing.

Nonetheless, it is not intended to supersede any national or regional regulations, but could be helpful for the coordination of national or regional Authorities (e.g. FTC in USA, European Commission in European Union, etc.) within the framework of regulations. The informative [Annex F](#) links the generic names to the specific requirements regarding some national or regional regulations.

For example, products destined for the European market should be labelled in accordance with the regulation identified as Regulation (EU) No. 1007/2011 of the European Parliament and of the Council of 27 September 2011 on textile fibre names and related labelling and marking of the fibre composition of textile products. Regulation 1007/2011 repeals Council Directive 73/44/EEC and Directives 96/73/EC and 2008/121/EC of the European Parliament and of the Council and includes some different and/or additional fibre denominations other than the present generic names (see [F.3](#) and [Table F.2](#)). The European Regulation takes precedence over this document.

[ISO/DIS 2076](#)

<https://standards.iteh.ai/catalog/standards/sist/0cbbcad-c-d59a-4476-b153-7ef3d3199838/iso-dis-2076>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/DIS 2076

<https://standards.iteh.ai/catalog/standards/sist/0cbbcadc-d59a-4476-b153-7ef3d3199838/iso-dis-2076>

Textiles — Man-made fibres — Generic names

1 Scope

This document lists the generic names used to designate the different categories of man-made fibres, based on a main polymer, currently manufactured on an industrial scale for textile and other purposes, together with the distinguishing attributes that characterize them. The term “man-made fibres” has been adopted for those fibres obtained by a manufacturing process, as distinct from materials which occur naturally in fibrous form.

This document presents recommendations of rules for the creation of the generic name ([Annex A](#)).

NOTE These rules have been introduced in the sixth edition of ISO 2076, and thus, they could not be applied to the existing generic names of the previous editions.

Annexes include the description of the fibre structures in case of fibre made of several components ([Annex B](#)) and the description of modified fibres ([Annex C](#)).

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

man-made fibre

fibre obtained by a manufacturing process

Note 1 to entry: The term “man-made” fibre can be named “manufactured” fibre or “chemical” fibre.

4 General

4.1 Introduction

The entries in [Table 1](#) are organized into five principal elements: generic name, other denominations, code, distinguishing attributes and chemical formulae.

4.2 Generic name (e.g. acetate)

This is the name to be used for the fibre whose attributes are described under the heading **Distinguishing attribute** in [Table 1](#). The use of this name shall be limited to those fibres that contain not more than 15 % by mass of property-enhancing additives prior to spinning (no limit is placed upon the proportion of additives that are not property enhanced). In both the English and French languages, the generic name shall be written without capital letters.

The generic name may also apply to a man-made fibre which results from a manufacturing process that can confer a distinguishing attribute.

4.3 Other denominations

When relevant, this is the denomination used for the fibre name in the regulation of some countries, which differs from the generic name.

The given denominations are relative to the following countries: China (identified as CN), countries of the European Union (EU), Japan (JP) and the USA (US). For further information on the regulation related to these countries, see [Annex F](#).

NOTE The country list can be extended in relation to the contribution of the concerned countries.

4.4 Abbreviated terms (e.g. CA)

This is a two- to four-letter designation used to facilitate the naming of man-made fibres, e.g. in sales and technical literature. In some cases, the system of abbreviated terms given to textile fibres is different from the one used for plastics.

NOTE The system of abbreviated terms for plastics is given in ISO 1043-1^[1].

4.5 Distinguishing attributes

These are attributes that differentiate one fibre from all the others. Chemical difference, which often results in distinctive property differences, is the main basis for classification in this document; other attributes are used, where necessary, to differentiate between otherwise similar man-made fibres. The distinguishing attributes are not necessarily those by which the fibres might be identified or the same as those used for naming chemical molecules, nor are they necessarily suitable for the analysis of fibre mixtures.

NOTE In these descriptions, the concepts “group”, “linkage” and “unit” have been used in the following manner:

- “group” is used to denote a functional chemical unit, e.g. hydroxyl groups on acetate;
- “linkage” is used to denote a chemical bond;
- “unit” is used to denote a repeating element.

4.6 Chemical formulae

These are indications of the chemical structure of the fibre. The examples do not comprise mandatory elements of this document given that, in some cases, the same chemical formula may be shared by more than one fibre category; e.g. cellulose II is shared by cupro, lyocell, modal and viscose.

5 Generic names

See [Table 1](#).

Table 1 — Generic names

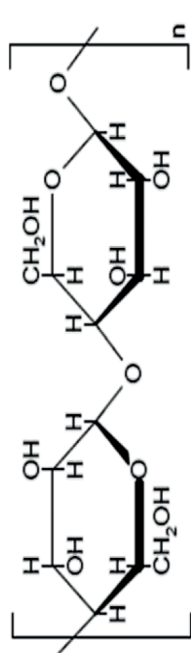
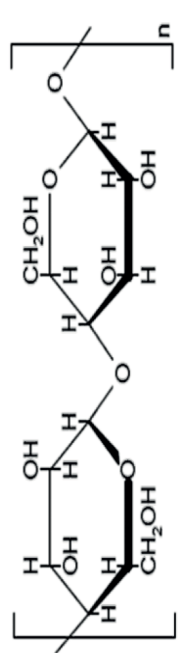
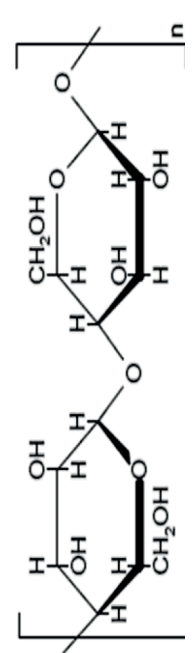
No.	Generic name	Other denominations	Abbr.	Distinguishing attribute	Examples of chemical formulae
5.1	cupro		CUP	Cellulose fibre obtained by the cuprammonium process.	<p>Cellulose II:</p> 
5.2	lyocell	rayon (US)	CLY	<p>Cellulose fibre obtained by an organic solvent spinning process. It is understood that:</p> <ol style="list-style-type: none"> 1) an “organic solvent” means essentially a mixture of organic chemicals and water; 2) “solvent spinning” means dissolving and spinning without the formation of a derivative. 	<p>Cellulose II:</p> 
5.3	modal	rayon (US)	CMD	<p>Cellulose fibre having a high breaking strength and a high wet modulus. The breaking strength B_c in the conditioned state and the force B_w required to produce an elongation of 5 % in its wet state are</p> $B_c \geq 1,3\sqrt{\rho_1 + 2\rho_2}$ $B_w \geq 0,5\sqrt{\rho_1}$ <p>where ρ_1 is the mean linear density (mass per unit length), in decitex. B_c and B_w are expressed in centinewtons.</p>	<p>Cellulose II:</p> 

Table 1 (continued)

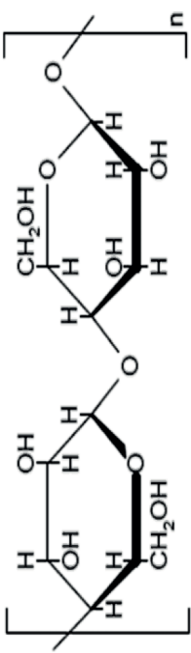


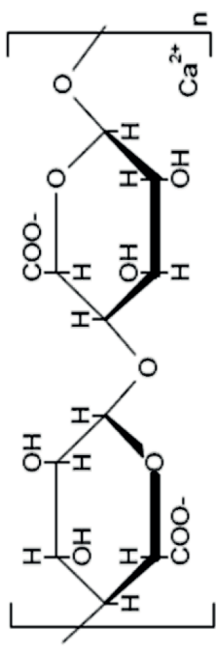
No.	Generic name	Other denominations	Abbr.	Distinguishing attribute	Examples of chemical formulae
5.4	viscose	rayon (JP, US) viscose or rayon (CN)	CV	Cellulose fibre obtained by the viscose process.	<p>Cellulose II:</p>  <p>where X = H or CH₃CO and the degree of esterification is at least 2,22 but less than 2,76.</p>
5.5	acetate		CA	Cellulose acetate fibre in which less than 92 % of the hydroxyl groups are acetylated.	<p>Secondary cellulose acetate:</p>  <p>where X = H or CH₃CO and the degree of esterification is at least 2,76 and 3.</p>
5.6	triacetate		CTA	Cellulose acetate fibre in which at least 92 % of the hydroxyl groups are acetylated.	<p>Cellulose triacetate:</p>  <p>where X = H or CH₃CO and the degree of esterification is between 2,76 and 3.</p>
5.7	alginate		ALG	Fibre obtained from the metal salts of alginic acid.	<p>Calcium alginate:</p> 

Table 1 (continued)

No.	Generic name	Other denominations	Abbr.	Distinguishing attribute	Examples of chemical formulae
5.11	elastane	polyurethane (JP) spandex (US) elastane or spandex (CN)	EL	Fibre composed of at least 85 % by mass of a segmented polyurethane and which, if stretched to three times its unstretched length, rapidly reverts substantially to the unstretched length when the tension is removed.	Macromolecules having alternate elastic and rigid segments with repetition of the group ---O---C---N--- O H
5.12	elastodiene ^b		ED	Fibre composed of natural or synthetic polyisoprene, or of one or more dienes polymerized with or without one or more vinyl monomers, and which, if stretched to three times its unstretched length, rapidly reverts substantially to the unstretched length when the tension is removed.	Natural polyisoprene extracted from the latex of <i>Hevea brasiliensis</i> , vulcanized: $\begin{array}{c} \text{---CH}_2\text{---} \\ \\ \text{H---C---} \\ \\ \text{---CH}_2\text{---} \end{array} \text{---S}_x \text{---} \begin{array}{c} \text{---CH}_2\text{---} \\ \\ \text{---C---} \\ \\ \text{CH}_3 \end{array} \text{---CH}_2\text{---}$ $\begin{array}{c} \text{---CH}_2\text{---} \\ \\ \text{---C---} \\ \\ \text{CH}_3 \end{array} \text{---CH}_2\text{---}$
5.13	fluorofibre		PTFE	Fibre composed of linear macromolecules made from aliphatic fluorocarbon monomers.	Polytetrafluoroethylene: $\text{---} \left[\text{---C---} \right]_n \text{---}$ F F
5.14	modacrylic		MAC	Fibre composed of linear macromolecules having, in the chain, at least 50 % and less than 85 % by mass of acrylonitrile.	Acrylic copolymers: $\text{---} \left[\text{---CH}_2\text{---} \right]_m \left(\text{---CH}_2\text{---} \right)_n \left[\text{---C---} \right]_p \text{---}$ H X Y CN If X = H and Y = Cl: acrylonitrile (vinyl chloride) copolymer If X = Y = Cl: acrylonitrile (vinylidene chloride) copolymer