International Standard



INTERNATIONAL ORGANIZATION FOR STANDARDIZATION•MEЖДУНАРОДНАЯ OPFAHИЗАЦИЯ ПО CTAHДAPTUЗАЦИИ•ORGANISATION INTERNATIONALE DE NORMALISATION

Assembly tools for screws and nuts — Hexagon socket screw keys — Metric series

Outils de manœuvre pour vis et écrous — Clés mâles coudées pour vis à six pans creux — Série métrique

Second edition - 1983-12-01 STANDARD PREVIEW (standards.iteh.ai)

Descriptors: tools, assembly tools, wrenches, socket head screws, dimensions, tests.

ISO 2936:1983 https://standards.iteh.ai/catalog/standards/sist/01214861-c6fe-4a97-ba74-9cca829ce531/iso-2936-1983

UDC 621.883.14

Ref. No. ISO 2936-1983 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been authorized has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 2936 was developed by Technical Committee ISO/TC 29, V IF W Small tools, and was circulated to the member bodies in August 1981.

Standards.iteh.ai

It has been approved by the member bodies of the following countries:

Poland

ISO 2936:1983

Yugoslavia

hIndia standards.iteh.ai/catalog/Romania/sist/01214861-c6fe-4a97-ba74-Australia 9cca829 South Africa Reproof Austria Israel Sri Lanka Belgium Italy Japan Sweden Brazil Egypt, Arab Rep. of Korea, Dem. P. Rep. of Switzerland France Korea, Rep. of United Kingdom Mexico **USSR** Germany, F. R.

The member bodies of the following countries expressed disapproval of the document on technical grounds:

Czechoslovakia USA

This second edition cancels and replaces the first edition (i.e. ISO 2936-1977).

Hungary

Assembly tools for screws and nuts — Hexagon socket screw keys — Metric series

iTeh STANDARD PREVIEW (standards.iteh.ai)

1 Scope and field of application

ISO 2936:1983

This International Standard relating to assembly tools for screws and nuts, deals with hexagon socket screw keys designated as number 112 in ISO 1703.

9cca829ce531/iso-2936-1983

It includes a table of dimensions of these keys and a method of test.

In addition it specifies the minimum hardness value that shall be met.


The specifications of this International Standard apply for tightening of screws of property class less than or equal to 12.9 as defined in ISO 898/1 and for tightening of socket set screws as defined in ISO 898/5.

2 References

ISO 898/1, Mechanical properties of fasteners — Part 1: Bolts, screws and studs.

ISO 898/5, Mechanical properties of fasteners — Part 5: Set screws and similar threaded fasteners not under tensile stresses.

ISO 1703, Assembly tools for screws and nuts - Nomenclature.

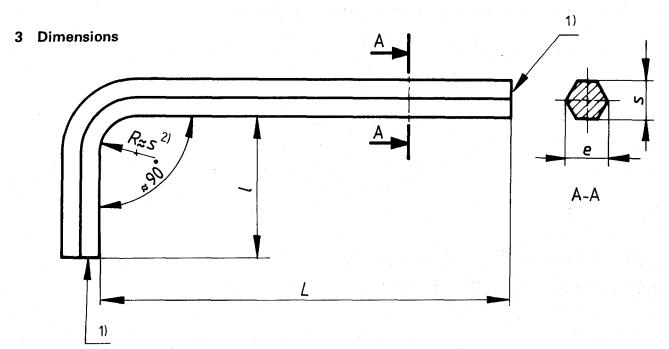

- 1) The corners may be sharp, rounded or chamfered and the radius of curvature or the chamfer respectively shall not be greater than half the difference between width across corners e and width across flats s. Each end shall be square with the axis of each arm within $\pm 4^{\circ}$.
- 2) R shall not be smaller than 1,5 mm.

iTeh STable 15 Dimensions REVIEW

Dimensions in millimetres

		s		(standards.iteh			
Size of key	Tolerance	max.	min.	max.	min.	$m{L} \leftarrow m{L} + m{L$	
0,7	+ 0,011 - 0,002	0,711	0,698 <u>ISO</u> s itch.ai/catalog/sta	2936:10 93	0,76	32	6
0,9	- 0,011 - 0,024	0,889		31/iso- 2.99 6-198	3 0,96	32	10
1,3	- 0,030 - 0,056	1,270	1,244	1,42	1,37	40	12
1,5	h9	1,50	1,475	1,68	1,632)	45	14
2	h10	2,00	1,96	2,25	2,18 ³⁾	50	16
2,5		2,50	2,46	2,82	2,753)	56	18
3		3,00	2,96	3,39	3,31 ³⁾	63	20
4		4,00	3,952	4,53	4,443)	70	25
5		5,00	4,952	5,67	5,58 ⁴⁾	80	28
6		6,00	5,952	6,81	6,71 ⁴⁾	90	32
8		8,00	7,942	9,09	8,97	100	36
10		10,00	9,942	. 11,37	11,23	112	40
12	h11	12,00	11,89	13,65	13,44	125	45
14		14,00	13,89	15,93	15,70	140	56
17		17,00	16,89	19,35	19,09	160	63
19		19,00	18,87	21,63	21,32	180	70
22		22,00	21,87	25,05	24,71	200	80
24		24,00	23,87	27,33	26,97	224	90
27		27,00	26,87	30,75	30,36	250	100
32		32,00	31,84	36,45	35,98	315	125
36		36,00	35,84	41,01	40,50	355	140

¹⁾ $e_{\text{max}} = 1.14 s_{\text{max}} - 0.03$

$$(from s = 1,5 up to s = 36)$$

3)
$$e_{\min} = 1.13 s_{\min} - 0.03$$

$$e_{\min} = 1,13 s_{\min}$$

(from
$$s = 8$$
 up to $s = 36$)

4)
$$e_{\min} = 1.13 s_{\min} - 0.02$$

²⁾ $e_{\min} = 1.13 s_{\min} - 0.04$

4 Test values

Table 2 — Test values

Size of key	Minimum hardness	Minimum proof torque ¹⁾	Size across flats of socket adapter		Key engagement ²⁾	
3			max.	min.	min.	
mm	HRC	N⋅m	mm	mm	mm	
0,7		0,08	0,724	0,711	1,5	
0,9		0,18	0,902	0,889	1,7	
1,3	7	0,53	1,295	1,270	2	
1,5]	0,82	1,545	1,520	2	
2	52	1,9	2,045	2,020	2,5	
2,5		3,8	2,560	2,520	3	
3		6,6	3,080	3,020	3,5	
4		16	4,095	4,020	5	
5	1	30	5,095	5,020	6	
6	· ·	52	6,095	6,020	8	
8	50	120	8,115	8,025	10	
10		220	10,115	10,025	12	
12	48	370	12,142	12,032	15	
14	ieh STA	590	14,142	14,032	17	
17	(cto	980	17,230	17,050	20	
19	(Sta	1360	19,275	19,065	23	
22		2110	22,275	22,065	26	
24 https://s	- 45 standards.iteh.ai/c:	2750	24,275	24,065	29	
27 maps.//	standards.iten.avca 9co	2829 3910 31/iso-20	27 ₂ 275	27,065	32	
32		6510	32,330	32,080	38	
36		9260	36,330	36,080	43	

¹⁾ $M_{\rm d} = 0.85 (0.7 \sigma_{\rm B}) (0.224 5 s^3)$

These values apply to the test only. In practice, key engagement is less.

5 Method of test

Insert the short arm of the key into a female hexagon socket adapter having a Rockwell hardness of not less than 60 HRC and apply the appropriate torque. Do not jerk or strike the key. Apply a steadily increasing load as near as possible to the end of the long arm until the proof torque is reached. The torque is calculated as the product of the applied load and the distance between the point of application of the load and the axis of the adapter. Test values are given in table 2.

Following the application of the test torque, the key shall show no permanent deformation or other damage which could influence usability.

 $[\]sigma_{\rm B}$ = tensile strength

²⁾ $t \approx 1.2 s (t \approx 1.5 s \text{ for sizes smaller than 1.5 mm}).$

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 2936:1983

https://standards.iteh.ai/catalog/standards/sist/01214861-c6fe-4a97-ba74-9cca829ce531/iso-2936-1983

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 2936:1983 https://standards.iteh.ai/catalog/standards/sist/01214861-c6fe-4a97-ba74-9cca829ce531/iso-2936-1983

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 2936:1983 https://standards.iteh.ai/catalog/standards/sist/01214861-c6fe-4a97-ba74-9cca829ce531/iso-2936-1983