

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
16790

ISO/TC 61/SC 5

Secretariat: DIN

Voting begins on:
2020-11-24

Voting terminates on:
2021-01-19

Plastics — Determination of drawing characteristics of thermoplastics in the molten state

Plastiques — Détermination des caractéristiques d'étirage des thermoplastiques à l'état fondu

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/FDIS 16790](https://standards.iteh.ai/catalog/standards/sist/d97499b6-ce59-4575-9f9b-f04267af5f4a/iso-fdis-16790)

<https://standards.iteh.ai/catalog/standards/sist/d97499b6-ce59-4575-9f9b-f04267af5f4a/iso-fdis-16790>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 16790:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/FDIS 16790

<https://standards.iteh.ai/catalog/standards/sist/d97499b6-ce59-4575-9f9b-f04267af5f4a/iso-fdis-16790>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	3
5 Apparatus	3
5.1 Apparatus for heating the polymer and forming the extrudate	3
5.1.1 General	3
5.1.2 Capillary extrusion rheometer	3
5.1.3 Extruder	4
5.2 Apparatus for drawing the polymer extrudate	5
5.2.1 Drawing unit	5
5.2.2 Drawing unit design	5
5.3 Data-acquisition system	7
6 Calibration	7
6.1 General	7
6.2 Test temperature	7
6.3 Capillary or rod die	7
6.4 Drawing force transducer	7
6.5 Drawing velocity and drawing acceleration	7
6.6 Drawing length	7
7 Sampling	8
8 Procedure	8
8.1 Cleaning the apparatus	8
8.2 Rheometer or extruder preparation	8
8.3 Loading the capillary rheometer barrel	9
8.4 Preheating	9
8.5 Running the extruder	10
8.6 Preliminary checks of the extrudates	10
8.6.1 Absence of defects	10
8.6.2 Check on drawing down under gravity	10
8.7 Determination of the extrudate behaviour	12
8.7.1 Determination of the mean velocity	12
8.7.2 Determination of the drawing force as a function of the drawing velocity	12
8.7.3 Measurement of melt strength	13
9 Calculation and expression of results	14
9.1 Initial cross-sectional area of the extrudate	14
9.2 Initial velocity	14
9.3 Drawing velocities	14
9.4 Drawing forces	15
9.5 Draw ratio	15
10 Precision	15
11 Test report	15
Bibliography	17

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

This second edition cancels and replaces the first edition (ISO 16790:2005), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the normative references have been updated;
- the figure keys have been completed;
- the test procedure and parameters have been revised.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Plastics — Determination of drawing characteristics of thermoplastics in the molten state

1 Scope

This document specifies a method for determining the drawing and break characteristics of molten plastics. The method involves the measurement of the force generated in deforming a molten filament under defined extrusion temperature and drawing conditions.

Data is generated under non-isothermal and non-homogeneous deformation conditions. However, it is useful for the interpretation of polymer behaviour in extensional flow.

The method is suitable for thermoplastics moulding and extrusion materials that can be extruded using a capillary extrusion rheometer, or an extruder with capillary rod die or other extrusion devices and have sufficient melt strength to be handled without difficulty.

The method is applicable to chemically stable materials that produce a uniform extrudate free from heterogeneities, bubbles, unmelted impurities, etc.

This method can provide information on

- processability for all extrusion techniques,
- the effect of mechanical and thermal history, and
- the effect of chemical structure, such as branching, entanglements and molecular mass.

This technique is one of a number of techniques that can be used to measure the extensional flow behaviour of a material. This method of measurement does not necessarily reproduce the drawing conditions to which thermoplastics are subjected to during their processing.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 11443, *Plastics — Determination of the fluidity of plastics using capillary and slit-die rheometers*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1 drawing

process of stretching a filament of polymer melt that is being continuously formed by a capillary extrusion rheometer or extruder or other extrusion device

**3.2
melt strength**

F_b
value of the melt tension at break of the extrudate

Note 1 to entry: Also known as the force to break.

Note 2 to entry: It is expressed in newtons.

**3.3
draw ratio at break
DR**

ratio of the *drawing velocity* (3.7) of the material at break to the *mean velocity* (3.4) of the material flowing from the die

**3.4
mean velocity**

v_m
average velocity of the extrudate at the die exit, determined as the ratio of volume flow rate to die cross-sectional area

Note 1 to entry: It is expressed in metres per second.

**3.5
initial diameter**

D_i
maximum diameter the extrudate attains after swelling on exiting from the die, the extrudate not yet having been subjected to significant drawing

Note 1 to entry: Initial diameter is expressed in metres.

Note 2 to entry: If no swelling of the extrudate occurs after exiting the die, the initial diameter is taken as the diameter of the die.

Note 3 to entry: This method can be unsuitable for testing materials that do not exhibit swelling of the extrudate after exiting the die as such materials will be difficult to handle in drawing off and will exhibit small *drawing forces* (3.8).

**3.6
initial velocity**

v_i
velocity of the extrudate near the die exit after swelling, the extrudate not yet having been subjected to significant *drawing* (3.1)

Note 1 to entry: It is determined at the position of the initial diameter of the extrudate.

Note 2 to entry: It is expressed in metres per second.

**3.7
drawing velocity**

v_t
velocity imposed on the lower end of the extrudate by the drawing unit

Note 1 to entry: It is expressed in metres per second.

**3.8
drawing force**

F_t
force exerted on the extrudate by the drawing unit

Note 1 to entry: It is expressed in newtons.

3.9 drawing length

 l_e

distance between the die exit and the point where the extrudate first contacts the drawing unit's rotating wheels

Note 1 to entry: It is expressed in metres.

3.10 drawing acceleration

 a

rate of increase in the *drawing velocity* (3.7)

Note 1 to entry: It is expressed in metres per square second.

3.11 drawing velocity at break

 v_b

velocity recorded at break when a constant *drawing acceleration* (3.10) is used

Note 1 to entry: It is expressed in metres per second.

4 Principle

Molten polymer is extruded from a capillary rheometer, extruder or other extrusion device at a specified temperature. The extrudate is drawn from the die by take-off wheels. Two techniques are used.

- a) A series of take-off wheel velocities is used to determine the drawing force as a function of the drawing velocity.
- b) A constant rate of acceleration of the take-off wheels is used to determine the melt strength (force to break) of the extrudate.

5 Apparatus


5.1 Apparatus for heating the polymer and forming the extrudate

5.1.1 General

The device to supply the molten polymer at a controlled temperature and flow rate shall consist of a heatable barrel [either a capillary extrusion rheometer (5.1.2) or an extruder (5.1.3)], the bore of which is closed at the bottom end by a die (see Figure 1). The test pressure shall be exerted on the melt contained in the barrel by a piston, a screw or pressurized gas.

5.1.2 Capillary extrusion rheometer

If a capillary extrusion rheometer is used, it shall have capillary dies, a piston, a temperature-measuring device and a pressure-measuring device meeting the requirements of ISO 11443.

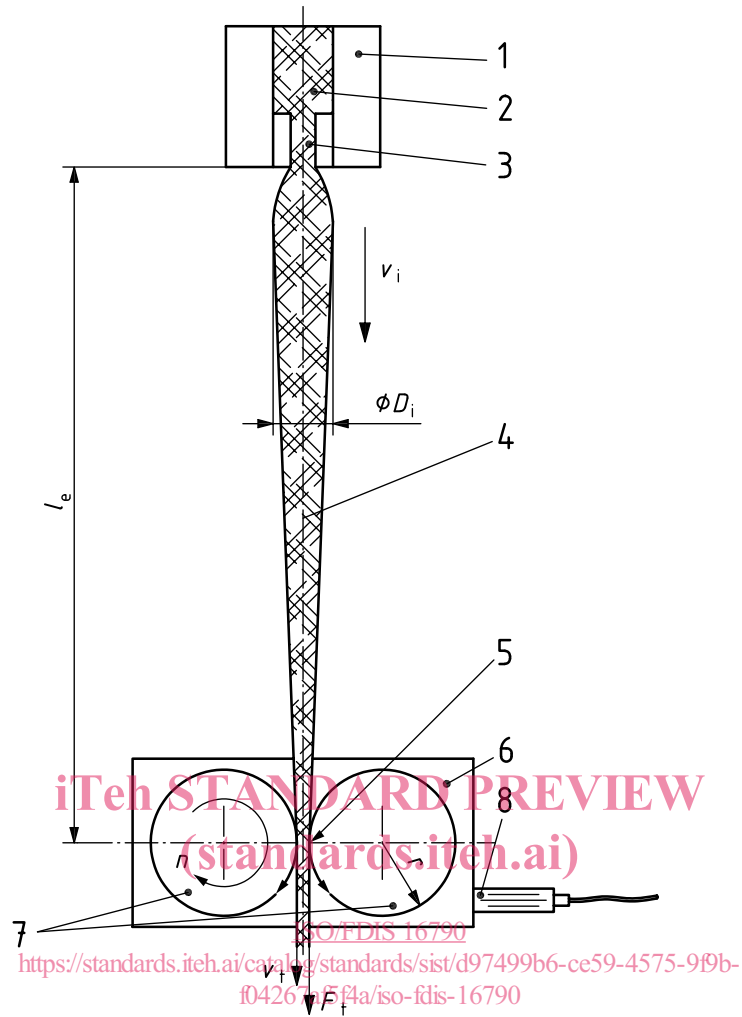

Key

- 1 rheometer or extruder
- 2 melt (temperature, T)
- 3 capillary (diameter, D ; length, l)
- 4 axis
- 5 extrudate/roller contact
- 6 drawing bench
- 7 drive rollers (radius, r ; rotational speed, n)
- 8 data acquisition (drawing force, F_t)
- D_i initial diameter
- l_e drawing length
- v_i initial velocity
- v_t drawing velocity ($= 2\pi rn$)

Figure 1 — Drawing unit — Direct drawing by two take-off rollers

5.1.3 Extruder

5.1.3.1 General

If an extruder is used, it shall be a small extruder with a screw diameter of 25 mm or less. This unit shall be equipped with a rod die and temperature-measuring device.

5.1.3.2 Melt pump

If available, a melt pump may be used to provide a uniform flow of material from the extruder to the die. If a melt pump is used, an extruder with a screw diameter larger than 25 mm may be used.

5.1.3.3 Dies

The die, of known dimensions, shall be angled vertically downwards to allow gravity to act on the extrudate.

For determining the apparent shear rate $\dot{\gamma}_{ap}$ and the apparent shear stress, τ_{ap} with one capillary die, in accordance with ISO 11443, the ratio l/D of the length, l , to the diameter, D , of the die shall be at least 16:1 and its inlet angle shall be 180° .

5.1.3.4 Temperature-measuring device

To measure the temperature of the molten polymer (see 6.2), thermocouples or platinum resistance sensors are preferred, but thermometers may be used.

5.2 Apparatus for drawing the polymer extrudate

5.2.1 Drawing unit

5.2.1.1 The drawing unit shall draw the extrudate over a specified length (the drawing length) at a controlled drawing velocity and measure the resulting drawing force.

5.2.1.2 The drawing unit shall have take-off wheels to draw the extrudate.

5.2.1.3 The drawing unit shall have controllers for the speed and acceleration of the take-off wheels.


5.2.1.4 The drawing unit shall have a force sensor to measure the drawing force exerted on the extrudate.

5.2.2 Drawing unit design

Drawing may be carried out directly under the die using two rollers to take off the extrudate without excessive slippage or pinching (see Figure 1). Alternatively, it may be carried out, after the extrudate passes around the groove of one or more free-return pulley(s), by a set of two rollers that pinch and take off the extrudate without excessive slippage (Figure 2 shows a possible design: other designs are applicable). Drawing can also be done by winding up the extrudate onto a single wheel. In all cases, the axis of the extrudate in contact with the rollers (see Figure 1), the first return pulley (see Figure 2) or the take-off wheel shall coincide with the capillary die axis.

Where the extrudate passes over a return roller, drawing is considered to occur only in the section between the die exit and the initial point of contact between the extrudate and the pulley groove. In this case, the speed and drawing force of the first return pulley should preferably be measured.

The return pulley may be cooled in order to prevent any sticking of the molten polymer. The same precaution may be taken for the drawing rollers. In both cases, it is important to ensure that these devices do not have a significant influence on the measurement of the drawing force due to frictional or inertial effects or on the drawing velocity and drawing acceleration due to slippage and pinching.

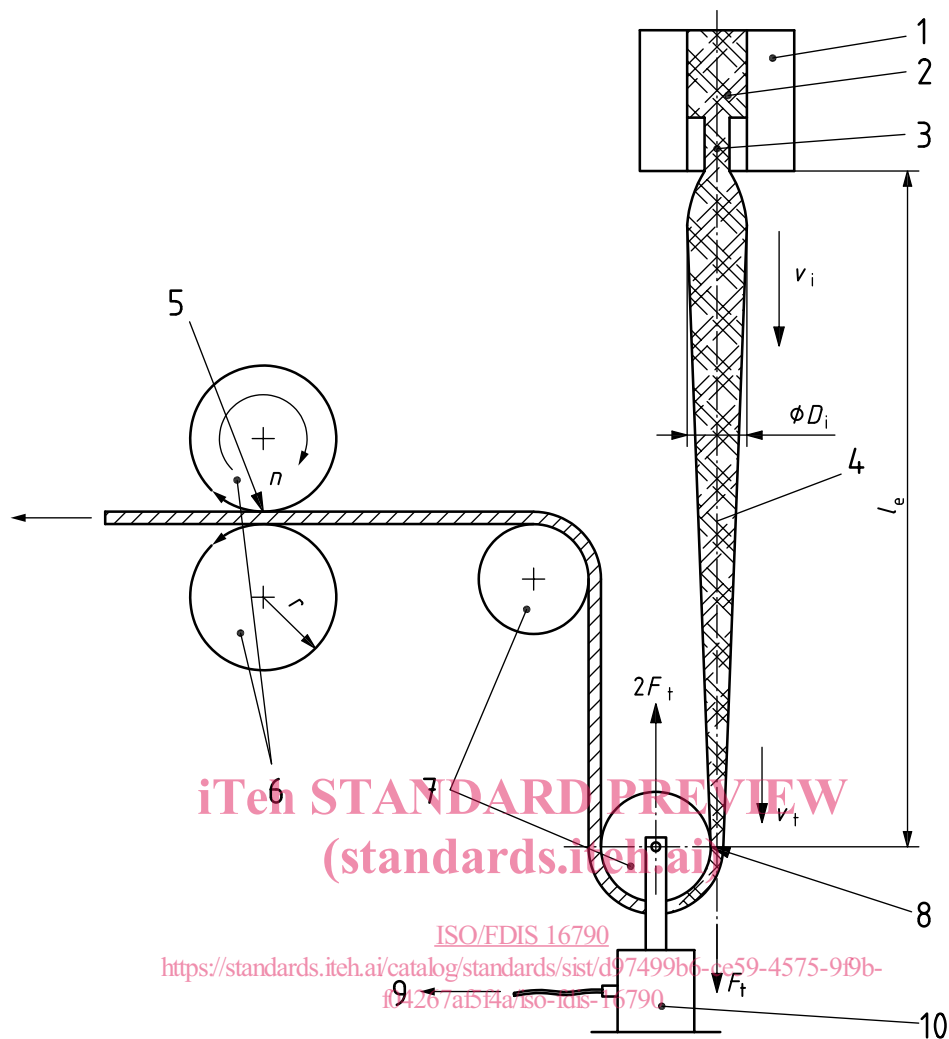

Key

- 1 rheometer or extruder
 - 2 melt (temperature, T)
 - 3 capillary (diameter, D ; length, l)
 - 4 axis
 - 5 driven, pinched extrudate
 - 6 drive rollers (radius, r ; rotational speed, n)
 - 7 return pulleys (free axis of rotation)
 - 8 extrudate contact
 - 9 data acquisition
 - 10 force transducer (drawing force, F_t)
- D_i initial diameter
 l_e drawing length
 v_i initial velocity
 v_t drawing velocity ($= 2\pi rn$)

Figure 2 — Drawing unit — Typical “take-off after return pulley” design

5.3 Data-acquisition system

The data-acquisition system shall be capable of continuously monitoring the drawing force, the drawing velocity, the temperature of the molten material, and the pressure of the melt at the entrance to the die throughout the test.

6 Calibration

6.1 General

The extruder or the rheometer shall be calibrated with respect to the measured variables and parameters, such as temperature, pressure, volume flow rates and capillary dimensions, in accordance with the procedures described in ISO 11443.

6.2 Test temperature

When capillary dies are used, the test temperature shall be either the temperature of the melt in the barrel near the capillary inlet or, if this is not possible, the temperature of the barrel wall near the capillary inlet. This also pertains to the rod die of the extruder. When the barrel wall temperature is measured, thermally conductive fluids may be used in the thermometer well to improve conduction.

The temperature-measuring device used during the test shall have a resolution of 0,1 °C and be calibrated to an accuracy of $\pm 0,5$ °C by a method traceable to certified reference standard(s).

No liquids that can contaminate the die and barrel and influence the ensuing measurements (e.g. silicone oil) shall be used as heat-transfer media during calibration. Woods metal has been found to be a suitable thermal conductor.

6.3 Capillary or rod die

ISO/FDIS 16790

<https://standards.iteh.ai/catalog/standards/sist/d97499b6-ce59-4575-9f9b-f04267af5f4a/iso-fdis-16790>

The dimensions of the die shall be measured to an accuracy of $\pm 0,007$ mm for the diameter, D , and $\pm 0,025$ mm for the length, l .

For comparisons between laboratories, a die having an l to D ratio of 16 to 1 and with a 180° inlet angle shall be used.

6.4 Drawing-force transducer

Calibration of the drawing-force transducer shall be carried out in accordance with the manufacturer's recommendations. The accuracy of the force measurement system shall have a maximum permissible error of ± 1 % of full scale.

6.5 Drawing velocity and drawing acceleration

The drawing velocity and drawing acceleration shall both have a maximum permissible error of ± 1 % of full scale. The apparatus may be calibrated with respect to these parameters by measuring the time for a known length of (non-stretchable) material, e.g. paper, to traverse the drawing rollers with and without acceleration, or from measurement of the rotational speed of the drawing rollers.

6.6 Drawing length

This is measured using a device such as a ruler or tape measure. The distance shall be measured to an accuracy of within ± 5 %.

For comparisons between laboratories, the drawing length shall be 100 mm \pm 10 mm.

NOTE This short drawing length minimizes the cooling of the extrudate and thus maintains a more uniform temperature range over the entire length of the extrudate.