

SLOVENSKI STANDARD SIST EN ISO 12460-2:2025

01-maj-2025

Lesne plošče - Ugotavljanje sproščanja formaldehida - 2. del: Metoda z majhno komoro (ISO 12460-2:2024)

Wood-based panels - Determination of formaldehyde release - Part 2: Small-scale chamber method (ISO 12460-2:2024)

Holzwerkstoffe - Bestimmung der Formaldehydabgabe - Teil 2: Kleinprüfkammerverfahren (ISO 12460-2:2024)

Panneaux à base de bois - Détermination du dégagement de formaldéhyde - Partie 2: Méthode à la petite chambre (ISO 12460-2:2024)

Ta slovenski standard je istoveten z: EN ISO 12460-2:2025

ICS:

79.060.01 Lesne plošče na splošno Wood-based panels in

general

SIST EN ISO 12460-2:2025 en,fr,de

iTeh Standards (https://standards.iteh.ai) Document Preview

SIST EN ISO 12460-2:2025

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025

EUROPEAN STANDARD NORME EUROPÉENNE EUROPÄISCHE NORM

EN ISO 12460-2

February 2025

ICS 79.060.01

English Version

Wood-based panels - Determination of formaldehyde release - Part 2: Small-scale chamber method (ISO 12460-2:2024)

Panneaux à base de bois - Détermination du dégagement de formaldéhyde - Partie 2: Méthode à la petite chambre (ISO 12460-2:2024) Holzwerkstoffe - Bestimmung der Formaldehydabgabe - Teil 2: Kleinprüfkammerverfahren (ISO 12460-2:2024)

This European Standard was approved by CEN on 24 February 2025.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025



EUROPEAN COMMITTEE FOR STANDARDIZATION COMITÉ EUROPÉEN DE NORMALISATION EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

EN ISO 12460-2:2025 (E)

Contents	Page
_	
European foreword	3

iTeh Standards (https://standards.iteh.ai) Document Preview

SIST EN ISO 12460-2:2025

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025

European foreword

The text of ISO 12460-2:2024 has been prepared by Technical Committee ISO/TC 89 "Wood-based panels" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 12460-2:2025 by Technical Committee CEN/TC 112 "Wood-based panels" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2025, and conflicting national standards shall be withdrawn at the latest by August 2025.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

Any feedback and questions on this document should be directed to the users' national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

Endorsement notice

The text of ISO 12460-2:2024 has been approved by CEN as EN ISO 12460-2:2025 without any modification.

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-202.

iTeh Standards (https://standards.iteh.ai) Document Preview

SIST EN ISO 12460-2:2025

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025



International Standard

ISO 12460-2

Wood-based panels — Determination of formaldehyde release —

Part 2:

Small-scale chamber method

Panneaux à base de bois — Détermination du dégagement de formaldéhyde —

Partie 2: Méthode à la petite chambre

SIST EN ISO 12460-2:20:

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025

Second edition 2024-02

iTeh Standards (https://standards.iteh.ai) Document Preview

SIST EN ISO 12460-2:2025

https://standards.iteh.ai/catalog/standards/sist/a4e891ef-0976-4b57-b503-63939ffa11ab/sist-en-iso-12460-2-2025



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Email: copyright@iso.org Website: www.iso.org

Website: www.iso.org
Published in Switzerland

Contents		Page
Forev	vord	iv
1	Scope	1
2	Normative references	
3	Terms and definitions	
4	General	2
5	Significance and use	2
6	Interferences	
7	Apparatus 7.1 Test chamber 7.1.1 General 7.1.2 Air exchange rate 7.1.3 Air circulation 7.1.4 Make-up air 7.1.5 Equipment for monitoring of test conditions 7.1.6 Air sampling port 7.2 Air sampling system 7.2.1 Sampling system for wet-chemistry analysis 7.2.2 Direct sampling	3 3 3 3 3 3 3 4 4 5
8	Sample material handling and specimen conditioning 8.1 Handling 8.2 Test specimen 8.3 Conditioning 8.4 Sealing of test piece edges	5 5
9 tps://sta	Procedure 9.1 Test conditions 9.2 Test procedure for materials 9.3 Air sampling 9.4 Analysis of air samples 9.4.1 General 9.4.2 Equivalence of analytical procedures – General requirements	6 7 7 4460 - 7
10	Calculation	8
11	Determination of air exchange rate	9
12	Test report	9
Anne	x A (informative) Test chambers	11
Anne	x B (informative) Conversion of formaldehyde test results	23
Anne	Annex C (normative) Analytical procedure of formaldehyde determination	
Anne	x D (informative) Establishing of a correlation	56
Biblio	ography	75

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 89, Wood-based panels.

This second edition cancels and replaces the first edition (ISO 12460-2:2018), which has been technically revised.

The main changes are as follows:

— implementation of different chamber sizes, analytical procedures, re-calculation of results to other standard parameters and establish a correlation between reference chamber method and the method used for factory production control.

A list of all parts in the ISO 12460 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Wood-based panels — **Determination of formaldehyde** release —

Part 2:

Small-scale chamber method

1 Scope

This document specifies a procedure for a chamber test with different options of chamber sizes to measure the formaldehyde concentrations in air from wood products under defined test conditions of temperature, relative humidity, loading and air exchange rate.

Results obtained from this small-scale chamber test method can be used for quality control (factory production control – 'FPC') based on correlation established by reference chamber test methods according to ISO, EN or ASTM standards. The establishment of a correlation is described in $\underline{\text{Annex D}}$.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- http://disco.org/obp.1939ffa11ab/sist-en-iso-12460-2-2025
 - IEC Electropedia: available at https://www.electropedia.org/

3.1

air exchange rate

N

quotient of air volume Q passing through the chamber per hour (m³/h) and the chamber volume (m³) expressed in (h⁻¹)

3.2

loading ratio

L

total exposed surface area, excluding panel edges, of the product being tested divided by the test chamber's volume (m^2/m^3)

3.3

make-up airflow

0

quantity of conditioned and filtered air fed into the chamber per unit time, in m³/h

3.4

Q/A ratio

ratio of air flow through the chamber (Q) to sample surface area (A), in m³/h m²

3.5

sample surface area

4

total area of all sample faces exposed in the chamber, in m²

3.6

measured concentration

 $\boldsymbol{\mathcal{C}}$

formaldehyde concentration (expressed in mg/m^3 and/or ppm rounded to 2 decimal places) under the defined environmental test parameters of this method. In the case of a establishing a correlation, it can be advantageous to round the results to 3 decimal places

3.7

chamber volume

V

interior volume of the test chamber, in m^3

4 General

This document specifies the measurement to quantify the amount of formaldehyde in an air sample from a test chamber accepted in a range of sizes (examples are described in $\underline{\text{Annex A}}$) and as determined by different analytical methods as specified in $\underline{\text{Annex C}}$. Other analytical procedures may be used to determine the quantity of formaldehyde in the air sample provided that such methods give equivalent results. The test report shall include full description of the analytical procedure employed.

The values stated in SI units are the standard values. Any values given in parentheses are for information only.

NOTE This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate health and safety practices and determine the applicability of regulatory limitations prior to use.

5 Significance and use

- **5.1** Various national and regional regulations on formaldehyde emission levels have been established for wood panels. This international test method was adapted from chamber test methods specified in different EN, ISO and ASTM standards. This test method provides a means of testing smaller samples and reduces the time required for testing compared with a reference chamber method.
- **5.2** Formaldehyde concentration levels obtained by this small-scale chamber method can differ from expected in full-scale indoor environments. Variations in product loading, temperature, relative humidity, and air exchange will affect formaldehyde emission rates and thus likely indoor air formaldehyde concentrations.
- **5.3** This test method is applicable for the use of a chambers from $0.004 \, \text{m}^3$ to $1 \, \text{m}^3$ in volume (see examples in Annex A) to evaluate the formaldehyde concentration in air using the following controlled conditions which are defined within this standard method:
- a) conditioning of specimens prior to testing;
- b) exposed surface area of the specimens in the test chamber;
- c) edge sealing;
- d) test chamber temperature and relative humidity;
- e) the *Q/A* ratio;
- f) air exchange rate within the chamber.

6 Interferences

Interferences of the used analytical methods should be determined by reference to other applicable standard test methods.

7 Apparatus

7.1 Test chamber

7.1.1 General

The interior volume of the small chamber shall be between 0,004 m³ and 1 m³ (examples see Annex A). The interior of the test chamber shall be free of refrigeration coils that condense water and items such as humidifiers with water reservoirs since water has the potential for collecting formaldehyde and thus influencing test results. The interior surfaces of the small chamber, including any sample support system, shall be a non-absorbent material. For example, stainless steel, aluminium, and polytetrafluoroethylene (PTFE) have been found appropriate as chamber lining materials. All joints except for doors used for loading and unloading specimens should be sealed. Doors shall be self-sealing.

7.1.2 Air exchange rate

The clean and conditioned air supply to the chamber shall either be monitored continuously or frequently during testing.

The air exchange rate shall not vary by more than ±5 %.

The effective air exchange shall be regularly checked, by using e.g. either a calibrated gas meter, or the tracer gas procedure (see <u>Clause 11</u>).

7.1.3 Air circulation Document Pr

Low speed mixing fans or multi-port inlet and outlet diffusers are two techniques that have been used successfully to ensure mixing of the chamber air over all sample surfaces. If the air exchange is higher than 10/h mixing fans are not necessary.

7.1.4 Make-up air

The make-up air should come from a filtered dust-free environment and contain no more than 0,006 mg/m³ of formaldehyde. Make-up air for the chamber shall pass through a calibrated air flow measuring device. If the make-up air is taken from a conditioning environment it should contain no more than 0,012 mg/m³.

7.1.5 Equipment for monitoring of test conditions

Measuring equipment and recording facilities capable of continuous or frequent monitoring of the specified test conditions with an error limit as follows:

Temperature: 0,1 K;

Relative humidity: 2 %;

Air exchange rate: 0,03/h.

7.1.6 Air sampling port

The exhaust flow (that is, chamber outlet) is normally used as the sampling point, although separate sampling ports in the chamber can be used. The sampling system shall be constructed of a material to minimize absorption (for example, glass or stainless steel), and the system should be maintained at the same temperature as the test chambers.

7.2 Air sampling system

7.2.1 Sampling system for wet-chemistry analysis

7.2.1.1 General


Figure 1 shows the principle of a sampling system for the determination of the formaldehyde concentration in the chamber air. The sampling tube shall be placed either in the air outlet, or inside the chamber, close to the air outlet.

Other sampling systems may be used based on the requirements of the analytical procedure used.

The numbers in brackets refer to the numbers in Figure 1:

7.2.1.2 sampling tube (1).

- one or two 30 ml up to 100 ml gas washing bottle(s) (2), with inserts like impinger or Muenke or frits, containing between 8 ml to 40 ml absorber solution, or DNPH cartridges for absorption and subsequent determination of formaldehyde.
- 7.2.1.4 silica absorber for drying the air (3).
- 7.2.1.5 gas flow valve (4).
- 7.2.1.6 gas sampling pump (5).
- 7.2.1.7
- gas meter (including a thermometer) for measuring the volume of air (7). 7.2.1.8
- 7.2.1.9 air pressure meter (8).

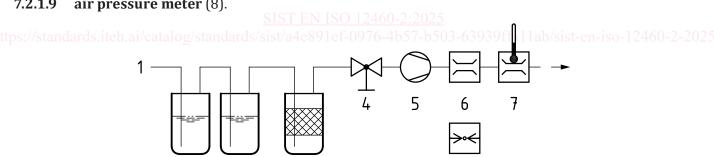

Key

- 1 sampling tube
- 2 gas washing bottle
- 3 silica absorber
- gas flow valve

- 5 gas sampling pump
- 6 gas flow meter
- gas meter with thermometer
- air pressure meter

Figure 1 — Example of a sampling system for the determination of formaldehyde concentration in