



Designation: ~~D1929–11~~ Designation: D1929 – 12

Standard Test Method for Determining Ignition Temperature of Plastics¹

This standard is issued under the fixed designation D1929; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope*

1.1 This fire test response test method² covers a laboratory determination of the flash ignition temperature and spontaneous ignition temperature of plastics using a hot-air furnace.

~~1.2 **Caution**—During the course of combustion, gases or vapors, or both, are evolved that may be hazardous to personnel. Adequate precautions should be taken to protect the operator.~~

~~1.2 **Caution**—During the course of combustion, gases or vapors, or both, are evolved that have the potential to be hazardous to personnel.~~

~~1.3 *This standard is used to measure and describe the response of materials, products, or assemblies to heat and flame under controlled conditions, but does not by itself incorporate all factors required for fire hazards or fire risk assessment of materials, products, or assemblies under actual fire conditions.*~~

~~1.4 *This standard is used to measure and describe the response of materials, products, or assemblies to heat and flame under controlled conditions, but does not by itself incorporate all factors required for fire-hazard or fire-risk assessment of the materials, products, or assemblies under actual fire conditions.*~~

~~1.4 *Fire testing is inherently hazardous. Adequate safeguards for personnel and property shall be employed in conducting these tests.*~~

~~1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. Specific precautionary statements are given in 1.2 and 1.3.*~~

NOTE 1—This test method and ISO 871-1996 are identical in all technical details.

2. Referenced Documents

2.1 ASTM Standards:³

D618 Practice for Conditioning Plastics for Testing

E176 Terminology of Fire Standards

2.2 International Standards:⁴

ISO 871-1996 Plastics—Determination of Ignition Temperature Using a Hot-Air Furnace

ISO 5725 Precision of Test Methods—Determination of Repeatability and Reproducibility for Standard Test Methods by Interlaboratory Tests

IEC 584-2 Thermocouples—Part 2: Tolerances

3. Terminology

3.1 For definitions of terms relating to fire, see Terminology E176.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *flash ignition temperature (FIT)*—the minimum temperature at which, under specified test conditions, sufficient flammable

¹ This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.30 on Thermal Properties.30.03). Current edition approved Sept. 15, 2011. Published September 2011. Originally approved in 1962. Last previous edition approved in 2010 as D1929–10. DOI:10.1520/D1929-11.

² Current edition approved April 15, 2012. Published June 2012. Originally approved in 1962. Last previous edition approved in 2011 as D1929 – 11. DOI:10.1520/D1929-12.

In 1996, this test method was totally revised to be technically equal to ISO 871-1996, and a specific air velocity is specified, which eliminates the need for approximations.

³ The following reference may be of interest in connection with this test method: Stetchkin, N. P., "A Method and Apparatus for Determining the Ignition Characteristics of Plastics," *Journal of Research*, National Institute of Standards and Technology, Vol 43, No. 6, December 1949 (RP 2052), p. 591.

⁴ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁴ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, http://www.ansi.org.

*A Summary of Changes section appears at the end of this standard.

gases are emitted to ignite momentarily upon application of a small external pilot flame.

3.2.2 *glowing combustion*—combustion of a material in the solid phase without flame but with emission of light from the combustion zone, caused by slow decomposition and carbonization at various points in the specimen, without general ignition occurring.

3.2.3 *spontaneous ignition temperature or self-ignition temperature (SIT)*—the minimum temperature at which the self-heating properties of the specimen lead to ignition or ignition occurs of itself, under specified test conditions, in the absence of any additional flame ignition source.

4. Significance and Use

4.1 Tests made under conditions herein prescribed can be of considerable value in comparing the relative ignition characteristics of different materials. Values obtained represent the lowest ambient air temperature that will cause ignition of the material under the conditions of this test. Test values are expected to rank materials according to ignition susceptibility under actual use conditions.

4.2 This test is not intended to be the sole criterion for fire hazard. In addition to ignition temperatures, fire hazards include other factors such as burning rate or flame spread, intensity of burning, fuel contribution, products of combustion, and others.

5. Apparatus

5.1 *Hot-Air Ignition Furnace*—A furnace similar to that shown in Fig. 1, consisting primarily of an electrical heating unit and specimen holder.

5.2 *Furnace Tube*—A vertical tube with an inside diameter of 100 ± 5 mm and a length of 230 ± 20 mm, made of a ceramic that will withstand at least 750°C . The vertical tube stands on the furnace floor, fitted with a plug for the removal of accumulated residue.

5.3 *Inner Ceramic Tube*—A ceramic tube that will withstand at least 750°C , with an inside diameter of 75 ± 5 mm, length of 230 ± 20 mm, and thickness of approximately 3 mm, placed inside the furnace tube and positioned 20 ± 2 mm above the furnace floor on three small spacer blocks. The top is covered by a disk of heat-resistant material with a 25 ± 2 -mm diameter opening in the center that is used for observation and passage of smoke and gases. The pilot flame is located immediately above the opening.

NOTE 2—Fire resistant materials such as silica glass and stainless steel have also been found suitable for this application.

5.4 *Air Source*—An outside air source to supply clean air near the top of the annular space between the ceramic tubes, through a copper tube at a steady and controllable rate. Air shall be heated and circulated in the space between the two tubes and enter the inner furnace tube at the bottom. Air shall be metered by a rotameter or other suitable device.

5.5 *Electrical Heating Unit*, contained within the mineral fiber sleeve and constructed of 50 turns of 1.3 ± 0.1 mm Nichrome V alloy wire, wound around the furnace tube and embedded in heat-resistant cement.

NOTE 3—Other constructions such as finely coiled wire embedded in molded ceramic fiber have also been found to be acceptable.

5.6 *Insulation*, consisting of a layer of mineral fiber, approximately 60-mm thick, and covered by a metal jacket.

5.7 *Pilot Igniter*, consisting of a nominal 1.8 ± 0.3 -mm inside diameter (ID) copper tubing attached to a gas supply of 94 % minimum purity propane and placed horizontally 5 ± 1 mm above the top surface of the disk cover. The pilot flame shall be adjusted to 20 ± 2 mm in length and centered above the opening in the disk cover.

5.8 *Specimen Support and Holder*—The specimen pan consists of a metal container of approximately 0.5-mm thick steel measuring 40 ± 2 mm in diameter by 15 ± 2 mm in depth. It is held in a ring of approximately 2.0-mm diameter stainless steel welding rod. The ring is welded to a length of the same type of rod extending through the cover of the furnace, as shown in Fig. 1. The bottom of the specimen pan shall be located 185 ± 5 mm down from the top of the inner furnace tube.

5.9 *Thermocouples*, 0.5-mm diameter, Chromel-Alumel (Type K) or Iron-Constantan (Type J), for temperature measurement connected to a calibrated recording instrument with a tolerance not exceeding $\pm 2^{\circ}\text{C}$. The thermocouple tolerance shall be in accordance with IEC 584-2, Table 1, Class 2 or better.

5.10 *Heating Control*—A suitable variable transformer or an automatic controller connected in series with the heating coils.

5.11 *Timing Device*, having an accuracy of at least 1 s.

6. Location of Thermocouples

6.1 Thermocouple TC_1 measures the temperature, T_1 , of the specimen. It is located as close as possible to the center of the upper surface of the specimen when the specimen is in place within the furnace. The thermocouple wire is attached to the specimen support rod.

6.2 Thermocouple TC_2 gives some indication of the temperature, T_2 , of the air traveling past the specimen. It is located 10 ± 2 mm below the center of the specimen pan. The thermocouple wire is attached to the specimen support rod.

NOTE 4—Thermocouple TC_2 may be installed through a hole drilled adjacent to the inspection plug below the specimen pan.

6.3 Thermocouple TC_3 measures the temperature, T_3 , of the heating coil. It is located adjacent to the furnace heating coil and is used as a reference for temperature adjustment purposes because of its faster response.

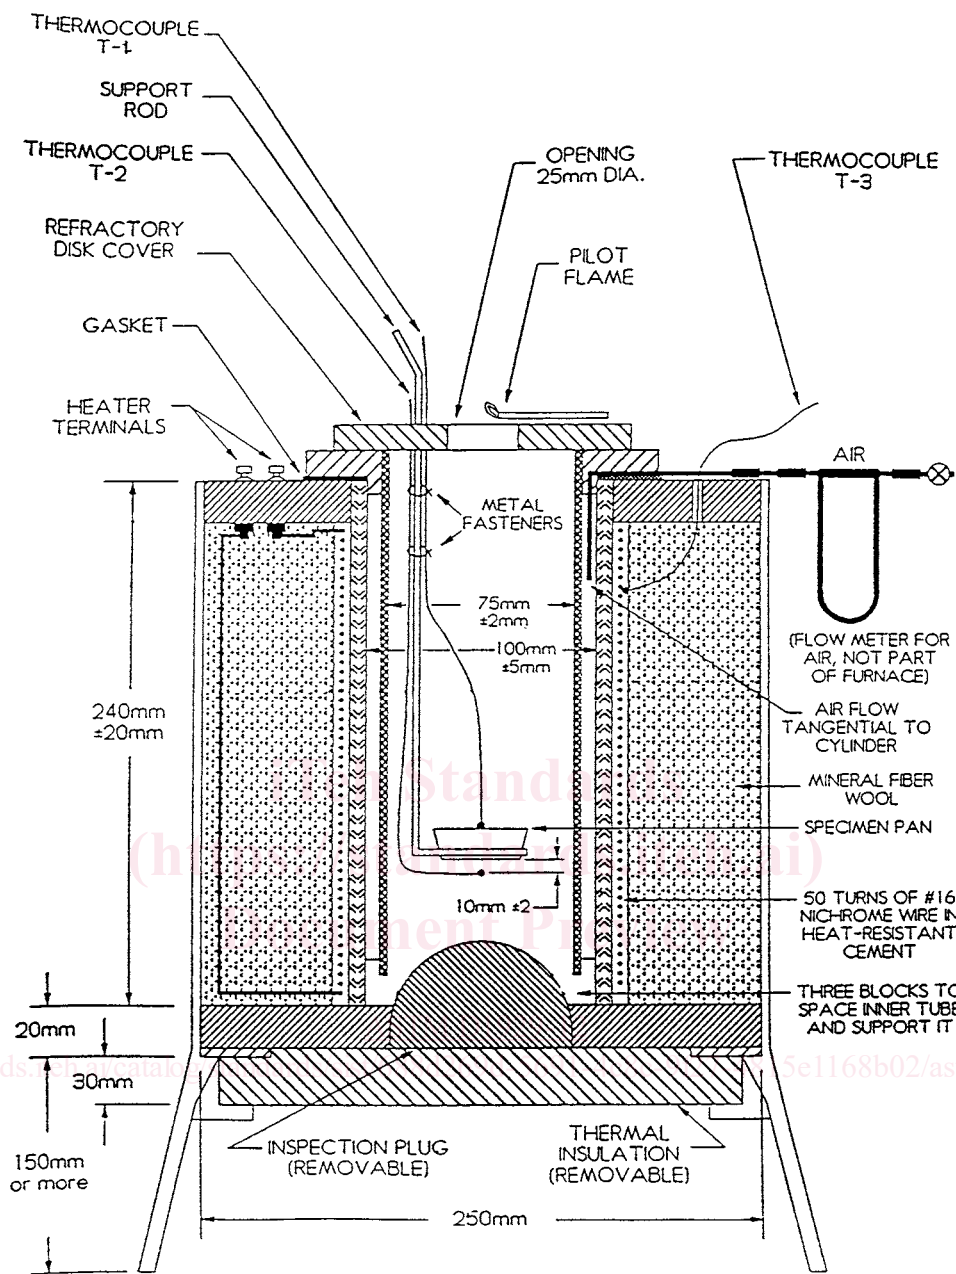


FIG. 1 Cross Section of Hot-Air Ignition Furnace

NOTE 5—Thermocouple TC_3 may be a 1.6 ± 0.1 -mm diameter metallic sheathed thermocouple.

7. Test Specimens

7.1 Materials supplied in any form, including composites, may be used, but it is essential that the form be described fully in the test report.

7.1 It is acceptable to use as test specimens materials, or products, supplied in any form, with some examples being pellets, powders and films. It is also acceptable to use composites as test specimens. The test report shall include full details of the form in which the test specimens have been tested.

NOTE 6—Specimens containing high levels of inorganic fillers are difficult to evaluate.

NOTE 7—The same material tested in different forms may give different results. 7—In some cases the same material will give different results if tested in different forms.

7.2 A specimen mass of 3.0 ± 0.2 g shall be used for materials having a density greater than 100 kg/m^3 . Materials may be tested in the form

7.2.1 *Instructions for Specific Types of pellets or powder, normally supplied for molding. For Test Specimens:*

7.2.1.1 For sheet materials, cut the sheet into squares of 20 ± 2 by 20 ± 2 mm maximum size, and stack these to a height that gives the required specimen mass.