# INTERNATIONAL STANDARD

ISO 13259

Third edition 2020-07

Thermoplastics piping systems for underground non-pressure applications — Test method for leaktightness of elastomeric sealing ring type joints

ISO 13259:2020 https://standards.iteh.ai/catalog/standards/sist/ec7b5a1b-47d0-439e-8b00-9c5d7bf7a451/iso-13259-2020



## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 13259:2020 https://standards.iteh.ai/catalog/standards/sist/ec7b5a1b-47d0-439e-8b00-9c5d7bf7a451/iso-13259-2020



#### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland

Contents		Page
Fore	eword	iv
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Terms and definitions  Principle	1
5	Apparatus 5.1 General 5.2 Components of the apparatus	2 2
6	Test pieces	
7	Temperature of conditioning and testing	5
8	Procedure 8.1 General procedure 8.2 Procedure for applying diametric deflection to spigot and socket	5
9	Test report	10

# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 13259:2020 https://standards.iteh.ai/catalog/standards/sist/ec7b5a1b-47d0-439e-8b00-9c5d7bf7a451/iso-13259-2020

#### **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see <a href="www.iso.org/directives">www.iso.org/directives</a>).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see <a href="https://www.iso.org/patents">www.iso.org/patents</a>).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see <a href="https://www.iso.org/iso/foreword.html">www.iso.org/iso/foreword.html</a>. (Standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 138, *Plastic pipes, fittings and valves for the transport of fluids*, Subcommittee SC 1, *Plastics pipes and fittings for soil*, waste and drainage (including land drainage), in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 155, *Plastics piping systems and ducting systems*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 13259:2018), of which it constitutes a minor revision.

The main changes compared to the previous edition are as follows:

— in <u>8.2</u>, the text was clarified and a calculation error was corrected.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at <a href="https://www.iso.org/members.html">www.iso.org/members.html</a>.

### Thermoplastics piping systems for underground nonpressure applications — Test method for leaktightness of elastomeric sealing ring type joints

### 1 Scope

This document specifies a test method for determining the leaktightness of elastomeric sealing ring type joints for buried thermoplastics non-pressure piping systems.

Unless otherwise specified in the referring standard, the tests are carried out at the following basic test pressures:

- $p_1$ : internal negative air pressure (partial vacuum);
- $p_2$ : a low internal hydrostatic pressure;
- $p_3$ : a higher internal hydrostatic pressure.

It also describes the following four test conditions under which the tests are performed:

- a) Condition A: without any additional diametric or angular deflection;/
- b) Condition B: with diametric deflection ards.iteh.ai)
- c) Condition C: with angular deflection;

ISO 13259:2020

d) Condition D: with simultaneous angular and diametric deflection e-8600-

The applicable selection of the test pressure(s) and the test condition(s) is/are specified in the referring standard.

#### 2 Normative references

There are no normative references in this document.

#### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <a href="https://www.iso.org/obp">https://www.iso.org/obp</a>
- IEC Electropedia: available at <a href="http://www.electropedia.org/">http://www.electropedia.org/</a>

#### 4 Principle

A test piece assembled from pipes and/or fittings is subjected to a specific initial internal negative air pressure,  $p_1$ , followed by a low specific initial internal hydrostatic pressure,  $p_2$ , and a higher internal hydrostatic pressure,  $p_3$ .

During testing the joint may be subjected to diametric and/or angular deflection(s). The referring product standard shall specify which of the test pressures and deflection conditions have to be carried out.

#### ISO 13259:2020(E)

Each pressure is maintained for a specific period during which the joint is monitored for leakage (see Clause 8).

It is assumed that the following test parameters are set by the referring standard:

- the test pressure(s),  $p_1$  [see 8.1, item e)],  $p_2$  [see 8.1, item g)] and  $p_3$  [see 8.1, item h)], as applicable, and the percentage of loss of partial vacuum [see 8.1, item e]];
- the required diametric and angular deflections and their combination with each other and/or the test pressure(s).

#### **Apparatus** 5

#### 5.1 General

The apparatus shall consist of a jig or any other arrangement capable of:

- applying the specified diametric and angular deflection; a)
- applying the specified test pressure(s), positive or negative; b)
- maintaining the test assembly in the required position throughout the test; c)
- resisting the forces resulting from the mass of the water in the test assembly and from the applied hydrostatic test pressure(s) during the test period.

  ANDARD PREVIEW


The apparatus shall not otherwise support the joint against the internal test pressure.

A typical arrangement, allowing angular and diametric deflection, is shown in Figure 1.

ISO 13259:2020

standards.iten.ai

https://standards.iteh.ai/catalog/standards/sist/ec7b5a1b-47d0-439e-8b00-9c5d7bf7a451/iso-13259-2020

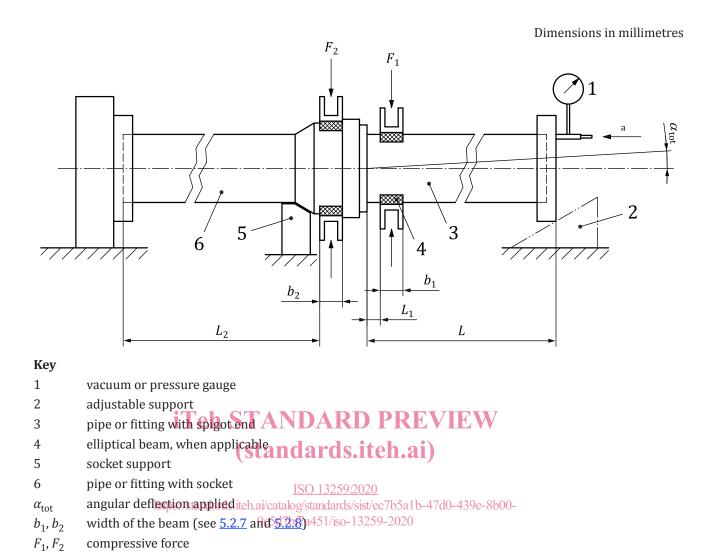

Connection to pressure source.

Figure 1 — Typical arrangement for applying diametric deflection and angular deflection

length of spigot-ended pipe or fitting, where  $L \ge d_e$  or  $L \ge 1\,000$ , whichever is the greater, in millimetres

distance between the end of pipe and the beam (in contact of the socket), where  $L_2 \ge 1~000$  for testing

pipes only. For testing other components (e.g. inspection chambers, manholes, fittings of large diameters)

#### 5.2 Components of the apparatus

 $L_2$  may be reduced.

distance between socket mouth and beam

L

 $L_1$ 

 $L_2$ 

а

- **5.2.1** The apparatus shall include the following items which each shall be capable of resisting the forces and pressures generated during the test.
- **5.2.2 End sealing devices**, having a size and using a sealing method appropriate to seal the non-jointed ends of the test assembly. The devices shall be restrained in a manner that does not exert longitudinal forces on the joint at positive pressures.
- **5.2.3 Hydrostatic pressure source**, connected to one of the sealing devices, or to the test piece, and capable of applying and maintaining the specified pressure [see <u>8.1</u>, items g) and h)].

- **5.2.4 Negative air pressure source**, connected to one of the sealing devices, or to the test piece, and capable of applying and maintaining the specified internal negative air pressure for the specified time. [See <u>8.1</u>, item e)].
- **5.2.5 Arrangement**, capable of venting air from the assembly.
- **5.2.6 Pressure measuring devices**, capable of checking conformity to the specified test pressure [(see 8.1, items e), g) and h)] located at the upper point of the test assembly.

When testing with diametric deflection is required the following items shall also be included.

**5.2.7 Mechanical** or **hydraulic device**, capable of applying the necessary diametric deflection to the spigot [see <u>8.1</u>, item b)] and acting on a beam which is free to move in the vertical plane square to the axis of the pipe. For pipes with a diameter equal to or greater than 400 mm, each beam can be elliptically shaped to suit the expected shape of the pipe when deflected as required, see <u>Figure 4</u>. The length of the beam or the curved part of the beam shall be greater than the contact area with the deflected spigot.

The following width,  $b_1$ , (see Figure 1), shall depend upon the external diameter,  $d_{\rm e}$ , of the pipe:

- $b_1 = 100 \text{ mm for } d_e \le 710 \text{ mm};$
- $b_1 = 150 \text{ mm for } 710 \text{ mm} < d_e \le 1000 \text{ mm};$
- $b_1 = 200 \text{ mm for } d_e > 1000 \text{ mm}.$

iTeh STANDARD PREVIEW

**5.2.8 Mechanical** or **hydraulic device**, capable of applying the necessary diametric deflection to the socket [see 8.1, item b)] and acting on a beam which is free to move in the vertical plane square to the axis of the socket. The length of the beam or the curved part of the beam shall be greater than the contact area with the deflected socket.


ISO 13259:2020

For pipes with a diameter equal to or greater than 400 mm, each beam may be elliptically shaped to suit the expected shape of the socket when deflected as required, see Figure 4.

The following width,  $b_2$ , shall depend upon the external diameter,  $d_{\rm e}$ , of the pipe:

- $b_2 = 30 \text{ mm for } d_e \le 110 \text{ mm};$
- $b_2 = 40 \text{ mm for } 110 \text{ mm} < d_e \le 315 \text{ mm};$
- $b_2 = 60 \text{ mm for } d_e > 315 \text{ mm}.$

When there is a risk that the stiffening elements (profiles) of a structured wall pipe or socket will deflect more than 0,1 times the profile height, the clamps shall be modified such that they will come into contact with the pipe wall between the profiles when the profile is deflected to between 0,9 times and 0,95 times the profile height (see Figure 2).

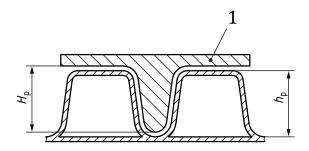

#### Key

- 1 modified loading plate
- $h_{\rm n}$  construction height
- $H_{\rm p}$  profile height of the loading plate;  $0.9h_{\rm p} \le H_{\rm p} \le 0.95h_{\rm p}$

Figure 2 — Example of modified loading plate

### 6 Test pieces

The test piece shall comprise an assembly of (a) pipe section(s) and/or fitting(s) including at least one elastomeric sealing ring joint.

The joint to be tested shall be assembled in accordance with the manufacturer's instructions where available.

The length, L, of the test pieces in pipe form shall be as specified in Figure 1.

The same test assembly shall be used for the entire specified test regime.

To reduce the volume of water needed, a sealed pipe of mandrel may be located within the test piece provided it is 100 % tight to the test pressures applied, and it is not of a shape that can provide support against possible deformation during the test.

When a fitting or any other ancillary component is to be tested, the appropriate end of the test piece shown in <u>Figure 1</u> is to be replaced by that component.

The component is fixed to the test rig and plugged in its open end(s) as appropriate for its design.

#### 7 Temperature of conditioning and testing

When testing with internal hydrostatic pressure using water, the test temperature shall be at the ambient temperature, unless otherwise specified in the referring standard. In case of dispute, the test shall be carried out at  $(23 \pm 5)$  °C.

During testing, pipes should be protected from direct sunlight.

NOTE This protection is intended to avoid heating during testing.

When testing with internal partial vacuum the test temperature shall be in the range of  $(23 \pm 5)$  °C and the temperature variation shall not exceed 2 °C during the testing.

#### 8 Procedure

#### 8.1 General procedure

Carry out the following procedure at the specified temperatures:

a) mount the test piece with sealed ends in the apparatus;