

ISO/FDIS 5146:2023(E)

~~2023-03-27~~

ISO TC 27/SC 01

Secretariat: SA

Coal and coke — Coal preparation plant — Density tracer testing for measuring performances of coal density separators

First edition

~~2023-07-01~~

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5146

<https://standards.iteh.ai/catalog/standards/sist/17df7327-f7c1-4dc7-a168-d40e64970470/iso-5146>

ISO/FDIS 5146:2023(E)

© ISO ~~2022~~2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office

CP 401 • Ch. de Blandonnet 8

CH-1214 Vernier, Geneva

Phone: +41 22 749 01 11

Fax: +41 22 749 09 47

Email: copyright@iso.org

Website: www.iso.org

Published in Switzerland

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5146

<https://standards.iteh.ai/catalog/standards/sist/17df7327-f7c1-4dc7-a168-d40e64970470/iso-5146>

Contents

Foreword	3
Introduction.....	4
1 Scope	5
2 Normative references	5
3 Terms and definitions.....	5
4 Test method.....	6
4.1 General	6
4.2 Apparatus.....	6
4.2.1 Density tracers	6
4.2.2 Density tracer retrieval or detection equipment	7
4.3 Procedure.....	7
4.3.1 Density tracer selection	7
4.3.2 Insertion of density tracers	7
4.3.3 Density tracer retrieval or detection and data capture	9
4.4 Data processing.....	9
4.4.1 Data acceptability.....	9
4.4.2 Calculation of partition coefficients	11
4.4.3 Confidence intervals for partition points	11
4.4.4 Two forms of the partition curve.....	12
4.4.5 Fitting the partition curves.....	14
4.4.6 Asymmetry factor for 5 Parameter Logistic	15
4.5 Reporting of test results	15
Annex A (informative) Density tracer properties	19
Annex B (informative) Test duration and aids for density tracer retrieval or detection	21
Annex C (informative) Selection of density tracers	24
Annex D (informative) Density tracer test report template	26
Annex E (informative) Interpretation of partition curves.....	29
Annex F (normative) Working with partition coefficients to floats.....	31
Annex G (informative) Equations in linear format.....	33
Bibliography	34

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 27, *Coal and coke*, Subcommittee SC 01, *Coal preparation: Terminology and performance*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The objective of this document is to provide the coal-preparation industry with an accurate, safe, rapid and site-based method for determining the density partitioning performances of density separators and to ~~utili~~utilize statistical and mathematical procedures to avoid personal biases in fitting partition curves to the observed data. To meet the second objective, this document includes a number of formulae which can be incorporated in a user spreadsheet.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5146

<https://standards.iteh.ai/catalog/standards/sist/17df7327-f7c1-4dc7-a168-d40e64970470/iso-5146>

Coal and Coke — Coal preparation plant — Density tracer testing for measuring performances of coal density separators

1 Scope

This document specifies the requirements for testing the performances of coal density separators using density tracers and provides a method for the presentation of test results.

This document is partly based in part on Australian Standard AS 5213, ~~Density tracer testing for measuring the performance of coal density separators.~~

This document is applicable to dense medium cyclones (DMCs) and dense medium baths, as follows:

- a) for a single separator;
- b) for a group of separators where the feed is distributed between them at a point downstream of density tracer insertion;
- c) for density tracers of any size; but rarely used for particles with maximum dimension less than 2 mm.

This document also provides guidance for testing the performances of other types of density separators with density tracers.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

AS 2418, *Coal and coke — Glossary of terms*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in AS 2418 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

cutoff time

time which follows the time of last *density tracer* (3.3) *insertion* (3.6) by 5 min plus the greater of *floats transit time* (3.5) or *sinks transit time* (3.7)

Note 1 to entry: Floats transit time is the average time in minutes since insertion into a separator feed for particles collected from, or detected in, a separator floats stream. Sinks transit time is the average time in minutes since insertion into a separator feed for particles collected from, or detected in, a separator sinks stream.

ISO/FDIS 5146:2023(E)

3.2

density separator

device for the cleaning of coal, in which particles are separated into two or more streams according to their densities

3.3

density tracer

non-porous particle of defined shape and density that is not easily broken or abraded

Note 1 to entry: Types include radio frequency identified (RFID) density tracers and non-RFID recoverable density tracers.

3.4

average probable deviation

écart probable moyen

(E_{pm})

one half of the difference between the densities corresponding to the 75 % and 25 % partition coefficients as obtained from the partition curve

3.5

floats transit time

average time in minutes since insertion (3.6) into a separator feed for particles collected from, or detected in, a separator floats stream

3.6

insertion

placement of a *density tracer* (3.3) into a separator feed stream, typically by dropping into a feed preparation screen oversize launder

3.7

sinks transit time

average time in minutes since insertion (3.6) into a separator feed for particles collected from, or detected in, a separator sinks stream

7.4 Test method

7.4.1 General

The test method specified in ~~Clauses~~ 4.2 to 4.5 covers the following:

- a) generation and capture of density tracer test data utilizing either:
 - i1) retrieved, re-usable non-RFID density tracers; or
 - ii2) automatically detected RFID density tracers;
- b) use of those data to estimate density partition coefficients;
- c) presentation of those data and results in tabular and graphical forms;
- d) fitting one of two alternative mathematical forms for the partition curve to the density partition coefficients;
- e) determination, from the partition curves, of key partitioning criteria.

7.2.4.2 Apparatus

7.2.4.2.1 Density tracers

For the purposes of this document, density tracers shall have the following properties:

- a) Shape and dimensions: any that can be fully described in the density tracer test report.

EXAMPLE Cubic, with edge length 13 mm.

- b) Tolerance on dimensions: 100 % within ± 10 % of nominal.
- c) Nominal densities: any.
- d) Tolerances on density, for cubic tracers of 8 mm edge length and larger:
- 1) for nominal relative density (RD) values up to 1,60: 99 % within $\pm 0,006$ RD of the nominal value;
- 2) for nominal RD values greater than 1,60: 99 % within $\pm 0,011$ RD of the nominal value.
- e) Density designation:
- 1) non-RFID density tracers: by engraving or colour-coding;
- 2) RFID density tracers: electronically written to an internal memory chip.

NOTE See Annex A for details of suitable density tracers.

7.2.4.2.2 Density tracer retrieval or detection equipment

If a test is to be conducted using non-RFID density tracers, apparatus for use as aids for retrieval shall be suitable for the circumstances. (see Annex B).

If a test is to be conducted using RFID density tracers, radio equipment shall be present for retrieval of data from each density tracer in the floats and sinks streams from the density separator(s) (see Annex B).

7.3.4.3 Procedure

7.3.4.3.1 Density tracer selection

Density tracer selection shall be as follows.

- a) Decide on one or more nominal sizes.
- b) For each nominal size, decide the nominal densities (guidance is provided in Annex C).
- c) For each nominal size, decide the number of density tracers to be used at each nominal density, being:
- 1) no less than 30; and
- 2) equal to the number selected at every other nominal density.
- d) Assemble those density tracers.

7.3.24.3.2 Insertion of density tracers

The following procedure shall be used for the insertion of density tracers.

- a) Decide on the insertion point and required test duration and calculate the required interval between density tracer insertions as the test duration in seconds divided by the total number of density tracers selected.


$$\frac{\text{(test duration in seconds)}}{\text{(total number of density tracers selected)}}$$

NOTE 1 Annex B provides further information on test durations.

- b) Ensure that retrieval personnel or detection equipment are in place and activated.
- c) Record the time at which the first density tracer was inserted.
- d) At approximately the calculated intervals, insert or drop the density tracers into the feed stream of the density separator(s) to be tested (see Figure 1), either manually or using a mechanical dispenser. The density order of density tracer insertions shall be either:
- i) pseudo-random, by mixing the selected density tracers prior to one-by one selection and insertion; or
 - ii) following a protocol whereby one density tracer of every selected size and density is inserted, one-by-one, followed by a second density tracer of every selected size and density, etc.
- e) Record the time at which the last density tracer was inserted.

NOTE 2 Unplanned interruptions to plant feed of up to 10 min duration can be tolerated, but tracer insertion shall be stopped, restarted when feed is resumed, and documented.


Figure 1 shows typical locations for the insertion of density tracers and for the retrieval or detection of density tracers.

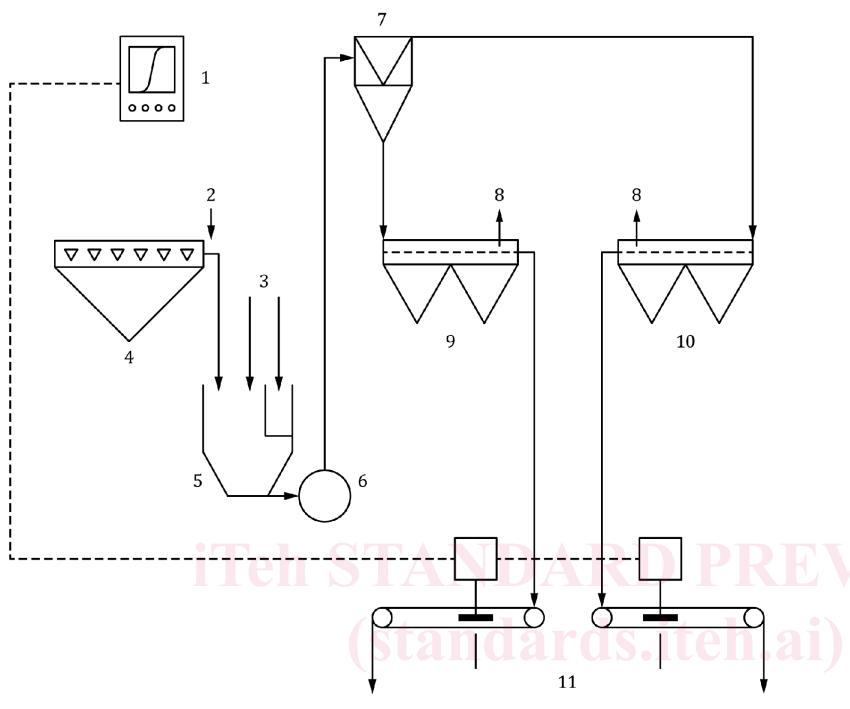

iteh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5146

<https://standards.iteh.ai/catalog/standards/sist/17df7327-f7c1-4dc7-a168-d40e64970470/iso-5146>

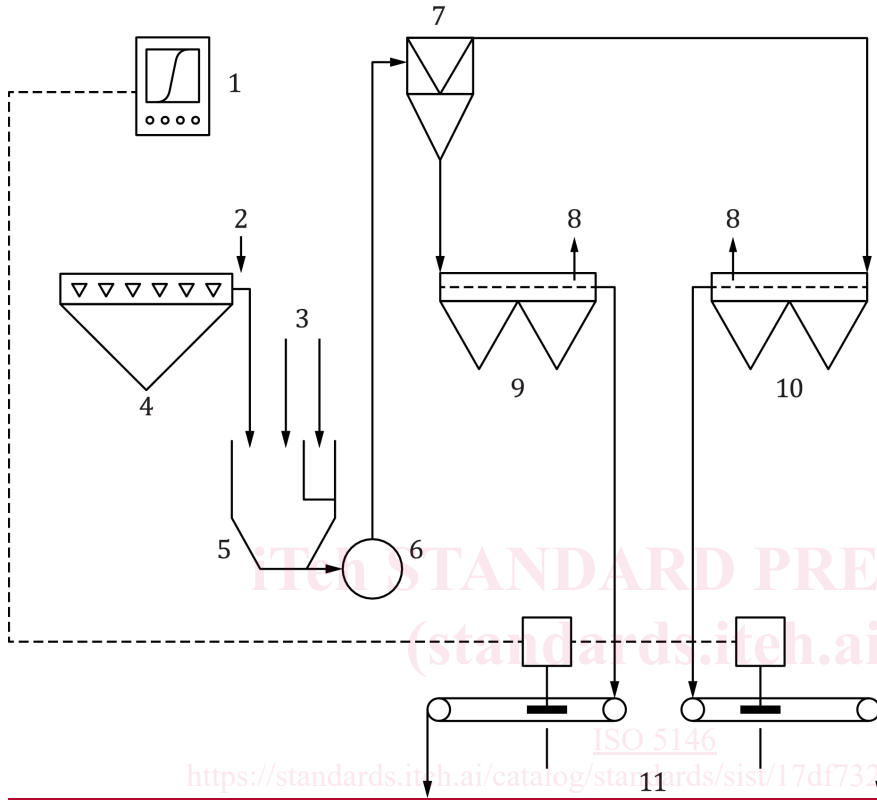

Key

- | | | | |
|---|--|----|---|
| 1 | real-time display of partition curve | 7 | DMC module |
| 2 | typically, density tracers would be added here | 8 | non-radio density tracers would be retrieved here |
| 3 | medium | 9 | sinks drain and rinse screen |
| 4 | de-sliming screen | 10 | floats drain and rinse screen |
| 5 | sump or wing tank | 11 | detectors for radio density tracers |
| 6 | pump | | |

NOTE 1 This is a simplified typical flowsheet showing points of addition and retrieval of density tracers. In this case, the separator is a dense medium cyclone.

NOTE 2 In this case, the separator is a dense medium cyclone.

NOTE 3 For RFID density tracers, alternative locations for detectors are at the drain-and-rinse screens.

Figure 1 — Example of a simplified density separator flowsheet

7.3.3.3.3 Density tracer retrieval or detection and data capture

7.3.3.3.3.1 Non-RFID density tracers

The procedure shall be as follows.

- a) Retrieve density tracers from the material on the floats drain and rinse screen(s) (see Figure 1) by hand or using a scoop or net or magnets. Place them in one or more containers marked "Floats" (see Figure 1, NOTES 1, 2 and 3).
- b) Retrieve density tracers from the material on the sinks drain and rinse screen(s) by hand or using a scoop or net or magnets. Place them in one or more containers marked "Sinks" (see Figure 1, NOTES 1, 2 and 3).
- c) Sort the density tracers retrieved from floats before the cutoff time according to their densities, and record the number at each density.
- d) Sort the density tracers retrieved from sinks before the cutoff time according to their densities, and record the number at each density.

In some circuits, screens cannot be readily accessed for density tracer retrieval, and alternative retrieval points should be sought. For example, primary density separator sinks may be fed directly to a secondary density separator without passing a drain-and-rinse screen. In that case, density tracers retrieved from secondary density separator floats and sinks should be reported as primary density separator sinks.

Any density tracers retrieved from the screens after the cutoff time should not be included in the test data.

If the density tracers are to be retrieved by magnets, they should be ferromagnetic.

7.3.3.3.3.2 Automatically detected RFID density tracers

The procedure shall be as follows.

- a) Detect and record the densities of RFID density tracers in the floats stream using RFID apparatus located downstream of the density separator (see Figure 1). In some cases, circuit configuration may dictate that two or more detection points are required.
- b) Detect and record the densities of RFID density tracers in the sinks stream using RFID apparatus located downstream of the density separator (see Figure 1). In some cases, circuit configuration may dictate that two or more detection points are required.

Any density tracers detected after the cutoff time shall not be included in the test data.

If access to suitable locations for detector placement is limited, alternative locations should be sought. For example, primary density separator sinks may be fed directly to a secondary density separator without passing a conveyor. In that case, density tracers retrieved from both floats and sinks of a secondary density separator should be reported as primary density separator sinks.

7.4.4 Data processing

7.4.4.1 Data acceptability

7.4.4.1.1 Selection of tracer densities

To be acceptable, the selected density tracer densities shall include the following eight RDs from Table 1:

- a) the four RDs which are closest to the d_{50} ;