
**Fasteners — Heat treated tapping
screws — Mechanical and physical
properties**

*Fixations — Vis à tôle traitées thermiquement — Caractéristiques
mécaniques et physiques*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 2702:2022

<https://standards.iteh.ai/catalog/standards/sist/0fee2fc8-120e-4d15-b466-400902cf34d4/iso-2702-2022>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 2702:2022

<https://standards.iteh.ai/catalog/standards/sist/0fee2fc8-120e-4d15-b466-400902cf34d4/iso-2702-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Materials.....	1
5 Mechanical and physical properties.....	2
5.1 General.....	2
5.2 Surface hardness.....	2
5.3 Case-hardened depth.....	2
5.4 Core hardness.....	3
5.5 Microstructure.....	3
5.6 Thread-forming ability.....	3
5.7 Torsional strength.....	3
5.8 Ductility.....	3
6 Test methods.....	4
6.1 General.....	4
6.2 Surface hardness test.....	4
6.3 Case-hardened depth determination.....	4
6.4 Core hardness test.....	5
6.5 Microstructure test.....	6
6.6 Drive test.....	6
6.7 Torsional test.....	7
6.8 Ductility test.....	8
7 Inspection.....	9
7.1 Manufacturer's inspection.....	9
7.2 Supplier's inspection.....	9
7.3 Purchaser's inspection.....	10
7.4 Delivery of test results.....	10
8 Marking and labelling.....	10
8.1 General.....	10
8.2 Marking on screws.....	10
8.3 Marking on packages (labelling).....	10
Bibliography.....	11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 2, *Fasteners*, Subcommittee SC 13, *Fasteners with non-metric thread*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 185, *Threaded and nonthreaded mechanical fasteners and accessories*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This fourth edition cancels and replaces the third edition (ISO 2702:2011), which has been technically revised.

The main changes are as follows:

- document newly structured with regard to requirements and test methods;
- new [Table 1](#) for mechanical and physical properties and related test methods (see [5.1](#));
- maximum case-hardened depth increased to 0,12 mm for ST2,2 and ST2,6 (see [5.3](#));
- maximum core hardness changed from 370 HV back to 390 HV and core hardness test specified more precisely (see [5.4](#) and [6.4](#));
- new clauses for ductility and ductility test added (see [5.8](#) and [6.8](#));
- test method for case-hardened depth determination modified (see [6.3](#));
- torsional test specified more precisely (see [6.7](#));
- new [Clause 7](#) for inspection added;
- new [Clause 8](#) for marking and labelling added.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Fasteners — Heat treated tapping screws — Mechanical and physical properties

1 Scope

This document specifies the mechanical and physical properties of heat treated tapping screws made of steel, with thread sizes ST2,2 to ST9,5 in accordance with ISO 1478, when tested at the ambient temperature range of 10 °C to 35 °C, and the related test methods.

Tapping screws are designed to form mating threads in sheet metals, without their own threads being deformed. Tapping screws are not intended to be pretensioned by design, even though they can experience varying degrees of low-level tensile stress after installation.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1478, *Tapping screws thread*

ISO 1891-4, *Fasteners — Vocabulary — Part 4: Control, inspection, delivery, acceptance and quality*

ISO 6507-1, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 16228, *Fasteners — Types of inspection documents*¹⁾

<https://standards.iteh.ai/catalog/standards/sist/0fee2fe8-120e-4d15-b466-400902cf34d4/iso-2702-2022>

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

tapping screw

sheet metal screw

screw with thread in accordance with ISO 1478 which, when driven into a hole, creates its own mating threads in the materials of the parts being assembled (usually thin metal sheets) without deforming its own thread

4 Materials

Tapping screws shall be made from cold heading steel that can be case-hardened (see e.g. ISO 4954, EN 10263-3, ASME B18.6.3, GB/T 6478, JIS G 3507-2).

5 Mechanical and physical properties

5.1 General

When tested by the methods specified in [Clause 6](#), tapping screws shall meet the mechanical and physical properties specified in [Clause 5](#), see also [Table 1](#).

The requirements of this Clause shall apply to fasteners as delivered by the supplier, i.e. without alteration from the as-delivered condition. In case of alteration or further processing performed by the purchaser, the purchaser shall assume responsibility for conformance of all characteristics altered by such processing.

Table 1 — Mechanical and physical properties, related test methods and relevant clauses

Property and clause number		Clause number of related test method
Material	4	—
Surface hardness	5.2	6.2
Case-hardened depth	5.3	6.3
Core hardness	5.4	6.4
Microstructure	5.5	6.5
Thread-forming ability	5.6	6.6
Torsional strength	5.7	6.7
Ductility ^a	5.8	6.8
^a Only as a routine test for in-process control.		

5.2 Surface hardness

The minimum surface hardness after heat treatment shall be 450 HV 0,3.

Upon request of the purchaser before the order, a maximum surface hardness can be specified to mitigate the risk of environmental hydrogen embrittlement (EHE).

5.3 Case-hardened depth

The case-hardened depth, CHD, shall conform to the values specified in [Table 2](#).

Table 2 — Case-hardened depth

Thread	Case-hardened depth CHD	
	mm	
	min.	max.
ST2,2 ST2,6	0,04	0,12
ST2,9 ST3,3 ST3,5	0,05	0,18
ST3,9 ST4,2 ST4,8 ST5,5	0,10	0,23
ST6,3 ST8 ST9,5	0,15	0,28

5.4 Core hardness

The core hardness after heat treatment shall be:

- 270 HV 5 to 390 HV 5 for threads \leq ST3,9;
- 270 HV 10 to 390 HV 10 for threads $>$ ST3,9.

Upon request of the purchaser before the order, the maximum core hardness can be limited to a lower value to mitigate the risk of environmental hydrogen embrittlement (EHE).

5.5 Microstructure

The microstructure shall show no band of free ferrite between the case-hardened zone and the core.

5.6 Thread-forming ability

Tapping screws shall form a mating thread without deforming their own thread when driven into the test plate.

5.7 Torsional strength

Tapping screws shall meet the minimum breaking torque values specified in [Table 3](#).

Table 3 — Minimum breaking torque

Thread	Minimum breaking torque Nm
ST2,2	0,45
ST2,6	0,9
ST2,9	1,5
ST3,3	2,0
ST3,5	2,7
ST3,9	3,4
ST4,2	4,4
ST4,8	6,3
ST5,5	10,0
ST6,3	13,6
ST8	30,5
ST9,5	68,0

5.8 Ductility

The head of the tapping screw shall not separate from the shank, (see “Passed test” in [Figure 4 b](#)).

6 Test methods

6.1 General

The tapping screw being tested shall be tested as received (coated or uncoated), and when necessary, after a suitable preparation.

6.2 Surface hardness test

The surface hardness test shall be carried out in accordance with ISO 6507-1, using a Vickers indenter with a test force of 2,942 N (HV 0,3). The impression of the pyramid shall be made on a flat surface, preferably on the screw head.

Surface hardness shall meet the requirements specified in [5.2](#).


6.3 Case-hardened depth determination

The case-hardened depth (CHD) shall be determined on a longitudinal section through the screw axis. Hardness determination shall be carried out in accordance with ISO 6507-1. A Vickers indenter with a test force of 2,942 N (HV 0,3) shall be used.

A hardness plot shall be performed perpendicular to the surface, beginning at the thread flank mid-point between crest and root (see point 4 in [Figure 1](#) a) for screws with thread above ST4,2 or, in the case of smaller tapping screws up to and including ST4,2, beginning at the root of the thread (see point 5 in [Figure 1](#) a).


When the threaded area does not allow a reliable measurement (e.g. complete carburization in the threads, thread laps), the bearing surface under the head of the screw shall be taken as reference location for case-hardened depth determination (see [Figure 1](#) b).

The case-hardened depth shall be the distance from the surface to the point at which the recorded hardness is 420 HV 0,3 (see [Figure 1](#) c).

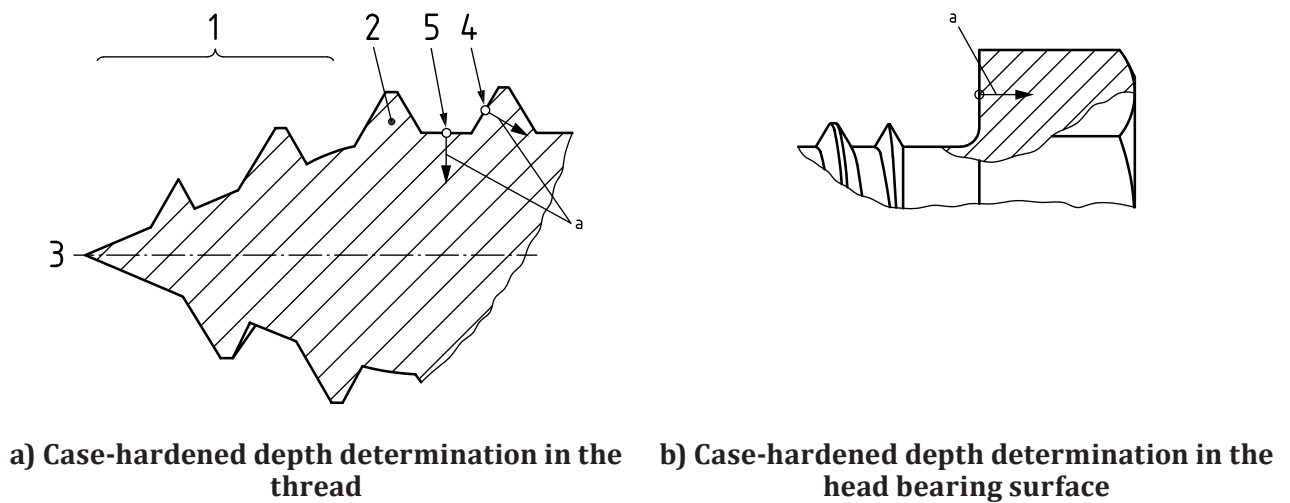

a) Case-hardened depth determination in the thread

b) Case-hardened depth determination in the head bearing surface

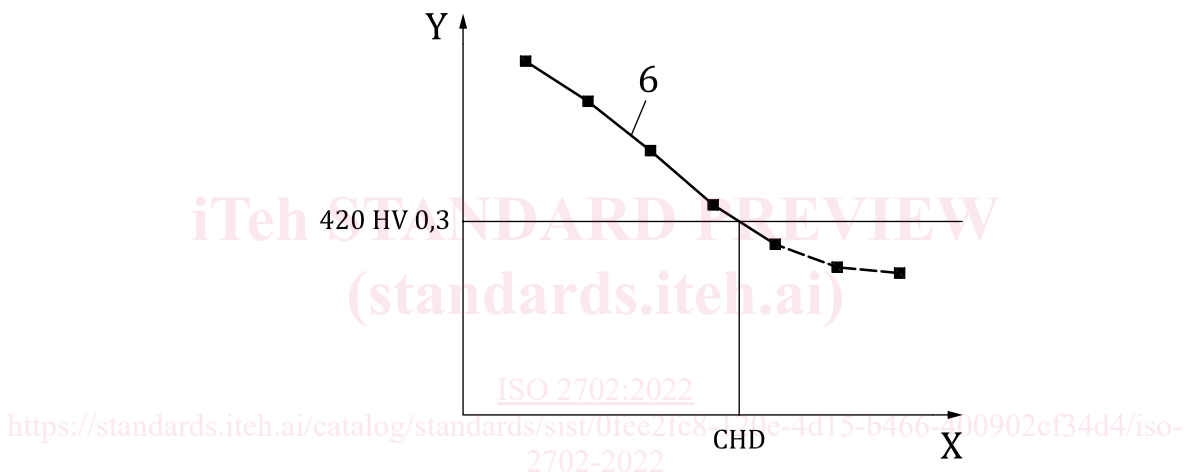

c) Determination of the case-hardened depth (CHD) at a hardness of 420 HV 0,3

Key

X	distance from surface	4	thread flank mid-point
Y	hardness	5	thread root
1	thread end	6	hardness plot
2	first fully formed thread	a	Direction of hardness plot.
3	axis of the screw		

Figure 1 — Determination of case-hardened depth

Case-hardened depth shall meet the requirements specified in 5.3.


6.4 Core hardness test

The core hardness test shall be carried out in accordance with ISO 6507-1:

- in the area of the fully formed thread,
- at a distance sufficiently behind the thread end,
- between the axis and the half-radius position,
- either on a longitudinal section through the screw axis or on (a) transverse section(s).

HV 5 shall be used for threads \leq ST3,9 and HV 10 for threads $>$ ST3,9.

The core hardness shall be determined in accordance with [Figure 2](#) by taking three readings in the area between the axis and the half-radius position. The hardness value shall be the average of these three readings.

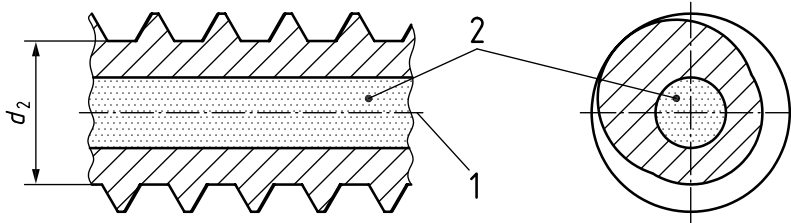

Key

- 1 axis of the screw
- 2 half-radius area (radius of $0,25d_{2,min}$ with $d_{2,min}$ as specified in ISO 1478)

Figure 2 — Half-radius area for core hardness determination

Core hardness shall meet the requirements specified in [5.4](#).

6.5 Microstructure test

The microstructure test shall be carried out by metallographic examination on a longitudinal section through the screw axis.

Microstructure shall meet the requirements specified in [5.5](#).

6.6 Drive test

The drive test serves to evaluate thread-forming ability of tapping screws by driving them into a test plate.

The test plate shall be made from low carbon steel with a carbon content of maximum 0,23 %. The hardness of the test plate shall be 130 HV to 170 HV determined in accordance with ISO 6507-1. The thickness of the test plate shall conform to the values specified in [Table 4](#).

The test hole shall be drilled, or punched and redrilled, or reamed to the hole diameter specified in [Table 4](#).

The tapping screw being tested shall be driven into the test plate until a fully formed thread protrudes through the plate.