
TPMS snap-in valves —

**Part 3:
Performances**

*Valves à boutonner («snap-in») pour TPMS —
Partie 3: Performances*

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

[ISO 18885-3:2021](https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021)

<https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 18885-3:2021

<https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Conditions for testing TPMS snap-in valves.....	2
4.1 General.....	2
4.2 Test fixtures.....	2
4.3 Installation.....	2
4.4 Ageing.....	2
5 Test methods.....	3
5.1 General.....	3
5.2 Adhesion.....	3
5.2.1 Test method.....	3
5.2.2 Performance.....	3
5.3 Valves core seal.....	3
5.3.1 General.....	3
5.3.2 Room temperature test.....	3
5.3.3 Low temperature test.....	4
5.3.4 High temperature test.....	4
5.4 Valve cap seal (optional, for sealing caps only).....	4
5.4.1 Test method.....	4
5.4.2 Performance.....	4
5.5 Valve to rim seal.....	5
5.5.1 General.....	5
5.5.2 Low temperature.....	5
5.5.3 High temperature.....	6
5.6 Installation test.....	6
5.6.1 General.....	6
5.6.2 Force to seat.....	6
5.6.3 Force to pull-out only for valve with sensor housing designed to be connected only after valve seating.....	7
5.6.4 Force to pull back (unseating).....	7
5.7 Burst.....	7
5.7.1 Test method.....	7
5.7.2 Performance.....	7
5.8 Ozone resistance.....	7
5.8.1 Test method.....	7
5.8.2 Performance.....	8
5.9 Flexing resistance.....	8
5.9.1 Test method.....	8
5.9.2 Performance.....	10
5.10 Corrosion test.....	10
5.10.1 Test method.....	10
5.10.2 Performance.....	10
5.11 Valve core torque test.....	11
5.11.1 Test method.....	11
5.11.2 Performance.....	11
5.12 Valve core cycling test.....	11
5.12.1 Test method.....	11
5.12.2 Performance.....	12
5.13 Valve flow rate.....	12
5.13.1 Test method.....	12
5.13.2 Performance.....	12

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 18885-3:2021](https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021)

<https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html (standards.iteh.ai).

This document was prepared by Technical Committee ISO/TC 31, *Tyres, rims and valves*, Subcommittee SC 9, *Valves for tube and tubeless tyres*. [ISO 18885-3:2021](https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45b15b35cd1e/iso-18885-3-2021)

This second edition cancels and replaces the first edition (ISO 18885-3:2019), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the flexing angle degree for the cycling flexing test has been revised;
- the flexing angle degree for the for the leakage test has been revised.

A list of all parts in the ISO 18885 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 18885-3:2021

<https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021>

TPMS snap-in valves —

Part 3: Performances

1 Scope

This document specifies test methods for TPMS snap-in tubeless valves that determine the minimum level of performances requested.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 9227, *Corrosion tests in artificial atmospheres — Salt spray tests*

ISO 18885-2, *TPMS snap-in valves — Part 2: Valve environment*

3 Terms and definitions (standards.iteh.ai)

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

unused valve

valve that has completed final curing processing at least 24 h previously, that has not been subjected to any test or service and that has been stored for no longer than four months in the dark at an ambient temperature between 18 °C and 28 °C, in an optimal and non-aggressive environment

Note 1 to entry: Rubber compounds can change characteristics during their life expectancy.

3.2

sealing cap

protective part that is matched with a valve stem and includes an elastomer seal

Note 1 to entry: An example of sealing cap is given in ISO 9413.

3.3

sensor housing

rigid case that is matched with a valve stem and contains TPMS sensor components

4 Conditions for testing TPMS snap-in valves

4.1 General

All the pressures mentioned in the testing procedures in [5.5.2](#), [5.5.3](#), [5.7.1](#), [5.9.1](#), [5.12.1](#), [5.13.1](#) are relative pressures.

4.2 Test fixtures

Break both edges on both sides of the valve hole either by a 45° chamfer or a radius from 0,3 mm to 0,4 mm. Emery cloth or suitable tooling is recommended. The material of the test fixture should be representative of the material of the actual rim.

The primary external seal of a snap-in valve in a valve hole is obtained from the rubber compression of the valve body onto the internal surface of the valve hole. Secondary external sealing can be present by the contact of the remaining part of the valve body exterior to the surface of the material around the valve hole. Either or both of these seals can be affected by the compound curvatures in the wheel rims and by stock thickness.

The test fixture used for each of the following tests shall be the worst case. The hole diameter and thickness for the considered test is specified in [Table 1](#).

Table 1 — Test fixtures

Nominal hole test	Diameter: 11,3 mm	
	Test hole mm	Plate thickness mm
Valve-to-rim seal test low and high temperature test – 5.5	$11,7_{-0,05}^0$	$1,8 \pm 0,05$
Installation tests: — force to seat: 5.6.2 — force to pull out: 5.6.3	$11,3_{-0}^0$	$3,5 \pm 0,05$
Ozone resistance – 5.8	$11,3_{-0}^{+0,05}$	$3,5 \pm 0,05$
Burst – 5.7 Flexing resistance – 5.9 Pull-back test – 5.6.4	$11,7_{-0,05}^0$	$1,8 \pm 0,05$

4.3 Installation

All valves, lubricated following the valve supplier recommendation or a solution of water and soap, shall be installed in a proper test fixture by applying valve insertion force to the housing or by applying valve traction force to the mouth of the valve, perpendicular to the plane of the valve mounting hole and directly through the centre of the valve mounting hole. However, no valve assembly which has damage resulting from installation shall be tested.

A valve shall be considered properly seated when all of the indicator ring, as defined in ISO 18885-2, is observed to be through the rim or valve mounting hole fixture.

After installation, valve assemblies shall be thoroughly dried in the sealing area before proceeding to tests.

4.4 Ageing

The ageing profile should be considered regarding the real-life case. The definition of ageing shall be agreed between the customer and the valve manufacturer.

5 Test methods

5.1 General

Each of the following tests shall be considered on unused valves.

5.2 Adhesion

5.2.1 Test method

Make two axial, parallel cuts 180° apart through the full thickness of the rubber cover down the entire length of the valve.

Pull each side of the button base away from the insert towards the cap thread end at 150 mm/min \pm 15 mm/min with a traction machine.

The test shall be conducted at 23 °C \pm 5 °C and without the TPMS housing.

Alternatively, pliers may be used instead of a traction machine.

5.2.2 Performance

Any separation between the stem and rubber, stem and cement or cement and rubber in excess of 41 mm², on each valve, shall be considered as a failure.

Any separation that made a strip along the complete valve axis direction shall be considered as a failure.

iTech STANDARD PREVIEW
(standards.itech.ai)

5.3 Valves core seal

[ISO 18885-3:2021](#)

5.3.1 General <https://standards.itech.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1f5b3f6d/iso-18885-3-2021>

To verify valve cores installed in TPMS snap-in valve assemblies (see [Figure 1](#)), the sensor may not be attached. The installation of the valve core in the valve shall meet the following conditions:

- pin position of the valve core: from +0,25 mm to -0,90 mm (relative to the valve mouth);
- standard torque:
- 0,34 Nm to 0,56 Nm for a valve core with metallic sealing;
- 0,23 Nm to 0,56 Nm for a valve core with non-metallic gasket.

The same valve core shall be tested in cascade as follows: room temperature test, low temperature test and finally high temperature test.

5.3.2 Room temperature test

5.3.2.1 Test method

Soak the valve assembly in clean water at 23 °C \pm 5 °C with mouth down vertically and not more than 100 mm below the surface of the water (see [Figure 1](#)).

Check for leakage with test pressures as follows:

- a) cup gasket seal: apply 35 kPa air pressure;
- b) barrel seal: apply 475 kPa air pressure.

5.3.2.2 Performance

Leakage at a rate less than 0,2 cm³/min or no bubble detaching during the test time of 1 min is considered acceptable.

5.3.3 Low temperature test

5.3.3.1 Test method

- a) Depress and release the valve core pin once after a 24 h minimum exposure at $-40\text{ °C} \pm 3\text{ °C}$; assembly pressure shall be maintained at $180\text{ kPa} \pm 15\text{ kPa}$.
- b) Check for leakage with ethanol or methanol at a minimum depth of 25 mm above valve mouth, with the assembly still pressurized to the corresponding pressure.
- c) Begin leak detection after 1 min soak period.

5.3.3.2 Performance

Leakage at a rate less than 0,2 cm³/min or no bubble detaching during the test time of 1 min is considered acceptable.

5.3.4 High temperature test

5.3.4.1 Test method

iTeh STANDARD PREVIEW

(standards.iteh.ai)

- a) Depress and release the valve core pin once after a 48 h minimum exposure at $100\text{ °C} \pm 3\text{ °C}$; pressure shall be maintained at $600\text{ kPa} \pm 15\text{ kPa}$ for applications equal to or below 450 kPa (see [Figure 1](#)).
ISO 18885-3:2021
<https://standards.iteh.ai/catalog/standards/sist/3addfe53-ca5c-468f-8dae-45ba1103f0d4/iso-18885-3-2021>
- b) Check for leakage with $66\text{ °C} \pm 3\text{ °C}$ clean water not more than 50 mm above valve mouth, with the assembly still pressurized to the pressure defined in [5.3.4.1, a](#).
- c) Begin leak detection after 1 min soak period.

5.3.4.2 Performance

Leakage at a rate less than 0,2 cm³/min or no bubble detaching during the test time of 1 min is considered acceptable.

5.4 Valve cap seal (optional, for sealing caps only)

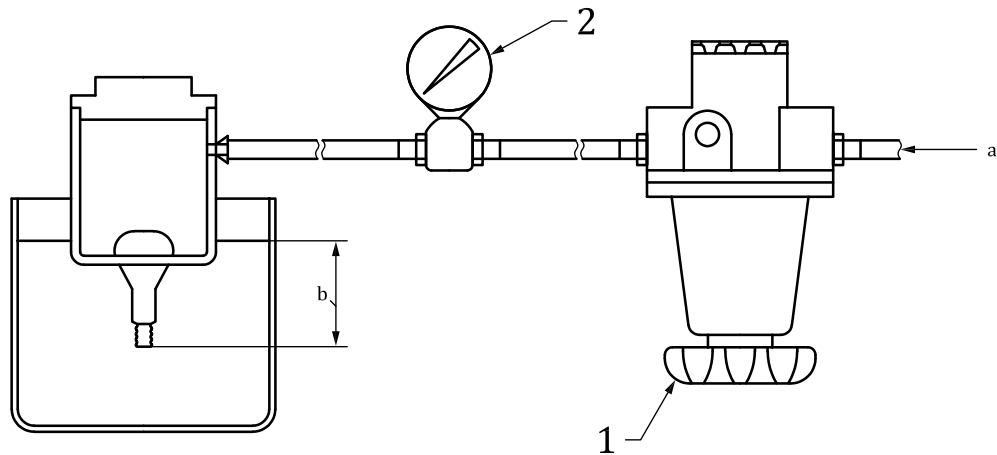
5.4.1 Test method

The test is performed at a room temperature between 18 °C and 28 °C.

- a) Screw the cap with sealing gasket at 0,15 Nm to 0,20 Nm torque on valve without core.
- b) Soak the valve assembly in clean water at $23\text{ °C} \pm 5\text{ °C}$ with mouth down vertically and not more than 100 mm under water surface (see [Figure 1](#)).
- c) Check for leakage with 475 kPa test pressure.

5.4.2 Performance

Leakage at a rate of less than 0,2 cm³/min or with no bubble detaching during the test time of 1 min is considered acceptable.

**Key**

- 1 regulator
- 2 gauge
- a Air supply.
- b Liquid level (100 mm maximum).

Figure 1 — Valve seal test description

ITeH STANDARD PREVIEW
(standards.iteh.ai)

5.5 Valve to rim seal**5.5.1 General**

Temperature tests are performed to subject the valves to extremes in temperature. Flexing of valves simulates possible operational conditions. If possible, the test should be performed with the presence of a sensor properly oriented that can limit the flexion of the valve.

The same valves and assemblies shall be tested in cascade, provided the low temperature test is conducted first.

5.5.2 Low temperature**5.5.2.1 Test method**

- a) Test valves shall be mounted in a test plate in accordance with 4.2 and 4.3.
- b) Assembly shall then be exposed to $-40\text{ °C} \pm 3\text{ °C}$ for 24 h minimum to ensure the valve seal area is at the test temperature, and pressure shall be maintained at $180\text{ kPa} \pm 15\text{ kPa}$.
- c) The valve assembly, still pressurized to $180\text{ kPa} \pm 15\text{ kPa}$, shall then be soaked valve mouth up in ethanol or methanol at $-40\text{ °C} \pm 3\text{ °C}$, valve button not more than 100 mm below the surface of the liquid (see Figure 4).
- d) With respect to the axis of the valve mounting hole, the soaked valve shall be flexed to a minimum angle of $10\text{ °} \pm 3\text{ °}$, if the flexibility of the system allows it. The cap end of the valve shall then be revolved one complete turn-around the axis of the mounting hole if it is possible. This single revolution shall be executed at a uniform rate without the application of torque to the valve body and accomplished within 15 s to 45 s.
- e) The assembly shall be returned in refrigerator at $-40\text{ °C} \pm 3\text{ °C}$ after each test and pressure shall be maintained at $180\text{ kPa} \pm 15\text{ kPa}$.
- f) Repeat points c) to e) at 0,5 h interval minimum for a total of five times.