
**Solid biofuels — Determination of
fines content in pellets**

*Biocombustibles solides — Détermination de la teneur en fines des
granulés*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5370:2023

<https://standards.iteh.ai/catalog/standards/sist/3b60b2f6-7440-4764-aceb-e293d78584f8/iso-5370-2023>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 5370:2023

<https://standards.iteh.ai/catalog/standards/sist/3b60b2f6-7440-4764-aceb-e293d78584f8/iso-5370-2023>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	1
5 Apparatus.....	2
6 Sample preparation.....	3
6.1 Sample size reduction.....	3
6.2 Size of the test portion.....	3
7 Procedure.....	4
7.1 Preparing of the sieving equipment.....	4
7.2 Sieving.....	4
8 Calculations.....	5
8.1 Proportion of fines.....	5
8.2 Quality control.....	5
9 Performance characteristics.....	5
10 Test report.....	5
Annex A (informative) Determination of coarse pellet fines (CPF).....	6
Annex B (informative) Determination of fractions of fines smaller than 3,15 mm.....	11
Annex C (informative) Performance data.....	13
Annex D (informative) Research study data.....	15
Bibliography.....	18

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 238, *Solid biofuels*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 335, *Solid biofuels*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

This document specifies a method for manual determination of the fines content in pellets. The fines content is defined as the percentage in mass of material below 3,15 mm in size (measured with a round hole perforated metal plate sieve according to ISO 3310-2). The fines content is an important parameter since excessive amounts of fines in consignments of pellets can cause problems either in transportation systems or during combustion, or both. It also can cause health problems if the dust is inhaled and it increases the risk of dust explosions. Many of these problems are connected to the tendency of stratification of fines caused by any movement of the pellets.

[Annex A](#) describes a procedure for determining the amount of coarse pellet fines ($3,15 \text{ mm} \leq \text{CPF} < 5,6 \text{ mm}$). The determination of the amounts of smaller fines particles, for example the fractions $< 1 \text{ mm}$ and $< 0,5 \text{ mm}$, is given in [Annex B](#).

NOTE 1 The upper limit of 5,6 mm for CPF was chosen because a sieve with an aperture diameter of 5,6 mm is the standard commercial sieve with the next-smallest aperture diameter after 6 mm, which corresponds to the diameter of the standard pellet size. When conducting the procedure for CPF as outlined in [Annex A](#), additional CPF are created as a result of the sieving procedure. Test results are therefore indicative and best used for comparative purposes rather than treated as CPF originally present in the sample.

NOTE 2 This document will replace ISO 18846.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5370:2023](#)

<https://standards.iteh.ai/catalog/standards/sist/3b60b2f6-7440-4764-aceb-e293d78584f8/iso-5370-2023>

Solid biofuels — Determination of fines content in pellets

1 Scope

This document specifies a method for determining the amount of material passing through a sieve with 3,15-mm-diameter round holes. It is intended for use in all applications (e.g. laboratories, production sites, field locations) where the measurement of fines is required.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

ISO 3310-2, *Test sieves — Technical requirements and testing — Part 2: Test sieves of perforated metal plate*

ISO 16559, *Solid biofuels — Vocabulary*

ISO 18135, *Solid biofuels — Sampling*

ISO 21945, *Solid biofuels — Simplified sampling method for small scale applications*

3 Terms and definitions

ISO 5370:2023

For the purposes of this document, the terms and definitions given in ISO 16559 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

coarse pellet fines

CPF

particles with a size ranging from $\geq 3,15$ mm to $< 5,6$ mm resulting from breakage of pellets during production or handling

Note 1 to entry: The fraction of CPF contains all particles which pass through a sieve with 5,6-mm-diameter round holes and which are retained on a sieve with 3,15-mm-diameter round holes (see ISO 3310-2).

4 Principle

A test portion is subjected to manual screening by means of a sieve with 3,15-mm-diameter round holes while utilizing specific test conditions (e.g. a template is used to guide the movement of the sieve, rotational speed is specified, the number of rotations is dependent on the nature of the material being tested) and the mass of the material passing through the sieve is determined as a mass percentage of the total mass of the test portion.

5 Apparatus


5.1 Sieve template, as illustrated in [Figure 1](#), consisting of a (14 ± 2) mm-thick wooden board with a hole cut in the centre to receive the sieve with collecting pan, all mounted on a base panel with the same size dimensions. The sieve template is for guiding the sieve during the screening process to ensure consistent motion of the sieve. The inner circle should have a smooth surface to enable smooth circular movements of the sieve with the collecting pan within the template. The template diameter is based on a factor of 1,4 multiplied by the sieve diameter.

The diameter of the sieve and the template, the target size of the sub-portion used for a single screening operation and the rotational speed are given in [Table 1](#).


Table 1 — Diameter of sieve and the template, size of the sub-portion and rotational speed

Sieve diameter mm		Inner diameter of template mm	Mass of sub-portion for a single sieving procedure		Approximate rotational speed r/min
			Recommended g	Range g	
400	Recommended sieve diameter	560	500	300 to 600	80
300	Alternative sieve diameters	420	280	170 to 340	95
450		630	630	380 to 760	77

The template shall be secured to the workplace (table) by, for example, clamps.

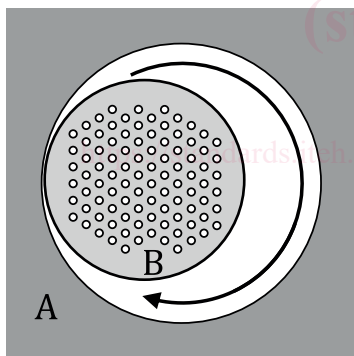

a) Top view

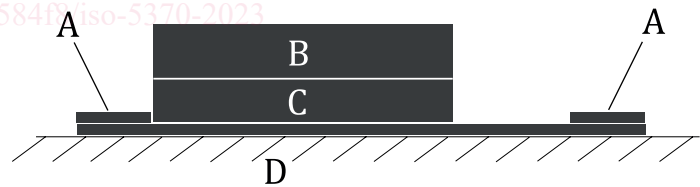

b) Cross-section

Key

- A template, with a wooden base
- B sieve
- C collecting pan
- D workplace, table

Figure 1 — Sieving apparatus with template

To facilitate operation, a lubricant may be used to improve the sliding properties of the collection pan in the template, such as graphite powder or silicon lubricant. Additionally, roller tables may be used.

5.2 Circular sieve with 3,15-mm-diameter round holes, and aperture geometry in accordance with ISO 3310-2. A sieve with a diameter of 400 mm is recommended. Other sieve diameters within the range of 300 mm to 450 mm may be used, but it is important to make sure the sieving criteria is adjusted for the specific sieve to be used (see [Table 1](#)). The frame of the sieve shall have a height which allows for free movement of the sample without losing material during the sieving process.

5.3 Sieve with 5,6-mm-diameter round holes. If coarse pellet fines ($3,15 \text{ mm} \leq \text{CPF} < 5,6 \text{ mm}$) are determined in accordance with [Annex A](#), the circular sieve shall have round holes with a diameter of 5,6 mm and aperture geometry in accordance with ISO 3310-2. All other requirements are given in [5.2](#).

5.4 Sieves, with metal wire cloth having aperture sizes smaller than 3,15 mm. If fines fractions smaller than 3,15 mm, for example $< 1 \text{ mm}$ or $< 0,5 \text{ mm}$, are determined in accordance with [Annex B](#), the circular or rectangle sieves shall have an aperture geometry in accordance with ISO 3310-1 and shall have a minimum effective sieve area of 250 cm^2 .

5.5 Collecting pan, for collection of material passing through the sieve, with the same diameter as the sieve.

5.6 Weighing container(s), of adequate size for weighing of the fractions. The collecting pan may also be used as a weighing container.

5.7 Balance, with suitable capacity to weigh the total mass of the sample plus any container used to hold the sample, capable of reading to the nearest 0,1 g.

5.8 Metronome or stopwatch, for confirmation of the rotational speed when performing the sieving procedure.

NOTE Use of a simple metronome, such as a mobile phone app, has been shown to be a convenient method for speed control.

6 Sample preparation

6.1 Sample size reduction

The laboratory sample used for the determination of the fines content shall be obtained in accordance with ISO 18135 or ISO 21945. The sampling strategy shall be such that special provisions are taken regarding the tendency for stratification of the fines in a consignment of pellets. For example, the entire quantity of pellets in a bag shall be taken as the laboratory sample. Due to the special provisions necessary regarding sampling for fines determination, the combined (raw) sample can end up being very large. The combined sample may be divided into one or more smaller test portions using appropriate methods of subdivision as outlined in ISO 14780 (e.g. a riffle box). For the test portion used for the determination of fines content, the minimum mass given in [6.2](#) shall be considered.

NOTE In bulk handling of large volumes of pellets there is often a risk of stratification of materials in storage bins. There is also the risk of incremental variations of fines in volumes of pellets due to batch-wise operation during transportation by rail carriages, trucks and ocean-going vessels.

6.2 Size of the test portion

The size of the test portion shall be selected in relation to pellet diameter as given in [Table 2](#).

Table 2 — Minimum mass of test portion depending on the pellet diameter

Pellet diameter mm	Minimum size of a test portion kg
6 to 8	3
> 8 (up to 25)	5

7 Procedure

7.1 Preparing of the sieving equipment

The template shall be placed on a table or work bench as shown in [Figure 1](#). It shall be fixed, for example with clamps, to ensure regular circular movements of the combination of sieve and collecting pan.

The sieve is placed on top of the collecting pan and together they are placed inside the template against the edge.

This sieving procedure is based on the use of a 400-mm-diameter sieve and a template of 560 mm inner diameter. When using a sieve with another size, the appropriate template shall be used.

7.2 Sieving

Weigh the test portion to the nearest 0,1 g and record the mass.

Place a first sub-portion on the sieve. The target mass of the sub-portion is 500 g but it is also permitted to use a mass within the range given in [Table 1](#). If a sieve with another diameter is being used, see [Table 1](#) for the size of sub-portions.

Sieve the sub-portion using circular rotations within the template at a rate of approximately 80 rotations per minute (r/min). At this speed ($10 \pm \frac{1}{4}$) rotations will take approximately 7,5 s and ($20 \pm \frac{1}{4}$) rotations will take approximately 15 s. Technicians performing the test procedure the first time should adjust their rotational speed in pre-tests using a stopwatch or a metronome. Rotational speed can also be checked from time to time using the stopwatch or the metronome. For other sieve sizes, an appropriate rotational speed shall be used; values for sieves with a diameter of 300 mm and of 450 mm are given in [Table 1](#). In all cases, the rotational speed should be sufficient to maintain most of the pellets in motion. Sieve rotations can be either clockwise or anticlockwise.

Empirical data for the sieving speed using sieves with a diameter of 400 mm and of 300 mm are given in [Annex D](#).

The total number of rotations will depend on the nature of the material being sieved and is given in [Table 3](#). The number of rotations will remain the same regardless of the sieve diameter being used.

Table 3 — Number of rotations for sieving procedure

Pellets to be sieved	Number of rotations
Pellets made for residential or commercial use where compliance limits for fines content is 1,0 % in mass or less	$10 \pm \frac{1}{4}$
Pellets made for commercial or industrial use where compliance limits for fines content is > 1 % in mass	$20 \pm \frac{1}{4}$

After completing the sieving of the sub-portion, transfer the coarse material retained on the sieve to another container. The fines fraction can be left inside the collecting pan or, if desired, can be transferred to a weighing container. Place the sieve back on the collecting pan, place both the collecting pan and the sieve back into the template against the edge and place the next sub-portion on the sieve. Repeat this sieving process until all sub-portions have been screened for fines.

Once the whole test-portion has been sieved, weigh the cumulated fines fraction (either in the tared weighed collecting pan or in a separate weighing container) to the nearest 0,1 g. For quality control, also weigh the cumulated coarse material that was retained on the sieve.

NOTE 1 The maximum mass of 600 g of a sub-portion allows the subsequent use of the sub-portion for the determination of durability according to ISO 17831-1.

NOTE 2 Sieving of pellets with low durability leads to formation of fines due to abrasion during sieving. The tendency of an over-estimation of the fines content increases with decreasing mechanical durability of the pellets.

8 Calculations

8.1 Proportion of fines

Calculate the percentage in mass of fines by dividing the mass of the cumulated fines fraction by the mass of the test portion used for the sieving procedure and multiply by 100.

The result shall be given to the nearest 0,1 % in mass for reporting.

8.2 Quality control

Calculate the difference between the mass of the test portion and the total mass of the cumulated fines fraction and the cumulated coarse material that was retained on the sieve and express the difference in per cent of the mass of the test portion. If the difference is larger than 2 % in mass, the causes for the deviation shall be investigated and the determination shall be repeated with a new test portion. If the difference after repeated determination still exceeds 2 % of the mass of the test portion, the size of the test portion and the difference in percentage mass shall be reported together with the fines content as per [8.1](#).

If the amount of CPF is determined according to [Annex A](#) from the sample used in [7.2](#), then the mass of cumulated CPF and the mass of cumulated coarse material that was retained on the sieve with 5,6-mm-diameter round holes can be calculated as a sum and used instead of cumulated coarse material retained on the sieve during the initial screening.

9 Performance characteristics ISO 5370:2023

The achievable performance of the method is given in [Annex C](#), showing the results obtained by an international laboratory comparison study carried out on two industrial samples of 6-mm-diameter pellets with different amounts of added fines and different mechanical durability.

Additional information about the recovery of fines, CPF and fines smaller than 3,15 mm depending on the number of rotational movements are given in [Annex D](#).

10 Test report

The test report shall include at least the following information:

- a) the identification of the laboratory performing the test and the date of the test;
- b) the identification of product (or sample) tested;
- c) a reference to this document, i.e. ISO 5370:2023;
- d) the mass of the test portion (as per [7.2](#));
- e) the result of the test on an as-received basis as indicated in [8.1](#);
- f) the difference between the mass of the test portion and the total mass of all fractions, in per cent of the mass of the test portion if the difference exceeds a mass fraction of 2 %;
- g) any unusual features noted during the determination, which can affect the result;
- h) any deviation from this document, or operations regarded as optional.