
**Corrosion of metals and alloys —
Guidelines and requirements for
corrosion testing in simulated
environment of deep-sea water**

*Corrosion des métaux et alliages — Lignes directrices et
recommandations relatives aux essais de corrosion dans
l'environnement simulé des eaux profondes*

iTeh STANDARDS REVIEW
(standards.iteh.ai)

ISO 5668:2023

<https://standards.iteh.ai/catalog/standards/sist/90d21c0c-12cc-4413-b5f1-b9d86eb1f519/iso-5668-2023>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 5668:2023

<https://standards.iteh.ai/catalog/standards/sist/90d21c0c-12cc-4413-b5f1-b9d86eb1f519/iso-5668-2023>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	1
5 Testing equipment.....	2
5.1 General.....	2
5.2 Test chamber.....	4
5.3 Environment controlling system.....	4
5.4 Experimental system.....	5
5.5 Safety instructions.....	7
6 Specimens.....	8
6.1 General.....	8
6.2 Immersion test specimen.....	8
6.3 Crevice corrosion specimen.....	9
6.4 Stress corrosion cracking specimen.....	9
6.5 Electrochemical test specimen.....	10
6.6 Other type of specimen.....	10
7 Testing procedure.....	11
7.1 Arrangement of specimens.....	11
7.2 Preparation of test solutions.....	11
7.3 Test conditions.....	11
7.4 Immersion test.....	13
7.5 Crevice corrosion test.....	13
7.6 Galvanic corrosion test.....	13
7.7 Stress corrosion cracking test.....	14
7.8 Electrochemical measurement.....	15
8 Evaluation of test specimens.....	15
9 Test report.....	16
Bibliography.....	17

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Corrosion is a crucial problem for subsea equipment and systems for oil/gas production, environmental observation, and scientific exploration due to exposure in deep-sea water. Guidelines for corrosion testing of metals and alloys exposed in deep-sea water have been given in ISO 23226.

This document provides guidelines and requirements for the corrosion testing of metals and alloys under the conditions of simulating the environment of deep-sea water. Thereby, the testing can be conducted based on the specified conditions and procedures, and the meaningful comparisons can be made for different tests.

This document applies to the immersion testing of specimens related to general corrosion and localized corrosion, stress corrosion cracking (SCC) testing and electrochemical testing in the simulated environment of deep-sea water in the laboratory.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5668:2023

<https://standards.iteh.ai/catalog/standards/sist/90d21c0c-12cc-4413-b5f1-b9d86eb1f519/iso-5668-2023>

Corrosion of metals and alloys — Guidelines and requirements for corrosion testing in simulated environment of deep-sea water

1 Scope

This document provides guidelines and requirements for the corrosion testing of metals and alloys in the simulated environment of deep-sea water, including principle, testing equipment, specimen preparation, testing procedure and evaluation after test. This document applies to the immersion testing, corrosion testing under stress condition and electrochemical testing in the simulated environment of deep-sea water in the laboratory.

Testing of other materials such as composites and elastomers can also be carried out in the simulated environment of deep-sea water with reference to this document, but the evaluation of these materials after the testing is different from that of metals and alloys.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 8044, *Corrosion of metals and alloys — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 8044 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1 deep-sea water

sea water zone with a depth generally ranging from 200 m to thousands of meters

Note 1 to entry: Deep-sea water has a corrosive environment with parameters such as temperature, salinity, dissolved oxygen content, microorganism and biofouling that are quite different from those in surface sea water.

3.2 simulated environment

environment for which the main corrosion factors are simulated

4 Principle

This document provides guidelines and requirements on corrosion tests in the simulated environment of deep-sea water using a suitable apparatus. The apparatus should be able to form a corrosive environment similar to the practical deep-sea water. The main environmental factors should include at least hydrostatic pressure, temperature, dissolved oxygen content and compositions of deep-sea water.

The immersion testing of metals and alloys in the simulated environment of deep-sea water for specimens with or without applied stress can be conducted using the apparatus. Electrochemical testing, galvanic corrosion measurement and slow strain rate testing for stress corrosion cracking under tensile condition can also be carried out when the apparatus is modified with these functions.

5 Testing equipment

5.1 General

5.1.1 The corrosion tests are carried out in a special testing apparatus which should be capable of simulating deep-sea corrosive environment.


5.1.2 The significant environmental factors affecting corrosion behaviours of metals and alloys should be included in the simulated deep-sea environment.

5.1.3 At least a test chamber, an environment controlling system and an experimental system should be included in the corrosion test apparatus of simulating deep-sea environment. The schematic diagram of a typical test apparatus and an actual test setup are shown in [Figure 1](#). The placement of specimens shown in the test chamber is just for the demonstration of different corrosion test functions. Different tests that can have interference with each other should not be conducted in the test chamber at the same time.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5668:2023](#)

<https://standards.iteh.ai/catalog/standards/sist/90d21c0c-12cc-4413-b5f1-b9d86eb1f519/iso-5668-2023>

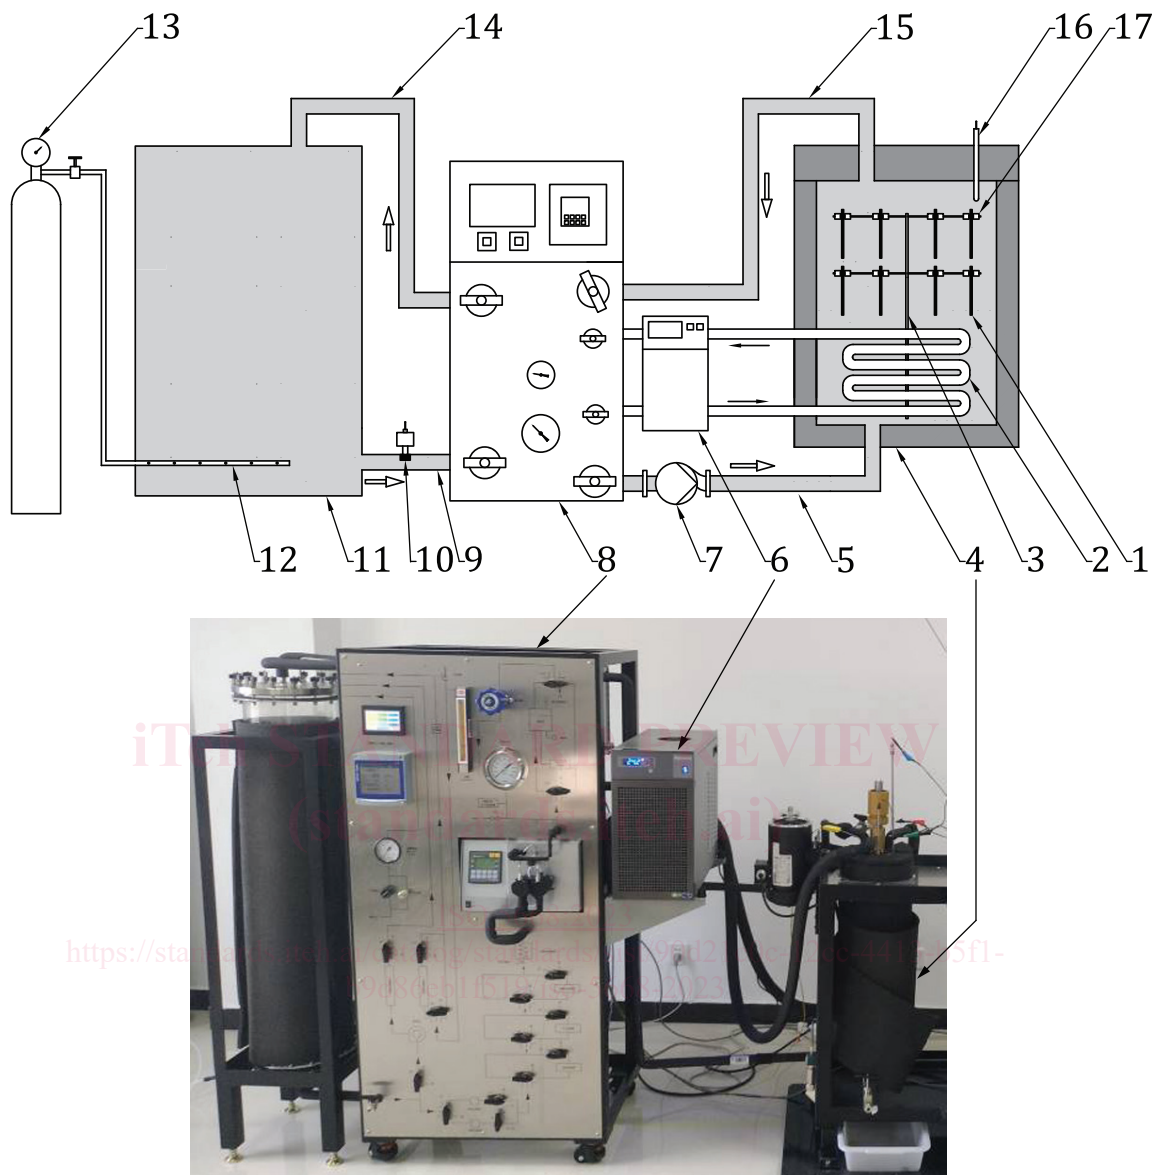

Key

- | | |
|----------------------------------|--|
| 1 specimen for immersion test | 10 probe for dissolved oxygen and/or other electrolyte factors |
| 2 cooling coil | 11 reservoir |
| 3 specimen support | 12 aeration/deaeration pipe |
| 4 test chamber | 13 oxygen or nitrogen gas |
| 5 chamber inlet pipe | 14 reservoir inlet pipe |
| 6 chiller | 15 chamber outlet pipe |
| 7 high-pressure pump | 16 pressure sensor and temperature sensor (thermoprobe) |
| 8 environment controlling system | 17 insulating sleeve |
| 9 reservoir outlet pipe | |

Figure 1 — Schematic diagram of apparatus and actual setup for simulated deep-sea environment corrosion test

5.1.4 All parts of the apparatus exposed to the test solution should be made of inert material which is corrosion resistant in the test environment to avoid contaminating the test solution and consumption or absorption of solute by the material of the apparatus. The recommended materials include non-metallic materials, such as UPVC, PTFE and metallic materials, such as titanium alloy, Hastelloy alloy, and stainless steel with high corrosion resistance.

5.2 Test chamber

5.2.1 The volume of the test chamber should be appropriate to hold test specimens and solution, and to guarantee a uniform environmental condition.

5.2.2 The structure and components of the test chamber should have sufficient pressure rating to withstand the test pressure. The safety instructions with the test chamber as a pressure container are given in [5.5](#).

5.2.3 The inlet and outlet pipes connecting to the test chamber are used to establish a test solution recycling and environment controlling system.

5.2.4 For in situ electrochemical corrosion testing, a connecting interface for electrochemical workstation should be included, and the cables and connectors inside and through the test chamber should have adequate pressure bearing capability and water tightness.

5.3 Environment controlling system

5.3.1 The test solution conditions including hydrostatic pressure, temperature, dissolved oxygen content, etc. are monitored and controlled by the environment controlling system. It is reasonable to apply additional reservoir to store the test solution and to facilitate the adjustment of the test solution conditions (excluding pressure) before injecting solution into the test chamber. The volume of the reservoir should be not less than twice that of the test chamber.

5.3.2 The high-pressure pump should be used to control the solution pressure in the test chamber and realize the solution circulation. The circulation rate of the solution can be determined according to the chamber volume and the test pressure. The pressure in the test chamber should be monitored throughout the test by installing a pressure gauge or sensor as shown in [Figure 1](#).

5.3.3 The temperature of the test solution is adjusted by the installation of the condensing cooling coil in the test chamber to simulate the deep-sea low temperature conditions. The installation of condensing cooling coil in the reservoir is also applicable. Thermal preservation measures should be taken for the whole solution circulation system, for example, wrapping the outer walls of the test chamber, the reservoir and the pipes with thermal insulation materials. The solution temperature in the test chamber should be monitored by a thermoprobe and controlled within ± 1 °C of the set value.

5.3.4 The dissolved oxygen content of the test solution should be adjusted by injecting nitrogen or oxygen gas into the reservoir before solution circulation. During the test, the dissolved oxygen content should be monitored and adjusted accordingly. The dissolved oxygen content in the testing solution can be measured using an electrochemical probe method as specified in ISO 5814.

5.3.5 If other conditions of the solution need to be controlled, such as salinity, pH value, etc., it is also advisable to adjust them in the reservoir before solution circulation according to the practical deep-sea environment to be simulated.

5.4 Experimental system

5.4.1 Specimen support in the chamber

The specimen support should be made of corrosion-resistant metal or non-metallic material, and the shape and size of the specimen support should be specified according to the volume of the test chamber and the test requirements.

For general immersion test, the specimens should be placed in the test chamber with support.

For crevice corrosion test, the crevice formers specified in ISO 18070 and ASTM G78 can be used.

For stress corrosion cracking test of constant load/displacement, the preloaded specimen in the loading jig should be used.

The above-mentioned specimen and assembly can be installed on the support by hanging or bolt fixing, and the insulation between the support and the specimen should be made to eliminate galvanic effect. In the multi-specimen test, sufficient spacing should be reserved to avoid the interference between specimens.

5.4.2 Loading device of slow strain rate tensile test

For stress corrosion cracking test under tension at a slow strain rate, a loading device can be added in the test chamber as shown in [Figure 2](#).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5668:2023

<https://standards.iteh.ai/catalog/standards/sist/90d21c0c-12cc-4413-b5f1-b9d86eb1f519/iso-5668-2023>