



Designation: C1608 – 12

# Standard Test Method for Chemical Shrinkage of Hydraulic Cement Paste<sup>1</sup>

This standard is issued under the fixed designation C1608; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This test method measures the internal (absolute) volume change of hydraulic cement paste that results from the hydration of the cementitious materials. This volume change is known as *chemical shrinkage*.

1.1.1 Procedure A, volumetric method.

1.1.2 Procedure B, the density method.

1.2 The values stated in SI units are to be regarded as the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. (Warning—Fresh hydraulic cementitious mixtures are caustic and may cause chemical burns to skin and tissue upon prolonged exposure.<sup>2</sup>)*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>3</sup>

[C114 Test Methods for Chemical Analysis of Hydraulic Cement](#)

[C186 Test Method for Heat of Hydration of Hydraulic Cement](#)

[C188 Test Method for Density of Hydraulic Cement](#)

[C219 Terminology Relating to Hydraulic Cement](#)

[C305 Practice for Mechanical Mixing of Hydraulic Cement Pastes and Mortars of Plastic Consistency](#)

[C511 Specification for Mixing Rooms, Moist Cabinets, Moist Rooms, and Water Storage Tanks Used in the Testing of Hydraulic Cements and Concretes](#)

[C670 Practice for Preparing Precision and Bias Statements for Test Methods for Construction Materials](#)

## 3. Terminology

3.1 *Definitions:*

3.1.1 *chemical shrinkage, n*—the absolute (internal) volume change accompanying the hydration of cement, due to the fact that the cement hydration products occupy less physical volume than the reactants.

3.1.2 All other terms are as defined in Terminology [C219](#).

## 4. Significance and Use

4.1 Numerous properties of cementitious materials are controlled by their initial hydration rate. Examples include early-age strength development, heat release, and crack resistance. One direct and convenient measure of this initial hydration rate is provided by the measurement of the chemical shrinkage of the cement paste during its hydration. As cement hydrates, the hydration products occupy less volume than the initial reacting materials (cement and water). Due to this volume change, a hydrating cement paste will sorb water from its immediate surroundings, when available. At early times, this sorption is in direct proportion to the amount of hydration that has occurred.<sup>4</sup> This method is based on the one developed by Geiker.<sup>5</sup> The results are relevant to understanding the hydration behavior of cements. This method does not measure the bulk volume changes (autogenous shrinkage) associated with chemical shrinkage nor the cracking potential of concretes produced with the evaluated cement.

## 5. Apparatus

5.1 *Devices for Determining Mass*, conforming to the requirements of Method [C114](#) and evaluated for precision and accuracy at a total load of 100 g.

5.2 *Constant Temperature Water Bath*—a water bath capable of maintaining a temperature of  $23.0 \pm 0.5$  °C, with a sufficient capacity to hold the specimens being evaluated. To

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee C01 on Cement and is the direct responsibility of Subcommittee C01.31 on Volume Change.

Current edition approved Oct. 15, 2012. Published November 2012. Originally approved in 2005. Last previous edition approved in 2007 as C1608 – 07. DOI: 10.1520/C1608-12.

<sup>2</sup> See the section on Safety, Manual of Cement Testing, *Annual Book of ASTM Standards*, Vol. 04.01.

<sup>3</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>4</sup> L.J. Parrott, M. Geiker, W.A. Gutteridge, and D. Killoh, "Monitoring Portland Cement Hydration: Comparison of Methods," *Cement and Concrete Research*, Vol. 20, 919-926, 1990.

<sup>5</sup> M. Geiker, "Studies of Portland Cement Hydration: Measurements of Chemical Shrinkage and a Systematic Evaluation of Hydration Curves by Means of the Dispersion Model," Ph.D. Thesis, Technical University of Denmark, Copenhagen, Denmark, 1983.

\*A Summary of Changes section appears at the end of this standard

avoid evaporative cooling, the surface of the water in the bath shall be covered with floating plastic balls or fitted with an insulated lid.

5.3 *Timing Device*—Clock that can measure time to the nearest minute.

5.4 For procedure A

5.4.1 *Capillary Tube*—A graduated glass capillary tube with graduations of 0.01 mL or smaller, and typically a capacity of 1.0 mL.

5.4.2 *Small Glass Vials (e.g., 22-mm diameter and 55-mm height) with Rubber Stoppers* that fit tightly into the glass vials and have a hole placed in each stopper with the graduated capillary tube inserted through the hole (as shown in Fig. 1). Fix the capillary tube in the stopper using a two-component epoxy or other suitable adhesive applied at the stopper's top and bottom surfaces.

5.5 For Procedure B

5.5.1 *Density bottle*, glass, capacity approximately 20 ml with internally conical glass stopper as shown in Fig. 2.

## 6. Reagents and Materials

6.1 Paraffin oil.

6.2 De-aerated water (prepared by boiling water and sealing it in a closed container before it has cooled.)

## 7. Procedure

7.1 *Preparation of Cement Paste*—Prepare the cement paste in accordance with the proportions and procedure described in Test Method C186 (Note 1). The pastes shall be prepared in a mixing room meeting the temperature and humidity require-

ments outlined in Specification C511. Record to the nearest minute the time when the water first contacts the dry cement powder.

NOTE 1—Other mixing procedures such as mixing in a Hobart mixer (see Practice C305) or kneading by hand in a sealed plastic bag may be used. The standard paste mixture uses 150 g of cement and 60 ml of water (water-cement ratio of 0.40). Adjust the volume of paste mixed to match the mixing equipment used. Other water-cement ratios may be used as long as they are stated in the test report; higher water-cement ratios may produce significant bleeding of the cement paste which will influence the results (by changing the effective water-cement ratio, etc.); lower water-cement ratios may lead to difficulties in preparing a fully compacted, homogeneous paste for subsequent evaluation and self-desiccation may occur.

7.2 Prepare a minimum of two replicate specimens as described below for either Procedure A or Procedure B.

7.3 Procedure A

7.3.1 Determine the mass of each empty glass vial to the nearest 0.01 g.

7.3.2 Carefully place the prepared cement paste into the glass vial to achieve a paste height between 5 mm and 10 mm in the vial (Note 2). Consolidate the paste in the vial by tapping the vial on a laboratory countertop, or placing it on a vibrating table, or some similar procedure.

NOTE 2—For applications requiring a water-cement ratio or water-cementitious material ratio of less than 0.40, it is recommended that the paste height be reduced to 3 mm or less. Thicker samples can experience a process called depercolation, resulting in the measured chemical

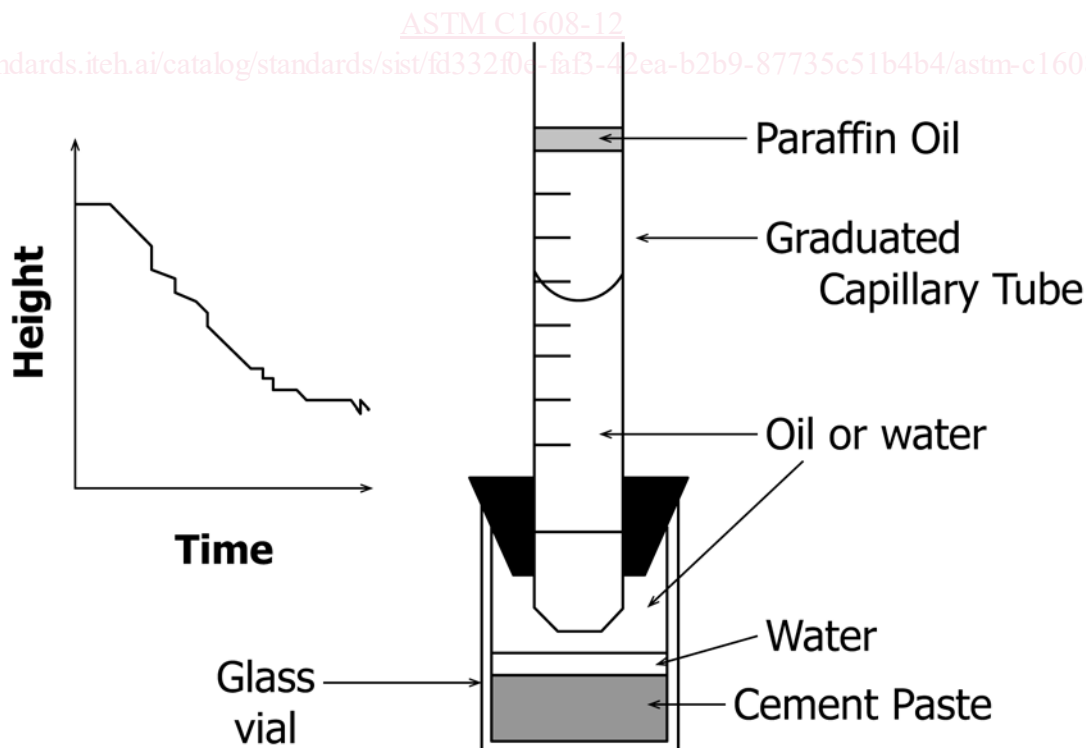


FIG. 1 Illustration of One Experimental Setup for Monitoring Chemical Shrinkage of Hydrating Cement Paste Using Procedure A.