

Standard Specification for Flexible Cellular Materials—Urethane for Furniture and Automotive Cushioning, Bedding, and Similar Applications¹

This standard is issued under the fixed designation D3453; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope*

1.1 This specification covers flexible cellular urethane materials intended for such uses as inserts for furniture cushions, mattresses, and similar applications.

1.2 This specification provides material and dimensional requirements and methods of tests for specific properties of load bearing, compression set, humid age resistance, pounding fatigue resistance, support factor and resilience.

1.3 This specification includes references to government regulations for burning characteristics of flexible cellular material used in specified applications.

1.4 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.5 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

NOTE 1—There is no equivalent ISO standard. Note 1—There is no equivalent ISO standard.

2. Referenced Documents

2.1 ASTM Standards:²

D3574 Test Methods for Flexible Cellular Materials—Slab, Bonded, and Molded Urethane Foams D3675 Test Method for Surface Flammability of Flexible Cellular Materials Using a Radiant Heat Energy Source

2.2 *Other Documents:* h.a/catalog/standards/sist/c39963c6-1a36-47a0-b889-3f6847c9ac61/astm-d3453-12 16CFR1632 (Previously DoC FF4-72), Standard for the Flammability of Mattresses³ MVSS-FMVSS 302 DoT Motor Vehicle Safety Standard³

DOT Federal Aviation Regulation (FAR), Part 25.853, Paragraph (b), and Appendix F³ Simplified Practice Recommendations R2-62 Bedding Products and Components (Mattresses, Springs, Bedsteads, and Cots)⁴

3. Classification

3.1 This specification covers eight grades of flexible cellular material that <u>may behave been</u> selected for use in accordance with load bearing and general physical properties, Table 1; four grades based on pounding-fatigue properties, Table 2; three grades based on cushioning performance properties, Table 3.

4. Basis of Purchase

4.1 Any product represented as complying with this specification shall meet all the requirements listed herein for its particular classification.

5. Burning Characteristics

5.1 Table 4 lists applicable government regulations on burning characteristics of material used in specified applications.

6. Dimensions

6.1 For Use as Mattress Inserts:

*A Summary of Changes section appears at the end of this standard

Copyright © ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959. United States

🦻 D3453 – 12


TABLE 1 Specific Physical Properties of Flexible Cellular Material

Grade Number		25 % Indentation Force	Compression (comp)	Moisture Resistance	
Ν	lbf	Deflection (IFD) Values, ^A N (lbf)	Set ^B After 90 % Deflection, % max	Compression Force Deflection Loss, % max	Compression Set ^B After Deflection, % max
245	55	245 ± 18 (55 ± 4)	15	20	20
196	44	$196 \pm 18 (44 \pm 4)$	15	20	20
151	34	$151 \pm 14 \ (34 \pm 3)$	15	20	20
120	27	$120 \pm 14 \ (27 \pm 3)$	15	20	20
93	21	$93 \pm 14 \ (21 \pm 3)$	15	20	20
67	15	$67 \pm 14 \ (15 \pm 3)$	20	20	25
40	9	$40 \pm 14 (9 \pm 3)$	25	_	30
22	5	$22 \pm 14 (5 \pm 3)$	30	_	35
Test method sections ^C		Bĺ	D	J1,C	J1,D
Specimen size, ^D mm (in.)		380 × 380 × 100	$50 \times 50 \times 25$	50 × 50 × 25	$50 \times 50 \times 25$
		(15 × 15 × 4)	(2 × 2 × 1)	$(2 \times 2 \times 1)$	(2 × 2 × 1)

^A Tolerances have been established to provide for grade designations. Closer tolerances, when desirable for specific applications, mayshall be agreed upon between the purchaser and the seller. $^{\it B}$ To be expressed as a percent of the original thickness.

^C See Section 7 for an explanation of the test methods referenced.

^D See 9.3 when indicated specimen sizes are not available.

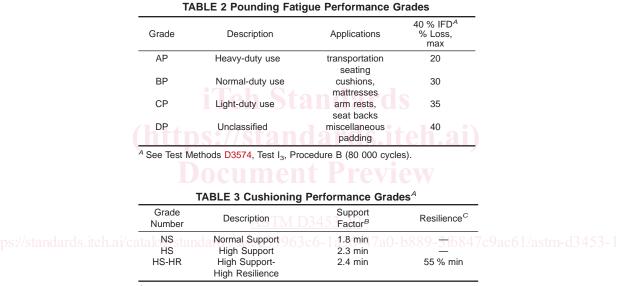

^A Grades also subject to specific physical properties in Table 1.

^B 65 % / 25 % IFD; See Test Methods D3574, Section 21 and Appendix X3.1.

^C Ball Rebound; see Test Methods D3574, Sections 68–72.

6.1.1 Sizes—The standard thickness and tolerance are specified in Table 5. These sizes have been adopted for mattress inserts to coordinate the insert with mattress ticking and other bed constructions. The other dimensions are specified in Table 7A of Simplified Practice Recommendations R2-62.

6.1.2 For Use as Furniture Cushion Inserts—The allowable tolerances on dimensions of furniture cushion inserts shall be as shown in Table 6.

7. Test Methods

7.1 The physical tests shall be in accordance with Test Methods D3574.

¹ This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.22 on Cellular Materials - Plastics and Elastomers.

Current edition approved Sept. 1, 2007Oct. 1, 2012. Published October 2007November 2012. Originally approved in 1976. Last previous edition approved in 20012007 as D3453 - 01.D3453 - 07. DOI: 10.1520/D3453-07.10.1520/D3453-12.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

Available from the Superintendent of Documents, U. S. Government Printing Office, Washington, DC 20402.

⁴ Available from the Clearing House for Federal Scientific and Technical Information, 5285 Port Royal Rd., Springfield, VA 22151.