
International Standard



3077

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Short link chain for lifting purposes — Grade T (8), calibrated, for chain hoists and other lifting appliances

Chaînes de levage à maillons courts, classe T (8), calibrées, pour palans à chaînes et autres appareils de levage

First edition — 1980-08-01

ITeH STANDARD PREVIEW
(standards.iteh.ai)

[ISO 3077:1980](#)

<https://standards.iteh.ai/catalog/standards/sist/ea535185-cd4d-4af1-bd5f-54e53570d7ec/iso-3077-1980>

UDC 621.86.065.4

Ref. No. ISO 3077-1980 (E)

Descriptors : chains, welded construction, hoists, specifications, dimensions, dimensional tolerances, tests, mechanical properties.

Price based on 9 pages

FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 3077 was developed by Technical Committee ISO/TC 111, *Round steel link chains, chain wheels, lifting hooks and accessories*, and was circulated to the member bodies in March 1978.

It has been approved by the member bodies of the following countries :

Australia
Austria
Belgium
Canada
Chile
Czechoslovakia
Germany, F.R.

India
Italy
Korea, Rep. of
Mexico
Poland
South Africa, Rep. of
Spain

ISO 3077:1980

Sweden

Turkey

United Kingdom

USA

USSR

Yugoslavia

The member bodies of the following countries expressed disapproval of the document on technical grounds :

France
Japan
Netherlands

Short link chain for lifting purposes — Grade T (8), calibrated, for chain hoists and other lifting appliances

1 SCOPE AND FIELD OF APPLICATION

This International Standard specifies requirements for lifting chains, grade T, accurately calibrated, for use as load chain in chain hoists and similar appliances. These are electrically welded round steel short link chains fully heat treated and tested, and comply with the general conditions of acceptance of ISO 1834.

The range of sizes covered in this International Standard is from 4 mm to 20 mm. The annex gives a range of temporary additional sizes 6 mm to 19 mm.

2 REFERENCES

ISO/R 388, *ISO metric series for basic thicknesses of sheet and diameters of wire.*

ISO/R 643, *Micrographic determination of the austenitic grain size of steels.*

ISO 1035/1, *Dimensions of hot rolled steel bars — Part 1: Round bars — Metric series.*¹⁾

ISO 1834, *Short link chain for lifting purposes — General conditions of acceptance.*²⁾

3 DEFINITIONS

For the purpose of this International Standard, the definitions given in ISO 1834 apply.

4 GENERAL CONDITIONS OF ACCEPTANCE

The chain shall comply fully with the requirements of ISO 1834 as well as those of this International Standard.

5 DIMENSIONS

5.1 Size of chain (see ISO 1834, clause 4, Definitions)

The size of chain shall be one of the sizes listed in table 2, column 1 corresponding to the nominal diameter (d_n) of the steel wire (ISO/R 388) or bar (ISO 1035/1) from which the chain is made.

NOTE — Control over the size of the material (bar or wire) from which the chain is made is important but this International Standard concerns finished chain and must assume that the inspector may not have the opportunity of retrospective measurement of the original material. The chain manufacturer will realize the need for the size of this material to be kept within accepted tolerances.

5.2 Material diameter

(See ISO 1834 for definition of material diameter and method of measurement.)

5.2.1 Tolerance on material diameter

For sizes less than 18 mm the diameter d of the material in the finished link shall nowhere differ from the nominal diameter by more than $\begin{matrix} +2 \\ -6 \end{matrix}$ %, except at the weld.

For sizes 18 mm and over, the diameter d of the material in the finished link shall nowhere differ from the nominal diameter by more than ± 5 %, except at the weld.

1) At present at the stage of draft. (Revision of ISO/R 1035/1-1969.)

2) At present at the stage of draft.

5.2.2 Tolerances at the weld

The dimension of the steel at the weld shall nowhere be less than the diameter d of the steel adjacent to the weld, or exceed it by more than the following tolerances. (See figure 1 and table 2).

Type 1 : 8 % of the nominal diameter in any direction.

Type 3 : 8 % of the nominal diameter in the direction perpendicular to the plane of the link and 17 % in other planes.

5.2.3 Area affected dimensionally by welding

The area affected dimensionally by welding shall not extend by more than 0,6 of the material diameter to either side of the centre of the link.

5.3 Length and width

The dimensions of the length and width of the links shall be as specified in table 2 and illustrated in figure 2.

5.3.1 Nominal dimensions

Preferred nominal dimensions are as follows :

- pitch p (i.e. inside length) : 3 times the nominal chain size (d_n);
- outside width w : 3,25 times the nominal chain size (d_n).

Where the chain has to fit a load wheel designed for different dimensions, the nominal pitch (inside length) and the nominal outside width shall be clearly specified at the time of the enquiry and order.

5.3.2 Tolerances

5.3.2.1 OUTSIDE WIDTH w (MEASURED ON THE CHAIN IN THE FINISHED CONDITION).

The outside width, w , measured clear of the weld zone is given by the formula :

$$w = \text{nominal outside width, } \begin{matrix} +0,075 d_n \\ 0 \end{matrix}$$

5.3.2.2 LENGTH (MEASURED ON THE CHAIN IN THE FINISHED CONDITION).

The inside length of one link or the sum L of the inside lengths of any number of links N measured bearing to bearing under a load not greater than half the specified proof force of the chain, shall not vary from the nominal length (N_p) by more than the following percentage tolerance :

$$\frac{\Delta L}{N_p} \times 100 = \begin{matrix} +(1,6/N + 0,33) \\ 0 \end{matrix} \%$$

TABLE 1 - Examples

Nominal size d_n mm	Number of links in chain N	Tolerance (plus only)	
		%	mm
6,3	1	1,93	0,37
	5	0,65	0,61
	21	0,406	1,61
10	1	1,93	0,58
	5	0,65	0,975
	21	0,406	2,56
20	1	1,93	1,16
	5	0,65	1,95
	21	0,406	5,12

6 MATERIAL AND MANUFACTURE

6.1 Quality of material

The steel shall be produced by the open hearth or electric process or by an oxygen blown process.

In its finished state as supplied to the chain maker it shall meet the following requirements as determined by check analysis on the rod, wire or finished link.

It shall be fully killed, shall possess reliable welding quality and shall contain alloying elements in sufficient quantities to guarantee the mechanical properties of the chain after appropriate heat treatment. The alloy steel used shall contain nickel and at least one of the following alloying elements :

- chromium,
- molybdenum.

Its content of sulphur and phosphorus shall be restricted as follows :

	Cast analysis	Check analysis
Sulphur max.	0,035 %	0,040 %
Phosphorus max.	0,035 %	0,040 %

The steel shall be made in conformity with fine grain practice to give an austenitic grain size of 5 or finer when tested in accordance with ISO/R 643.

This could be accomplished, for example, by ensuring that it contains sufficient aluminium or an equivalent element to permit the manufacture of chain stabilized against strain age embrittlement during service; a minimum value of 0,02 % metallic aluminium is given for guidance.

Within the above limitations it is the responsibility of the chain maker to select steels so that the finished chain, suitably heat treated, meets the mechanical properties specified in this International Standard.

6.2 Heat treatment

All chain shall be hardened and tempered before being subjected to the manufacturing test force.

6.3 Manufacturing test force

During manufacture, the heat treated chain shall be subjected to a force of 60 % of the minimum breaking force specified in table 4, or table 6, column 5.

6.4 Proof force (acceptance)

The proof force shown in table 4, column 2 or table 6, column 2, shall be applied only when called up in connection with acceptance testing and inspection, since, in this grade, the manufacturing test force (see 6.3) assumes the function prescribed in ISO 1834, clause 6.5.

7 TEST REQUIREMENTS**7.1 Mechanical properties and test forces**

The mechanical properties shall be as specified in table 3 and the test forces to be applied for each size are specified in table 4 and table 6.

7.2 Selection of samples

Samples shall be selected as specified in ISO 1834. The length of the lot from which the inspector selects the samples shall be 200 m or lesser length.

7.3 Static tensile test**7.3.1 Testing machine and method**

The testing machine and method of testing shall be as specified in ISO 1834.

7.3.2 Tensile test

The breaking force shall be not less than that specified in table 4, column 3 or table 6, column 3.

7.3.3 Total ultimate elongation

The total ultimate elongation as defined in ISO 1834 shall be not less than 10 %.

8 INSPECTION**8.1 Provision for inspection**

The provision for inspection shall be as specified in ISO 1834.

8.2 Acceptance

The acceptance procedure shall be as specified in ISO 1834.

9 MARKING**9.1 Quality marking**

The quality mark for the chain is T or 8. It shall be applied as specified in ISO 1834.

9.2 Identification marking

The identification marking shall be as specified in ISO 1834.


9.3 Inspection marking

The inspection marking shall be as specified in ISO 1834.

10 TEST CERTIFICATE

The manufacturer shall, if required, supply a certificate of test and examination with every supply of chain containing the information detailed in ISO 1834. A typical form is given in ISO 1834, annex C.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
ISO 3077:1980
<https://standards.iteh.ai/catalog/standards/sist/e425185-ed4d-4e81-b15f-54e53570d7ec/iso-3077-1980>

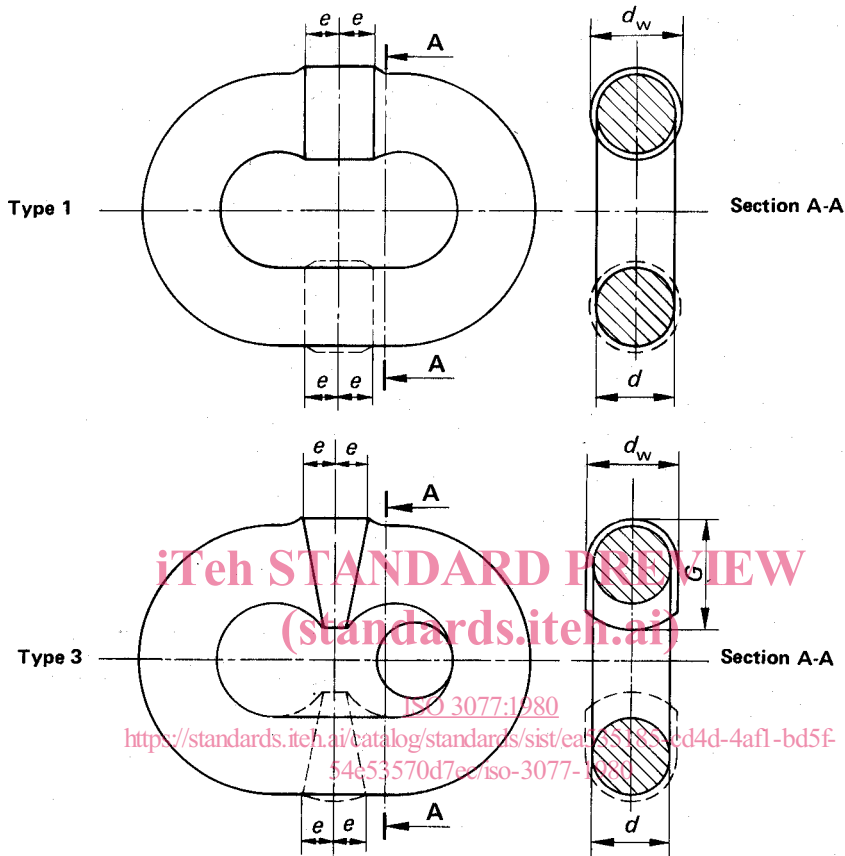

d_n = size (nominal diameter of the material)

d = measured diameter of the material except at the weld

d_w = measured diameter of the material at the weld (type 1 welded chain) or the weld dimension perpendicular to the plane of link (type 3 welded chain)

G = dimension in other planes (type 3 welded chain)

e = length affected by welding on either side of the centre of the link

For all welds

$$e \leq 0,6 d_n$$

$$\text{For } d_n < 18 \text{ mm, } d = d_n + \frac{2}{6} \%$$

$$\text{For } d_n \geq 18 \text{ mm, } d = d_n \pm 5 \%$$


Weld tolerance :

$$\text{Type 1 : } d_w = d + \begin{matrix} 0,08 \\ 0 \end{matrix} d_n$$

$$\text{Type 3 : } d_w = d + \begin{matrix} 0,08 \\ 0 \end{matrix} d_n$$

$$G = d + \begin{matrix} 0,17 \\ 0 \end{matrix} d_n$$

FIGURE 1 – Material and weld tolerances

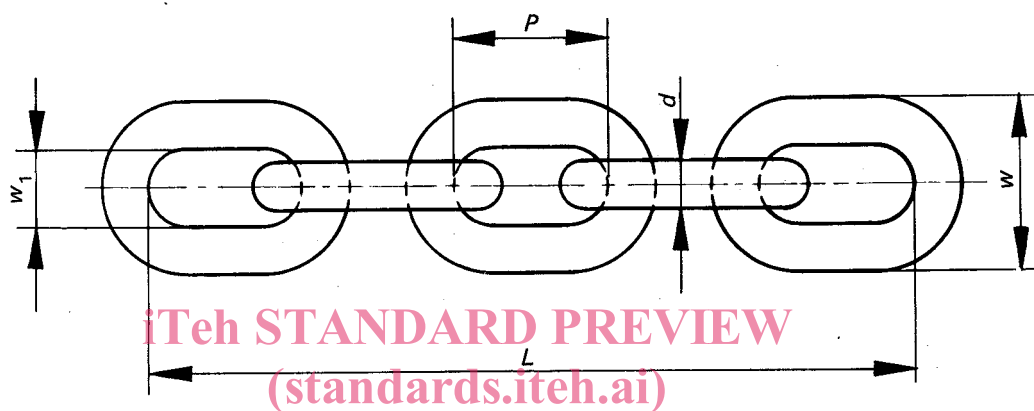

Given in terms of the nominal size of the chain d_n :

ISO 3077:1980

Pitch P (inside length); preferred value $3 d_n$

Outside width w except at the weld; preferred value $3,25 d_n$

Inside width w_1 ; minimum permitted value $1,25 d_n$ except at the weld, or such minimum value as will prevent kinking.
 Length L (see 5.3.2.2).

FIGURE 2 – Chain and link dimensions

TABLE 2 — Dimensions of grade T (8) calibrated chain
(for symbols see figures 1 and 2)

Dimensions in millimetres

(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
Nominal size d_n	Diameter tolerance $(d - d_n)$	Maximum tolerance at the weld (see figure 1)		Preferred pitch (inside length) $(3 d_n)$	Pitch tolerance on the single link (+ only)	Preferred outside width w $(3,25 d_n)$	Outside width tolerance (+ only) away from weld $(0,075 d_n)$
		Types 1 and 3 $(d_w - d)$	Type 3 $(G - d)$				
4	+ 0,08 - 0,24	0,32	0,7	12	0,23	13	0,30
5	+ 0,10 - 0,30	0,4	0,85	15	0,29	17	0,38
6,3	+ 0,13 - 0,38	0,5	1,05	19	0,37	21	0,48
7,1	+ 0,14 - 0,43	0,57	1,2	21	0,41	23	0,54
8	+ 0,16 - 0,48	0,64	1,35	24	0,46	26	0,60
9	+ 0,18 - 0,54	0,72	1,55	27	0,52	30	0,68
10	+ 0,20 - 0,60	0,8	1,7	30	0,58	33	0,75
11,2	+ 0,22 - 0,67	0,9	1,9	34	0,66	37	0,84
12,5	+ 0,25 - 0,75	1,0	2,15	38	0,73	41	0,94
14	+ 0,28 - 0,84	1,12	2,4	42	0,81	46	1,05
16	+ 0,32 - 0,96	1,28	2,7	48	0,93	52	1,2
18	± 0,90	1,44	3,05	54	1,04	59	1,35
20	± 1,0	1,6	3,4	60	1,16	65	1,5

TABLE 3 – Mechanical properties

Mechanical property	Requirement
Mean stress at specified minimum breaking force $\frac{2F_{m \min}}{\pi d_n^2}$	800 MPa(N/mm ²)
Mean stress at proof force $\frac{2F_e}{\pi d_n^2}$	400 MPa(N/mm ²)
Ratio of proof force (acceptance) to specified minimum breaking force	50 %
Specified minimum total ultimate elongation	10 %
Mean stress at working load limit	200 MPa(N/mm ²)

NOTES

- The stresses quoted in table 3 are obtained by dividing the force by the total cross-section of both sides of the link i.e. they are mean stresses. The stress is in fact not uniform and particularly at the extrados the maximum fibre stress is considerably greater.
- The working load may be selected to comply with national regulations but it must in no case exceed the load in table 4, column 4 or table 6, column 4.

(standards.iteh.ai)

ISO 3077:1980

<https://standards.iteh.ai/catalog/standards/sist/ea535185-cd4d-4af1-bd5f-34e33570d7ec/iso-3077-1980>

TABLE 4 – Grade T (8), calibrated, test requirements

(1)	(2)	(3)	(4)	(5)
Nominal size d_n mm	Force (acceptance) kN	Minimum breaking force kN	Working load limit t	Manu- facturing test force kN
4	10,1	20,2	0,5	12
5	15,8	31,6	0,8	19
6,3	25	50	1,25	30
7,1	31,7	63,4	1,6	38
8	40,3	80,6	2,0	48
9	51	102	2,5	61
10	63	126	3,2	76
11,2	79	158	4,0	94
12,5	99	198	5,0	119
14	124	248	6,3	149
16	161	322	8,0	193
18	204	408	10,0	245
20	252	504	12,5	302