

ISO/TC 206

Secretariat: JISC

Voting begins on:  
2023-04-26

Voting terminates on:  
2023-06-21

**Fine ceramics (advanced ceramics, advanced technical ceramics) — Mechanical properties of ceramic composites at room temperature — Determination of the interlaminar shear strength and shear modulus of continuous-fibre-reinforced composites by the compression of double-notched test pieces and by the Iosipescu test**

*Céramiques techniques — Propriétés mécaniques des céramiques composites à température ambiante — Détermination de la résistance au cisaillement interlaminaire et du module de cisaillement des composites renforcés par des fibres continues, par la compression d'éprouvettes à double entaille et par l'essai Iosipescu*

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number  
ISO/FDIS 20505:2023(E)

© ISO 2023

# iTeh Standards (<https://standards.iteh.ai>) Document Preview

ISO 20505:2023

<https://standards.iteh.ai/catalog/standards/iso/9e81e22a-f121-41fe-9f92-dfb2b5e7a1ae/iso-20505-2023>



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b>	<b>iv</b>
<b>1 Scope</b>	<b>1</b>
<b>2 Normative references</b>	<b>1</b>
<b>3 Terms and definitions</b>	<b>1</b>
<b>4 Principle</b>	<b>4</b>
4.1 General	4
4.2 Double-notched test	4
4.3 Iosipescu test	4
<b>5 Apparatus</b>	<b>5</b>
5.1 Test machine	5
5.2 Load train	5
5.2.1 Generalities	5
5.2.2 Test fixtures	6
5.3 Strain gauges for Iosipescu test specimen	8
5.4 Data acquisition	9
5.5 Dimension-measuring devices	9
<b>6 Test specimens</b>	<b>9</b>
6.1 Double-notched test piece	9
6.2 Iosipescu test piece	11
<b>7 Test specimen preparation</b>	<b>12</b>
7.1 Machining and preparation	12
7.2 Bonding of the gauges	12
7.3 Number of test specimens	12
<b>8 Test procedures</b>	<b>12</b>
8.1 Displacement rate	12
8.2 Measurement of test specimen dimensions	13
8.3 Testing technique	13
8.3.1 Specimen mounting	13
8.3.2 Measurements	14
8.4 Test validity	15
<b>9 Calculation of results</b>	<b>16</b>
9.1 Shear strength	16
9.1.1 Double-notched test piece	16
9.1.2 Iosipescu test piece	16
9.2 Shear strain (Iosipescu test)	17
9.3 Shear-stress-shear-strain curves	17
9.4 Elastic shear modulus, pseudo-elastic shear modulus	17
9.5 Statistics	18
<b>10 Report</b>	<b>18</b>
<b>Annex A (informative) New materials: verification of shear stress field in the Iosipescu test</b>	<b>20</b>
<b>Bibliography</b>	<b>21</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 206, *Fine ceramics*.

This second edition cancels and replaces the first edition (ISO 20505:2005), which has been technically revised.

The main changes are as follows:

- Scope revised to include the possibility of measuring the interlaminar shear modulus through the use of a gauges-instrumented Iosipescu sample;
- new entries added to [Clause 3](#);
- [5.3](#) and [7.2](#) specify requirements on the gauges-instrumented Iosipescu sample;
- [9.3](#), [9.4](#) and [9.5](#) define formulae to determine the shear modulus;
- material orientation added to [Figure 2](#) and [Figure 3](#);
- subclause on test validity added ([8.4](#));
- [Table 1](#) and [Table 2](#) updated;
- [Annex A](#) replaced by a method to verify the shear stress field in the Iosipescu test to ensure that there are no coupling effects that make this document unsuitable for determining the interlaminar shear properties of the material;
- minor editorial corrections;
- structure revised;
- symbols and notation modified in accordance with ISO 19634.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

iTeh Standards  
(<https://standards.itih.ai>)  
Document Preview

ISO 20505:2023

<https://standards.itih.ai/catalog/standards/iso/9e81e22a-f121-41fe-9f92-dfb2b5e7a1ae/iso-20505-2023>



# Fine ceramics (advanced ceramics, advanced technical ceramics) — Mechanical properties of ceramic composites at room temperature — Determination of the interlaminar shear strength and shear modulus of continuous-fibre-reinforced composites by the compression of double-notched test pieces and by the Iosipescu test

## 1 Scope

This document specifies a method for the determination of interlaminar shear strength at ambient temperature by the compression of a double-notched test piece and a method for the determination of interlaminar shear strength and modulus at ambient temperature by the Iosipescu test. This document applies to all ceramic matrix composites with a continuous fibre reinforcement, having unidirectional (1D), bidirectional (2D) and multidirectional (xD, with  $x > 2$ ) fibre architecture, where a major part of reinforcements is a stack of plies.

This document is applicable to material development, material comparison, quality assurance, characterization, reliability and design data generation. The simpler compression test method of a double-notched test piece is applicable only when the shear strength has to be measured.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 17161, *Fine ceramics (advanced ceramics, advanced technical ceramics) — Ceramic composites — Determination of the degree of misalignment in uniaxial mechanical tests*

ISO 19634, *Fine ceramics (advanced ceramics, advanced technical ceramics) — Ceramic composites — Notations and symbols*

ISO 20507, *Advanced ceramics — Vocabulary*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 20507 and ISO 19634 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 3.1 shear section

section located between the notches of test sample

Note 1 to entry: Due to the orientation of the test sample (see [Figures 2](#) and [3](#)), the shear plane is orthogonal to direction 3 and parallel to the stack of plies (plane 1, 2). Therefore, the shear mechanism occurs between the composite plies and the resulting shear properties, with respect to the definition given in ISO 20507, are labelled as “interlaminar”.

### 3.2 initial shear section area

$S_0$   
shear section area before test between the notches of the test piece at room temperature

### 3.3 shear section area


$S_e$   
effective shear loaded section area of the test piece at room temperature

Note 1 to entry: This effective shear loaded section area is determined when a valid failure occurs in a plane parallel to the shear plane in an Iosipescu test sample.

### 3.4 shear force

$F$   
force parallel to the shear section carried by the test specimen at any time during the shear test

Note 1 to entry: See [Figure 1](#).

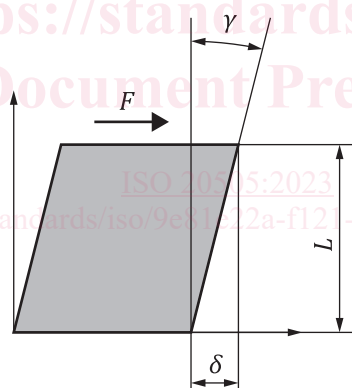

#### Key

$F$  shear force  
 $\gamma$  shear strain

$L$  height of the cubic element  
 $\delta$  displacement

**Figure 1 — Shear force and shear strain**

### 3.5 maximum shear force

$F_m$   
maximum force parallel to the shear section during a test or at fracture



**3.6****interlaminar shear strength** $\sigma_{ILSS,m,i,3}$ 

ratio of the maximum shear force to the initial shear section area

Note 1 to entry: With respect to the material orientation defined in ISO 19634, subscript "i" is for the direction of the load with respect to the material orientation and subscript "3" is for the material orientation orthogonal to the shear plan (see [Figures 2](#) and [3](#)).

**3.7****shear strain** $\gamma$ 

change in angle between two adjacent sides of a cubic-shaped stress element submitted to a shear force

Note 1 to entry: Although shear strain is defined as an angle, for small strains this measure becomes the ratio of displacement  $\delta$  to the height of the stress element  $L$  (see [Figure 1](#)).

**3.8****strain** $\epsilon_{ij}$  $\epsilon_{\theta}$ 

ratio of deformation to initial strain gauge length

Note 1 to entry: The subscripts "ij" and " $\theta$ " indicate the orientation of the strain gauge with respect to test sample orientation.

**3.9****shear stress** $\sigma_{ILSS,i,3}$ 

ratio of the shear force to the initial shear section area at any time during the test

Note 1 to entry: With respect to the material orientation defined in ISO 19634, subscript "i" is for the direction of the load with respect to the material orientation and subscript "3" is for the material orientation orthogonal to the shear plan (see [Figures 2](#) and [3](#)).

**3.10****measurement zone**

part of the test piece, in the plane perpendicular to direction 1 or 2 (see [Figures 2](#) and [3](#)), between the notches

**3.11****elastic shear modulus** $G_{i,3}$ 

ratio of shear stress to corresponding shear strain

Note 1 to entry: For general use the reference plane for  $G_{i,3}$  is defined by the axes i and 3.

Note 2 to entry: If the plane is defined by the normal axis, the elastic modulus is noted  $G_i$ .

**3.12****pseudo-elastic shear modulus** $G_{p,i,3}$ 

slope of the linear section not starting from the origin of the shear-stress-shear-strain curve, if any  $G_{p,i,3}$  is defined as the proportionality ratio:

$$G_{p,i,3}(\sigma'_{ILSS}, \sigma''_{ILSS}) = \frac{\sigma'_{ILSS} - \sigma''_{ILSS}}{\gamma'' - \gamma'}$$

where  $(\gamma', \sigma'_{ILSS})$  and  $(\gamma'', \sigma''_{ILSS})$  lie on the linear section of the shear-stress-shear-strain curve

Note 1 to entry: For general use the reference plane for  $G_{p,i,3}$  is defined by the axes i and 3.

Note 2 to entry: If the plane is defined by the normal axis, the elastic modulus is noted  $G_{pi}$ .

Note 3 to entry: For material with nonlinear shear stress-strain behaviour, only stress-strain couples can be fixed.

## 4 Principle

### 4.1 General

The interlaminar shear strength of continuous-fibre reinforced ceramic composites, as determined by this document, can be measured by the compression of double-notched test pieces or by the Iosipescu test. The interlaminar shear modulus shall be measured by the Iosipescu test.

NOTE The test is performed at constant displacement rate, up to failure.

### 4.2 Double-notched test

A double-notched test piece of uniform width is loaded in compression to induce failure by shear between two centrally located notches machined halfway through the thickness and spaced a fixed distance apart on opposing faces (see [Figure 2](#)).

NOTE Some attempts to measure shear strain and shear modulus on a double-notched test piece with the use of a virtual strain gauge through digital image correlation analysis have been investigated, but results are not consistent enough to validate shear modulus determination with this test method.

### 4.3 Iosipescu test

A test specimen with two centrally located V notches (see [Figure 3](#)) is submitted to a translation of its part B parallel to the plies plane while its part A is kept still.

The displacement of part B with respect to part A results in an assumed uniform shear field in the measurement zone.

Force and strain are measured and recorded simultaneously, from which shear modulus and shear strength can be determined.

NOTE Before the failure, for high levels of shear stress, debonding of strain gauges often occurs. Consequently, this test method is not suited to provide a valid shear-stress-shear-strain curve in the vicinity of the interlaminar shear strength.

Schematics of the test pieces are shown in [Figures 2](#) and [3](#).

Considering the orientation of the stack of plies with respect to the notches and the material orientation definitions defined in ISO 19634,  $\sigma_{ILSS,13}$ , and  $G_{13}$  (or  $G_1$ ) as well as  $\sigma_{ILSS,23}$ , and  $G_{23}$  (or  $G_2$ ) can be determined.