

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
24131-1

ISO/TC 5/SC 2

Secretariat: AFNOR

Voting begins on:
2023-01-05

Voting terminates on:
2023-03-02

**Internal protection by polymeric
lining for ductile iron pipes —
Requirements and test methods —**

**Part 1:
Polyurethane lining**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/FDIS 24131-1](https://standards.iteh.ai/catalog/standards/sist/fa585181-17ed-4907-88b4-145421095f28/iso-fdis-24131-1)

<https://standards.iteh.ai/catalog/standards/sist/fa585181-17ed-4907-88b4-145421095f28/iso-fdis-24131-1>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 24131-1:2023(E)

© ISO 2023

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/FDIS 24131-1

<https://standards.iteh.ai/catalog/standards/sist/fa585181-17ed-4907-88b4-145421095f28/iso-fdis-24131-1>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

| | |
|---|-----------|
| Foreword | iv |
| Introduction | v |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Technical requirements | 3 |
| 4.1 General..... | 3 |
| 4.2 Surface preparation..... | 3 |
| 4.3 Surface roughness..... | 4 |
| 4.4 Lining appearance..... | 4 |
| 4.5 Lining thickness..... | 4 |
| 4.6 Adhesion..... | 4 |
| 4.7 Cross linkage..... | 4 |
| 4.8 Non-porosity..... | 5 |
| 4.9 Hardness..... | 5 |
| 4.10 Protection of pipe ends..... | 5 |
| 4.11 Marking..... | 5 |
| 4.12 Repairs..... | 5 |
| 5 Performance requirements | 6 |
| 5.1 General..... | 6 |
| 5.2 Materials in contact with water intended for human consumption..... | 6 |
| 5.3 Abrasion resistance only for sewage applications..... | 6 |
| 5.4 Chemical resistance only for sewage applications..... | 6 |
| 5.5 Indirect impact resistance..... | 6 |
| 5.6 Resistance to hot water..... | 6 |
| 5.7 Specific lining resistance..... | 6 |
| 5.8 Resistance to ovalization..... | 7 |
| 5.9 Elongation at break..... | 7 |
| 6 Test methods | 7 |
| 6.1 Routine tests..... | 7 |
| 6.1.1 Surface preparation..... | 7 |
| 6.1.2 Surface roughness..... | 7 |
| 6.1.3 Lining appearance..... | 7 |
| 6.1.4 Lining thickness..... | 7 |
| 6.1.5 Adhesion..... | 7 |
| 6.1.6 Differential scanning calorimetry (DSC)..... | 8 |
| 6.1.7 Non-porosity..... | 8 |
| 6.1.8 Hardness..... | 8 |
| 6.1.9 Marking..... | 8 |
| 6.1.10 Repairs..... | 8 |
| 6.2 Performance test..... | 8 |
| 6.2.1 Abrasion resistance only for sewage applications..... | 8 |
| 6.2.2 Chemical resistance only for sewage applications..... | 8 |
| 6.2.3 Indirect impact resistance..... | 8 |
| 6.2.4 Resistance to hot water..... | 9 |
| 6.2.5 Specific lining resistance..... | 9 |
| 6.2.6 Resistance to ovalization..... | 10 |
| 6.2.7 Elongation at break..... | 10 |
| Annex A (normative) Quality assurance | 11 |
| Annex B (informative) Handling, transportation and storage | 13 |
| Bibliography | 14 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 5, *Ferrous metal pipes and metallic fittings*, Subcommittee SC 2, *Cast iron pipes, fittings and their joints*.

A list of all parts in the ISO 24131 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The ISO 24131 series specifies the requirements and test methods applicable to factory applied polymeric linings for ductile iron pipes according to ISO 2531, ISO 7186 and ISO 16631. The ISO 24131 series is intended to include several types of polymeric linings.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO/FDIS 24131-1](https://standards.iteh.ai/catalog/standards/sist/fa585181-17ed-4907-88b4-145421095f28/iso-fdis-24131-1)

<https://standards.iteh.ai/catalog/standards/sist/fa585181-17ed-4907-88b4-145421095f28/iso-fdis-24131-1>

Internal protection by polymeric lining for ductile iron pipes — Requirements and test methods —

Part 1: Polyurethane lining

1 Scope

This document specifies the requirements and test methods applicable to factory applied internal polyurethane lining for ductile iron pipes according to ISO 2531, ISO 7186 and ISO 16631.

It covers internal linings for use in the conveyance of raw water, potable water and sewage water for operating temperature up to 50 °C.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2531, *Ductile iron pipes, fittings, accessories and their joints for water applications*

ISO 7186:2011, *Ductile iron products for sewerage applications*

ISO 16631, *Ductile iron pipes, fittings, accessories and their joints compatible with plastic (PVC or PE) piping systems, for water applications and for plastic pipeline connections, repair and replacement*

ISO 8503-1, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 1: Specifications and definitions for ISO surface profile comparators for the assessment of abrasive blast-cleaned surfaces*

ISO 868, *Plastics and ebonite — Determination of indentation hardness by means of a durometer (Shore hardness)*

ISO 62, *Plastics — Determination of water absorption*

ISO 4624, *Paints and varnishes — Pull-off test for adhesion*

ISO 527-3, *Plastics — Determination of tensile properties — Part 3: Test conditions for films and sheets*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2531 and the following apply.


ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1 polyurethane lining

factory applied lining which consists of *polyurethane* (3.2) on the inside of the pipe

Note 1 to entry: See [Figure 1](#).

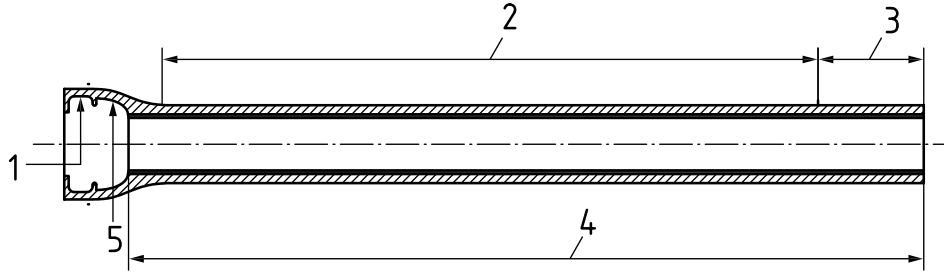

Key

- 1 gasket seat
- 2 pipe barrel
- 3 spigot end
- 4 lining
- 5 internal socket profile

Figure 1 — Location of the defined pipe areas

iteh STANDARD PREVIEW
(standards.iteh.ai)

3.2 polyurethane

polymers made by combining diisocyanates and polyols

3.3 operating temperature

applicable temperatures under which the product maintains its properties

3.4 chalking

superficial reaction of *polyurethane lining* (3.1) due to exposure to UV-radiation

Note 1 to entry: The process is confined to the surface only and results in a dulling of the surface.

3.5 minimum lining thickness

minimum value of the lining thickness measured at the lined item

3.6 adhesion

force per unit area, applied perpendicular to the surface, which is necessary to separate the lining from its substrate

3.7 cross linkage

chemical reaction between *polyurethane* (3.2) resin and hardener to form the final cured lining

3.8 non-porosity

absence of electrical puncture in a high voltage test (holiday test) under defined test conditions

3.9 hardness

resistance of the lining to the penetration of a ball under defined test conditions

3.10**protection of pipe ends**

factory applied coating/lining on spigot end and internal socket profile of pipes

Note 1 to entry: See [Figure 1](#).

3.11**abrasion resistance**

ability of materials and structures to withstand abrasion

3.12**indirect impact resistance**

impact energy applied from outside of the pipe with deformation to which a lining can withstand without damage under defined test conditions

3.13**specific lining resistance**

surface related electric resistance of the lining perpendicular to the pipe wall

3.14**ovalization**

100 times the measured vertical deflection, (caused by the applied load) divided by the measured pipe external diameter

3.15**routine test**

test carried out to control the manufacturing process

Note 1 to entry: The frequency of the test is defined by this document or the manufacturer.

3.16**performance test**

test which is done once and thereafter only when there is a change in the lining material or lining process

4 Technical requirements**4.1 General**

The following technical requirements shall be demonstrated by routine tests applied in production, on in-process and finished lined products with defined frequency. Routine tests shall be in accordance with the overview of requirements provided in [Table A.2](#).

Quality assurance for polyurethane lining shall be in accordance with [Annex A](#).

4.2 Surface preparation

Prior to lining application, all surfaces to be lined shall be substantially clean and free from oil, grease and moisture.

In cold weather, or anytime when moisture tends to condense on the surface of the pipe, it shall be uniformly warmed for sufficient time to dry prior to cleaning. The surface temperature shall be maintained at least 3 °C above the dew point.

Surface preparation shall be designed in order to reach the required performances specified in this document. It is the responsibility of the manufacturer to demonstrate the fitness for purpose of surface

preparation technology and to put in place a quality control procedure to ensure the stability of those performances.

NOTE The requirements of Class Sa 2.5 of ISO 8501-1 and ≤ Rating 3 dust quantity and Class 2 for dust size of ISO 8502-3 can be applied.

4.3 Surface roughness

The surface roughness Ra in accordance with ISO 8503-1 shall be at least 12,5 µm which is equivalent to anchored profile Rz of 63 µm or higher if required by the lining material provider or manufacturer.

4.4 Lining appearance

The lining of the final product shall be of

- uniform colour, except for permitted marking;
- uniform appearance and smoothness, except for allowable repairs;
- free of visible defects (i.e. pinholes, bubbles, blisters, wrinkles, cracks or voids).

Slight superficial colour variations due to repairs or long exposure to sunlight (chalking) are permissible.

4.5 Lining thickness

When measured in accordance with the method defined in 6.1.4, the lining thickness shall be as indicated in Table 1 for water applications and in Table 2 for sewage applications.

Table 1 — Minimum lining thickness and test tension for water applications

| Nominal size | Minimum lining thickness | Test tension |
|--------------|--------------------------|--------------|
| DN | µm | kV |
| 80 to 2 600 | 800 | 4 |

Table 2 — Minimum lining thickness and test tension for sewage applications

| Nominal size | Minimum lining thickness | Test tension |
|--------------|--------------------------|--------------|
| DN | µm | kV |
| 80 to 700 | 800 | 4 |
| 800 to 2 600 | 1 000 | 5 |

4.6 Adhesion

Adhesion shall be tested in accordance with the test method defined in 6.1.5 on production samples.

The lining adhesion shall achieve an average value of at least 8,0 MPa. The manufacturer shall determine the test locations on the products.

4.7 Cross linkage

Determination of cross linkage by hardness measurement of the lining materials serves as a production control. It is calibrated by a differential scanning calorimetry (DSC) test, see 6.1.6.

The test shall be carried out directly after production on a cured proxy sample under the same production condition as the pipe at room temperature (23 ± 2) °C. The test method of ISO 868 shall be used.

4.8 Non-porosity

When tested in accordance with the test method defined in [6.1.7](#), the lining shall be free from porosity. For 800 µm minimum lining thickness, the test tension shall be 4 kV. For 1 000 µm minimum lining thickness, the test tension shall be 5 kV. The scanning electrode shall be passed over the surface of the lining being inspected with a continuous, relative movement not exceeding 300 mm/s. This requirement does not apply to pipe ends.

The electrode shall not be damaged and shall be in constant touch with the lining.

For thicker linings, a higher test voltage may be used by agreement between the manufacturer and the purchaser.

4.9 Hardness

The different applications (e.g. drinking water, sewage) can use different hardness which are indicated in the pipe manufacturer's catalogue. They shall be tested in accordance with [6.1.8](#).

4.10 Protection of pipe ends

Spigot end and internal socket profile (see [Figure 1](#)) shall be coated in accordance with ISO 2531, ISO 7186 and ISO 16631.

4.11 Marking

All pipes shall be marked legibly and durably according to the pipe standards, ISO 2531, ISO 7186 and ISO 16631. Reference to this document shall be legibly and durably applied by any method upon the external surface.

Marking shall be checked in accordance with the test method described in [6.1.9](#).

4.12 Repairs

Repairs shall be carried out when there is a fault. The fault can be

- localized damage,
- holding point,
- earthing surface for the non-porosity test, or
- other lining fault.

The lining manufacturer should establish the repair procedure. The material to be used shall satisfy two conditions:

- be suitable for protecting pipes under the required service conditions;
- be compatible in all aspects with the previously applied lining.

The repairs shall conform to the requirements specified in [4.5](#), [4.7](#) and [4.8](#).

The information about handling, transportation and storage of polyurethane lined pipes is given in [Annex B](#).